



**HAL**  
open science

## Catalytic hydroesterification of lignin: A versatile and efficient entry into fully biobased tunable materials

Ruqaya Buhaibeh, Tiphaine Richard, Régis M Gauvin, Mathieu Sauthier,  
Clément Dumont

► **To cite this version:**

Ruqaya Buhaibeh, Tiphaine Richard, Régis M Gauvin, Mathieu Sauthier, Clément Dumont. Catalytic hydroesterification of lignin: A versatile and efficient entry into fully biobased tunable materials. *Green Chemistry*, 2023, 25 (5), pp.1842-1851. 10.1039/d2gc03708d . hal-04019857

**HAL Id: hal-04019857**

**<https://hal.science/hal-04019857>**

Submitted on 8 Mar 2023

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Catalytic hydroesterification of lignin: A versatile and efficient entry into fully biobased tunable materials

Ruqaya Buhaibeh<sup>[a]</sup>; Tiphaine Richard<sup>[a,b]</sup>; Régis M. Gauvin<sup>[a,c]</sup>; Mathieu Sauthier<sup>[a]</sup>; Clément Dumont<sup>\*[a,b]</sup>

<sup>a.</sup> Univ. Lille, CNRS, Centrale Lille, ENSCL, Univ. Artois, UMR 8181-UCCS-Unit8 de Catalyse et Chimie du Solide F-59000 Lille (France)

<sup>b.</sup> ICAM site de Lille, 6 rue Auber, 59016 Lille Cedex (France)


<sup>c.</sup> Chimie ParisTech, PSL University, CNRS, Institut de Recherche de Chimie Paris, 75005 Paris (France)

Electronic Supplementary Information (ESI) available: experimental details for compounds catalytic reactivity, optimizations of lignin catalytic modification, additional characterization data (NMR, SEC, DSC).

**Abstract:** Hydroxyl groups of several industrial grade lignins are esterified thanks to palladium-catalyzed hydroesterification reactions with CO and olefins, fatty esters or 1,3-butadiene. The reaction is efficient, salt-free and allows introducing aliphatic chains to lignin through ester linkage. Technical and modified lignins are characterized by NMR, IR, SEC and thermal properties are evaluated by DSC. The esterified lignins show modified glass transition temperatures that depend on the substitution degree of the hydroxyl groups and on the nature of the aliphatic chains that have been introduced. The implementation of this catalysis also opens up the possibility of inserting new reactive functionalities such as esters or unsaturations from abundant and/or biobased reactants.

## Introduction

Non-renewable fossil resources continue to play a major role in the chemical industry, materials manufacturing, and energy production. Their consumption releases increasingly more CO<sub>2</sub> into the atmosphere, playing a negative role in climate change and depleting the planet's resources. For a more sustainable economy, the use of renewable carbon for the production of materials and chemicals is particularly attractive as it allows recycling and storage of CO<sub>2</sub>. Lignocellulosic biomass is one of the major alternative sources to oil, is not an edible resource and is available in large quantities. Lignin represents about 20 % of lignocellulosic biomass and 100 million tons of lignin are currently industrially produced as side product of the paper industry and within second-generation bioethanol production plants. Lignin is a bio-based polymer with high aromatics content and is clearly very attractive for plastic industry. Still, the compound is essentially used as low-value fuel and is currently 98 % burned to generate electricity and heat.<sup>1</sup> The valorization of lignins for the production of materials is indeed largely impeded by weak mechanical properties and poor compatibility with synthetic polymers. To overcome these limitations, some research fields involve the functionalization of phenolic and aliphatic hydroxyl groups of lignin to improve its properties and thus offer access to new valorization routes.<sup>2</sup> Among the chemical transformations of lignin, esterification reactions are particularly used in the development of new material solutions. The esterification of hydroxyl groups present in lignins has been for example used to improve the compatibility of lignin in blends,<sup>3</sup> to use lignin as a macromonomer,<sup>4</sup> or to graft polymerization initiators.<sup>5</sup> Other fields of application also use esters such as adhesives,<sup>6</sup> lubricants,<sup>7</sup> anti-UV films<sup>8</sup> or energy production.<sup>9</sup> However, if aliphatic alcohols can be readily involved in esterification reactions with carboxylic acids, the phenol functions of lignins show a much lower reactivity.<sup>10</sup> Thus, these transformations currently involve "activated carboxylic acids" through the use of the Steglich reaction<sup>11</sup> (with DCC/DMAP), acid halide<sup>12</sup> or anhydride<sup>13</sup>. Nevertheless, these reactions have the disadvantage of using harmful reagents generating salts or deleterious co-products in stoichiometric amounts. Consequently, this significantly increases the environmental impact of these transformations. As an environmentally friendly pathway, ester functionalization methodologies using homogeneous catalysis such as the carbonylative telomerization reaction<sup>14</sup> have shown high efficiency for efficient lignin functionalization (Scheme 1).

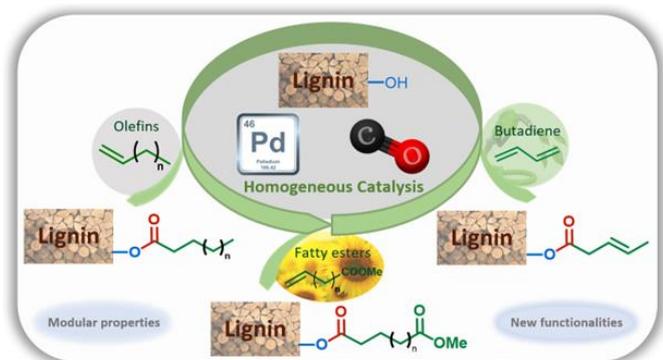


**Scheme 1** Overall scheme for Pd-catalyzed hydroesterification on lignin

The present article proposes to open a new lignin functionalization pathway via the implementation of ester synthesis through the hydroesterification reaction of olefins. This catalytic transformation affords esters that are thus readily obtained from the combination of carbon monoxide, an alkene and a nucleophilic alcohol. This reaction is atom-economical and avoids formation of stoichiometric amounts of salts.<sup>15</sup> Different kinds of catalysts have been studied for this reaction, including base metals such as cobalt<sup>16</sup> and nickel<sup>17</sup> as developed by W. Reppe in the 1960s. However, these catalysts require drastic conditions of temperature and pressure, which significantly counterbalance the interest in their use. On the other hand, palladium catalysis proceeds under softer reaction conditions, is more tolerant to functionalities and thus appears as highly suitable to convert a functionalized derivative such as lignin without prior purification.<sup>18</sup> Interestingly, the practicality of this industrially relevant reaction opens the way to efficient and atom-economical syntheses of esterified lignins from olefins, either as bulk products from large scale petroleum-based process, or as bio-based terpenes and unsaturated fatty acids or esters.

## Results and Discussion

The study aiming at the synthesis of esterified lignins from the hydroesterification reaction was initiated with guaiacol and benzyl alcohol as substrates to check the efficiency of the reaction towards both aliphatic and phenolic hydroxyl groups. Such functionalities are found in lignin (Scheme 2) and the use of such simple molecules is highly suitable to collect spectroscopic references for the assessment of lignin grafting by <sup>1</sup>H NMR (see below). For this purpose, a simple and industrially relevant olefin, 1-hexene, was used as co-reagent. Standard reaction conditions classically used for the hydroesterification of olefins with simple aliphatic alcohols were initially applied for the transformation of the substrates.<sup>18</sup>

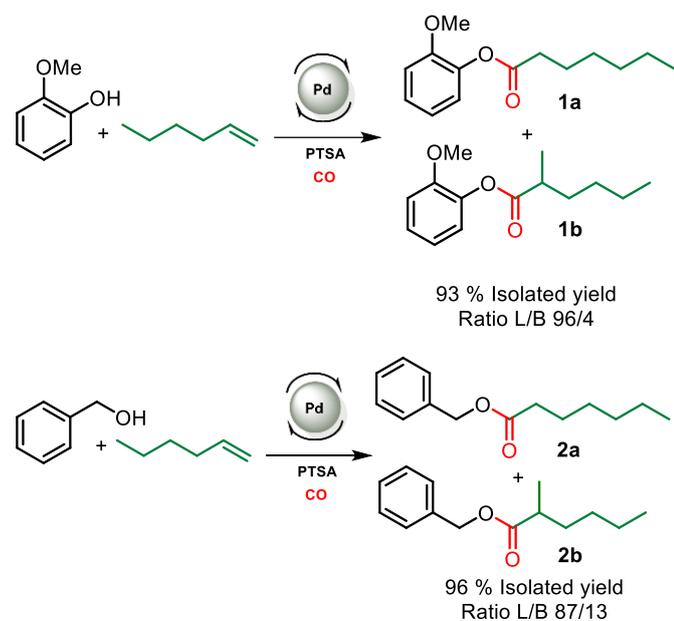

**Scheme 2** Hydroesterification of 1-hexene with guaiacol (top) and benzyl alcohol (bottom). Reaction conditions: [Pd]: Pd(OAc)<sub>2</sub> / PPh<sub>3</sub> - 120 °C, 22 h, 30 bar CO, THF. L/B ratio determined in <sup>1</sup>H NMR, see figure SI1.

The catalyst is prepared in situ by combining 1 mol% of Pd(OAc)<sub>2</sub> with 0.25 equivalents in respect to alcohol of both PPh<sub>3</sub> and *para*-toluenesulfonic acid (PTSA). With these reaction conditions, a very high conversion (99 %) of phenol was obtained and the ester was isolated with 93 % yield. <sup>1</sup>H NMR of the isolated product evidences the presence of two isomers with linear (L) **1a** and branched (B) **1b** structures with a measured L/B ratio of 96/4. The yield of the ester **2** derived from benzyl alcohol was 96 % and a slightly higher proportion of branched isomer was obtained (L/B = 87/13). These molecules validate the possibility of carrying out the hydroesterification reaction of olefins with hydroxyl groups in THF which is known as suitable solvent for lignin. Interestingly, both types of alcohols present within the lignin structure are amenable to efficient conversion into esters. The same reaction parameters were then used for the hydroesterification of Kraft lignins with 1-hexene. This industrially available material was used as received for all the catalytic tests. As the polymeric structure of the industrial grade Kraft lignin is very different from the pure simple compounds used, a first optimization study was initiated in order to maximize the conversion of the alcohols (Table 1).

The impact of the reaction temperature on the conversion of the OH groups in lignin was first studied. At 90 °C, 28 % of the total alcohols were converted (entry 1). Increasing the reaction temperature improves the substitution degree from 51 % (100 °C) to 61 % (120 °C) (entries 2 and 3). Although the reaction is rather efficient in terms of substitution degrees, it is noteworthy that large amounts of precipitated lignin were observed at the end of the catalytic runs. For example, at 120 °C, half of the initial lignin is lost as insoluble material. This precipitate proved to be also insoluble in commonly used organic solvents or water. The formation of this material during the reaction may be due to well reported condensation reactions in an acidic environment.<sup>19</sup> This insoluble fraction is not drastically influenced by the reaction temperature, as 32 % to 52 % of material is obtained between 90 °C and 120 °C. A reduced amount of acid leads to decreased substitution degree that ranges from 61 % with 0.25 equivalents of PTSA /OH to 28 % with 0.08 (entries 3 to 5). As expected in the case of the hydroesterification reaction, a high acid concentration is clearly needed to promote the formation of catalytically-relevant palladium hydrides and, hence, reach higher substitution degrees. The amount of PTSA doesn't drastically impact the formation of the insoluble lignin and rather similar amounts of functionalized lignin are obtained in most cases (for example, compare entries 3 and 5). A control test at 120 °C with lignin without PTSA in THF also generate insoluble compounds thus indicating that the observed insolubilities doesn't come from the acid used at this temperature (entry 6).

A kinetic study performed with reaction conditions of entry 3 indicates that 6 hours of reaction are necessary to reach 61 % of substitution degree (entries 7-9 and entry 3) without improving the mass of recoverable lignin. Reducing the amount of olefin decreases the conversion of hydroxyl groups from 61 % to 39 % and 22 % with respectively 8 eq, 3 eq and 1.5 eq of 1-hexene. On the other hand, the decrease of olefin equivalents seems to play a role in the formation of the insoluble lignin fraction, as the %weight of functionalized lignin increased from 52 % to 72 % by reducing the amount of olefin from 8 eq to 1.5 eq (entries 3 and 10-11). It is notorious that lignin badly tolerates lipophilic chains and tends to precipitate in the presence of alkanes. It can thus be hypothesized that the starting lignin precipitated upon addition of 1-hexene in the reactor and further cured within the precipitate under the reaction conditions used. Other solvents were thus explored in order to find a better solubilizing medium for all the reagents. The reaction was first carried out in DMSO but no conversion was observed due to the fact that 1-hexene is poorly soluble in this solvent (biphasic liquid/liquid system formed), thus limiting the contact between all the reagents and catalyst. It should be noted that with DMSO, no lignin was insoluble at the end of the reaction (entry 12). The use of dioxane allowed an excellent conversion of 70 % and a slight improvement in the mass of lignin recovered (compare entries 3 and 13). With this solvent, a further decrease of the number of equivalents of olefin allowed a higher recovery of functionalized lignin (entries 14 and 15).

**Table 1** – Optimization of the palladium catalyzed hydroesterification of 1-hexene with lignin



Entry	Hexene (eq/OH)	PTSA (eq/OH)	T (°C)	Solvent	t (h)	Conv <sup>[a]</sup> OH <sup>total</sup>	%W <sup>[b]</sup>
1	8	0.25	90	THF	22h	28 %	32 %
2	8	0.25	100	THF	22h	51 %	33 %
3	8	0.25	120	THF	22h	61 %	52 %
4	8	0.15	120	THF	22h	42 %	24 %
5	8	0.08	120	THF	22h	28 %	42 %
6	8	0	120	THF	22h	0 %	54 %


7	8	0.25	120	THF	2 h	14 %	21 %
8	8	0.25	120	THF	4 h	42 %	33 %
9	8	0.25	120	THF	6 h	61 %	26 %
10	3	0.25	120	THF	22h	39 %	56 %
11	1.5	0.25	120	THF	22h	22 %	72 %
12	8	0.25	120	DMSO	22h	0 %	98 %
13	8	0.25	120	Dioxane	22h	70 %	56 %
14	3	0.25	120	Dioxane	22h	72 %	105 %
15	1.5	0.25	120	Dioxane	22h	67 %	113 %

Conditions : 0.5 g of Kraft lignin, 10 mL of solvent, Pd(OAc)<sub>2</sub> 1 mol% in respect to OH group, PPh<sub>3</sub> 0.25 eq per OH group, 30 bar of CO; a) Conversion of total OH groups on the recovered part of lignin - comparison of the amount of chains grafted on the lignin with the quantity of available hydroxyl groups, determined by <sup>1</sup>H NMR with pentafluorobenzaldehyde as internal standard; b) Weight of lignin recovered in proportion to the amount of starting lignin.

No insoluble lignin was observed after reaction and the recovered masses of 105 % and 113 % are in agreement with the increase of mass due to the grafting of the aliphatic ester chains on the lignin.

Other parameters such as the pressure of CO, the catalytic charge in Pd and the amount of solvent were studied without significant improvement of the substitution degrees nor the lignin insolubility (see S.I. Table SI 1).

Detailed characterization by <sup>1</sup>H NMR of the product obtained in entry **15** of Table **1** evidences the presence of alkyl chains with characteristic signals at 0.7-1.1 ppm corresponding to the terminal CH<sub>3</sub>, 1.1-1.6 ppm for the CH<sub>2</sub> groups of the aliphatic chain and at 1.6-1.95 ppm for the CH<sub>2</sub> in the β position of the ester (Figure 1). These spectroscopic data correlate well with the data recorded for hydroesterified guaiacol and benzyl alcohol (Figures SI 1 and SI 3).

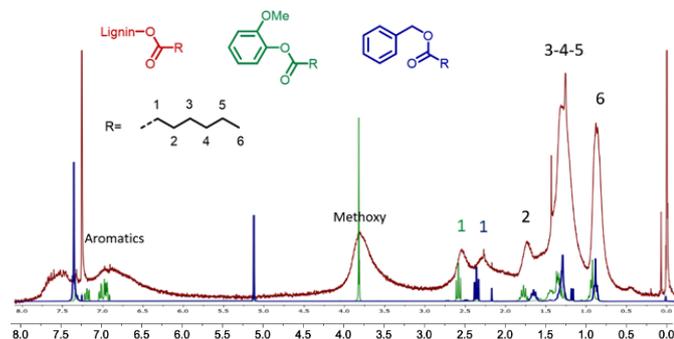


**Figure 1** Comparison of the <sup>1</sup>H NMR spectra of the hydroesterified lignin (red spectrum) with those of esters of guaiacol (green) and benzyl alcohol (blue).

Most particularly, the presence of the peak at 2.15-2.85 ppm corresponding to the CH<sub>2</sub> in α position to the ester indicates the presence of esters grafted onto the phenolic groups of the lignin. The α-CH<sub>2</sub> of esters from aliphatic alcohols are less deshielded and give signals at 2.10-2.45 ppm as confirmed by the <sup>1</sup>H NMR data recorded for the hydroesterified benzyl alcohol. All the <sup>1</sup>H NMR spectra of the compounds obtained during the optimization of the reaction have this same pattern. Only the intensity of the alkyl peaks with respect to the methoxy and aromatic groups of lignin differ according to the degree of substitution.

The comparative study of the infrared spectra of native and modified lignin highlights a band at 1728 cm<sup>-1</sup> characteristic of the C=O elongations corresponding to the new ester functions grafted on the lignin (Figure 2). The decrease in intensity of the broad band at 3360 cm<sup>-1</sup> (O-H stretching) evidences the conversion of the hydroxyl groups. Also note the decrease after reaction of the bands at 1511 cm<sup>-1</sup> and 1270 cm<sup>-1</sup> corresponding respectively to the O-H deformations of phenolic alcohols and aliphatic alcohols. This suggests that the reaction occurs on both phenols and aliphatic alcohols. New intense characteristic bands also appear at 2928, 1121 and 679 cm<sup>-1</sup> corresponding to the C-H and C-C elongations of the aliphatic chains grafted on lignin. The esterification of the hydroxyl groups is also confirmed by the <sup>31</sup>P NMR analysis performed after the derivatization of the reaction product with 2-chloro-4,4,5,5-tetramethyl-1,3,2-dioxaphospholane.<sup>20</sup> The comparison with the analytical data recorded for the technical lignins

(see S.I. Table SI 2) shows a conversion of 75 % of the total OH of Kraft lignin, including 91 % of phenolic alcohol and 68 % of aliphatic alcohols (table 2 entry 1). Up to 30 % of the carboxylic acids are also substituted, possibly as a side reaction of internal esterification with aliphatic OH. Other complementary analyses are available in supporting information such as 2D HSQC NMR (Figure SI 41)

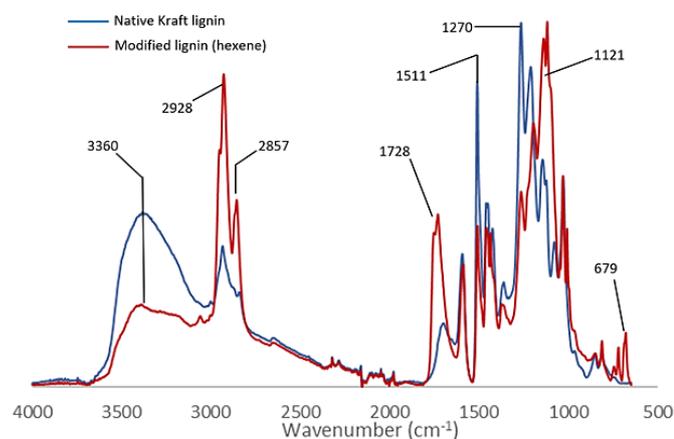

**Figure 2** Comparison of IR spectra of technical (blue) and modified kraft lignin (red)

The optimized protocol with 1-hexene was applied to other commercially available lignins. Substitution degrees of 84 % and 85 % were respectively obtained with Organosolv and Soda lignins (Table 2 entry 2 and 3). This demonstrates the broad applicability of this methodology to other types of lignin. The linear to branched ratio of esters (L/B in table 2) was quantified using quantitative  $^{13}\text{C}$  NMR and showed similar results to the simple molecules with less than 10 % of branched isomer. The palladium content in the lignins was measured by ICP in order to evaluate the amount of metal leached in the final material. The ICP titrations indicate that only 25 % of the catalyst remains in the lignin. Thus, most of the catalyst is extracted from the lignin thanks to the purification steps. A major line of future development of our process is isolation and recovery of the spent metal catalyst.

**Table 2** Scope of the hydroesterification of 1-hexene on lignins from different extraction processes

Lignin-O-C(=O)-CH<sub>2</sub>-CH<sub>2</sub>-CH<sub>2</sub>-CH<sub>2</sub>-CH<sub>2</sub>-CH<sub>3</sub>





E	Lignin	Conversion [%] <sup>[a]</sup>				L/B <sup>[b]</sup>	ICP (%wt Pd)
		OH <sub>tot</sub>	OH <sub>al</sub>	OH <sub>ph</sub>	COOH		
1	Kraft	75	91	68	30	92/8	0.152
2	Organosolv	84	84	82	73	97/3	0.228
3	Soda	85	100	80	65	93/7	0.190

Conditions: 0.5 g of lignin, 10 mL of Dioxane, Pd(OAc)<sub>2</sub> 1 mol% in respect to OH groups, 25 eq/Pd of PPh<sub>3</sub> and PTSA, 3 eq/OH 1-hexene, 30 bar of CO  
a) Conversion of total, aliphatic, and phenolic OH groups, respectively, and of acid groups, determined by  $^{31}\text{P}$  NMR with a correction factor considering modified lignin content. see correction factor calculation after table SI2. b) determined by  $^{13}\text{C}$  NMR, see SI15.

From Kraft lignin, other olefins were grafted to probe the impact of the chain size on the thermal properties of the new materials (Table 3). The reaction with 1-octene leads to conversions of 87 % of total lignin alcohols (100 % of aliphatics and 81 % of phenolics – entry 2). 1-decene gives slightly lower results with 70 % conversion while 1-dodecene gives the best results with 91 % alcohol functionalization (entries 3 and 4).

Regarding thermal properties, Kraft lignins functionalized with esters carrying a 6-carbon chain issuing from 1-hexene, the glass transition temperature ( $T_g$ ) of the compounds drops from 140 °C (technical Kraft lignin) to 102 °C (entry 1). With 8 and 12 carbon chains, the  $T_g$  is further lowered to 80 °C and 72 °C respectively (entry 2 and 4). Concerning the 10-carbons chain from 1-decene, the glass transition temperature of the sample is the highest of the series (110 °C) and this can be explained by a lower substitution degree (entry 3).

**Table 3** Impact of olefin length in hydroesterification on kraft lignin properties




E	Olefin	Conversion [%] <sup>[a]</sup>				DSC T <sub>g</sub> (°C)	SEC		
		OH <sub>tot</sub>	OH <sub>al</sub>	OH <sub>ph</sub>	COOH		M <sub>n</sub>	M <sub>w</sub>	Đ
1	1-Hexene 	75	91	68	30	102	2600	4400	1.7
2	1-Octene 	87	100	81	44	80	2900	5100	1.7
3	1-Decene 	70	82	64	40	110	2500	4000	1.6
4	1-Dodecene 	91	90	91	58	72	3100	6700	2.2

Conditions: 0.5 g of Kraft lignin, 10 mL of Dioxane, Pd(OAc)<sub>2</sub> 1 mol% in respect to OH groups, 25eq/Pd of PPh<sub>3</sub> and PTSA, 3 eq/OH olefin, 30 bar of CO a) Conversion of total, aliphatic, and phenolic OH groups, respectively, and of acid groups, determined by <sup>31</sup>P NMR with correction factor (see SI).

SEC measurements were run on the isolated materials to determine the number average molecular weight  $M_n$  and the dispersity  $\bar{D}$  (see S.I. table SI 4). SEC analysis of used technical Kraft lignin after acetylation revealed a number average molecular weight  $M_n$  of 1800 g.mol<sup>-1</sup> with a dispersity  $\bar{D}$  of 3.1. After hydroesterification with 1-hexene, higher molecular weight ( $M_n$ = 2600 g.mol<sup>-1</sup>) corresponding to the large amount of grafted chains on the macromolecule is observed. For similar conversion rates, the more carbons in the grafted chain, the higher the molecular weight, as expected. SEC analysis indicate  $M_n$  values of 2900 g.mol<sup>-1</sup> with the material obtained from the hydroesterification of 1-octene and of 3100 g.mol<sup>-1</sup> with 1-dodecene (Table 3 entry 2 and 4).

This new synthesis procedure opens up opportunities for bio-sourced fatty acid grafting through the transformation of the unsaturation while the carboxylic acid remains pending. The most abundant fatty acid, oleic acid, has been reacted by using the optimized reaction conditions. With this internal olefin, 26 % of the hydroxyl groups were converted (see Table 4 entry 1). A deeper analytic study showed that only the aliphatic hydroxyl groups are substituted. In addition, <sup>1</sup>H NMR indicates the presence of untouched unsaturations (double bonds) within the product. Thus, the hydroesterification reaction has not occurred, and the grafting was essentially obtained from a classical esterification of aliphatic alcohols with oleic acid in the presence of PTSA. The reaction with methyl oleate results in a slightly improved alcohol conversion that reaches 29 %. With this starting material, 12 % of the hydroxyl groups have been esterified thanks to the carbonylation reaction (entry 2).

**Table 4** Hydroesterification of fatty acids, fatty ester and estragole on kraft lignin


E	Olefin	Conversion [%] <sup>[a]</sup>																		
		OH <sub>tot</sub>	OH <sub>al</sub>	8.0	7.5	7.0	6.5	6.0	5.5	5.0	4.5	4.0	3.5	3.0	2.5	2.0	1.5	1.0	0.5	0.0
1		26	85	0	60	1 %														
2		29	92	3	87	12 %														
3		36	68	22	31	100 %														
4		90	89	90	8	100 %														
5		48	75	36	50	100 %														

Conditions: 0.5 g of Kraft lignin, 10 mL of Dioxane, Pd(OAc)<sub>2</sub> 1 mol% in respect to the OH groups, 25eq/Pd of PPh<sub>3</sub> and PTSA, 3 eq/OH of olefin, 30 bar of CO; a) Conversion of total, aliphatic, and phenolic OH groups, respectively, and of acid groups, determined by <sup>31</sup>P NMR with correction factor (see SI). b) Comparison between direct esterification and carbonylation by hydroesterification - Determined by <sup>1</sup>H NMR considering the remaining unsaturations on the lignin (5.2-5.5 ppm)

As internal olefins proved to be less reactive, we turned our attention towards 10-undecenoic acid, derived from renewable ricinoleic acid via thermolytic pathway. Indeed, this terminal olefin exhibits a higher reactivity than oleic acid in carbonylative esterification. A conversion of 36 % of the total alcohols was obtained, including 22 % of the phenols, exclusively via hydroesterification reactions (entry 3). The highest conversions were obtained with the ester derivative methyl 10-undecenoate with 90 % conversion of hydroxyl groups including 90 % of phenolic groups (entry 4). As a further example, estragole as a terminal

olefin bearing an aromatic group leads to 48 % overall conversion of hydroxyl groups, including 36 % substitution of phenol groups (entry 5). Remarkably, in the present study, this enhanced reactivity pattern of terminal olefins favours the grafting of the hydroxyl sites through the hydroesterification reaction rather than classical esterification or transesterification processes.

The  $^1\text{H}$  NMR analysis of lignin modified with 10-undecenoate shows the presence of methyl ester groups with a strong, sharp peak at 3.6 ppm (Figure 3, label 6). The assignment is further evidenced by the sharper linewidth of this signal compared to others from the material, as expected by the higher chain mobility from the grafted ester chain ends. The protons of the carbon atom in alpha position relative to the carbonyl groups are also observed in the range 2.2-2.7 ppm as two signals (Figure 3, labels 1 and 5).

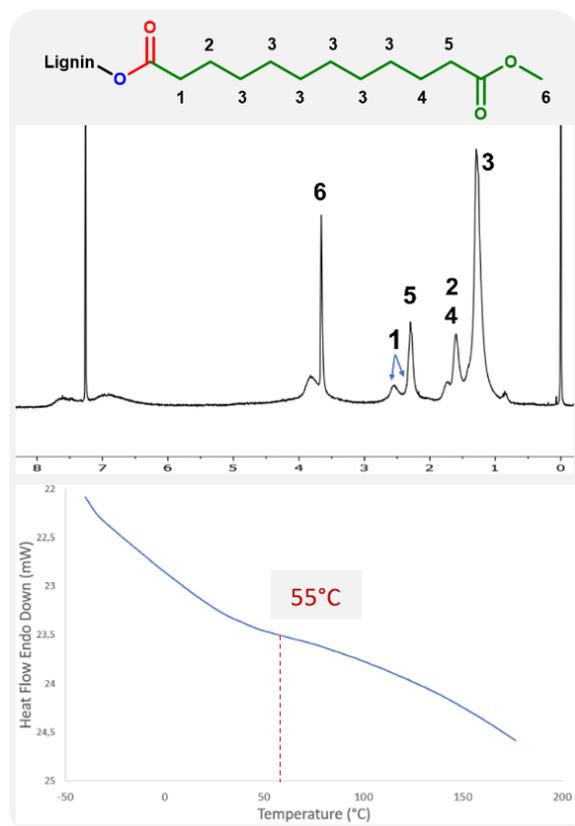

**Figure 3.**  $^1\text{H}$  NMR and DSC analysis of the product of hydroesterification of methyl 10-undecenoate with Kraft lignin (Table 4, entry 4)

The influence from the addition of this long aliphatic tail into the lignin is also evidenced by DSC with a glass transition temperature of 55 °C.


The practicality of our approach to lignin materials functionalization with methyl 10-undecenoate was probed further through a scale-up of the process. It proved to be amenable to a 100 grams scale: the resulting fully biosourced lignin-vegetable oil-based resin could then be readily shaped on hot-plates (Figure 4). This functionalized lignin is particularly interesting due to the improved compatibility provided by the long fatty chains, combined with the availability of the reactive ester functions which can be used in the formulation of blends or as a polyester macromonomer.



**Figure 4** Lignin shaping on hot plates after hydroesterification of methyl 10-undecenoate – upscaling of the experiment from Table 4 entry 4


Grafting of other polymerizable functionalities is also attractive for the valorization of lignin as a material. More specifically, unsaturations have aroused a recent interest.<sup>21</sup> Indeed, these alkenes, in addition to being directly polymerizable by metathesis, thiol-ene or radical polymerization, can also be used as a precursor for epoxy resins.<sup>22</sup> In this regard, the hydroesterification

reaction can be a clean solution for grafting unsaturations onto lignin using butadiene as a reagent. Butadiene has several advantages. As a gas under ambient conditions, the removal of excess butadiene is straightforward and the reagent is simply released at the reactor opening, easing up purification procedures. Furthermore, although butadiene is nowadays mostly petroleum-based, it can also be obtained from bioethanol.<sup>23</sup> The methoxycarbonylation of 1,3-butadiene described by M. Beller<sup>24</sup> shows the feasibility of using this gas as a reagent with aliphatic alcohols. As part of our study, this reaction was first performed with guaiacol as a phenol model to ensure the reactivity of phenols as nucleophile. In contrast to the hydroesterification reaction of non-conjugated olefins (vide supra), the hydroesterification of butadiene requires a different catalytic system and softer reaction conditions. A combination of Pd(OAc)<sub>2</sub> with dppb (1,4-bis(diphenylphosphino)butane) is used to generate the catalyst, benzoic acid is employed as co-catalyst. The reaction with guaiacol was evaluated with 1 mol% of Pd(OAc)<sub>2</sub>, 6 equivalents per Pd of dppb at 120 °C for 24 h under 25 bar of carbon monoxide. At the end of the reaction, 90 % conversion of the starting guaiacol was observed, with formation of two isomers in a 6:4 ratio. Their purification can be performed by silica gel column chromatography, though similar properties hinder the efficiency of the separation. The isomers differ in the position of the double bond on the aliphatic chain, mostly as the *trans* isomers from <sup>1</sup>H and <sup>13</sup>C NMR (See SI). The **β-δ** isomer was isolated with 52 % yield and the **α-β** isomer with 11 % yield (Scheme 3). It should be noted that no additional isomers were observed during the study, the low isolated yields are due to the arduous separation of these two products as analytically pure compounds. In addition, the same procedure was carried out with benzylic alcohol as substrate. As in the case of guaiacol, a mixture of two isomers was obtained in 94 % yield with ratio of 60 % **β-δ** isomer and 40 % **α-β** isomer (see S.I. Figure SI 9).

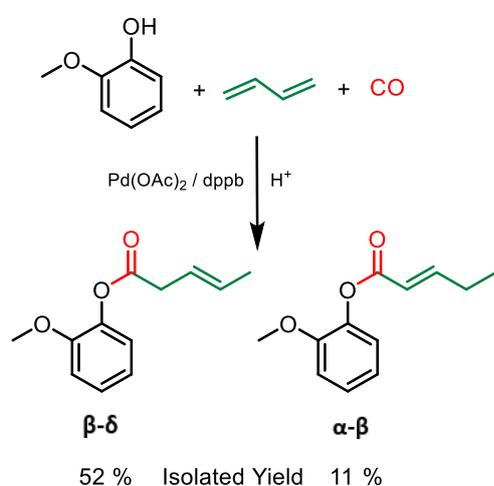

**Scheme 3** Hydroesterification of butadiene with guaiacol - Reaction conditions: Guaiacol 9 mmol, benzoic acid 0.3 eq, butadiene 7 eq, Pd(OAc)<sub>2</sub> 1 mol%, dppb 6 eq/Pd, 120 °C, 24 h, 25 bar CO, THF.


The implementation of this procedure on Kraft lignin leads to conversion of 43 % of all types of alcohols, including 40 % of phenols and 47 % of aliphatic alcohols (Table 5 entry 1). As in the case of the simple molecules, two isomers are observed as shown by <sup>1</sup>H NMR analysis of the product (see below for details). The integration of proton signals evidences a selectivity of 63 % for **β-δ** and 37 % for **α-β** isomers. Interestingly, increasing the reaction time does not improve the conversion, but does increase the ratio of **α-β** isomer (entry 2). The catalyst thus appears to initially functionalize the alcohols with the unsaturation in the **β-δ** position as the kinetic product of the reaction, and then subsequently isomerizes the double bond to the **α-β** position, thus forming the thermodynamic product. This assumption is confirmed as a reduced catalyst loading of 0.5 % leads to a lower selectivity toward the isomer **α-β** which accounts for 14 % of the mixture (entry 3). In order to maximize the functionalization of lignin alcohols, a higher catalytic loading up to 1.6 mol% of Pd was also investigated and allowed an increase of the total conversion to 67 %. Under these conditions, 52 % of the phenols and almost all of the aliphatic alcohols were converted (entry 4). Finally, such as in the case of olefin hydroesterification described above, the use of dioxane significantly increases the efficiency of the reaction. With this solvent, the reaction reaches 95 % conversion of the alcohols (93 % of phenols - entry 5). Other optimization parameters such as the reaction time or temperature have also been studied and showed a limited impact on the conversion of lignin's hydroxyl groups (see S.I. Table SI 3)

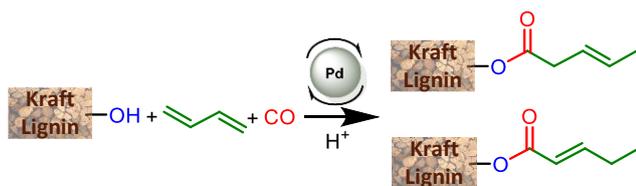**Table 5** Hydroesterification of butadiene with Kraft lignin

E	Pd(OAc) <sub>2</sub> (eq/OH)	t (h)	Conversion [%] <sup>[a]</sup>			Isomers	
			OH <sub>tot</sub>	OH <sub>al</sub>	OH <sub>ph</sub>	Ratio β-δ <sup>[b]</sup>	Ratio α-β <sup>[b]</sup>
1	1 %	15	43	47	40	63 %	37 %
2	1 %	48	46	51	43	47 %	53 %
3	0,5 %	15	13	28	6	86 %	14 %
4	1,6 %	15	67	56	70	86 %	14 %
5 <sup>[c]</sup>	1 %	15	95	99	93	95 %	5 %

Conditions: 0.5 g of Kraft lignin, 6 eq/Pd of dppb, 7 eq/OH of butadiene, 10 mL of degassed THF, 50 bar CO and 30 eq/Pd of benzoic acid, 110 °C; a) Conversion of total OH groups: comparison of the amount of chains grafted onto the lignin with the quantity of available hydroxyl groups; determined by <sup>1</sup>H NMR with pentafluorobenzaldehyde as internal standard; b) Ratio calculated by <sup>1</sup>H NMR from the integrals of signals between 2.17–2.4 and 2,7–3,45 ppm. c) Reaction performed with dioxane instead of THF

Detailed analysis of the <sup>1</sup>H NMR spectrum recorded for the material obtained from entry 5 of Table 5 shows extensive grafting of chains containing unsaturation into the lignin. The spectrum fits very well with the spectra recorded for the products obtained from simple compounds guaiacol and benzyl alcohol (Figure 5 A). The weak characteristic signals centered at 1.15 ppm, 2.25 ppm and 6.02 ppm (see labels e, g and h) show the presence of the α-β isomer as a minor component compared to the strong peak at 1.6 ppm (label d) assigned to the β-δ isomer. The presence of two signals at 2.75-3.25 ppm and 3.25-3.5 ppm corresponds to the α-CH<sub>2</sub> of the ester resulting from respectively the aliphatic and phenolic groups (labels a and i). Note also the presence of low molecular weight polybutadiene in the product due to the polymerization of butadiene under this reaction temperature. The integration of the <sup>1</sup>H NMR signals allowed a quantification of the amount of polymer, which is estimated between 5 to 10 %wt. The conversion of the two types of lignin alcohols is confirmed by the <sup>31</sup>P NMR analysis of the product after phosphorylation (Figure 5 B). The <sup>31</sup>P NMR spectrum recorded for the functionalized lignin shows very weak signals in the 146 - 150 ppm and 138 - 145 ppm ranges thus indicating that most of the aliphatic and phenolic hydroxyl groups have been converted. Carboxylic acids are also converted after reaction (signals between 134 and 136 ppm). Speculatively associated to internal esterification reactions as seen above, the reaction being performed under acidic conditions. The SEC analysis reveals a molecular weight of 5100 g.mol<sup>-1</sup> and a polydispersity index of 2.3. The M<sub>n</sub> value after modification with butadiene is significantly higher compared to those obtained above with other olefins most probably due to the presence of polybutadiene, whose shoulder is clearly observed in SEC analysis at short retention times (see S.I figure SI 40).

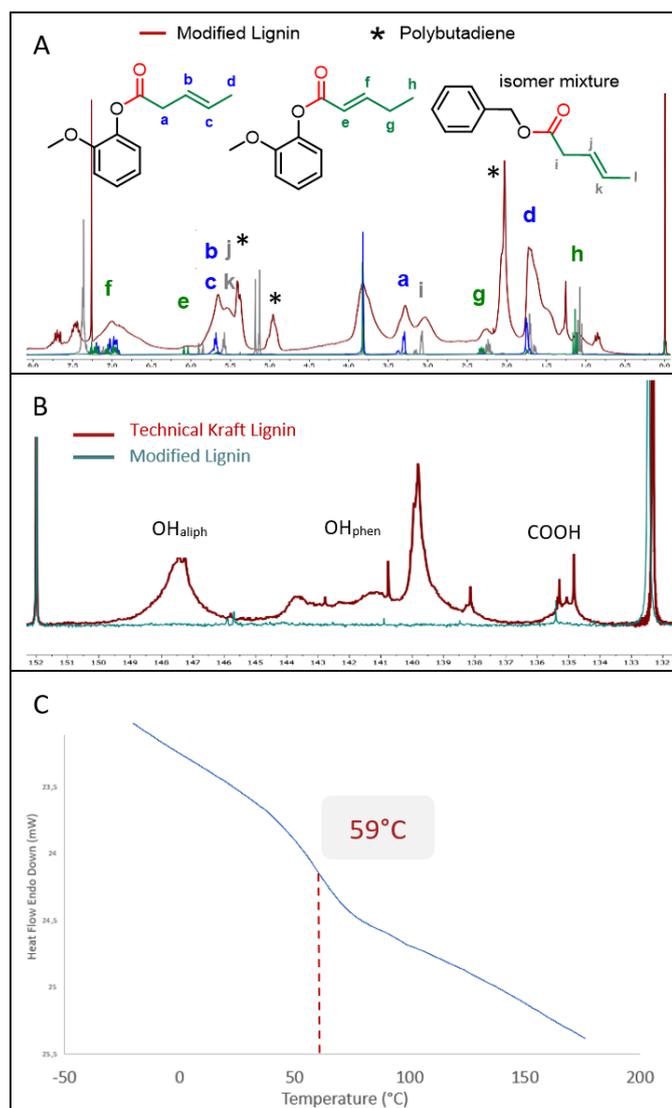

**Figure 5.**  $^1\text{H}$  NMR (A),  $^{31}\text{P}$  NMR with intensities calibrated on the internal standard (B) and DSC (C) analysis of the product of hydroesterification of butadiene with Kraft lignin (Table 5, entry 5).

Interestingly, DSC analysis of this product gives a glass transition temperature of  $59^{\circ}\text{C}$ , similar to that observed with methyl 10-undecenoate (Figure 5 C). Although the grafted chains are shorter, the presence of unsaturation and a slightly higher conversion seem to significantly impact the glass transition temperature. This modified lignin thus presents new interesting properties from a thermal point of view, with visibly improved compatibility with solvents. This material is for example soluble in toluene. Furthermore, the C-C unsaturations grafted via our catalytic functionalization protocol allow the modified lignin to be further chemically modified, for instance as macromonomer for innovative green polymer materials.

## Conclusions

A new method of lignin functionalization through the palladium-catalyzed hydroesterification reaction has been developed. The reaction readily converts hydroxyl groups of lignin into esters from a reaction with CO and an olefin without generating salts in stoichiometric amounts. Importantly, the method is effective for all types of alcohol functions, whether aliphatic or phenolic. The characterization of the esterified lignins was carried out using a combination of spectroscopic methods (NMR and IR). Thanks to a comparative study using simple molecules which provides a robust tool for the assessment of selectivity towards all alcohol types, the lignin grafting with ester functions was fully determined. Under suitable reaction conditions and broadly available catalysts, up to about 90 % of the hydroxyl groups in Kraft lignin have been readily converted. The process also proved to be suitable with other types of lignins such as Organosolv and Soda. Interestingly, the chain length of the grafted esters can be tuned by varying the nature of the starting olefin. DSC and SEC analyses demonstrated the modulation of the physicochemical properties of lignin depending on the length of the grafted chain. An ICP study also indicates that only limited amount of palladium is contained in the

final product thanks to its removal during the purification phase. Reagents such as butadiene or bio-based fatty esters have allowed the introduction of new reactive functions within lignin while significantly lowering glass transition temperatures. Furthermore, a scale-up to 100 g scale was successfully carried out, resulting in a moldable bio-sourced material. Thanks to the versatility of this approach, new lignin-based shapable resins can thus be produced and these can be functionalized with cross-linkable functions such as double bonds or esters. Thus, our versatile catalytic process offers an efficient and selective entry towards new biosourced thermosetting polyester materials based on lignin with highly tunable properties.

## Materials and methods

### General considerations

Kraft lignin was provided by UPM Biochemicals, Organosolv by ChemicalPoint and Soda by GreenValue Enterprises LLC. Lignins were dried at reduced pressure at 60 °C for 48 h before use. Chemicals were purchased from Aldrich, Alfa Aesar, Acros and Strem. Butadiene was purchased from Linde Gas France. Tetrahydrofuran was purified using a MBraun SPS-800 solvent purification system. DSC measurements were carried out using a Perkin-Elmer DSC 4000 differential scanning calorimeter. The measurements were done with a heating rate of 10 K/min in the temperature range from 243 K to 453 K, under nitrogen flow (20 ml/min).

NMR spectra were recorded in CDCl<sub>3</sub> (99.8 % atom D), purchased from Aldrich. <sup>1</sup>H NMR spectra were obtained at either 300 and 400 MHz, <sup>13</sup>C were recorded at 75 MHz with <sup>1</sup>H decoupling and 101 MHz with both <sup>1</sup>H and <sup>31</sup>P decouplings, and <sup>31</sup>P spectra were acquired at 121 and 162 MHz with <sup>1</sup>H decoupling. Chemical shifts (<sup>1</sup>H and <sup>13</sup>C) were referenced in parts of million relative to TMS ( $\delta=0.00$  ppm) and were referenced to the residual solvent peak (<sup>1</sup>H, CDCl<sub>3</sub> 7.26 ppm). Diffuse reflectance infrared spectra were collected with a Harrick cell on a Nicolet Avatar spectrometer fitted with a MCT detector. Typically, 64 scans were accumulated for each spectrum (resolution of 4 cm<sup>-1</sup>).

The number-average ( $M_n$ ), the weight-average ( $M_w$ ) molecular weights and the dispersity ( $\mathcal{D}$ ) of the product were determined by Size Exclusion Chromatography (SEC) in tetrahydrofuran at 40 °C at a flow rate of 1 mL.min<sup>-1</sup>. Sample concentration was of 0.50 w%.  $M_n$ ,  $M_w$ , and  $\mathcal{D}$  were determined from the Refractive Index (RI) signal using a calibration curve based on polystyrene (PS) standards from Polymer Standards Service, on a Waters apparatus equipped with Waters Styragel columns HR2, HR3, HR5 and HR5E.

Nickel (231,604 nm) and palladium (340,458 nm) concentrations were determined using an Agilent's 5110 Vertical Dual View ICP-OES equipped with a OneNeb nebulizer, a quartz double pass spray chamber and a quartz torch (Agilent). Quantifications were carried out by an external calibration approach.

### Titration of the hydroxyl groups in the technical lignins and modified lignins

<sup>31</sup>P NMR experiments were carried out following a previously reported method<sup>25</sup>: Lignin (30 mg) was dissolved in a CDCl<sub>3</sub>/pyridine mixture (1:1.6 v/v, 0,5 mL). The phosphitylation reagent, 2-chloro-4,4,5,5-tetramethyl-1,3,2-dioxaphospholane (150  $\mu$ L), and the internal standard N-hydroxy-6-norbornene-2,3-dicarboximide (100  $\mu$ L of 0.1 M solution in 1:1.6 v/v CDCl<sub>3</sub>/pyridine mixture) were added successively. Chromium(III) acetylacetonate (100  $\mu$ L of 0.014M solution) in the same CDCl<sub>3</sub>/pyridine mixture was added to the solution in order to homogenize and accelerate phosphorus relaxation. Spectra were recorded with a 15 sec relaxation time and an average number of 512 scans. Chemical shifts are relative to the signal of the phospholane hydrolysis product at 132.2 ppm. The integrated value of the internal standard was used for calculation of the absolute amount of each functional group. Comparison between the amount of technical lignin functional group and the amount of hydroesterified lignin functional groups gave the substitution ratio of hydroxyl groups. This method includes a correction factor for integrations of modified lignins considering the reduced lignin content (see SI).

### General procedure for olefins/fatty esters hydroesterification on lignin

An autoclave was charged with lignin (500 mg), palladium acetate (6 mg, 0.027 mmol), triphenylphosphine (175 mg, 0.67 mmol), and paratoluenesulfonic acid (115 mg, 0.67 mmol). After performing three vacuum/N<sub>2</sub> cycles, degassed dioxane (10 mL) and degassed olefin (9.15 mmol) were added into the autoclave. The reactor was pressurized under 30 bar of carbon monoxide and then heated to 120 °C for 22 h under magnetic stirring with a cross magnet. After cooling, the excess gas was evacuated, the solvent was evaporated, and the crude was solubilized in 3 mL THF and precipitated with petroleum ether (30 mL). The product was washed 3 times with petroleum ether (10 mL) The resulting brown powder was dried at 60 °C under reduced pressure for 24 h.

### General procedure for butadiene hydroesterification on kraft lignin

Kraft lignin (500 mg), palladium acetate (6 mg, 0.026 mmol), 1,4-bis(diphenylphosphino)butane (70 mg, 0.16 mmol), and benzoic acid (100 mg, 0.82 mmol) were introduced into an autoclave. After performing three vacuum/N<sub>2</sub> cycles, distilled and degassed THF (10 mL) is added to the reaction medium and the autoclave is cooled to -40 °C. Butadiene (2 mL, 1.2 g, 22 mmol) is condensed in a Schlenk tube kept cold by an acetone/dry ice mixture and then introduced into the reactor by cannula. The reactor is pressurized under 50 bar of carbon monoxide and then heated at 120 °C for 22 h under magnetic stirring with a cross-shaped magnet. After the reaction, the reactor is cooled to room temperature and the excess gas is evacuated. The solvent is extracted with a rotary

evaporator. The crude is solubilized in 3 mL THF and the modified lignin is precipitated in 30 mL petroleum ether. After settling for one hour, the lignin is recovered and dried under vacuum at 80 °C overnight.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

We acknowledge the Ministère de l'Enseignement Supérieur, de la Recherche et de l'Innovation, the CNRS, the Hauts-de-France Region and Icam for their financial support. We acknowledge C. Delabre for HR-MS analysis. ICP analyses were performed in the « Spectrométrie par torche à plasma » platform of the Research Federation Michel-Eugène Chevreul hosted by the LASIRE laboratory.

## Notes and references

- 1 a) D. S. Bajwa, G. Pourhashem, A. H. Ullah and S. G. Bajwa, *Ind. Crops Prod.*, 2019, **139**, 111526. b) Laurichesse and L. Avérous, *Prog. Polym. Sci.*, 2014, **39**, 1266–1290.
- 2 A. E. Kazzaz, Z. H. Feizi and P. Fatehi, *Green Chem.*, 2019, **21**, 5714–5752.
- 3 O. Gordobil, I. Egüés, R. Llano-Ponte and J. Labidi, *Polym. Degrad. Stab.*, 2014, **108**, 330–338.
- 4 K. Huang, S. Ma, S. Wang, Q. Li, Z. Wu, J. Liu, R. Liu and J. Zhu, *Green Chem.*, 2019, **21**, 4964–4970.
- 5 a) Y. Xu, L. Yuan, Z. Wang, P. A. Wilbon, C. Wang, F. Chu and C. Tang, *Green Chem.*, 2016, **18**, 4974–4981. b) C. Wang and R. A. Venditti, *ACS Sustain. Chem. Eng.*, 2015, **3**, 1839–1845.
- 6 R. Paul, B. John and S. K. Sahoo, *Biomacromolecules*, 2022, **23**, 816–828.
- 7 M. A. Jedrzejczyk, S. Van den Bosch, J. Van Aelst, K. Van Aelst, P. D. Kouris, M. Moalin, G. R. M. M. Haenen, M. D. Boot, E. J. M. Hensen, B. Lagrain, B. F. Sels and K. V. Bernaerts, *ACS Sustain. Chem. Eng.*, 2021, **9**, 12548–12559.
- 8 J. Huang, Q. Guo, R. Zhu, Y. Liu, F. Xu and X. Zhang, *Int. J. Biol. Macromol.*, 2021, **189**, 635–640.
- 9 D. Wang, S. H. Lee, J. Kim and C. B. Park, *ChemSusChem*, 2020, **13**, 2807–2827.
- 10 Difference of reactivity between aliphatic alcohol and phenol in esterification reaction through carbodiimide coupling: R. Shelkov, M. Nahmany and A. Melman, *Org. Biomol. Chem.*, 2004, **2**, 397–401.
- 11 T. Saito, R. H. Brown, M. A. Hunt, D. L. Pickel, J. M. Pickel, J. M. Messman, F. S. Baker, M. Keller and A. K. Naskar, *Green Chem.*, 2012, **14**, 3295–3303.
- 12 a) S. Laurichesse, C. Huillet and L. Avérous, *Green Chem.*, 2014, **16**, 3958–3970. b) P. Buono, A. Duval, L. Averous and Y. Habibi, *ChemSusChem*, 2017, **10**, 984–992.
- 13 C. Scarica, R. Suriano, M. Levi, S. Turri and G. Griffini, *ACS Sustain. Chem. Eng.*, 2018, **6**, 3392–3401.
- 14 C. Dumont, F. Belva, R. M. Gauvin and M. Sauthier, *ChemSusChem*, 2018, **11**, 3917–3922.
- 15 a) J. F. Knifton, *J. Org. Chem.*, 1976, **41**, 2885–2890. b) Knifton, J. F. J. Am. Oil Chem. Soc. 1978, 55 (5), 496–499 c) Shell (Drent, E.) EP 0,271,144, 1988 d) Shell (Drent, E.) EP 0,186,228, 1986
- 16 W. Reppe, N. V. Kutepow, K. R. Rueppurr, H. Bille. U.S. Patent. 3.014.962. 1961. 18
- 17 W. Reppe, N. V. Kutepow, W. Kölsch. DE 927090 C. 1955
- 18 a) G. Kiss, *Chem. Rev.*, 2001, **101**, 3435–3456. b) I. del Río, C. Claver and P. W. N. M. van Leeuwen, *Eur. J. Inorg. Chem.*, 2001, **2001**, 2719–2738.
- 19 K. Shimada, S. Hosoya and T. Ikeda, *J. Wood Chem. Technol.*, 1997, **17**, 57–72.
- 20 a) A. Granata and D. S. Argyropoulos, *J. Agric. Food Chem.*, 1995, **43**, 1538–1544. b) G. Gellerstedt, *Ind. Crops Prod.*, 2015, **77**, 845–854.
- 21 a) L. C. Over and M. A. R. Meier, *Green Chem.*, 2015, **18**, 197–207. b) A. Duval and L. Avérous, *ChemSusChem*, 2017, **10**, 1813–1822
- 22 M. Jawerth, M. Lawoko, S. Lundmark, C. Perez-Berumen and M. Johansson, *RSC Adv.*, 2016, **6**, 96281–96288.
- 23 G. Pomalaza, P. A. Ponton, M. Capron and F. Dumeignil, *Catal. Sci. Technol.*, 2020, **10**, 4860–4911.
- 24 M. Beller, A. Krotz and W. Baumann, *Adv. Synth. Catal.*, 2002, **344**, 517–524.
- 25 a) A. Granata, D. S. Argyropoulos, *J. Agric. Food Chem.* 1995, **43**, 1538–1544; b) G. Gellerstedt, *Ind. Crops Prod.* 2015, **77**, 845–854.