



HAL
open science

Green ultrafiltration membranes

Yaocihuatl Medina-Gonzalez, Jean-Christophe Remigy

► **To cite this version:**

Yaocihuatl Medina-Gonzalez, Jean-Christophe Remigy. Green ultrafiltration membranes. 2nd International Congress on Green Process Engineering, 2nd European Process Intensification Conference, Jun 2009, Venise, Italy. pp.0. hal-04029598

HAL Id: hal-04029598

<https://hal.science/hal-04029598>

Submitted on 15 Mar 2023

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Open Archive Toulouse Archive Ouverte (OATAO)

OATAO is an open access repository that collects the work of Toulouse researchers and makes it freely available over the web where possible.

This is an author-deposited version published in: <http://oatao.univ-toulouse.fr/>
Eprints ID : 3007

To link to this article :

URL : <http://www.gpe-epic2009.org/>

To cite this version : Medina Gonzalez, Y. and Remigy, Jean-Christophe (2009) [*Green ultrafiltration membranes*](#). In: 2nd International Congress on Green Process Engineering, 2nd European Process Intensification Conference, 14-17 June 2009, Venise, Italie.

Any correspondence concerning this service should be sent to the repository administrator: staff-oatao@inp-toulouse.fr

GREEN ULTRAFILTRATION MEMBRANES

Medina-Gonzalez Y., Remigy J. C.*

Laboratoire de Génie Chimique, Université Paul Sabatier, 118 Route de Narbonne, 31062

Toulouse Cedex

remigy@chimie.ups-tlse.fr

Abstract

As it is generally accepted, utilization of membranes have several advantages, nevertheless, fabrication of membranes is a process that is not as clean as it could be. In fact, polymeric membranes are currently fabricated by wet phase inversion. In this method, a solution of a polymer and a porogen is cast on a glass plate. The glass plate is then immersed into a coagulation bath. This coagulation bath consists in a non-solvent of the polymer; this non-solvent must be miscible with the polymer solvent. A polymeric porous membrane is then obtained. Depending on the polymer, solvents like NMP, DMF, DMSO acetone, cyclohexane, chloroform, etc are used. On this method, the solvent is currently lost during the manufacturing process: it is mixed with the non-solvent and sent directly to the wastewater treatment plant.

The aim of this work was the utilization of solvents derived from renewable resources, biodegradable and non VOCs to obtain membranes by a green way. Methyl-(s)-lactate has been used as solvent for cellulose acetate. LiCl and CaCl₂ were used as porogens and water was used as coagulation bath. These two salts are naturally present into sea or brackish waters and they have been used in this work as green porogens.

The membranes obtained were characterized using SEM (Scanning Electronic Microscope). Water permeability and molecular cut off were determined too. Different sizes of PEG (4,600-200,000 of Mw, Aldrich, France) were used for tests of molecular cut off [1].

CaCl₂ used as porogen, produced membranes with a “sponge like” structure; this structure is very appropriate to obtain pressure resistant membranes as our tests demonstrated, this membrane supported up to 5 bars, a smooth surface without defects was revealed on MEB observations. Membranes fabricated with LiCl as porogen presented vacuoles and probably some defects at the membrane surface. The obtained MWCO was from 15 to 35 kDa that lies on the ultrafiltration domain.

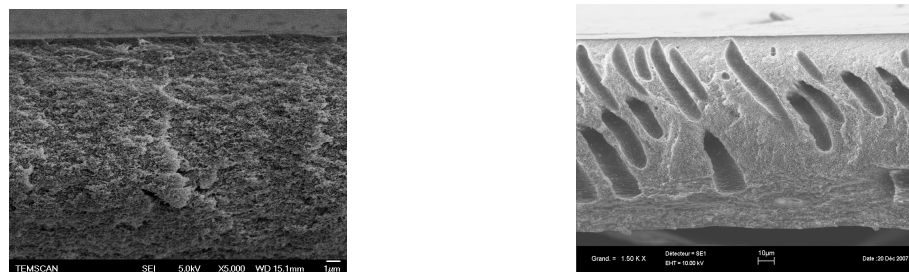


Fig 1 Membranes obtained by using (a) CaCl₂ and (b) LiCl as porogens

[1] C. Causserand, S. Rouaix, A. Akbari, P. Aimar, *J. Membr. Sci.* 238 (2004) 177–190.