



HAL
open science

ZnGa₂O₄ and ZnGa₂O₄:N thin films applied as sensors for detection of acetaldehyde in ethanol

Idio Alves de Sousa Filho, Jose Fernando Dagnone Figueiredo, Valérie Bouquet, Andre Luiz Menezes de Oliveira, Ronan Lebullenger, Iêda Maria Garcia dos Santos, Maryline Guilloux-Viry, Odile Merdrignac-Conanec, Ingrid Távora Weber

► To cite this version:

Idio Alves de Sousa Filho, Jose Fernando Dagnone Figueiredo, Valérie Bouquet, Andre Luiz Menezes de Oliveira, Ronan Lebullenger, et al.. ZnGa₂O₄ and ZnGa₂O₄:N thin films applied as sensors for detection of acetaldehyde in ethanol. *Physica B: Condensed Matter*, 2023, 658, pp.414834. 10.1016/j.physb.2023.414834 . hal-04115620

HAL Id: hal-04115620

<https://hal.science/hal-04115620>

Submitted on 21 Nov 2023

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution - NonCommercial 4.0 International License

CRedit author statement

Idio Alves de Sousa Filho: Writing- Original Draft Preparation, Conceptualization, Formal Analysis, Reviewing and Editing.

José Fernando Dagnone Figueiredo: Conceptualization, Investigation, Methodology, Formal Analysis

Valerie Bouquet: Writing, Reviewing and Editing, Resources, Supervision.

André Luiz Menezes de Oliveira: Writing- Original Draft Preparation, Reviewing and Editing.

Ronan Lebullanger: Writing, Reviewing and Editing, Resources.

Iêda Maria Garcia dos Santos: Writing, Reviewing and Editing, Resources.

Maryline Guilloux-Viry: Writing, Reviewing and Editing, Resources, Supervision.

Odile Merdrignac-Conanec: Writing, Reviewing and Editing, Resources, Supervision.

Ingrid Tavora Weber: Writing, Reviewing and Editing, Resources, Supervision, Funding acquisition.

ZnGa₂O₄ and ZnGa₂O₄:N thin films applied as sensors for detection of acetaldehyde in ethanol

Idio Alves de Sousa Filho^{1*}, *José Fernando Dagnone Figueiredo*^{3,4,5}, *Valerie Bouquet*³, *André Luiz Menezes de Oliveira*^{3,6}, *Ronan Lebullenger*³, *Ieda Maria Garcia Santos*⁶, *Maryline Guilloux-Viry*³, *Odile Merdrignac-Conanec*³, *Ingrid Tavora Weber*^{2,4}.

¹*QuiARA, Instituto de Química, Universidade Federal Rural do Rio de Janeiro, Seropédica, RJ, Brazil 23897-000*

²*Instituto de Química, Universidade de Brasília, Brasília, DF, Brazil 70910-900*

³*Univ Rennes, CNRS, ISCR – UMR 6226, F-35000 Rennes, France*

⁴*LIMC, Dept. de Química Fundamental, Universidade Federal de Pernambuco, Recife, PE, Brazil 50740-560*

⁵*Universidade Federal Rural de Pernambuco, Cabo de Santo Agostinho, PE, Brazil 52171-900*

⁶*NPE/LACOM, Dept. de Química, Universidade Federal da Paraíba, Campus I, João Pessoa, PB, Brazil 58059-900;*

**Corresponding author: idiofilho@ufrj.br*

Abstract

Acetaldehyde, a byproduct of fermentation, is a highly toxic contaminant. Therefore, it is important to develop cost-effective, fast-response and portable acetaldehyde sensors to monitor the formation of this contaminant in the process. Herein, we have evaluated the potential use of ZnGa_2O_4 and $\text{ZnGa}_2\text{O}_4\text{:N}$ (referred as ZnGaON) films as vapor sensors of ethanol containing acetaldehyde. Sensors based on ZnGa_2O_4 films were successfully prepared by PLD on Al_2O_3 substrates containing interdigitated Pt electrodes. The nitridation was carried out under NH_3 gas flow at $700\text{ }^\circ\text{C}$, to obtain ZnGaON films. The prepared sensors presented high sensitivity to acetaldehyde, allowing identification of acetaldehyde in ethanol (300 ppm). This acetaldehyde concentration corresponds to the limit established by Brazilian legislation to sugarcane alcoholic beverages (*caçapa*). The ZnGaON sensor should be operated at moderate temperature ($450\text{ }^\circ\text{C}$), and response time of 43 s and recovery time of 26 s are quite fast. The results strongly suggest that ZnGaON may be considered a potential candidate for the development of an efficient screening test for a highly sensitive and selective identification of acetaldehyde in beverages, foods, or fuel.

Keywords: ZnGa_2O_4 , ZnGaON, PLD, Gas Sensors, Acetaldehyde, acetaldehyde-containing ethanol

1. Introduction

The development of cost-effective, fast-response and portable sensors for the detection of toxic and dangerous gases is in high demand due to the need to protect the well-being and quality of human health, as well as monitoring environment contamination. One target substance to be monitored is acetaldehyde because it is highly carcinogenic according to the International Agency for Research on Cancer [1]. One important way to acetaldehyde exposure is fermented foods and alcohol consumption since it can be naturally produced during fermentation process [2,3]. Thus, monitoring acetaldehyde in fermented foods and drinks is a point of great interest for food industry.

Gas chromatography (GC) and mass spectrometry (MS) are the reference techniques for acetaldehyde identification [4]. However, these techniques involve specific and expensive instrumentation and long periods of analysis [2–4]. So, the development of low cost, simple and reliable acetaldehyde sensor is considered as an actual alternative for screening tests. In this context, semiconductor sensors can be a quite interesting alternative due to their robustness, long term stability and low cost [5,6].

Semiconductor-based ethanol sensors are numerous in the literature [5,7–14], but very few works dealing with acetaldehyde detection can be found [3,15–19]. For instance, Veríssimo *et al.* [15] determined the acetaldehyde content in ciders using the solid phase micro-extraction followed by detection with an acoustic wave sensor based on a piezoelectric quartz crystal coated with a polyoxometalate salt. Gunasekaran *et al.* [16] prepared ZnO:F thin films and used them as gas sensors for acetaldehyde detection in air. Donato *et al.* [17] developed a sensor based on ZnO deposited on crystal microbalance to detect acetaldehyde in air. In other work, Mani *et al.* [3] prepared undoped, and Ni, Co and Cu-doped ZnO nanostructured films by chemical spray pyrolysis technique and employed them as sensors for a variety of gas, including methanol, ethanol, acetone, formaldehyde, acetaldehyde, among others. The authors observed, at room temperature, the highest selectivity for the films towards acetaldehyde with a detection limit of 10 ppm.

Among a variety of semiconductor sensors for gas detection, spinel-based materials have attracted much interest for such applications due to their compositional and structural flexibility, which allow different chemical modifications in order to tune their properties [20–22]. In this context, zinc gallium oxide (ZnGa_2O_4) and oxynitride ($\text{ZnGa}_2\text{O}_4:\text{N}$) can offer a great potential alternative to be used in sensing practical devices.

ZnGa₂O₄ is a wide band gap semiconductor, with band gap energy between 4.5-5.2 eV and it presents interesting luminescent emission [23]. This oxide is transparent in near-UV region, with a strong blue luminescence under excitation of either ultraviolet light or low-voltage electrons [24,25]. Besides these interesting properties, an advantage that makes ZnGa₂O₄ a promising material for the use in electronic devices is its high resistance in aggressive chemical environments and its stability in a wide range of temperature [26]. On the other hand, zinc gallium oxynitride (ZnGa₂O₄:N, hereafter referred as ZnGaON) presents high interest for visible-light photocatalytic activity [27–30]. It may also be very interesting for gas sensing applications, as showed by Kerlau *et al* [31], who used screen printed gallium oxynitride thin films and observed an important response in the presence of ethanol, CO and propane.

In this paper, we report the preparation of ZnGa₂O₄ and ZnGaON films using the pulsed laser deposition (PLD) technique. The oxynitride films were obtained by nitridation of the PLD-deposited oxide films under NH₃ gas flow at 700°C. Based on different literature studies and on the investigations performed by Mani *et al* concerning oxide sensors for detection of different gases [3], both oxide and oxynitride films were investigated for detection of acetaldehyde-containing ethanol aiming a possible screening test of beverages as, for example, the Brazilian cachaça. Our study provides insights into the preparation of promising gas sensor devices for efficient and sensitive acetaldehyde detection.

1.2 Experimental

1.2.1 Preparation of ZnGa₂O₄ and ZnGaON films

For the deposition of thin films using PLD technique, labmade sintered target of ZnGa₂O₄ was prepared by the conventional solid-state reaction using stoichiometric amounts of Ga₂O₃ (Strem Chemicals – 99,99%) and ZnO (Alfa Aesar – 98%) as starting chemical materials. The reactants were weighed grinded in an agate mortar for about 25 min, uniaxially pressed at 150 kg cm⁻² and pellets were calcined at 1100 °C for 12h to obtain ZnGa₂O₄[32].

The ZnGa₂O₄ target was used to grow thin films by PLD onto screen-printed interdigitated Pt electrodes on polycrystalline Al₂O₃ substrates equipped with a Pt resistance heater printed on the reverse side (Figure 1). Before deposition, alumina substrates with platinum electrodes were cleaned by rinsing with distilled water and isopropanol and dried with a hot air gun. Alumina was chosen as a substrate because it is cheap, stable, tough, besides

presenting high mechanical, thermal and chemical resistance [33]. Considering preliminary studies carried out by our research group, the best conditions for films preparation were determined as: deposition at room temperature for 30 min, laser beam energy of 220 mJ, operating at 5 Hz and oxygen pressure in the deposition chamber regulated at 0.06 mbar. A KrF excimer laser with 248 nm radiation wavelength was used.

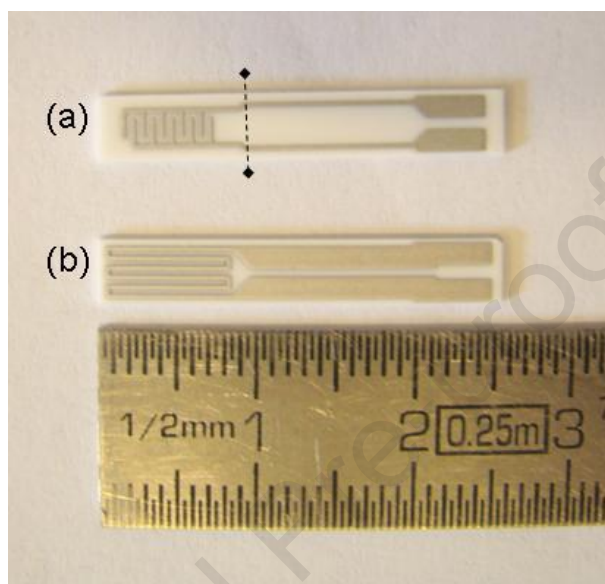


Figure 1 - Al_2O_3 substrate equipped with (a) interdigitated Pt electrodes at one side and (b) Pt heater at the reverse side. Interdigitated area at left of the dashed line.

The preparation of ZnGaON films was carried out by heat treatment under ammonia gas flow of the room temperature PLD-grown ZnGa_2O_4 films in a tubular furnace. First, the films were heated, under N_2 flow, up to $400\text{ }^\circ\text{C}$ at a heating rate of $10\text{ }^\circ\text{C min}^{-1}$. Then, the N_2 gas was replaced by NH_3 (20 L h^{-1}) and the temperature raised up to $700\text{ }^\circ\text{C}$ at a rate of $10\text{ }^\circ\text{C min}^{-1}$ [32]. The films remained at this temperature under NH_3 flow for a period of 24 h and then, were inertially cooled. Thin films were also deposited by PLD at $650\text{ }^\circ\text{C}$ in order to compare the sensor properties of the crystalline oxide ZnGa_2O_4 and the oxynitride.

The films were analyzed by X-Ray diffraction (XRD, Bruker D8 monochromatic $\text{CuK}\alpha_1$ radiation) and Scanning Electron Microscopy with Field Emission Gun (FEG-SEM, Jeol 6301-F for imaging).

1.2.2 Sensing Tests

Sensing tests were performed in a teflon testing chamber. Resistance measurements of sensors were simultaneously made by a Picoammeter/Voltage Source (Model 6487 – Keithley,

USA) combined with a scanner (Switch System Model 7001 – Keithley, USA), connected to a computer via an IEEE port. Gas flows were fixed at 6.5 L h⁻¹ for pure ethanol, acetaldehyde, and methanol, while a flow at 1.0 L h⁻¹ was used for acetaldehyde-containing ethanol sensing experiments. Prior to gas exposure, electrical resistances of the sensors were stabilized under carrier gas (synthetic air for pure ethanol and acetaldehyde tests and synthetic air saturated with ethanol for acetaldehyde-containing ethanol test). After 10 min of exposure to testing gas, the sensors were purged for 20 min using carrier gas flow (synthetic air or synthetic air saturated with ethanol) to allow the sensors to recover. The concentration of acetaldehyde in the mixture with ethanol was 300 mg L⁻¹ (300 ppm), with reference to the limit established in the Brazilian legislation for the formulation of sugarcane liquor [34].

Operating temperatures of sensors ranged from 200 to 500 °C [35,36]. Sensor signals defined as R_{gas}/R_0 or R_0/R_{gas} (depending on the reducing/oxidizing character of the atmosphere and sensor signal >1 by convention), where R_0 is the sensor resistance in reference gas (air) and R_{gas} is the sensor resistance under test gas, were used to assess the sensitivity of the sensors. Response time (t_{90}) was determined as the time required for the resistance to fall by 90% and recovery time (t_{90R}) as the time necessary for the resistance to recover 90% of its initial value. Each response consists in an average response of three similar sensors.

1.3 Results and Discussion

1.3.1 Film characteristics

A single-phase spinel-like ZnGa₂O₄ labmade target was successfully obtained to prepare the precursor films, as displayed in Figure S1, which shows its XRD pattern. As expected, the films deposited at 650 °C presented the crystalline ZnGa₂O₄ phase whereas no peak was observed for the film deposited at room temperature (Figure S2), which is consistent with an amorphous nature. Amorphous films favor the nitridation process, as already described in literature [35–37], that reports a better nitridation performance when the oxide precursor is amorphous or highly disordered. The films, with a thickness of about 500 nm, covered well the grains of the substrate, with good adhesion as well as with quite good electrode substrate coverage even at the Pt/Al₂O₃/ interface as shown in Figure 2.

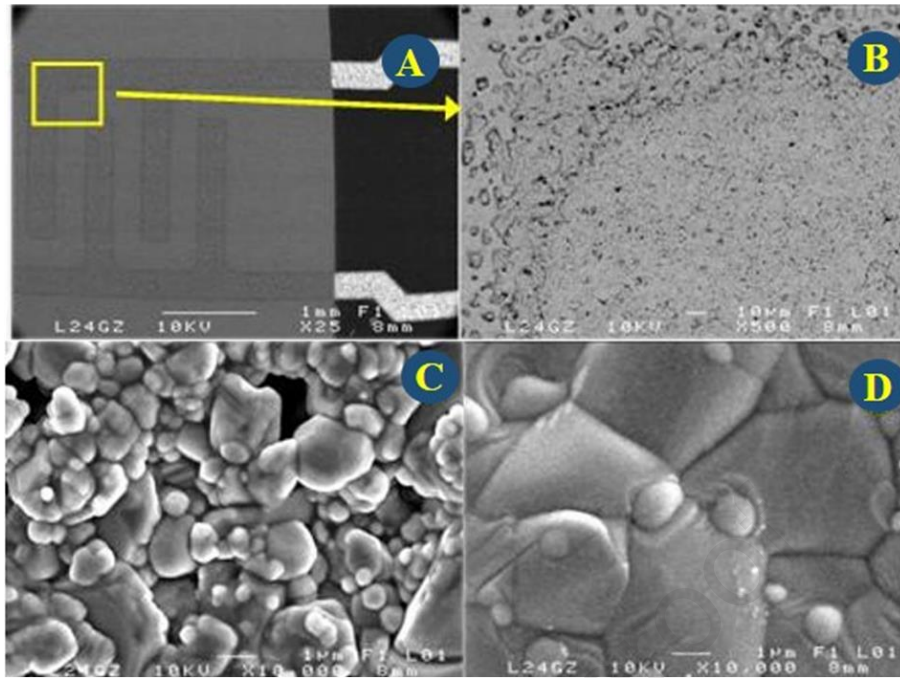


Figure 2 – FE-SEM images of ZnGa_2O_4 films grown by PLD, on Pt/alumina substrate electrodes. (A) overview of the film deposited at at $650\text{ }^\circ\text{C}$ and, (B) detail of intermediate region between alumina substrate and Pt electrode; (C) detail of the film covering electrodes and (D) the film in the intermediate region.

The amorphous films were submitted to heat treatment at $700\text{ }^\circ\text{C}$ under NH_3 in order to obtain nitrated ZnGa_2O_4 (ZnGaON). XRD patterns of films after nitridation (Figure 3A) suggest the formation of an oxynitride poorly crystalline phase by two small peaks at $2\theta = 34.5^\circ$ and 36.8° , which could be related to (006) and (103) crystallographic planes by analogy with GaO_xN_y (ICDD 32-0398), respectively. The nitrated samples exhibited porous and rough aspect, as expected [31,32,38], with quite good substrate coverage even at the Pt/ Al_2O_3 /interface. After nitridation, it can be clearly observed on the FE-SEM images the small grains of the films on the large grains of alumina (Figure 3B and 3C). The film presented good adhesion after nitridation (i.e. high enough to enable the sensing measurements), contrary to what de Lucas *et al.* [39] have observed for GaN_xO_y films deposited on GaAs substrates by chemical vapor deposition.

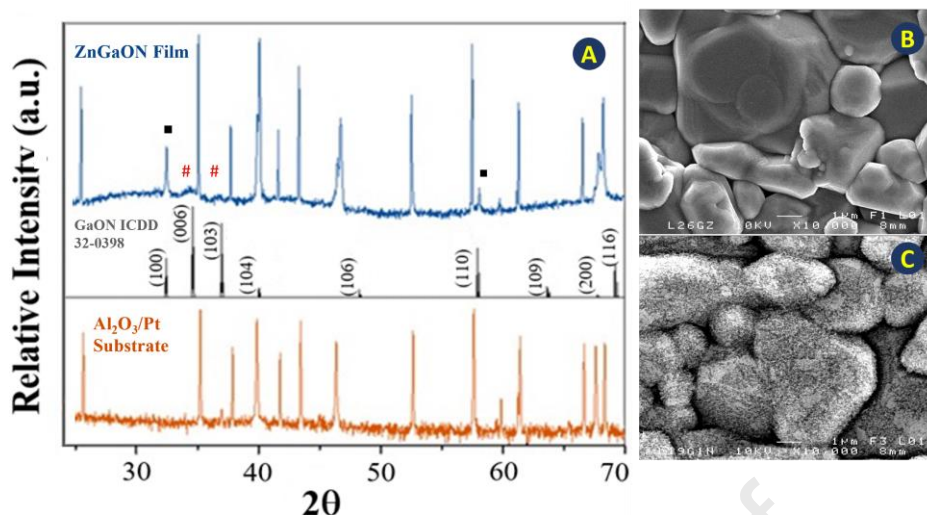


Figure 3 – (A) XRD patterns of the “ZnGaON” film on Pt/alumina. Film grown by PLD at room temperature for 30 min using ZnGa_2O_4 target and nitrided at 700 °C for 24 h. #ZnGaON and ■ unidentified peaks. (B) FE-SEM images of the film deposited at room temperature (amorphous film on alumina grains), (C) FE-SEM images after nitrided at 700 °C.

1.3.2 Gas sensing measurements.

A preliminary study was performed to assess the potential of the sensor towards pure ethanol (Figure S3) and pure acetaldehyde (Figure S4). The first test was carried out exposing sensors to ethanol vapor and the results showed that both crystalline ZnGa_2O_4 and ZnGaON films (Figure S3) presented a maximum response at 400 °C (sensitivity = 275 and 140 respectively). According to literature, the sensing mechanism in gallate-based sensors results from the presence of ionic defects such as oxygen vacancies or cationic vacancies [20,40]. In the present case, ZnGa_2O_4 and ZnGaON presented similar temperatures of maximum sensitivity, with better results for the oxide. Sensitivity values obtained in the present work are smaller than those reported by Kerlau *et al.* [31] using a GaON thick film ($S_{\text{max}} \approx 1000$). Moreover, Kerlau *et al.*[31] observed maximum sensitivity at lower temperature (275 °C).

Results for acetaldehyde using both sensors, ZnGa_2O_4 and ZnGaON, are displayed in Figure S4 and showed a greater sensitivity to acetaldehyde than to ethanol. The most promising result was observed for ZnGaON, with $S_{\text{max}} \sim 11000$ at 400 °C, a remarkable response, which showed ~70-fold increase in maximum sensitivity comparing to ethanol. Ahmadnia-Feyzabad *et al.* [41] also observed a higher response to acetaldehyde than to ethanol using SnO_2 -based sensors. The authors attribute this fact to an easier adsorption and decomposition of aldehyde on the surface of the sensor. In relation to sensitivity and selectivity of the sensors, Mani *et al* [3] evaluated the potential employment of undoped ZnO and Ni, Co, and Cu-doped ZnO-based

sensors to detect a variety of gas and confirmed the highest selectivity of the sensors to acetaldehyde at room temperature.

Table 1 lists the acetaldehyde gas sensing performances of the prepared ZnGa₂O₄ and ZnGaON based sensors in comparison with different other oxide-based sensors reported in the literature. Concerning recovery time, values of $t_{90R} = 1260$ s and $t_{90} = 143$ s for ZnGa₂O₄ at 450 °C and $t_{90R} = 208$ s and $t_{90} = 145$ s for ZnGaON at 400 °C were observed (Figure S4). According to the preliminary studies, ZnGaON responds faster and recovers even faster to acetaldehyde gas.

Table 1. Comparison of acetaldehyde gas sensing performance of different sensor materials

Sensor	Gas conc. (ppm)	Temp. (°C)	Response (R_0/R_{gas})	Ref
ZnO branched nanorods	100	Room temp.	2.85	[3]
Co-doped ZnO nanorods	100	Room temp.	800	[3]
ZnO microflowers	250	400	8	[8]
In ₂ O ₃ nanospheres	100	300	11	[18]
PdO@ZnO	100	350	76	[19]
Au@SnO ₂	500	300	0.85	[42]
Al-doped ZnO	10	500	2250	[43]
ZnO platelets	50	Room temp.	50	[53]
ZnGa ₂ O ₄	300	450	1450	
ZnGaON	300	400	11000	This work
ZnGaON	300	450	1130	

As films showed quite high response to acetaldehyde, the ability of differentiating pure ethanol and acetaldehyde-containing ethanol was then investigated (Figure 4). According to the parameters established by Brazilian laws, a limit of 30 mg of acetaldehyde is allowed per 100 mL (300 ppm) of anhydrous ethanol for alcoholic drinks [34]. In Europe, the concentration of acetaldehyde in alcoholic beverages is generally below 500 pm [44]. Maximum sensitivity for acetaldehyde in ethanol was achieved at 450 °C (Figure 4B), for both ZnGa₂O₄ and ZnGaON. The response time (t_{90}) and recovery time (t_{90R}) were calculated as displayed in Figure 4A.

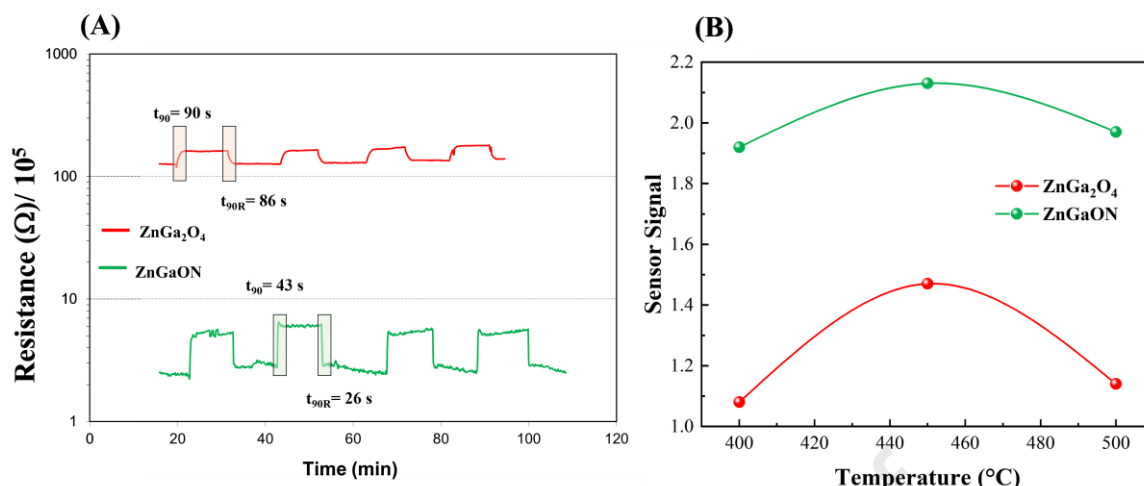


Figure 4 – (A) Time dependent resistance of the ZnGa₂O₄ and ZnGaON sensors during exposure to acetaldehyde in ethanol background (300 ppm) at 450 °C; (B) Sensor signals (R_{gas}/R_0) of ZnGa₂O₄ and ZnGaON sensors towards acetaldehyde exposure in ethanol background as a function of operating temperature.

The oxide and oxynitride sensors showed to be able to identify acetaldehyde in ethanol, however, ZnGaON showed a faster response and recovery time. The faster response observed for ZnGaON has been associated to the greater number of active sites on the surface, since formation of oxynitride typically increases the specific surface area [45–48]. It was also observed that the presence of acetaldehyde in ethanol accelerates the desorption of species from the sensor surface as if alcohol promoted a faster cleaning. This may be associated with the high affinity of ethanol with the surface [7–11,49].

In a previous work of our research group on nitridation of ZnGa₂O₄ powders [32], it was observed by EDS analysis that oxide and oxynitride exhibit different amounts of Zn (and consequently different quantity of cation vacancy), indicating that a meaningful loss of Zn upon ZnGa₂O₄ nitridation occurred, favored by increasing temperature. It has been stated that, during nitridation, a ZnGa₂O₄ spinel phase may undergo phase transformation, being correlated with the lengthening of the Zn-O bonds that favors to bonds breakage and, therefore, loss of Zn cations [50]. Concerning cationic stoichiometry in ZnGa₂O₄ materials, Wang *et al* [51] deposited the ZnGa₂O₄ films on different substrates and observed that evaluated the Zn/Ga ratio decreases as the temperature of deposition increases above 200 °C due to the higher vapor pressure of Zn in comparison to Ga, being consistent with our previous work [32].

Recently, Chen *et al* [20] prepared formaldehyde sensor based on CdGa₂O₄ and CdGa₂O₄ decorated CdO nanocrystals and stated that cationic substitution plays an important role on the amount of adsorbed oxygen species on the surface and on the improvement of the

sensing response. As it is known Zn/Ga stoichiometry variation can directly affect sensor sensitivity. Tung *et al* [52] carried out thermodynamic studies of the response of ZnGa_2O_4 as a sensor for NO_2 and H_2S gases and observed an increase in sensitivity when the molecules bind to Ga, indicating that the loss of Zn may be associated with the increased sensitivity observed for the sensors studied in this work.

It is important to highlight the possibility of using the same material sensor for detecting different molecules, such as ethanol, methanol, ammonia, acetone, formaldehyde, acetaldehyde, among others. Works in literature also reported the possibility of using gas sensors to detect acetaldehyde in the presence of other interfering gases [15–17,19,53,54]. For instance, Su *et al* [55] prepared sensors based on NiO nanoplates and investigated the performance towards detection of different gases. According to these authors, the NiO sensor is more sensitive to ethanol than any other studied gas, which was attributed to the similar energy between the adsorbed oxygen and the LUMO of ethanol that improve reaction between alcohol molecule and the adsorbed oxygen on the sensor surface.

Concerning the sensitivity, Mani *et al* [3] observed that the sensors were more sensitive to acetaldehyde compared to other gases. In relation to selectivity, the authors evidenced that the Co-doped ZnO sensors showed the highest selectivity towards acetaldehyde detection in the presence of formaldehyde. They stated that, although formaldehyde bond dissociation energy was comparable to acetaldehyde (364 kJ mol^{-1}), a lower response to formaldehyde was obtained due to electron donating effects, where the number of electrons released during the reduction of acetaldehyde is greater than in formaldehyde. Mani *et al*. [3] still emphasized that the sensor sensitivity is dependent on the surface nanostructure morphology. The authors showed that undoped ZnO branched nanorods presented a quicker response and recovery times due to a more open space with loosely packed particle structure. Similar nanostructure characteristics were observed for Co and Cu-doped ZnO samples. Conversely, Ni-doped ZnO sensor exhibited compactly packed nanostructure that may to slow response and recovery times. The authors stated that the morphology and size of the nanostructure determines the degree of electron confinement in the prepared sensors, which is in accordance with Yang *et al*. [56]. In their study, Yang *et al*. [56] stated that gas sensing in semiconductor metal oxides is based on the change of electrical conductivity induced by the gas adsorption/desorption on the surface, and the reactions on surface are strongly dependent on the size, shape, and surface state of sensing materials. Therefore, a sensor with high sensing performance could be obtained by finely tuning the size and shape of the nanoparticles on the material surface [56].

Although the main objective of this work was to prepare ZnGa₂O₄ and ZnGaON film-based sensors for acetaldehyde detection in ethanol for applications in alcoholic beverages, response sensitivity studies of the sensors to methanol (Figure S5) and water vapor (Figure S6) were carried out, showing the possibility of applying the prepared sensors for other target molecules. However, our results demonstrated highest sensitivity to acetaldehyde.

Based on all the presented facts, we believe that the stoichiometric imbalance of Zn/Ga together with the presence of oxygen vacancies created by N³⁻ incorporation and the nanostructured grained surface of the ZnGa₂O₄:N may be playing a vital role in the highest sensor response in detecting acetaldehyde in ethanol when compared to ZnGa₂O₄ sensor. It is still important to highlight that the highest sensitivity of sensors prepared in this work to acetaldehyde is strongly related to its lower bond dissociation energy compared to other gas molecules as suggested by Mani *et al* [3]. In addition, despite being stable at temperatures of 450 °C as the oxynitride-based sensor (ZnGaON) was prepared at 700 °C, the sensor was not tested at higher temperatures to avoid thermal surface oxidation. Thus, it is safe for the sensor works at 450 °C to preserve its stability, as a possible thermal oxidation should only effectively occur from 750 °C [5,6].

1.4 Conclusions

ZnGaON films were prepared by nitridation amorphous ZnGa₂O₄ previously obtained by PLD at room temperature. Nitridation provided well-adhered films with a continuous porous surface, which is quite suitable for gas sensing application. Crystalline ZnGa₂O₄, were also deposited by PLD at 650 °C. Both films, ZnGa₂O₄ and ZnGaON, showed to be able to detect acetaldehyde in ethanol vapor (300 mg L⁻¹) and have high potential for use as sensor to acetaldehyde in screening tests. Best results were obtained with the nitrided films, ZnGaON, which showed $t_{90} = 43$ s and $t_{90R} = 26$ s, operating at 450 °C. All these results suggest that ZnGaON, and even ZnGa₂O₄, may be considered a potential candidate for the development of an efficient screening test for a highly selective and selective identification of acetaldehyde in beverages, foods, or fuel.

1.5 Acknowledgements

The authors wish to thank the CNPq, CAPES, FAPDF, FACEPE (Brazilian funding agencies) for their financial support, and the Institut des Sciences Chimiques de Rennes, University of Rennes I. A.L.M.O. would also like to thank FAPESQ/PB - SSECT (17/2022) for the awarded fellowship.

1.5 References

- [1] I.A. for R. on A. Cancer, Personal habits and indoor combustions, IARC Monogr. Eval. Carcinog. Risks to Humans. 100 (2012) 319–331.
- [2] P. Romano, G. Suzzi, L. Turbanti, M. Polsinelli, Acetaldehyde production in *Saccharomyces cerevisiae* wine yeasts, FEMS Microbiol. Lett. 118 (1994) 213–218. <https://doi.org/10.1111/j.1574-6968.1994.tb06830.x>.
- [3] G.K. Mani, J.B.B. Rayappan, ZnO nanoarchitectures: Ultrahigh sensitive room temperature acetaldehyde sensor, Sensors Actuators, B Chem. 223 (2016) 343–351. <https://doi.org/10.1016/j.snb.2015.09.103>.
- [4] C. Wang, P. Sahay, Breath analysis using laser spectroscopic techniques: Breath biomarkers, spectral fingerprints, and detection limits, Sensors. 9 (2009) 8230–8262. <https://doi.org/10.3390/s91008230>.
- [5] N. Yamazoe, New approaches for improving semiconductor gas sensors, Sensors Actuators B. 5 (1991) 7–19. [https://doi.org/10.1016/0925-4005\(91\)80213-4](https://doi.org/10.1016/0925-4005(91)80213-4).
- [6] A.A. and R.B. George F. Fine, Leon M. Cavanagh, Metal Oxide Semi-Conductor Gas Sensors in Environmental Monitoring, Sensors. 10 (2010) 5469–5502. <https://doi.org/10.3390/s100605469>.
- [7] E. Wongrat, N. Chanlek, C. Chueaiarrom, B. Samransuksamer, N. Hongsith, S. Chooapun, Low temperature ethanol response enhancement of ZnO nanostructures sensor decorated with gold nanoparticles exposed to UV illumination, Sensors Actuators, A Phys. 251 (2016) 188–197. <https://doi.org/10.1016/j.sna.2016.10.022>.
- [8] L. Zhu, Y. Li, W. Zeng, Hydrothermal synthesis of hierarchical flower-like ZnO nanostructure and its enhanced ethanol gas-sensing properties, Appl. Surf. Sci. 427 (2018) 281–287. <https://doi.org/10.1016/j.apsusc.2017.08.229>.
- [9] C. Han, X. Chen, D. Liu, P. Zhou, S. Zhao, H. Bi, D. Meng, D. Wei, Y. Shen, Fabrication of shrub-like CuO porous films by a top-down method for high-performance ethanol gas sensor, Vacuum. 157 (2018) 332–339. <https://doi.org/10.1016/j.vacuum.2018.09.004>.
- [10] D. An, N. Mao, G. Deng, Y. Zou, Y. Li, T. Wei, X. Lian, Ethanol gas-sensing characteristic of the Zn₂SnO₄ nanospheres, Ceram. Int. 42 (2016) 3535–3541. <https://doi.org/10.1016/j.ceramint.2015.10.161>.
- [11] F.H. Saboor, A.A. Khodadadi, Y. Mortazavi, M. Asgari, Microemulsion synthesized silica/ZnO stable core/shell sensors highly selective to ethanol with minimum sensitivity to humidity, Sensors Actuators B. 238 (2017) 1070–1083. <https://doi.org/10.1016/j.snb.2016.07.127>.
- [12] Q. Wan, Q.H. Li, Y.J. Chen, T.H.W.L. He, J.P.L.L. Lin, Q. Wan, Q.H. Li, Y.J. Chen, T.H. Wang, Fabrication and ethanol sensing characteristics of ZnO nanowire gas sensors, Appl. Phys. Lett. 3654 (2008) 2002–2005. <https://doi.org/10.1063/1.1738932>.
- [13] E. Comini, G. Faglia, G. Sberveglieri, Z. Pan, Z.L. Wang, Stable and highly sensitive gas sensors based on semiconducting oxide nanobelts, Appl. Phys. Lett. 1869 (2008) 28–31. <https://doi.org/10.1063/1.1504867>.
- [14] B.E.R. Leite, I.T. Weber, E. Longo, J.A. Varela, A New Method to Control Particle Size and Particle Size Distribution of SnO₂ Nanoparticles for Gas Sensor Applications **,

- (2000) 965–968.
- [15] M.T.S.R.G. Marta I.S. Veríssimo, José A.F. Gamelas, Mário M.Q. Simões, Dmitry V. Evtuguin, Quantifying acetaldehyde in cider using a Mn(III)-substituted polyoxotungstate coated acoustic wave sensor, *Sensors and Actuators B-Chemical*. 255 (2017) 2608–2613. <https://doi.org/10.1016/j.snb.2017.09.068>.
- [16] E. Gunasekaran, M. Ezhilan, G.K. Mani, P. Shankar, A.J. Gunasekaran, J.B.B. Rayappan, K.J. Babu, Fluorine Doped ZnO Thin Film As Acetaldehyde Sensor, *Semicond. Sci. Technol.* 33 (2018) 095005. <https://iopscience.iop.org/article/10.1088/2053-1583/abe778>.
- [17] N. Donato, G. Neri, S.G. Leonardi, Z. Fusco, A. Tricoli, High performance flame-made ultraporous ZnO-based QCM sensor for acetaldehyde, *I2MTC 2019 - 2019 IEEE Int. Instrum. Meas. Technol. Conf. Proc.* 2019-May (2019) 1–5. <https://doi.org/10.1109/I2MTC.2019.8826872>.
- [18] R.K. Chava, H.Y. Cho, J.M. Yoon, Y.T. Yu, Fabrication of aggregated In₂O₃ nanospheres for highly sensitive acetaldehyde gas sensors, *J. Alloys Compd.* 772 (2019) 834–842. <https://doi.org/10.1016/j.jallcom.2018.09.183>.
- [19] S.M. Majhi, H.J. Lee, H.N. Choi, H.Y. Cho, J.S. Kim, C.R. Lee, Y.T. Yu, Construction of novel hybrid PdO-ZnO p-n heterojunction nanostructures as a high-response sensor for acetaldehyde gas, *CrystEngComm*. 21 (2019) 5084–5094. <https://doi.org/10.1039/c9ce00710e>.
- [20] H. Chen, L. Sun, G.D. Li, X. Zou, Well-Tuned Surface Oxygen Chemistry of Cation Off-Stoichiometric Spinel Oxides for Highly Selective and Sensitive Formaldehyde Detection, *Chem. Mater.* 30 (2018) 2018–2027. <https://doi.org/10.1021/acs.chemmater.7b05251>.
- [21] M.N. Da Silva, J.M. De Carvalho, M.C. De Abreu Fantini, L.A. Chiavacci, C. Bourgaux, Nanosized ZnGa₂O₄:Cr³⁺ Spinel as Highly Luminescent Materials for Bioimaging, *ACS Appl. Nano Mater.* 2 (2019) 6918–6927. <https://doi.org/10.1021/acsanm.9b01417>.
- [22] R.J. Wiglusz, A. Watras, M. Malecka, P.J. Deren, R. Pazik, Structure evolution and up-conversion studies of ZnX₂O₄:Er³⁺/Yb³⁺ (X = Al³⁺, Ga³⁺, In³⁺) nanoparticles, *Eur. J. Inorg. Chem.* (2014) 1090–1101. <https://doi.org/10.1002/ejic.201301351>.
- [23] S. Luo, G.F. Harrington, K.T. Wu, T. Lippert, Heteroepitaxial (111) ZnGa₂O₄ Thin Films Grown on (00.1) Sapphire by Pulsed Laser Deposition, *Phys. Status Solidi - Rapid Res. Lett.* (2020). <https://doi.org/10.1002/pssr.202000270>.
- [24] T. Dazai, S. Yasui, T. Taniyama, M. Itoh, Cation-Deficiency-Induced Crystal-Site Engineering for ZnGa₂O₄:Mn²⁺ Thin Film, *Inorg. Chem.* 59 (2020) 8744–8748. <https://doi.org/10.1021/acs.inorgchem.0c00359>.
- [25] C.R. Garcia, J. Oliva, L.A. Diaz-Torres, E. Montes, G. Hirata, J. Bernal-Alvarado, C. Gomez-Solis, Controlling the white phosphorescence ZnGa₂O₄ phosphors by surface defects, *Ceram. Int.* 45 (2019) 4972–4979. <https://doi.org/10.1016/j.ceramint.2018.11.197>.
- [26] A. Luchechko, O. Kravets, Novel visible phosphors based on MgGa₂O₄-ZnGa₂O₄ solid solutions with spinel structure co-doped with Mn²⁺ and Eu³⁺ ions, *J. Lumin.* 192 (2017) 11–16. <https://doi.org/10.1016/j.jlumin.2017.05.046>.
- [27] C.-C. Hu, H. Teng, Gallium Oxynitride Photocatalysts Synthesized from {Ga(OH)₃ for Water Splitting under Visible Light Irradiation, *J. Phys. Chem. C*. 114 (2010) 20100–20106. <https://doi.org/10.1021/jp1070083>.
- [28] T. Hisatomi, K. Maeda, D. Lu, K. Domen, The effects of starting materials in the synthesis of (Ga_{1-x}Zn_x)(N_{1-x}O_x) solid solution on its photocatalytic activity for overall water splitting under visible light, *ChemSusChem*. 2 (2009) 336–343. <https://doi.org/10.1002/cssc.200800156>.

- [29] K. Maeda, K. Domen, Solid solution of GaN and ZnO as a stable photocatalyst for overall water splitting under visible light, *Chem. Mater.* 22 (2010) 612–623. <https://doi.org/10.1021/cm901917a>.
- [30] C.C. Hu, Y.L. Lee, H. Teng, Influence of indium doping on the activity of gallium oxynitride for water splitting under visible light irradiation, *J. Phys. Chem. C* 115 (2011) 2805–2811. <https://doi.org/10.1021/jp1105983>.
- [31] M. Kerlau, O. Merdrignac-conanec, P. Reichel, N. B[^], U. Weimar, Preparation and characterization of gallium (oxy) nitride powders Preliminary investigation as new gas sensor materials, *Sensors Actuators, B Chem.* 115 (2006) 4–11. <https://doi.org/10.1016/j.snb.2005.07.068>.
- [32] J.F.D. Figueiredo, V. Bouquet, S. Députier, O. Merdrignac-Conanec, I. Peron, E.P. Marinho, A.G. Souza, I.M.G. Santos, M. Guilloux-Viry, I.T. Weber, Zinc-gallium oxynitride powders: effect of the oxide precursor synthesis route, *Cerâmica*. 59 (2013) 269–276. <https://doi.org/10.1590/S0366-69132013000200012>.
- [33] D.X. Ju, H.Y. Xu, Z.W. Qiu, Z.C. Zhang, Q. Xu, J. Zhang, J.Q. Wang, B.Q. Cao, Near Room Temperature, Fast-Response, and Highly Sensitive Triethylamine Sensor Assembled with Au-Loaded ZnO/SnO₂ Core-Shell Nanorods on Flat Alumina Substrates, *ACS Appl. Mater. Interfaces*. 7 (2015) 19163–19171. <https://doi.org/10.1021/acsami.5b04904>.
- [34] S. Alexandre Nixon, V. Gregorio, H. Jorge, Certification adds value to Brazilian “cachaça,” *Food Sci. Technol.* 27 (2007) 681–687. <https://doi.org/10.1590/S0101-20612007000400002>.
- [35] S.D. Wolter, B.P. Luther, D.L. Waltemyer, C. Öneby, S.E. Mohny, R.J. Molnar, X-ray photoelectron spectroscopy and x-ray diffraction study of the thermal oxide on gallium nitride, *Appl. Phys. Lett.* 70 (1997) 2156–2158. <https://doi.org/10.1063/1.118944>.
- [36] Y. Zhou, C. Ahyi, T. Isaacs-Smith, M. Bozack, C.C. Tin, J. Williams, M. Park, A. jen Cheng, J.H. Park, D.J. Kim, D. Wang, E.A. Preble, A. Hanser, K. Evans, Formation, etching and electrical characterization of a thermally grown gallium oxide on the Ga-face of a bulk GaN substrate, *Solid. State. Electron.* 52 (2008) 756–764. <https://doi.org/10.1016/j.sse.2007.10.045>.
- [37] J. Watson, K. Ihokura, G.S.V. Coles, The tin dioxide gas sensor, *Meas. Sci. Technol.* 4 (1993) 711–719. <https://doi.org/10.1088/0957-0233/4/7/001>.
- [38] O.R. Nunez, A.J. Moreno Tarango, N.R. Murphy, C. V. Ramana, Nitrogen incorporation and composition facilitated tailoring of the optical constants and dispersion energy parameters of tungsten oxynitride films, *J. Alloys Compd.* 683 (2016) 292–301. <https://doi.org/10.1016/j.jallcom.2016.04.182>.
- [39] M.C. Marco de Lucas, F. Fabreguette, M. Linsavanh, L. Imhoff, O. Heintz, C. Josse-Courty, M.T. Mesnier, V. Potin, S. Bourgeois, M. Sacilotti, Structure and properties of GaN_xO_y films grown by nitridation of GaAs (100) substrates, *J. Cryst. Growth.* 261 (2004) 324–329. <https://doi.org/10.1016/j.jcrysgro.2003.11.022>.
- [40] M.R. Wu, W.Z. Li, C.Y. Tung, C.Y. Huang, Y.H. Chiang, P.L. Liu, R.H. Horng, NO gas sensor based on ZnGa₂O₄ epilayer grown by metalorganic chemical vapor deposition, *Sci. Rep.* 9 (2019) 1–9. <https://doi.org/10.1038/s41598-019-43752-z>.
- [41] S. Ahmadnia-Feyzabad, A.A. Khodadadi, M. Vesali-Naseh, Y. Mortazavi, Highly sensitive and selective sensors to volatile organic compounds using MWCNTs/SnO₂, *Sensors Actuators, B Chem.* 166–167 (2012) 150–155. <https://doi.org/10.1016/j.snb.2012.02.024>.
- [42] S.K. Tripathy, A. Mishra, S.K. Jha, R. Wahab, A.A. Al-Khedhairy, Synthesis of thermally stable monodispersed Au@SnO₂ core-shell structure nanoparticles by a

- sonochemical technique for detection and degradation of acetaldehyde, *Anal. Methods*. 5 (2013) 1456–1462. <https://doi.org/10.1039/c3ay26549h>.
- [43] R. Yoo, D. Li, H.J. Rim, S. Cho, H.S. Lee, W. Lee, High sensitivity in Al-doped ZnO nanoparticles for detection of acetaldehyde, *Sensors Actuators, B Chem.* 266 (2018) 883–888. <https://doi.org/10.1016/j.snb.2018.03.102>.
- [44] (SCCS) Scientific Committee on Consumer Safety, Opinion on Acetaldehyde, *EFSA J.* (2012) revision 11 December 2012.
- [45] T. Martins, R. Lebullenger, V. Bouquet, M. Guilloux-viry, I. Maria, G. Santos, T. Ingrid, SrSnO₃:N - Nitridation and evaluation of photocatalytic activity, 649 (2015) 491–494. <https://doi.org/10.1016/j.jallcom.2015.05.203>.
- [46] D. Logvinovich, R. Aguiar, R. Robert, M. Trottmann, S.G. Ebbinghaus, A. Reller, A. Weidenkaff, Synthesis, Mo-valence state, thermal stability and thermoelectric properties of SrMoO_{3-x}N_x (x>1) oxynitride perovskites, *J. Solid State Chem.* 180 (2007) 2649–2654. <https://doi.org/10.1016/j.jssc.2007.06.035>.
- [47] M. Widenmeyer, C. Peng, A. Baki, W. Xie, R. Niewa, A. Weidenkaff, Approaching compositional limits of perovskite - Type oxides and oxynitrides by synthesis of Mg_{0.25}Ca_{0.65}Y_{0.1}Ti(O,N)₃, Ca_{1-x}Y_xZr(O,N)₃ (0.1 ≤ x ≤ 0.4), and Sr_{1-x}La_xZr(O,N)₃ (0.1 ≤ x ≤ 0.4), *Solid State Sci.* 54 (2016) 7–16. <https://doi.org/10.1016/j.solidstatesciences.2015.11.016>.
- [48] I. Marozau, A. Shkabko, G. Dinescu, M. Döbeli, T. Lippert, D. Logvinovich, M. Mallepell, C.W. Schneider, A. Weidenkaff, A. Wokaun, Pulsed laser deposition and characterization of nitrogen-substituted SrTiO₃ thin films, *Appl. Surf. Sci.* 255 (2009) 5252–5255. <https://doi.org/10.1016/j.apsusc.2008.07.159>.
- [49] M. Kerlau, P. Reichel, N. Bârsan, U. Weimar, S. Delsarte-Guéguen, O. Merdrignac-Conanec, Detection of propane by “GaON” thick-film gas sensors, *Sensors Actuators, B Chem.* 122 (2007) 14–19. <https://doi.org/10.1016/j.snb.2006.05.001>.
- [50] V.B. Ram Boppana, D.J. Doren, R.F. Lobo, Analysis of Ga coordination environment in novel spinel zinc gallium oxy-nitride photocatalysts, *J. Mater. Chem.* 20 (2010) 9787–9797. <https://doi.org/10.1039/c0jm01928c>.
- [51] W.K. Wang, Y.J. Xu, S.Y. Huang, K.F. Liu, P.C. Tsai, Structural characteristics and photoluminescence properties of sputter-deposition ZnGa₂O₄ thin films on sapphire and Si(100) substrates, *Coatings*. 9 (2019) 1–9. <https://doi.org/10.3390/coatings9080469>.
- [52] J. Tung, Y. Chiang, D. Wang, P. Liu, Adsorption of NO₂ and H₂S on ZnGa₂O₄ (111) Thin Films : A First-Principles Density Functional Theory Study, *Appl. Sci.* 4 (2020).
- [53] G.K. Mani, J.B.B. Rayappan, Novel and facile synthesis of randomly interconnected ZnO nanoplatelets using spray pyrolysis and their room temperature sensing characteristics, *Sensors Actuators, B Chem.* 198 (2014) 125–133. <https://doi.org/10.1016/j.snb.2014.02.101>.
- [54] U.T. Nakate, Y.T. Yu, S. Park, High performance acetaldehyde gas sensor based on p-n heterojunction interface of NiO nanosheets and WO₃ nanorods, *Sensors Actuators, B Chem.* 344 (2021). <https://doi.org/10.1016/j.snb.2021.130264>.
- [55] C. Su, L. Zhang, Y. Han, C. Ren, X. Chen, J. Hu, M. Zeng, N. Hu, Y. Su, Z. Zhou, Z. Yang, Controllable synthesis of crescent-shaped porous NiO nanoplates for conductometric ethanol gas sensors, *Sensors Actuators, B Chem.* 296 (2019) 126642. <https://doi.org/10.1016/j.snb.2019.126642>.
- [56] C. Yang, X. Su, J. Wang, X. Cao, S. Wang, L. Zhang, Facile microwave-assisted hydrothermal synthesis of varied-shaped CuO nanoparticles and their gas sensing properties, *Sensors Actuators, B Chem.* 185 (2013) 159–165. <https://doi.org/10.1016/j.snb.2013.04.100>.

Declaration of interests

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

The authors declare the following financial interests/personal relationships which may be considered as potential competing interests:

Journal Pre-proof