



**HAL**  
open science

## Glassy and liquid Sb<sub>2</sub>S<sub>3</sub>: insight into the structure and dynamics of a promising functional material

Mohammad Kassem, Chris Benmore, Andrey Tverjanovich, Takeshi Usuki, Maxim Khomenko, Daniele Fontanari, Anton Sokolov, Koji Ohara, Maria Bokova, Shinji Kohara, et al.

### ► To cite this version:

Mohammad Kassem, Chris Benmore, Andrey Tverjanovich, Takeshi Usuki, Maxim Khomenko, et al.. Glassy and liquid Sb<sub>2</sub>S<sub>3</sub>: insight into the structure and dynamics of a promising functional material. *Journal of Materials Chemistry C*, 2023, 11 (14), pp.4654-4673. 10.1039/D3TC00081H . hal-04124971

**HAL Id: hal-04124971**

**<https://hal.science/hal-04124971v1>**

Submitted on 11 Jun 2023


**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Glassy and Liquid $\text{Sb}_2\text{S}_3$ : Insight into the Structure and Dynamics of Promising Functional Material

Mohammad Kassem, Chris J. Benmore, Andrey Tverjanovich, Takeshi Usuki, Maxim Khomenko, Daniele Fontanari, Anton Sokolov, Koji Ohara, Maria Bokova, Shinji Kohara, and Eugene Bychkov\*

**ABSTRACT:** Antimony sesquisulfide  $\text{Sb}_2\text{S}_3$  has become an outstanding advanced functional material in a variety of rapidly growing application fields: smart integrated photonics from the visible to telecom window, cost-efficient photovoltaics, energy storage and transformation. Rational design and tailoring of the required components needs a deep insight into the atomic structure and dynamics of liquid and amorphous  $\text{Sb}_2\text{S}_3$ , but the detailed information is missing in contrast to crystalline counterparts. Using high-energy X-ray diffraction and Raman spectroscopy over an extended temperature range, supported by first-principles simulations as well as by electrical and thermal studies, we show that the high optical and electric contrast between the SET (crystalline) and RESET (amorphous) logic states is related to the different short and intermediate range order in orthorhombic and vitreous  $\text{Sb}_2\text{S}_3$ . It includes a strong asymmetry of the Sb-S nearest neighbor distances and a different coordination of antimony sites in the crystal vs. a distorted trigonal environment of defect octahedral  $\text{SbS}_3$  entities in glassy  $\text{Sb}_2\text{S}_3$ . Fast crystallization rate at elevated temperatures in liquid antimony sesquisulfide is related to the enhanced fragility, approaching that of telluride phase-change materials, and to a large fraction of *ABAB* squares (*A*: Sb; *B*: S), combined with a remarkable slowdown of the diffusion processes in the vicinity of the glass transition temperature, ensuring a good retention of the amorphous state. Further improvements maybe achieved using anionic (Se) or cationic (Bi) substitution that decreases the temperature of a semiconductor-metal transition and allows bandgap engineering, important for both photonics and photovoltaics.

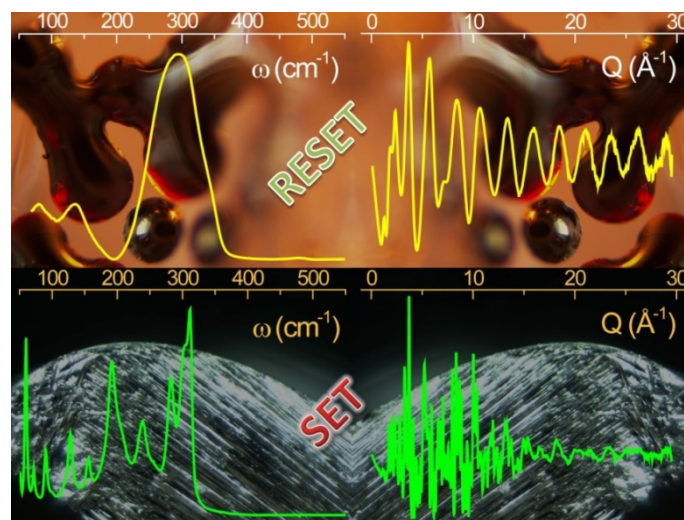

TOC Figure

\* email address: [bychkov@univ-littoral.fr](mailto:bychkov@univ-littoral.fr)

# 1. INTRODUCTION

Antimony sesquisulfide  $\text{Sb}_2\text{S}_3$  appears to be emerging and promising advanced functional material for a variety of rapidly growing application fields:

(1) *Wide gap phase-change material (PCM) for both electrically and light tunable visible photonics or ultralow loss photonics at telecommunication wavelengths.*  $\text{Sb}_2\text{S}_3$  can be used for smart reprogrammable photonic systems with a nanosecond switching time, holographic and nonvolatile ultrathin displays of extremely high resolution, integrated photonic circuits, switchable metasurfaces and varifocal metalens, nanophotonic and on-chip devices, dielectric nanoantennas, etc.<sup>1-6</sup>

(2) *High-performance composite anode for sodium and lithium batteries.* Antimony sesquisulfide nanorods, nanoparticles and powders, sometimes combined with other sulfides and encapsulated into doped carbon matrix or activated carbon, provide a superior rate capability, excellent cyclic stability and capacity retention, as well as fast-charging capacity and highly decreased interfacial resistance.<sup>7-10</sup>

(3) *Alternative absorber material for thin-film solar cells.* Antimony sulfide thin films belong to emerging earth-abundant low-cost photovoltaic materials having reasonable optical bandgap, tremendous low-light harvesting, excellent moisture and air stability.<sup>11,12</sup>

(4) *Thermoelectric material.* High thermoelectric power of  $\text{Sb}_2\text{S}_3$  seems to be promising for thermoelectric applications.<sup>13</sup> However, nanostructured or amorphous antimony sesquisulfide is mostly used as a dopant decreasing the thermal conductivity and increasing the Seebeck coefficient of composite thermoelectrics (lead chalcogenides,  $(\text{Bi,Sb})_2\text{Te}_3$ , etc.) yielding a significantly enhanced figure of merit  $zT$ .<sup>14,15</sup>

Rational design and tailoring of optimized functional materials based on  $\text{Sb}_2\text{S}_3$  need a deep insight into the atomic structure and dynamics of antimony sesquisulfide. The crystal structure of  $\text{Sb}_2\text{S}_3$  has been extensively studied both at ambient conditions<sup>16-18</sup> and under high pressure.<sup>19-26</sup> Nevertheless, the atomic structure of vitreous and liquid antimony sesquisulfide is largely unknown except for classical X-ray diffraction studies of glassy  $\text{Sb}_2\text{S}_3$  reported forty years ago and suffering from a limited accessible  $Q$ -range and insufficient  $r$ -space resolution.<sup>27-29</sup> In case of PCM applications,<sup>30-32</sup> a special attention should be paid to the origin of a high optical and electric contrast between the SET (crystalline) and RESET (amorphous) logic states since antimony sesquisulfide differs considerably from the benchmark telluride PCM ( $\text{GeTe-Sb}_2\text{Te}_3$ , GST, or doped  $\text{Sb}_2\text{Te}$ ) in both chemical bonding and local antimony environment. The metavalent bonding<sup>33</sup> seems to be missing in  $\text{Sb}_2\text{S}_3$ ; and the four-fold coordinated antimony sites, present in GST and  $\alpha\text{-Sb}_2\text{Te}_3$ ,<sup>34,35</sup> were not observed in vitreous  $\text{Sb}_2\text{S}_3$ ,<sup>27-29</sup> even though there is a controversy in amorphous tellurides related to the antimony local order.<sup>36,37</sup>

Using high-energy X-ray diffraction and Raman spectroscopy supported by first-principles simulations, we will unravel a detailed structural organization of bulk glassy and liquid  $\text{Sb}_2\text{S}_3$  over an extended temperature range,  $298 \leq T \leq 1143$  K. Thermal properties and electrical conductivity measurements will also be provided showing a remarkable contrast in electronic properties between amorphous, crystalline and liquid states. Finally, diffusion coefficients and viscosity of liquid  $\text{Sb}_2\text{S}_3$  will be computed and compared with known experimental data, which reveal a significant fragility of molten antimony sesquisulfide in comparison with canonical dielectric  $\text{As}_2\text{S}_3$ . All these results will explain promising PCM performance of  $\text{Sb}_2\text{S}_3$  and an overall trend in functional properties going down on the Periodic Table.

## 2. EXPERIMENTAL SECTION

**2.1. Glassy  $\text{Sb}_2\text{S}_3$  Preparation.** A two-step synthesis was applied for glassy  $\text{Sb}_2\text{S}_3$ . First, a crystalline sample was prepared from high-purity antimony (99.999%, Cerac) and sulfur (99.999%, Alfa Aesar) in evacuated and sealed silica tube. Then, a small quantity of *c*- $\text{Sb}_2\text{S}_3$  was placed in a thin-walled silica capillary, evacuated to  $10^{-4}$  mbar and sealed. The capillary was slowly heated in a furnace to 1050 K and kept at this temperature for one hour with subsequent cooling to 900 K. After additional equilibration step for at least 30 minutes, the sample was splat-quenched under argon atmosphere onto a fused silica plate cooled down to  $\approx 250$  K.

**2.2. Thermal and Electrical Measurements.** A TA instruments Q200 thermal analyzer was used for differential scanning calorimetry (DSC). The synthesized samples of 3-5 mg were encapsulated in a sealed aluminum pan and heated at a rate of  $10 \text{ K min}^{-1}$  under a dry nitrogen atmosphere to determine the glass transition  $T_g$  and crystallization temperatures. The ac and dc conductivity measurements were done over the  $330 \leq T \leq 450$  K temperature range. A Hewlett Packard 4339B high resistance meter with applied voltage of 100 volts was used for the dc experiments. The ac conductivity over the 100 Hz to 15 MHz frequency range was measured using a Hewlett Packard 4194A impedance meter.

**2.3. Raman Spectroscopy Measurements.** A LabRam HR microRaman spectrometer (Jobin Yvon Horiba Group) was used for the measurements at room temperature. Raman scattering was excited by a 785 nm solid-state laser and recorded in the  $50\text{--}850 \text{ cm}^{-1}$  spectral range. The laser power was 0.75 mW. Two to three spectra were registered for each sample at different positions to verify the sample homogeneity and the absence of photoinduced phenomena. Raman spectra over the temperature range  $293 \leq T \leq 873$  K were measured using a Senterra Raman spectrometer (Bruker) equipped with a microscope and a Linkam TS1000 hot stage. The spectra were excited by a 785 nm laser diode with a power of 1 mW and recorded in the  $75\text{--}1500 \text{ cm}^{-1}$  spectral range (reliable data above  $100 \text{ cm}^{-1}$ ). Glassy  $\text{Sb}_2\text{S}_3$  was placed in a silica tube (2 mm ID/3 mm OD, length 12 mm) and sealed under vacuum.

**2.4. High-Energy X-ray Diffraction.** The 6-ID-D beamline at the Advanced Photon Source (Argonne National Laboratory, Chicago) was used for high-energy X-ray diffraction measurements at ambient conditions and as a function of temperature. The photon energy was 99.9593 keV, and the wavelength was  $0.124035 \text{ \AA}$ . A two-dimensional (2D) setup was used for data collection with a Varex area detector,  $2880 \times 2880$  pixels, and a pixel size of  $150 \times 150 \mu\text{m}^2$ . The sample-to-detector distance was 287.7 mm for a room-temperature setup, and 334.9 mm for furnace measurements over the  $673 \leq T \leq 1143$  K temperature range on cooling. Cerium dioxide was used as a calibrant. The exposure time was  $0.2 \text{ s} \times 1500$  frames, using one dark-field image file followed by five light files. Glass samples were fixed on a Kapton tape for the room temperature measurements. A  $\text{Sb}_2\text{S}_3$  sample in evacuated silica tube (2 mm ID/3 mm OD) was used for the furnace experiments. The 2D diffraction patterns were reduced using the Fit2D software.<sup>38</sup> The measured background intensity (either the Kapton tape or the empty silica at

various temperatures) was subtracted, and corrections were made for the different detector geometries and efficiencies, sample self-attenuation, and Compton scattering using standard procedures,<sup>39</sup> providing the X-ray structure factor  $S_X(Q)$ .

$$S_X(Q) = w_{\text{SbSb}}(Q)S_{\text{SbSb}}(Q) + w_{\text{SbS}}(Q)S_{\text{SbS}}(Q) + w_{\text{SS}}(Q)S_{\text{SS}}(Q), \quad (1)$$

where  $w_{ij}(Q)$  are  $Q$ -dependent X-ray weighting coefficients and  $S_{ij}(Q)$  the Faber-Ziman partial structure factors.

Canonical  $\text{As}_2\text{S}_3$  glass and liquid were also measured at the BL04B2 beamline of the SPring-8 facility (Hyogo Prefecture, Japan) using a dedicated two-axis diffractometer equipped with four CdTe detectors at low angles and three Ge diodes at high diffraction angles.<sup>40</sup> The temperature measurements were carried out from 300 to 1223 K in a furnace. The 7-detector setup and incident X-ray energy of 112.6386 keV allows the diffraction pattern to be collected up to  $Q = 30 \text{ \AA}^{-1}$  with a high signal-to-noise ratio and sufficient energy resolution to discriminate both fluorescence from the sample and higher harmonic reflections from the monochromator crystal. The empty silica tube at different temperatures was also measured and used for background intensity subtraction. Further data analysis included absorption, Compton scattering, and polarization corrections using standard procedures<sup>41</sup> giving the total X-ray structure factor  $S_X(Q)$ .<sup>42,43</sup>


**2.5. First-Principles Simulations.** The DFT calculations of vibrational spectra were carried out using Gaussian 16 software.<sup>44</sup> The structural optimization and harmonic vibrational frequency calculations were performed for size-limited clusters:  $\text{SbSb}_3\text{H}_3$ ,  $\text{SbS}_3\text{H}_3$ ,  $\text{Sb}_2\text{S}_4\text{H}_2$  (chair and boat conformations),  $\text{Sb}_2\text{S}_5\text{H}_4$ ,  $\text{Sb}_2\text{S}_6\text{H}_4$ ,  $\text{Sb}_3\text{S}_6\text{H}_3$ ,  $\text{Sb}_6\text{S}_{12}\text{H}_6$ ,  $\text{Sb}_{12}\text{S}_{18}\text{H}_2$ , and  $\text{Sb}_{12}\text{S}_{16}$ . The Becke three-parameter hybrid exchange functional<sup>45</sup> and the Lee–Yang–Parr correlation functional (B3LYP)<sup>46</sup> were used for these simulations. The small-core relativistic pseudopotential basis set (cc-pVTZ-PP)<sup>47</sup> and the effective core potentials<sup>48</sup> were applied for cluster geometry optimization and Raman intensity calculations. Most of the structures were optimized using the tight convergence option ensuring adequate convergence and reliability of computed wavenumbers. Extra quadratically convergent self-consistent field procedure<sup>49</sup> was used for difficult convergence cases. Further details of the DFT simulations are reported elsewhere.<sup>50–52</sup>

Modeling of the diffraction data was carried out using Born–Oppenheimer molecular dynamics implemented within the CP2K package.<sup>53</sup> The generalized gradient approximation (GGA) and the PBE0 hybrid<sup>54,55</sup> exchange–correlation functional combining the exact Hartree–Fock and DFT approaches were used, providing a better agreement with experiment.<sup>56–59</sup> The Grimme dispersion corrections D3BJ<sup>60</sup> were also employed, improving first-principles molecular dynamics (FPMD) results for chalcogenide systems.<sup>61,62</sup> The applied FPMD technique was similar to previous reports.<sup>34,63</sup> The initial atomic configurations for vitreous  $\text{Sb}_2\text{S}_3$  were created and optimized using the RMC\_POT++ code<sup>64</sup> against the experimental  $S_X(Q)$ . The size of the cubic simulation box, containing 200 atoms (80 Sb and 120 S), was chosen to match the experimental density. Further optimization was carried out using DFT, applying the molecularly optimized correlation consistent polarized triple-zeta valence basis set along with the norm-conserving relativistic Goedecker–Teter–Hutter-type pseudopotentials.<sup>65</sup> FPMD simulations were performed using a canonical  $NVT$  ensemble with a Nosé–Hoover<sup>66,67</sup> thermostat. The simulation boxes were heated from 300 K to 900 K using 100 K steps for 20–25 ps each. At 900


K (above melting), the systems were equilibrated for 70 ps and cooled down to 300 K using the same temperature steps but with a longer simulation time (25-45 ps). Final equilibration and data collection at 300 K were performed for 59 ps. Additional simulations were carried out between 850 and 1150 K (step 100 K for 40-50 ps each) consistent with experimental data. The connectivity and ring statistics were analyzed using the R. I. N. G. S. package<sup>68</sup> and a modified connectivity program.<sup>69</sup> The pyMolDyn code<sup>70</sup> applying the Dirichlet-Voronoi tessellation was used for the calculation of microscopic voids and cavities.

### 3. RESULTS AND DISCUSSION

**3.1. Glass-Forming, Thermal and Electric Properties.** Glassy antimony sesquisulfide was reported to be a difficult material to vitrify.<sup>27</sup> Nevertheless, the applied splat-quenching technique<sup>56</sup> in thin-walled silica capillaries allows fully vitreous small droplets of *g*-Sb<sub>2</sub>S<sub>3</sub> to be obtained. Typical DSC traces for glassy Sb<sub>2</sub>S<sub>3</sub> and canonical *g*-As<sub>2</sub>S<sub>3</sub> are shown in Figure 1. The two end-members are consistent with the reported thermal properties for (Sb<sub>2</sub>S<sub>3</sub>)<sub>x</sub>(As<sub>2</sub>S<sub>3</sub>)<sub>1-x</sub> pseudo-binaries,  $x \leq 0.9$ :<sup>71-73</sup> the glass transition temperature  $T_g$  monotonically increases with  $x$  from 472 K ( $x = 0$ ) to 492 K ( $x = 1$ ), the exothermic crystallization feature emerges above  $x = 0.5$ , grows and shifts toward lower  $T$ , emphasizing the increasing crystallization ability.

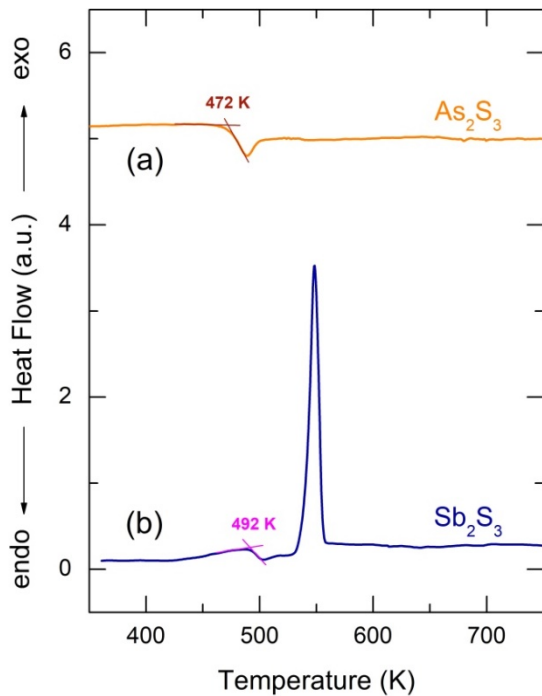

**Figure 1.** DSC traces of glassy (a) As<sub>2</sub>S<sub>3</sub> and (b) Sb<sub>2</sub>S<sub>3</sub>. The derived glass transition temperatures are also indicated.

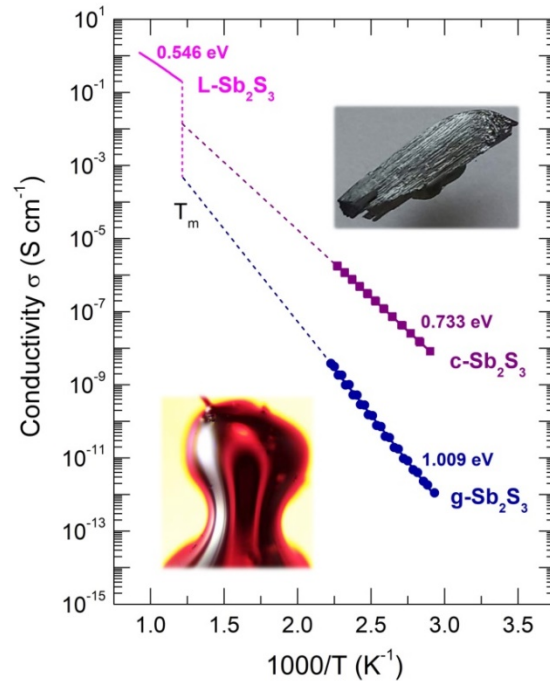

**Figure 2.** Conductivity  $\sigma(T)$  of glassy (*g*), crystalline (*c*) samples (this work), and liquid *L*-Sb<sub>2</sub>S<sub>3</sub>.<sup>74</sup> The inserts show *g*-Sb<sub>2</sub>S<sub>3</sub> and *c*-Sb<sub>2</sub>S<sub>3</sub>.


The conductivity temperature dependences  $\sigma(T)$  for glassy and crystalline (this work), and molten<sup>74</sup> Sb<sub>2</sub>S<sub>3</sub> are shown in Figure 2 using an Arrhenius plot:

$$\sigma(T) = \sigma_0 \exp(-E_a/k_B T), \quad (2)$$

where  $\sigma_0$  is the pre-exponential factor,  $E_a$  the conductivity activation energy, and  $k_B$  and  $T$  have their usual meaning. We note a significant electrical contrast between glassy and crystalline

samples,  $\approx 4.5$  orders of magnitude at room temperature with corresponding difference in activation energy,  $E_a^{\text{cryst}} = 0.733$  eV but  $E_a^{\text{glass}} = 1.009$  eV. The conductivity increases on melting by three orders of magnitude compared to extrapolated glass value, while the activation energy drops nearly by a factor of 2. The pre-exponential factor appears to be very similar for all three  $\text{Sb}_2\text{S}_3$  phases,  $400 \leq \sigma_0 \leq 800$  S  $\text{cm}^{-1}$ , and indicates a conductivity mechanism over extended (delocalized) electron states.<sup>75</sup> The obtained results are consistent with the reported values of conductivity parameters and optical bandgap  $E_g$  for bulk crystalline samples and amorphous or crystalline thin films,  $1.5 \leq E_g(c\text{-Sb}_2\text{S}_3) \leq 1.8$  eV and  $2.0 \leq E_g(a\text{-Sb}_2\text{S}_3) \leq 2.4$  eV.<sup>1,76-79</sup> In addition, the conductivity seems to be intrinsic since  $2E_a \cong E_g$ .

**3.2. Nanocrystalline  $\text{Sb}_2\text{S}_3$ .** Insufficiently rapid quenching rate or wrong starting temperature for splat-cooling yields a nanocrystalline alloy, which is slightly different from the stable orthorhombic polymorph, space group  $Pnma$ .<sup>16</sup> The observed Bragg peaks mostly correspond to orthorhombic antimony sesquisulfide, but we should note slight deviations of the peak positions and their different amplitudes compared to the reference compound, Figure 3a. Besides, a non-negligible amorphous fraction is also present and possibly some traces of monoclinic high- $T$   $\text{Sb}_2\text{S}_3$  polymorph, which is metastable at room temperature.<sup>18</sup>

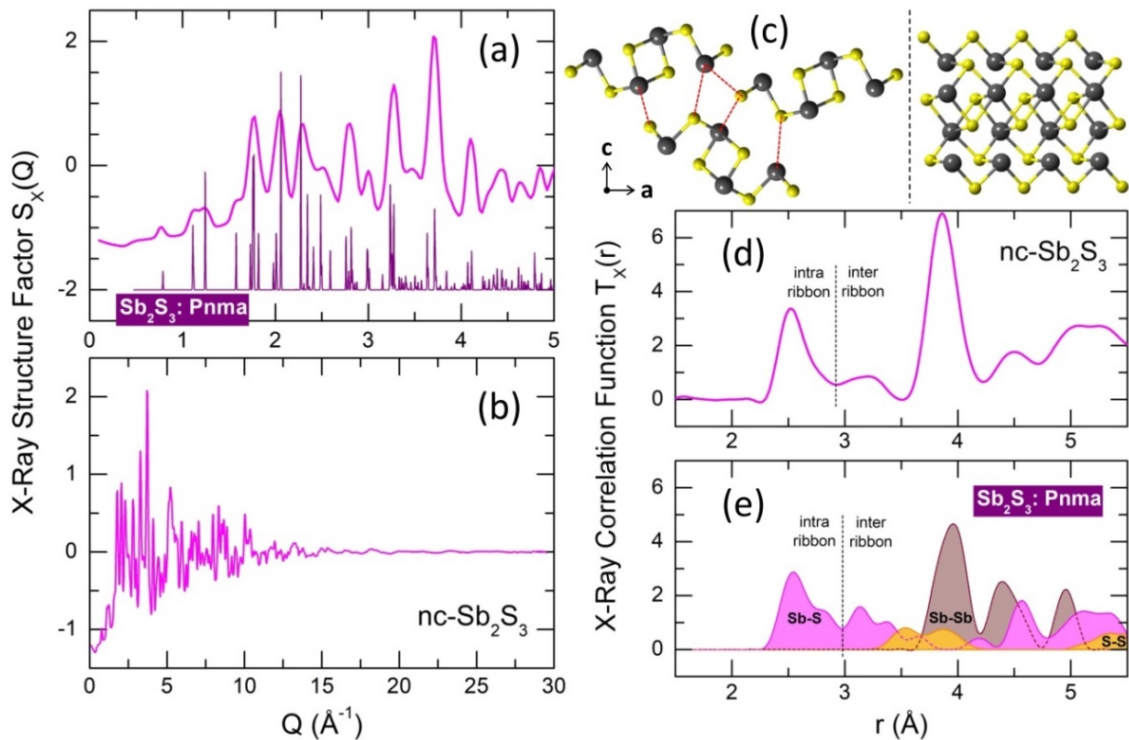

**Figure 3.** Nanocrystalline ( $nc$ ) and orthorhombic  $\text{Sb}_2\text{S}_3$ . (a) Bragg peaks of the nanocrystalline sample in comparison with orthorhombic polymorph<sup>16</sup>, space group  $Pnma$ ; (b) X-ray structure factor  $S_X(Q)$  over the entire  $Q$ -range; (c)  $(\text{Sb}_4\text{S}_6)_\infty$  ribbons in orthorhombic  $\text{Sb}_2\text{S}_3$ : *left*, atomic arrangements using projection on the  $(a, c)$  plane, *right*, a single ribbon oriented parallel to the  $b$  axis; (d) X-ray total correlation function  $T_X(r)$  of  $nc\text{-Sb}_2\text{S}_3$ ; (e)  $\text{Sb-S}$  (magenta),  $\text{Sb-Sb}$  (light brown) and  $\text{S-S}$  (yellow)  $T_{ij}(r)$  partials for orthorhombic  $\text{Sb}_2\text{S}_3$ . The dashed red lines in (c), *left* panel, show the shortest inter-ribbon  $\text{Sb-S}$  distances (3.167-3.642  $\text{\AA}$ ). The black dashed lines in (d) and (e) separate intra- (2.455-2.854  $\text{\AA}$ ) and inter-ribbon  $\text{Sb-S}$  nearest contacts.

The X-ray total correlation function  $T_X(r)$  of nanocrystalline  $\text{Sb}_2\text{S}_3$ , Figure 3d, obtained by the usual Fourier transform of the structure factor  $S_X(Q)$ , Figure 3b,


$$T_X(r) = 4\pi\rho_0 r + \frac{2}{\pi} \int_0^{Q_{\max}} Q[S_X(Q) - 1] \sin Qr M(Q) dQ, \quad (3)$$

where  $M(Q)$  is a modification function and  $\rho_0$  is the experimental number density, confirms characteristic differences between nanocrystalline and orthorhombic antimony sesquisulfides. The latter is formed by infinite quasi one-dimensional (1D)  $(\text{Sb}_4\text{S}_6)_\infty$  ribbons oriented parallel to the  $\mathbf{b}$  axis, Figure 3c. The inner Sb(II) atoms have 5 sulfur neighbors forming a distorted square pyramid with Sb(II) species located 0.17 Å below the basal plan of the pyramid. The outer Sb(I) counterparts reside at the apex of trigonal  $\text{SbS}_3$  units connected by two-fold sulfur at the ribbon periphery and three-fold sulfur toward Sb(II) and the ribbon interior. The average intra-ribbon antimony coordination appears to be  $\langle N_{\text{Sb-S}}^{\text{intra}} \rangle = 4$  while their sulfur neighbors have  $\langle N_{\text{S-Sb}}^{\text{intra}} \rangle = 2.67$ . The Sb(II)-S nearest neighbor (NN) distances reveal a strong Peierls distortion,  $r_{\text{Sb(II)-S}}^{5\text{F}} = 2.70 \pm 0.16$  Å, while the intra-ribbon contacts for trigonal Sb(I) are uniform,  $r_{\text{Sb(I)-S}}^{3\text{F}} = 2.53 \pm 0.01$  Å. The 1D- $(\text{Sb}_4\text{S}_6)_\infty$  entities are held together by rather strong inter-ribbon forces forming puckered sheets within the  $(\mathbf{a}, \mathbf{c})$  plane. The shortest Sb-S inter-ribbon distances,  $3.167 \leq r_{\text{Sb-S}}^{\text{inter}} \leq 3.642$  Å, are smaller than the sum of the van der Waals radii,  $r_{\text{S}}^{\text{vdW}} = 1.8$  Å and  $r_{\text{Sb}}^{\text{vdW}} = 2.2$  Å,<sup>80</sup> but larger than the Sb-S intra-ribbon NN contacts,  $2.455 \leq r_{\text{Sb-S}}^{\text{intra}} \leq 2.854$  Å. The intra- and inter-ribbon separations are well distinguished using the  $T_{\text{SbS}}(r)$  partials for both orthorhombic and nanocrystalline  $\text{Sb}_2\text{S}_3$ , Figure 3d,e. The main difference between the two forms resides in the inter-ribbon connectivity. In average, each antimony in orthorhombic  $\text{Sb}_2\text{S}_3$  has three short Sb-S inter-ribbon contacts,  $\langle N_{\text{Sb-S}}^{\text{inter}} \rangle = 3$ , while the connectivity in  $nc\text{-Sb}_2\text{S}_3$  is reduced,  $\langle N_{\text{Sb-S}}^{\text{inter}} \rangle \approx 1.5$ . In other words, the 1D- $(\text{Sb}_4\text{S}_6)_\infty$  ribbons are becoming more isolated in nanocrystalline lattice.


**3.3. Raman Spectroscopy and DFT Modeling.** Typical Raman spectra of glassy  $\text{Sb}_2\text{S}_3$  as a function of temperature are shown in Figure 4b. The temperatures between  $293 \leq T \leq 423$  K correspond to the solid glass, Figure 4a. Above  $T_g = 492$  K, the supercooled liquid rapidly crystallizes at 523 K, Figure 4c, just in the vicinity of DSC crystallization onset. Cooling down the crystallized sample, one obtains a typical spectrum of orthorhombic  $\text{Sb}_2\text{S}_3$ , characterized by multiple Raman-active modes  $\Gamma = 10A_g + 5B_{1g} + 10B_{2g} + 5B_{3g}$ , expected for the  $Pnma$  polymorph.<sup>81</sup> Usually, about ten modes are clearly distinguishable.<sup>20,21,26</sup>

The Raman spectrum of  $L\text{-Sb}_2\text{S}_3$  at 873 K appears to be reminiscent of its glassy counterpart, Figure 4d, except for a strong S-S stretching at 490  $\text{cm}^{-1}$ . Assuming a dissociation reaction  $2\text{Sb-S} \rightleftharpoons \text{Sb-Sb} + \text{S-S}$ , we also should expect a broad Sb-Sb stretching at  $\approx 145$   $\text{cm}^{-1}$  as in amorphous antimony,<sup>82,83</sup> also confirmed by DFT modeling, Figure S1 in the Supporting Information. A low-frequency vibration feature below 180  $\text{cm}^{-1}$  may contain both Sb-S bending and Sb-Sb stretching. We should however note that the appearance of intense S-S stretching in liquid  $\text{Sb}_2\text{S}_3$  can be a transient phenomenon. Previously, both sulfur and antimony were detected on heating or laser-induced processing of amorphous  $\text{Sb}_2\text{S}_3$  thin films, partly as intermediate species.<sup>84-87</sup> A limited accessible temperature range for our in situ Raman measurements does not enable further experiments at higher  $T$ . Nevertheless, a temperature-dependent dynamics on melting was observed over a limited  $T$ -range, Figure S2.



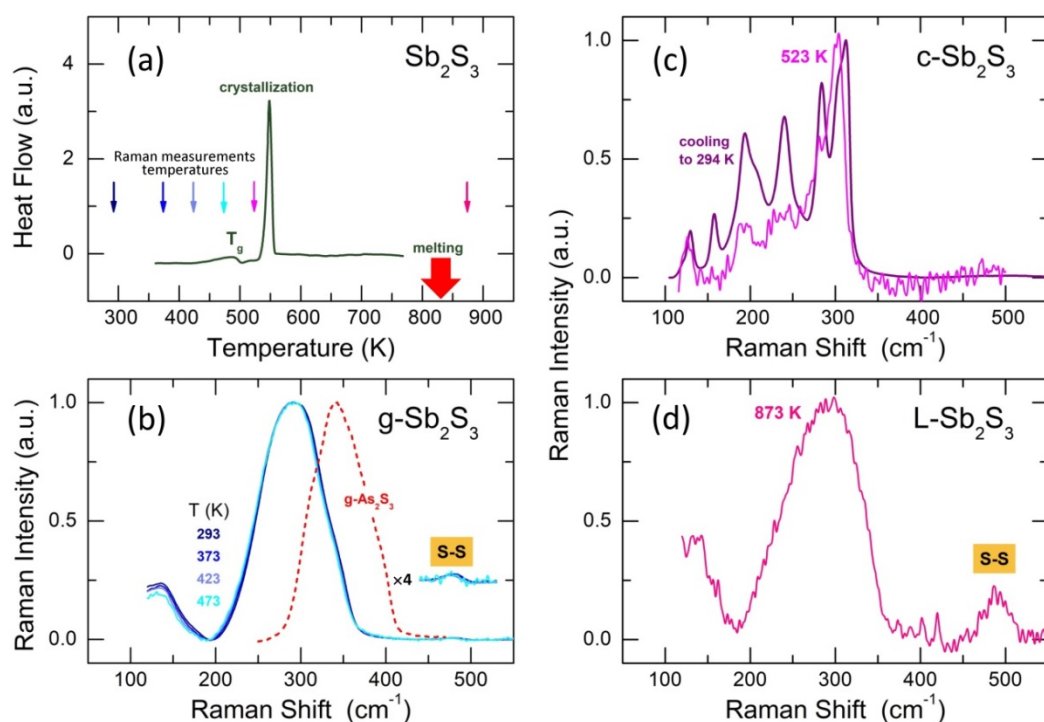

**Figure 4.** Raman spectra of antimony sesquisulfide: (a) DSC trace of  $g$ - $\text{Sb}_2\text{S}_3$ , the arrows show the Raman measurement temperatures; (b) spectra of a solid glass as a function of temperature, the insert shows S-S stretching at  $\approx 490 \text{ cm}^{-1}$ ; (c) spectra of orthorhombic polymorph at 523 K and after cooling to room temperature; (d) Raman spectrum of molten  $\text{Sb}_2\text{S}_3$  at 873 K. The dashed red line in (b) also shows the As-S stretching envelope in  $g$ - $\text{As}_2\text{S}_3$ . See text for further details.

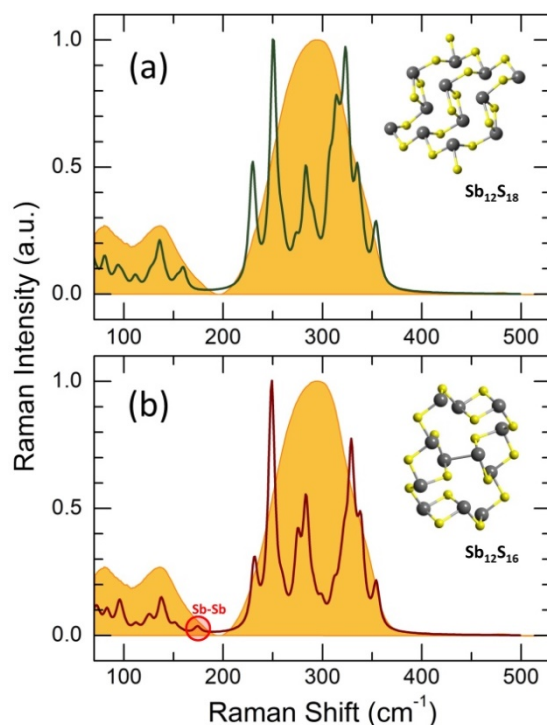


**Figure 5.** DFT Raman spectra of (a)  $\text{Sb}_{12}\text{S}_{18}\text{H}_2$  and (b)  $\text{Sb}_{12}\text{S}_{16}$  size-limited clusters in comparison with experimental Raman spectrum of  $g$ - $\text{Sb}_2\text{S}_3$ , highlighted in yellow for the two panels. The terminal hydrogen species in (a) are omitted, and the H-related vibrations are removed from the spectrum. The inserts show DFT-optimized clusters. Weak Sb-Sb stretching in (b) is emphasized by the red circle.

Basically, a broad asymmetric unresolved feature centered at  $\nu_{\max}^{\text{Sb}_2\text{S}_3} \approx 292 \text{ cm}^{-1}$  in glassy  $\text{Sb}_2\text{S}_3$  is similar to that in  $g\text{-As}_2\text{S}_3$  ( $\nu_{\max}^{\text{As}_2\text{S}_3} \approx 340 \text{ cm}^{-1}$ ) but shifted to lower frequencies, Figure 4b, roughly scaling with the molecular mass ratio,  $\nu_{\max}^{\text{Sb}_2\text{S}_3} / \nu_{\max}^{\text{As}_2\text{S}_3} \approx \sqrt{M_{\text{As}_2\text{S}_3} / M_{\text{Sb}_2\text{S}_3}}$ . Amorphous  $\alpha\text{-Sb}_2\text{S}_3$  thin films and antimony-containing bulk sulfide glasses reveal similar vibrational features.<sup>2,88-92</sup> Assuming trigonal antimony local coordination<sup>27</sup> and the above resemblance in Raman spectra, various DFT simulations have been carried out. Isolated pyramidal units  $\text{SbS}_3\text{H}_3$ , corner-  $\text{CSb}_2\text{S}_5\text{H}_4$  and edge-sharing  $\text{ESb}_2\text{S}_4\text{H}_2$  dimers of different conformation, and small rings,  $\text{Sb}_3\text{S}_6\text{H}_3$  or  $\text{Sb}_6\text{S}_{12}\text{H}_6$ , systematically reveal overestimated Sb-S stretching frequencies, centered at  $320 \leq \langle \nu_{\max}^{\text{Sb-S}} \rangle \leq 350 \text{ cm}^{-1}$ , Figure S3 in the Supporting Information. Reasonable results yield complicated clusters  $\text{Sb}_{12}\text{S}_{18}\text{H}_2$  and  $\text{Sb}_{12}\text{S}_{16}$ , originating from the modified ribbons in orthorhombic  $\text{Sb}_2\text{S}_3$  but with exclusively trigonal antimony coordination, Figure 5. Both symmetric and asymmetric stretching frequencies, as well as low-frequency bending and deformation modes below  $190 \text{ cm}^{-1}$  are well reproduced by these clusters. As expected, the Sb-Sb stretching in  $\text{Sb}_{12}\text{S}_{16}$  is overlapping with Sb-S bending and deformation making impossible to distinguish these vibrations experimentally. In contrast, the S-S stretching at  $490 \text{ cm}^{-1}$  is clearly visible in Raman scattering, Figure 4b,d, and confirmed by DFT simulations, Figure S3, cluster  $\text{Sb}_2\text{S}_6\text{H}_4$ . The geometry of DFT-optimized size-limited clusters is consistent with crystalline references and glassy  $\text{Sb}_2\text{S}_3$ , Figure S4 and S5, specifically that of  $\text{Sb}_{12}\text{S}_{18}\text{H}_2$  and  $\text{Sb}_{12}\text{S}_{16}$ .

Raman spectroscopy measurements show that the glass structure hardly evolves at  $T \lesssim T_g$ ; a negligible red shift of the Sb-S stretching envelope can only be observed, Figure 4b. The rapid crystallization above  $T_g$  seems to be related to the presence of modified structural motifs originating from the  $(\text{Sb}_4\text{S}_6)_\infty$  entities, although the Sb(II) species lose their 5-fold coordination in the glass. Further insight into the atomic glass structure yields high-energy X-ray diffraction supported by first-principles molecular dynamics (FPMD).

**3.4. High-Energy X-Ray Diffraction over the Extended Temperature Range.** Typical X-ray structure factors  $S_X(Q)$  for  $g\text{-Sb}_2\text{S}_3$ , supercooled (673–773 K) and normal ( $T \geq 843 \text{ K}$ ) liquids are shown in Figure 6a-c. The  $S_X(Q)$ 's exhibit well-defined oscillations up to  $30 \text{ \AA}^{-1}$ , ensuring high-resolution in the  $r$ -space. The oscillations amplitude decreases with increasing temperature but more significant changes are observed at low  $Q \lesssim 5 \text{ \AA}^{-1}$ .

Except distinct first sharp diffraction peak (FSDP) at  $Q_0 = 1.22 \text{ \AA}^{-1}$ , typical for a large majority of chalcogenide glasses, glassy  $\text{Sb}_2\text{S}_3$  reveals an additional low- $Q$  feature at  $Q_{\text{Sb}} = 1.75 \text{ \AA}^{-1}$ , specific for antimony, which emerges and increases in glassy  $(\text{Sb}_2\text{S}_3)_x(\text{As}_2\text{S}_3)_{1-x}$  pseudo-binaries with increasing  $x$ .<sup>71</sup> Later, we will see that the  $1.75 \text{ \AA}^{-1}$  feature corresponds to the principle peak  $\text{PP}_{\text{Sb}}$  in the Sb-Sb partial structure factor  $S_{\text{SbSb}}(Q)$ , diverging from that in the  $S_{\text{SS}}(Q)$  partial at  $Q_{\text{S}} = 2.24 \text{ \AA}^{-1}$  because of a large difference in atomic size of antimony and sulfur, whose covalent radii are  $r_{\text{Sb}} = 1.45 \text{ \AA}$  and  $r_{\text{S}} = 1.03 \text{ \AA}$ .<sup>93,94</sup> The FSDP and  $\text{PP}_{\text{Sb}}$  are better visible after removing the background underneath the low- $Q$  features using the subtraction procedure,<sup>95,96</sup> Figure 6a.

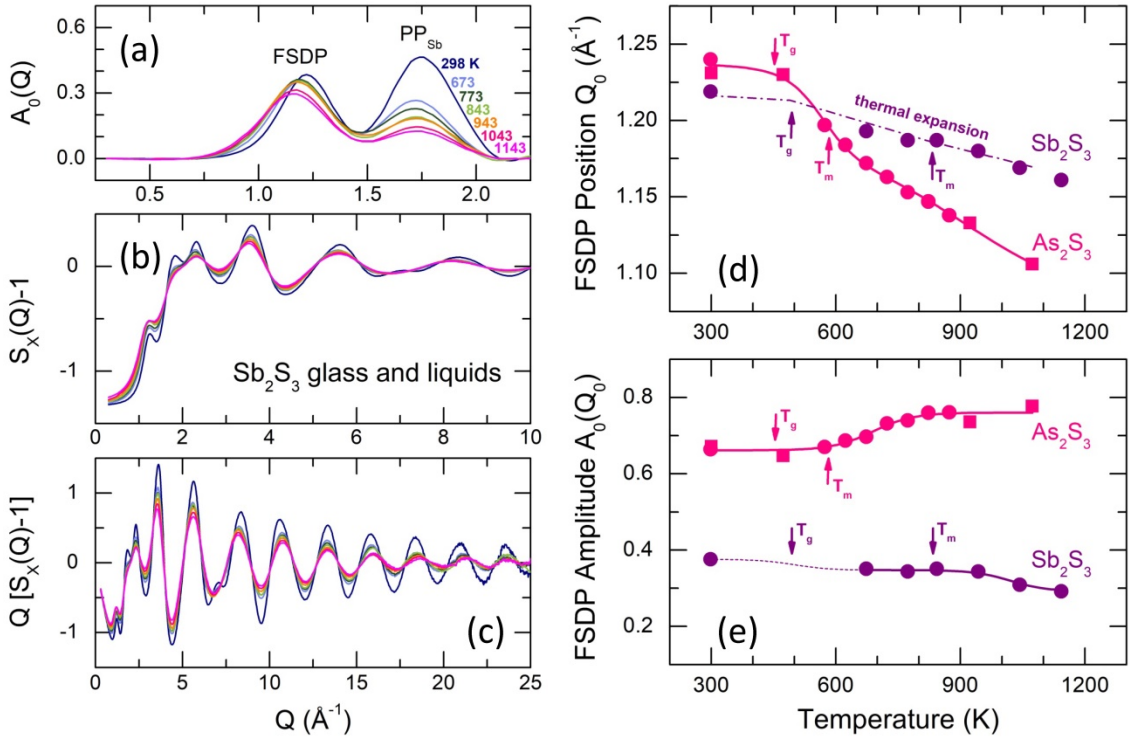


**Figure 6.** High-energy X-ray diffraction data in  $Q$ -space for glassy and liquid Sb<sub>2</sub>S<sub>3</sub>: (a) isolated first sharp diffraction peak (FSDP) and Sb-Sb diffraction feature PP<sub>Sb</sub> as a function of temperature; (b) X-ray structure factor  $S_X(Q)$  over a limited  $Q$ -range and (c) interference function  $Q[S_X(Q)-1]$  as a function of temperature; (d) the FSDP position  $Q_0(T)$  and (e) amplitude  $A_0(Q_0, T)$  for antimony and arsenic sesquisulfides. The dash-dotted line for Sb<sub>2</sub>S<sub>3</sub> in (d) shows the expected  $Q_0(T)$  trend taking into account the thermal expansion. The arrows show the glass transition temperature  $T_g$  and melting point  $T_m$  for As<sub>2</sub>S<sub>3</sub> and Sb<sub>2</sub>S<sub>3</sub>. The solid and dashed lines in (d) and (e) are a guide to the eye.

The FSDP amplitude  $A_0(Q_0)$  slightly decreases in intensity with increasing  $T$  and shifts to lower  $Q$ , Figure 6a. In contrast, changes in the PP<sub>Sb</sub> amplitude are more significant (especially between the solid glass and liquids) and similar to other peaks and distant oscillations, Figure 6b,c. In addition, these temperature changes are characteristic for chalcogenide glasses and liquids, while the FSDP behaves differently. Comparison with canonical As<sub>2</sub>S<sub>3</sub> reveals both a common trend and a dissimilarity, Figure 6d,e. In particular, the FSDP position  $Q_0(T)$  for Sb<sub>2</sub>S<sub>3</sub> follows the thermal expansion,  $Q_0(T) \propto \rho(T)^{1/3}$ ,<sup>97</sup> where  $\rho(T)$  is the macroscopic number density, while  $Q_0(T)$  for As<sub>2</sub>S<sub>3</sub> is not. We will discuss this topic later.


The X-ray total correlation functions  $T_X(r)$  for glassy and liquid Sb<sub>2</sub>S<sub>3</sub>, obtained by the usual Fourier transform of  $S_X(Q)$ , are shown in Figure 7. The first peak at  $2.484 \pm 0.004$  Å corresponds to Sb-S nearest neighbors followed by a strongly asymmetric second neighbor (2<sup>nd</sup>N) peak at  $3.83 \pm 0.02$  Å with additional unresolved correlations between 2.8 and 3.4 Å. The third distinct feature at 5.7 Å seems to be related to a center-center distance between the Sb-S entities. All peaks become less intense and broader with increasing temperature, also leading to a stronger overlapping between NN and second neighbor correlations. More distant broad peaks at 7.3 and 9 Å appear to be hardly visible in  $L$ -Sb<sub>2</sub>S<sub>3</sub>. Gaussian fitting of the NN and 2<sup>nd</sup>N correlations is inappropriate because of the peak asymmetry. Typical fitting with asymmetric functions is shown in Figure 7a and yields reasonable results. The average antimony coordination  $N_{Sb-X}$ , where  $X = S$  and/or Sb, was found to be trigonal and consisting of two contributions,

$N_{\text{Sb-X}} = N_{\text{Sb-S}} + N_{\text{Sb-Sb}} = 2.90(5) + 0.10(5)$ , Figure 7c (see also Table 1). The Sb-S and Sb-Sb NN distances slightly increase with temperature; the both interatomic separations,  $r_{\text{Sb-S}} = 2.484 \pm 0.004 \text{ \AA}$  and  $r_{\text{Sb-Sb}} = 2.92 \pm 0.02 \text{ \AA}$ , are consistent with crystalline and amorphous references for trigonal antimony sulfides and elemental Sb.<sup>16-18,93,98</sup> Typical broadening of the Sb-S NN feature as a function of temperature is shown in Figure 7f. Both supercooled and normal liquids  $\text{Sb}_2\text{S}_3$  exhibit a monotonic increase of  $w_{\text{Sb-S}}(T)$ .

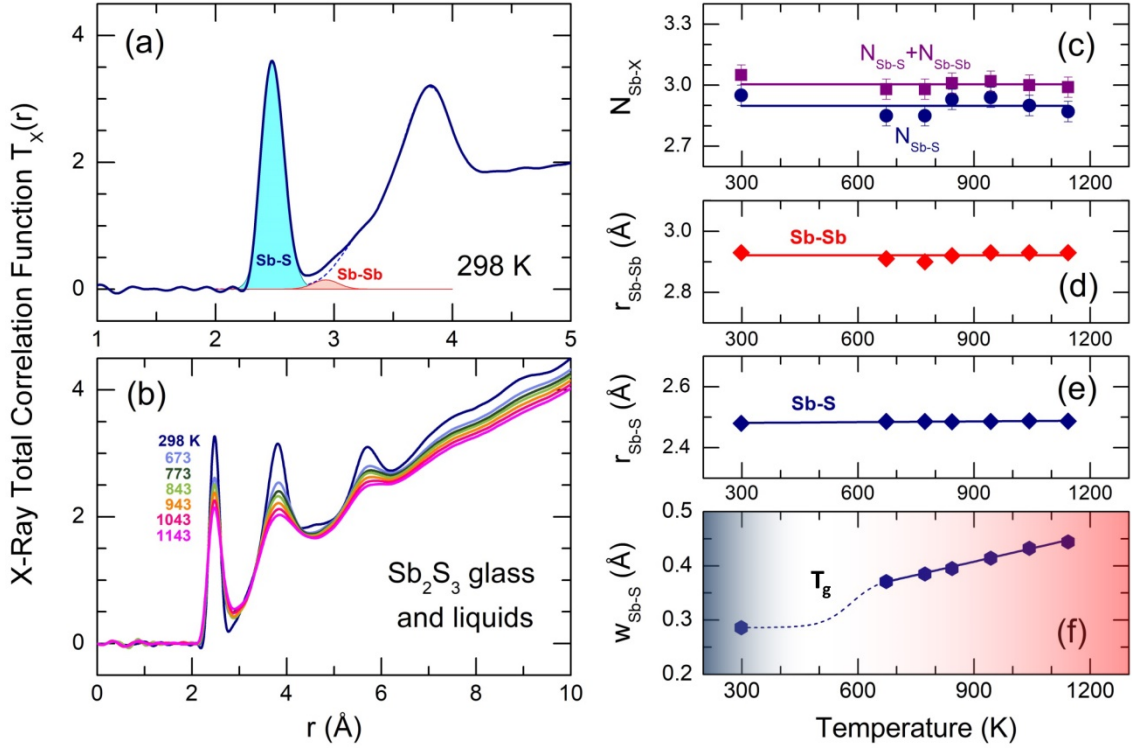

**Figure 7.** High-energy X-ray diffraction data in  $r$ -space for glassy and liquid  $\text{Sb}_2\text{S}_3$ : (a) typical  $T_X(r)$  fitting with asymmetric functions; Sb-S and Sb-Sb nearest neighbor (NN) correlations are highlighted in cyan and light red, respectively; (b) total correlation functions  $T_X(r)$  over the temperature range  $298 \leq T \leq 1143 \text{ K}$ ; (c) antimony local coordination number as a function of temperature; (purple squares)  $N_{\text{Sb-S}} + N_{\text{Sb-Sb}}$ , (dark blue circles)  $N_{\text{Sb-S}}$ ; interatomic NN distances (d) Sb-Sb and (e) Sb-S as a function of  $T$ ; (f) temperature dependence of asymmetric peak width for Sb-S NN correlations  $w_{\text{Sb-S}}$ ; the solid glass and supercooled or normal liquid temperature domains are highlighted in blue and red, respectively. The dashed line in (f) is a guide to the eye. The other solid lines are a least-square fit of the experimental data.

**3.5. First-Principles Molecular Dynamics Modeling of Glassy and Liquid  $\text{Sb}_2\text{S}_3$ .** The derived FPMD interference functions  $Q[S_X(Q)-1]$  and pair-distribution functions  $g_X(r)$  for the two extremes in experimental series at 300 and 1150 K are shown in Figure 8. As it was reported earlier,<sup>56-59</sup> the FPMD with hybrid functional PBE0 yields a good agreement with experimental data for chalcogenide systems. The FPMD replicas in  $Q$ -space reproduce well both the positions and amplitudes of oscillations for  $Q[S_X(Q)-1]$ , Figure 8a,b. As a result, the derived interatomic distances in  $r$ -space are also consistent with the diffraction results, Figure 8c,d. In contrast, FPMD modeling with the standard functional PBE suffers from over- or underestimated correlations in  $Q$ - and  $r$ -space as it is shown in Figure S6.

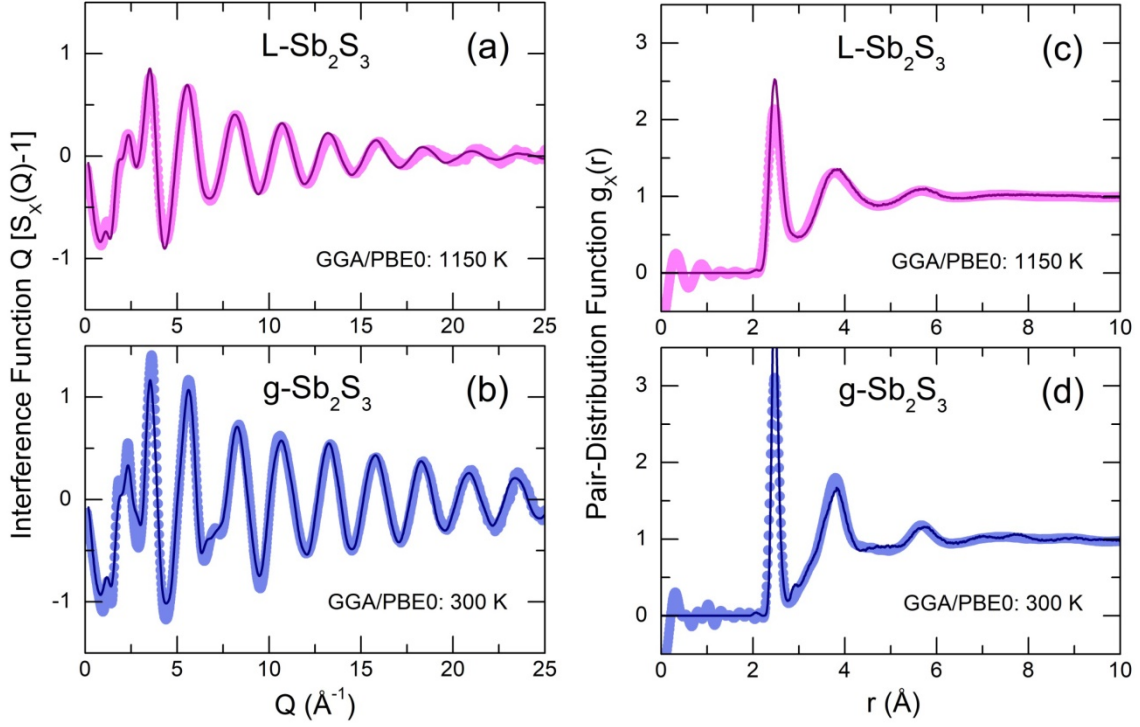


**Figure 8.** FPMD modeling results using hybrid functional GGA/PBE0 in comparison with experimental high-energy X-ray diffraction data for  $\text{Sb}_2\text{S}_3$ ; interference function  $Q[S_x(Q)-1]$  at (a) 1150 K and (b) 300 K; pair-distribution function  $g_x(r)$  at (c) 1150 K and (d) 300 K. The solid circles correspond to experimental data; the solid lines are the FPMD results.

**Table 1.** Interatomic distances  $r_{ij}$  and partial coordination numbers  $N_{ij}$  in glassy and liquid  $\text{Sb}_2\text{S}_3$ .

Temperature (K)	S-S		Sb-S		Sb-Sb	
	$r_{\text{S-S}}$ (Å)	$N_{\text{S-S}}$	$r_{\text{Sb-S}}$ (Å)	$N_{\text{Sb-S}}$	$r_{\text{Sb-Sb}}$ (Å)	$N_{\text{Sb-Sb}}$
High-Energy X-Ray Diffraction						
298	–	–	2.480(6)	2.95(4)	2.93(2)	0.10(5)
673	–	–	2.486(6)	2.85(4)	2.91(2)	0.13(5)
773	–	–	2.486(6)	2.85(4)	2.90(2)	0.13(5)
843	–	–	2.485(6)	2.93(4)	2.92(2)	0.08(5)
943	–	–	2.486(6)	2.94(4)	2.93(2)	0.08(5)
1043	–	–	2.488(6)	2.90(4)	2.93(2)	0.10(5)
1143	–	–	2.487(6)	2.87(4)	2.93(2)	0.12(5)
First-Principles Molecular Dynamics						
300	2.07	0.07	2.471	2.93	2.90	0.10
700	2.07	0.08	2.474	2.88	2.90	0.12
800	2.07	0.08	2.478	2.89	2.90	0.12
850	2.07	0.08	2.478	2.92	2.91	0.12
950	2.07	0.08	2.482	2.91	2.91	0.13
1050	2.08	0.08	2.480	2.95	2.90	0.13
1150	2.07	0.08	2.478	2.94	2.90	0.13

The partial structure factors  $S_{ij}(Q)$  and pair-distribution functions  $g_{ij}(r)$  are revealed in Figure 9a,b. We note divergent positions of  $PP_{Sb}$  and  $PP_S$  for the  $S_{SbSb}(Q)$  and  $S_{SS}(Q)$  partials, as well as a negative amplitude of  $S_{SbS}(Q)$  in this range, explaining the appearance of additional low- $Q$  feature at  $Q_{Sb} = 1.75 \text{ \AA}^{-1}$  in the X-ray structure factor discussed above, Figure 6a-c. Astonishingly, the FSDP origin appears to be related to Sb-S correlations instead of expected Sb-Sb counterparts. We note, however, that in glassy  $As_2S_3$ , the FSDP origin changes from As-As (major contribution) and As-S (minor component) at ambient pressure to mostly As-S correlations above 4 GPa, Figure S7 in the Supporting Information.

The partial pair-distributions  $g_{ij}(r)$  are consistent with experimental findings. The Sb-S NN peak at  $2.477 \pm 0.004 \text{ \AA}$  exhibits an asymmetric shape, increasing with temperature, Figure S8. The fitting with asymmetric functions yields very similar results to the experimental data,  $\langle N_{Sb-S} \rangle = 2.91 \pm 0.03$ , and the antimony local trigonal coordination is completed by the Sb-Sb nearest neighbors at  $2.903 \pm 0.002 \text{ \AA}$ ,  $\langle N_{Sb-Sb} \rangle = 0.12 \pm 0.01$ , Table 1. The Sb-S second neighbors are located rather close to the Sb-S NN correlations and overlap significantly with increasing temperature despite the shift of  $r_{Sb-S}^{2nd}$  to higher distances from  $3.36 \text{ \AA}$  (300 K) to  $3.51 \text{ \AA}$  (1150 K), mostly because of a strong broadening of the NN and 2<sup>nd</sup>N correlations, Figure S8.

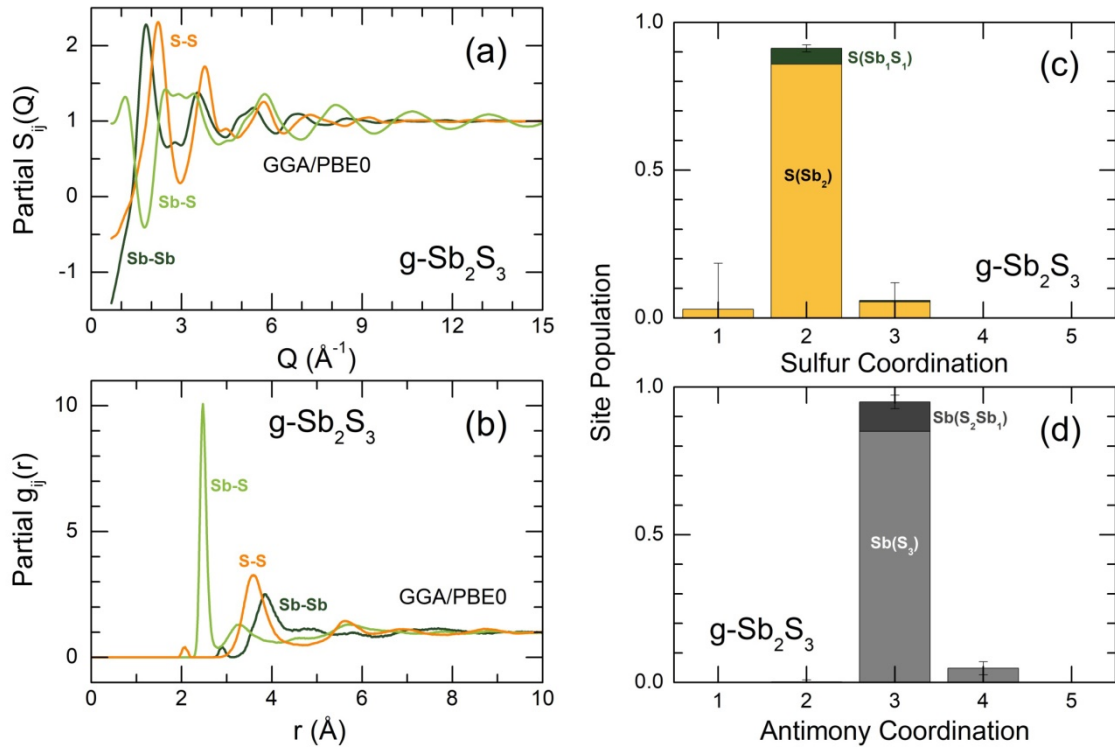


**Figure 9.** Derived FPMD partial functions for glassy  $Sb_2S_3$  at 300 K in (a)  $Q$ -space,  $S_{ij}(Q)$ , and (b)  $r$ -space,  $g_{ij}(r)$ ; and local coordination numbers for (c) sulfur,  $N_{S-X}$ , and (d) antimony,  $N_{Sb-X}$ , where  $X = S$  or  $Sb$ .

The  $g_{SS}(r)$  partial also shows S-S homopolar bonds at  $2.07 \text{ \AA}$ , Figure 9b,  $\langle N_{S-S} \rangle = 0.08 \pm 0.01$ , Table 1. The Raman spectroscopy confirms this result, Figure 4b. Nevertheless, their concentration is too low to be observed by high-energy X-ray diffraction. Figure 8c,d reveals that the S-S FPMD diffraction features are less intense compared to experimental noise of  $g_X(r)$ .

Sulfur and antimony coordination distributions are plotted in Figure 9c,d. As expected, the overwhelming majority of the two species have a two-fold (91%) and trigonal (95%) local

coordination, respectively. With increasing temperature, the population of two-fold sulfur and three-fold antimony decreases, while the fractions of under- and over-coordinated species grow, Figure S9. The number of sulfur or antimony local configurations with homopolar bonds, that is,  $S(Sb_1S_1)$  instead of  $S(Sb_2)$  or  $Sb(S_2Sb_1)$  vs.  $Sb(S_3)$  remains low at all temperatures.

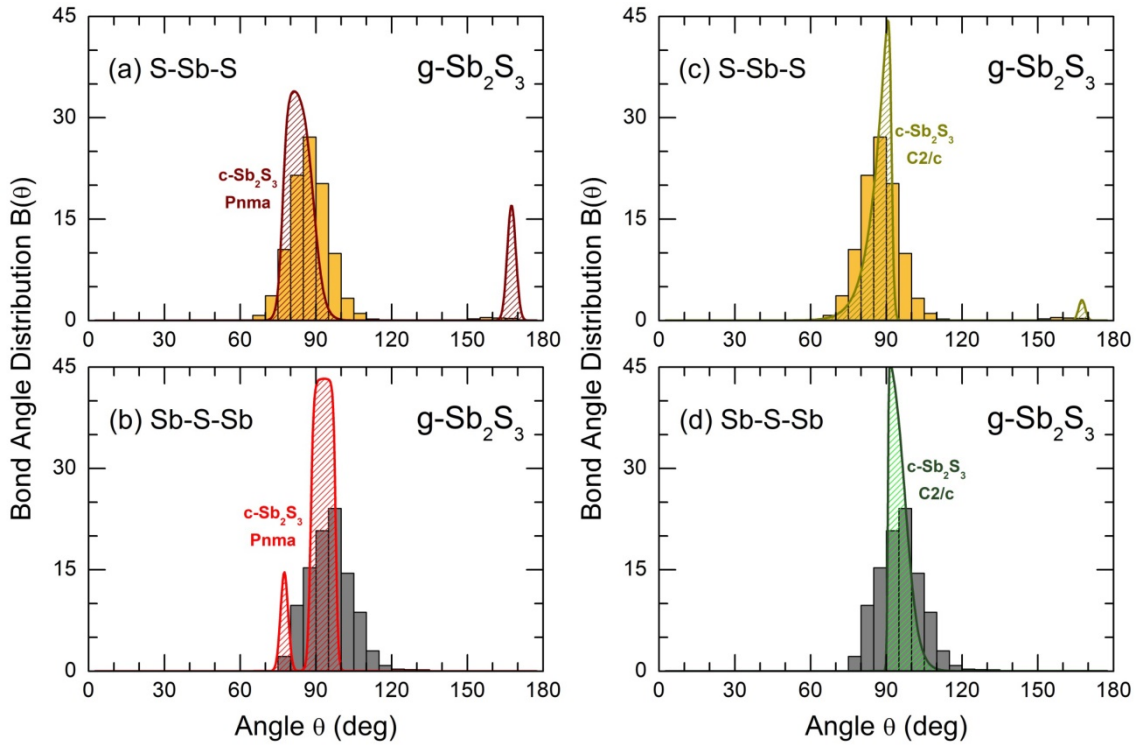


**Figure 10.** Bond angle distributions  $B(\theta)$  for glassy  $Sb_2S_3$ : (a) S-Sb-S and (b) Sb-S-Sb angles in comparison with orthorhombic  $Sb_2S_3$ , space group  $Pnma$ ;<sup>16</sup> and (c) S-Sb-S and (d) Sb-S-Sb in comparison with monoclinic  $Sb_2S_3$ , space group  $C2/c$ .<sup>18</sup>

The bond angle distributions  $B(\theta)$  for S–Sb–S and Sb–S–Sb triplets in glassy  $Sb_2S_3$  are plotted in Figure 10 in comparison with two crystalline counterparts: orthorhombic and monoclinic  $Sb_2S_3$ . The geometry of  $SbS_3$  trigonal pyramids is different from that in canonical  $g-As_2S_3$ ; the maximum of a broad asymmetric distribution  $B_{SSbS}(\theta)$  is located at  $87^\circ$  in opposite to  $98^\circ$  in arsenic sesquisulfide,<sup>99</sup> ensuring a more compact local structure of  $g-Sb_2S_3$ . Roughly speaking,  $SbS_3$  pyramids can be considered as distorted defect octahedral entities, whose three missing Sb-S bonds became excessively long, and the corresponding sulfur species were transformed into the second neighbors. The above mentioned fitting of  $T_{SbS}(r)$  partials, Figure S8, is consistent with this hypothesis, revealing three  $2^{nd}N$  correlations at  $\approx 3.4$  Å. The remnants of octahedral geometry are also evidenced by a weak contribution at  $\theta \approx 160^\circ$ . The  $B_{SSbS}(\theta)$  distributions in orthorhombic and monoclinic polymorphs are rather similar to that in the glass, especially in the high-temperature  $C2/c$  form, including a low-intensity component at  $168 \pm 4^\circ$  of four-fold coordinated Sb(5)/Sb(6) species.<sup>16</sup> The 5-fold coordinated Sb(II) atoms in orthorhombic  $Sb_2S_3$  yield an intense contribution at  $\theta \approx 171^\circ$ .<sup>16</sup>

The connectivity of trigonal pyramids, reflected by  $B_{SbSbSb}(\theta)$  peaked at  $97^\circ$ , is also appeared to be in favor of more compact structure of glassy  $Sb_2S_3$  compared to canonical  $g-As_2S_3$ . The  $B_{AsSAs}(\theta)$  distribution in the latter has a maximum at  $105^\circ$ .<sup>99</sup> Crystalline  $Sb_2S_3$  counterparts

exhibit similar connectivities to glassy antimony sesquisulfide, slightly less evident for the orthorhombic polymorph.

As expected, the supercooled and normal  $\text{Sb}_2\text{S}_3$  liquids are characterized by even more distorted  $\text{Sb-S}$  polyhedra and polyhedral connectivities. Both  $B_{\text{SbSb}}(\theta)$  and  $B_{\text{SbSSb}}(\theta)$  distributions become broader and less symmetric with increasing temperature, Figure S10.

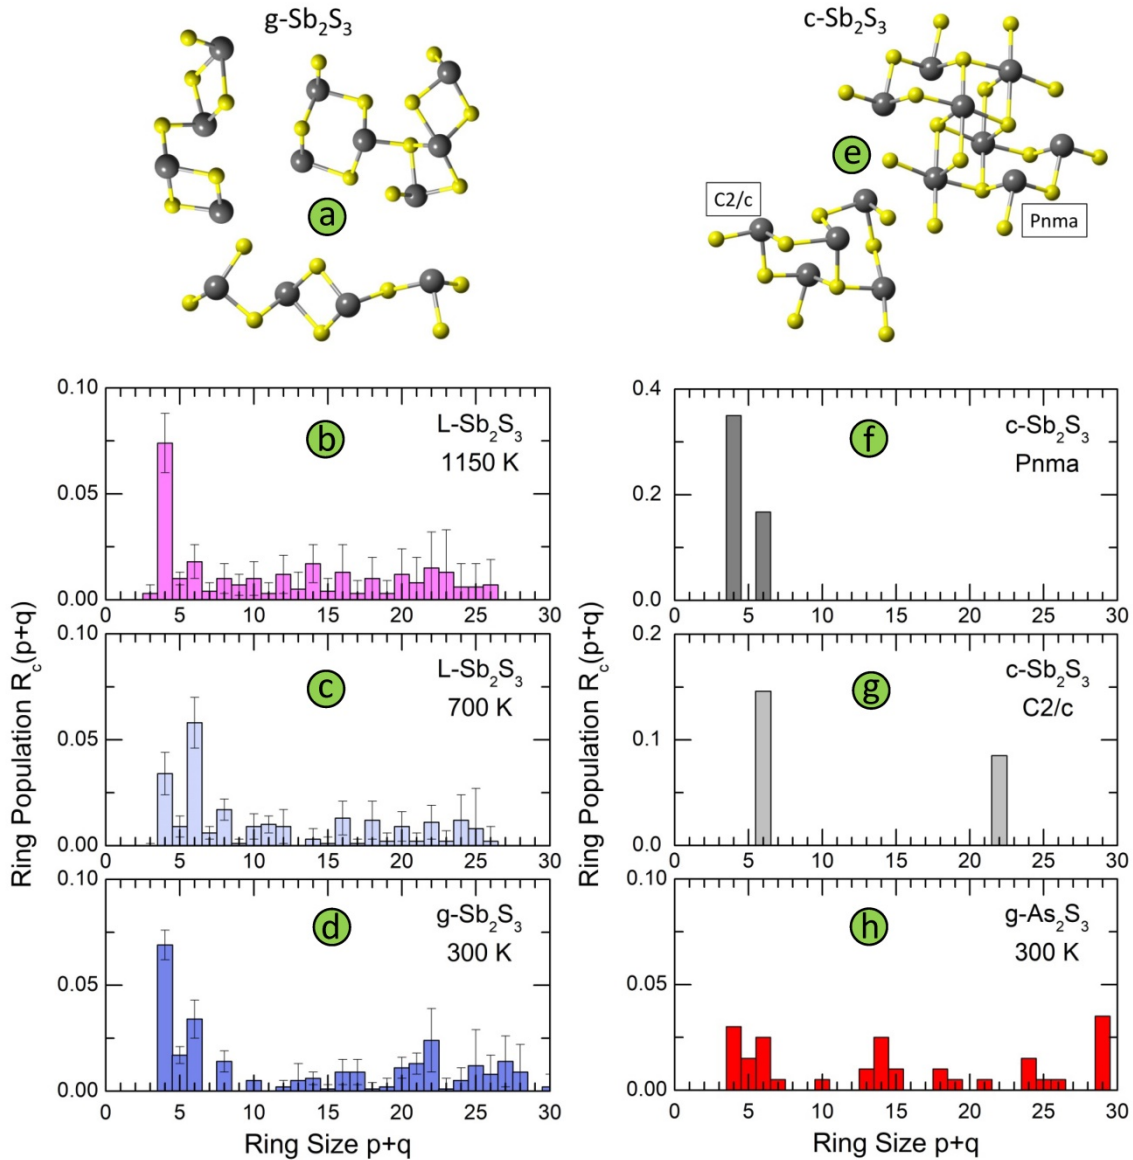


**Figure 11.** Structural motifs and ring statistics; (a) typical fragments in  $g\text{-Sb}_2\text{S}_3$ ; ring statistics in glassy, and liquid  $\text{Sb}_2\text{S}_3$  as a function of temperature: (b) 1150 K (normal liquid), (c) 700 K (supercooled liquid), and (d) 300 K (solid glass); (e) structural motifs in monoclinic  $\text{Sb}_2\text{S}_3$ , space group  $C2/c$ ,<sup>18</sup> and orthorhombic  $\text{Sb}_2\text{S}_3$ , space group  $Pnma$ ;<sup>19</sup> ring statistics in (f) orthorhombic  $\text{Sb}_2\text{S}_3$ , (g) monoclinic  $\text{Sb}_2\text{S}_3$ , and (h) glassy  $\text{As}_2\text{S}_3$ .

The connectivity analysis shows that 96% of Sb and S are forming a single connected fragment. The homopolar bonds in the glass network are mostly related to few Sb-Sb and S-S dimers. Typical structural fragments in  $g\text{-Sb}_2\text{S}_3$  are shown in Figure 11a. We note a certain similarity in the intermediate range order and ring statistics with orthorhombic and monoclinic polymorphs, Figure 11, expected from the bond angle distributions. The orthorhombic crystal has  $ABAB$



squares ( $A$ : Sb;  $B$ : S) and six-membered rings  $Sb_3S_3$ ; the monoclinic form, in addition to 6-fold entities, exhibits also big  $Sb_{11}S_{11}$  rings, Figure 11g. Glassy and liquid  $Sb_2S_3$  reveal a large variety of even- and odd-membered rings  $Sb_pS_q$ ,  $3 \leq p+q \leq 30$ , related to chemical and topological disorder. Nevertheless, the most populated entities have size  $p+q = 4$  and 6. The big rings, showing a broad distribution peaked at  $p+q = 22$ , become progressively unstable with increasing temperature. Their derived population  $R_c(p+q)$ <sup>68</sup> appears to be comparable with temporal fluctuations, reflected by the  $R_c(p+q)$  uncertainty. At the highest temperature (1150 K), the population of  $ABAB$  squares exceeds any other  $R_c(p+q)$ , at least, by a factor of 4, Figure 11b.

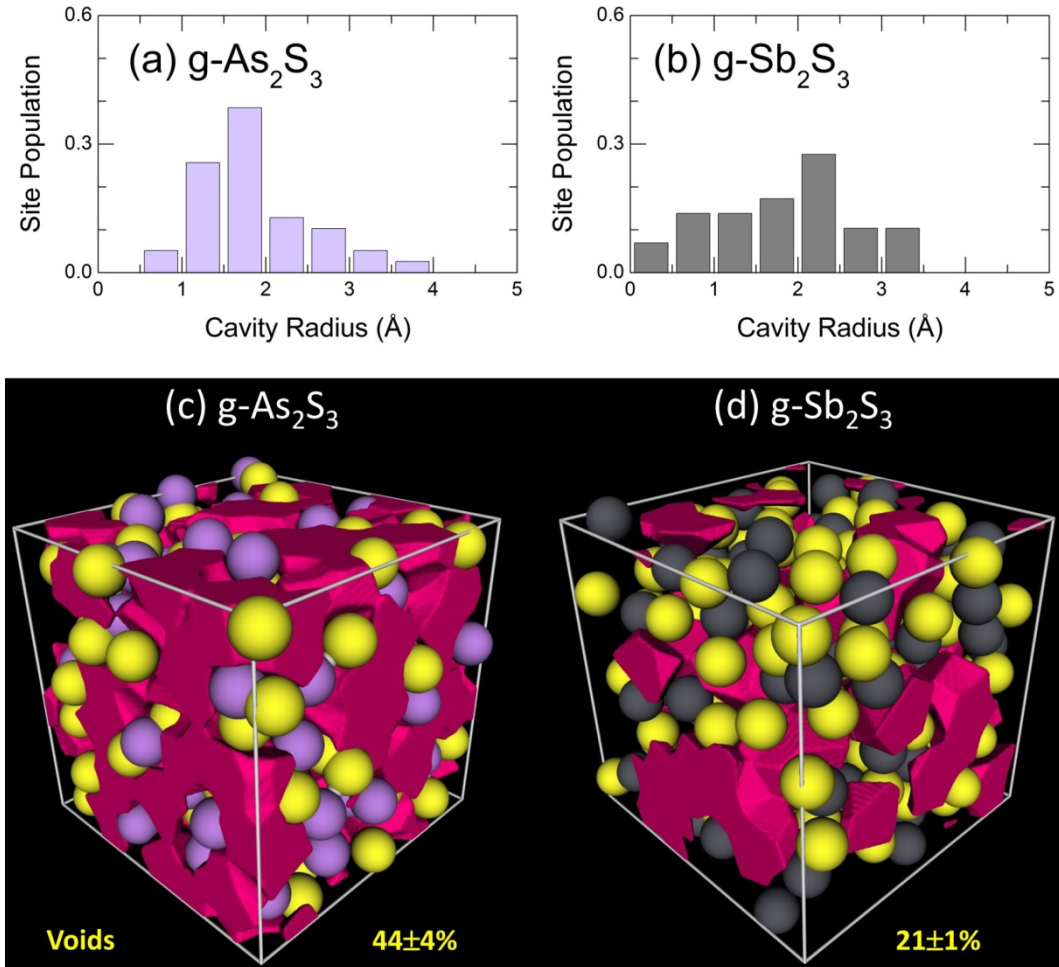

**Figure 12.** Void statistics: characteristic cavity radii in glassy (a)  $As_2S_3$  and (b)  $Sb_2S_3$ ; microscopic voids in (c)  $g-As_2S_3$  and (d)  $g-Sb_2S_3$ .

The ring statistics in  $g-As_2S_3$  is rather similar to that in glassy antimony sesquisulfide. As it was reported previously,<sup>99</sup> the 12-membered rings  $As_6S_6$ , the only rings in monoclinic orpiment<sup>100</sup> and triclinic anorpiment<sup>101</sup>  $As_2S_3$  are absent in glassy arsenic sulfide, Figure 11h.

More dense packing of glassy antimony sesquisulfide, evidenced by bond angle distributions  $B_{SSbS}(\theta)$  and  $B_{SbSSb}(\theta)$ , suggests less microscopic voids and cavities in the glass network compared to  $g-As_2S_3$ . The Dirichlet-Voronoi tessellation<sup>70</sup> allows the cavity fraction  $V_c$ , normalized to the volume of the FPMD simulation box,  $0 \leq V_c \leq 1$ , to be computed. The results are given in Figure 12 for the two pnictide sesquisulfides. As expected, the  $V_c$  in  $g-Sb_2S_3$  is by a

factor of two smaller than that of its arsenic counterpart,  $21\pm 1\%$  vs.  $44\pm 4\%$ , respectively. The average size distribution of microscopic voids is rather similar in the two cases,  $0.5 \leq r_c \leq 4 \text{ \AA}$ , where  $r_c$  is the cavity radius, Figure 12a,b, although the average  $\langle r_c \rangle$  is slightly smaller in glassy  $\text{As}_2\text{S}_3$ .

In summary, glassy and liquid antimony sesquisulfide has distinctly different structural features compared to orthorhombic  $\text{Sb}_2\text{S}_3$ . First, the antimony short range order in the crystal has a bimodal site distribution: 5-fold coordinated Sb(II) species with a strong Peierls distortion and regular trigonal Sb(I) entities. The Sb-S bonding asymmetry is absent in glassy and liquid polymorphs, characterized by a distorted antimony trigonal environment and shorter average  $\langle r_{\text{Sb-S}}^{\text{NN}} \rangle$  distances,  $2.64\pm 0.15 \text{ \AA}$  (*c*- $\text{Sb}_2\text{S}_3$ , *Pnma*) vs.  $2.48\pm 0.01 \text{ \AA}$  (*g*- and *L*- $\text{Sb}_2\text{S}_3$ ). This difference is clearly seen by  $^{121}\text{Sb}$ -Mössbauer spectroscopy,<sup>102</sup> which is very sensitive to the local antimony environment.<sup>103</sup>


Second, the intermediate range order in orthorhombic and glassy  $\text{Sb}_2\text{S}_3$  is also different. The crystal structure is composed of infinite  $1\text{D}-(\text{Sb}_4\text{S}_6)_\infty$  ribbons with rather strong inter-ribbon interactions, while the glass network has a 2D layered structure, roughly reminiscent of that in canonical  $\text{As}_2\text{S}_3$  but with remarkable differences. We should note comparable glass transition temperatures for the two vitreous alloys, Figure 1, similar shape of the Raman spectra, Figure 4, identical pnictide and sulfur local coordination and resembling ring statistics. However, the topology of antimony defect octahedral sites  $\text{SbS}_3$ , evidenced by bond angle distributions, is closer to crystalline  $\text{Sb}_2\text{S}_3$  forms than to vitreous  $\text{As}_2\text{S}_3$ .

**3.6. Electronic Structure and Atomic Dynamics in Glassy and Liquid  $\text{Sb}_2\text{S}_3$ .** The total electronic density of states (eDOS), calculated from the Kohn-Sham eigenvalue spectra, is shown in Figure 13. The valence band (VB) consists of three sub-bands between the Fermi energy  $E_F$  and  $-20 \text{ eV}$ , as in a large majority of crystalline and glassy chalcogenides.<sup>58,75,104-106</sup> The upper asymmetric part, mostly involving sulfur and antimony *p*-electron populations, shows a predominant contribution at  $-2.8 \text{ eV}$  (*g*- $\text{Sb}_2\text{S}_3$  at 300 K) or  $-2.3 \text{ eV}$  (*L*- $\text{Sb}_2\text{S}_3$  at 1050 K), related to S  $3p$  lone pairs. The bonding states at lower energies consist of Sb  $5p$ ,  $5d$  and  $5s$  together with S  $3p$  orbitals. The middle sub-band centered at  $-10.7 \text{ eV}$  (*g*- $\text{Sb}_2\text{S}_3$ ) or  $-10.0 \text{ eV}$  (*L*- $\text{Sb}_2\text{S}_3$ ) has predominantly the *s*-character as well as the low-energy part at approximately  $-15 \text{ eV}$ . The bandgap for glassy ( $E_g = 2.28 \text{ eV}$ ) and liquid ( $E_g = 1.06 \text{ eV}$ ) antimony sesquisulfide are consistent with the reported optical data<sup>1,76-79</sup> and electrical measurements (Figure 2).

The derived eDOS is in good agreement with experimental data<sup>107</sup> and previously reported simulation results.<sup>22,106,108-110</sup> We should however note that simulations with the standard functionals yield strongly underestimated bandgap (roughly by a factor of 2) in addition to insufficient agreement with the nearest and second neighbor correlations (see also Figure S6).

The inverse participation ratio (IPR)<sup>104,111</sup> (Figure 13a,d) characterizes the degree of localization of a single-particle Kohn-Sham eigenfunction  $\psi(\mathbf{r})$

$$\text{IPR} = \frac{\int d\mathbf{r} |\psi(\mathbf{r})|^4}{(\int d\mathbf{r} |\psi(\mathbf{r})|^2)^2}. \quad (4)$$

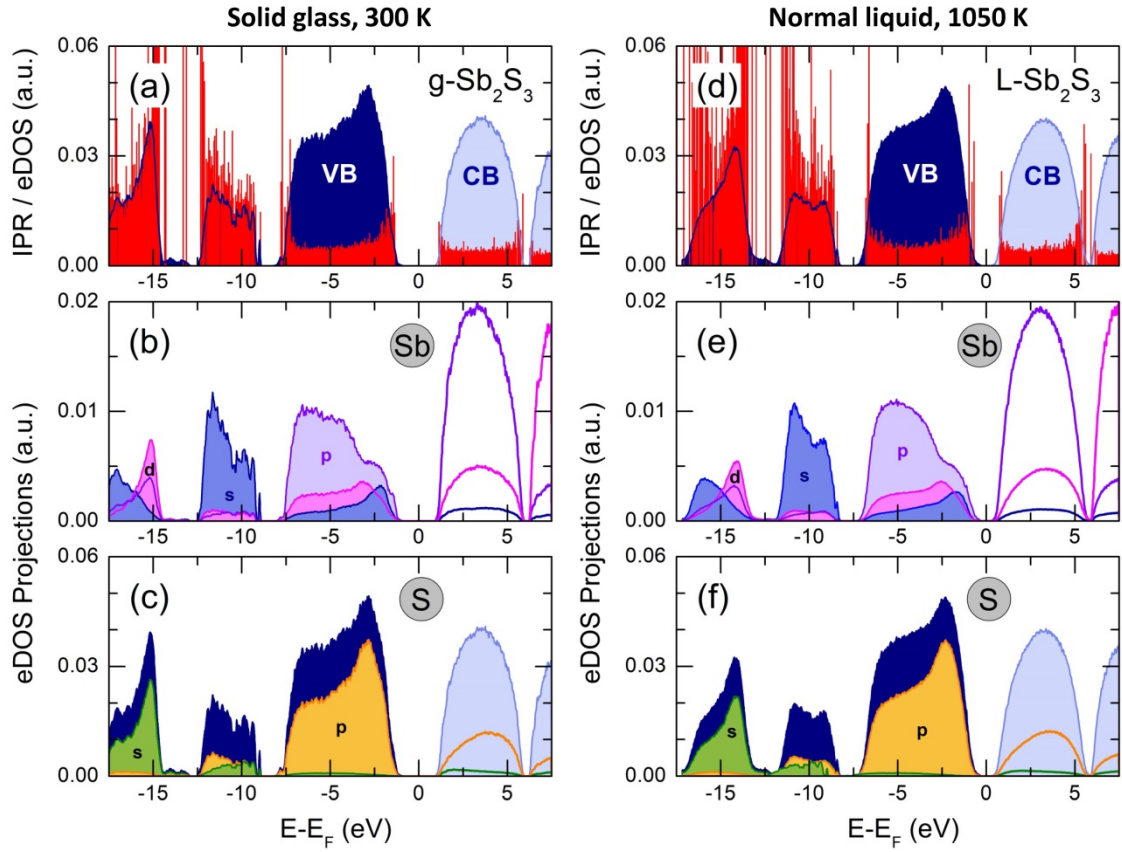

**Figure 13.** Electronic properties of glassy and liquid  $\text{Sb}_2\text{S}_3$ ; solid glass at 300 K: (a) the electronic density of states (eDOS) and the inverse participation ratio (IPR, red spikes), the projected eDOS (pDOS) on (b) antimony  $s$  (blue),  $p$  (violet), and  $d$  (magenta), and (c) sulfur  $s$  (green) and  $p$  (yellow) pseudo-wave functions; normal liquid at 1050 K: (d) eDOS and IPR, (e) antimony pDOS, (f) sulfur pDOS. The valence band (VB) is highlighted in dark blue, the conduction band (CB) in light blue. See text for further details.

A small IPR value ( $\propto N^{-1}$ , where  $N$  is the number of atoms in the simulation box) corresponds to an extended (delocalized) wave function, while a large IPR ( $\lim \text{IPR} \rightarrow 1$ ) indicates a strong localization around specific covalent bond. Similar to previously reported results<sup>58,104,111</sup> and theoretical predictions,<sup>75</sup> the electron states in glassy and liquid  $\text{Sb}_2\text{S}_3$  are mostly localized at the band tails (that is, the top of the valence and the bottom of the conduction bands) and in lower-lying bonding states. The remaining electron states in the vicinity of the bandgap are delocalized.

Benchmark telluride PCMs are characterized by low viscosity and high fragility of the melt<sup>112-116</sup> ensuring fast atomic mobility at elevated temperature, which enables a rapid crystallization within the nanosecond range, and a good retention of amorphous phase in the vicinity of  $T_g$  and at lower  $T$ . The simulated dynamics in  $\text{Sb}_2\text{S}_3$  reveals fast diffusion at high temperatures and a sudden decrease of diffusivity approaching the glass transition.

Typical Sb and S mean square displacements  $\langle r^2(t) \rangle$  are shown in Figure 14a,b


$$\langle r^2(t) \rangle = \left\langle \frac{1}{N_i} \left\{ \sum_{i=1}^{N_i} [r_i(t) - r_i(0)]^2 \right\} \right\rangle, \quad (5)$$

where  $r_i(0)$  and  $r_i(t)$  are the positions of particle  $i$  for the initial time and time  $t$ , respectively,  $N_i$  the total number of particles  $i$  in the simulation box, and the angle brackets represent the

average over initial times. Below 30 fs, a ballistic regime is observed, mostly depending on atomic mass  $m_i$ <sup>117</sup>

$$\langle r^2(t) \rangle \propto (k_B T / m_i) t^2, \quad (6)$$

where  $k_B$  and  $T$  are the Boltzmann constant and temperature. On a log-log scale, the slope  $s = 2$  is indicative of this regime, Figure 14b.

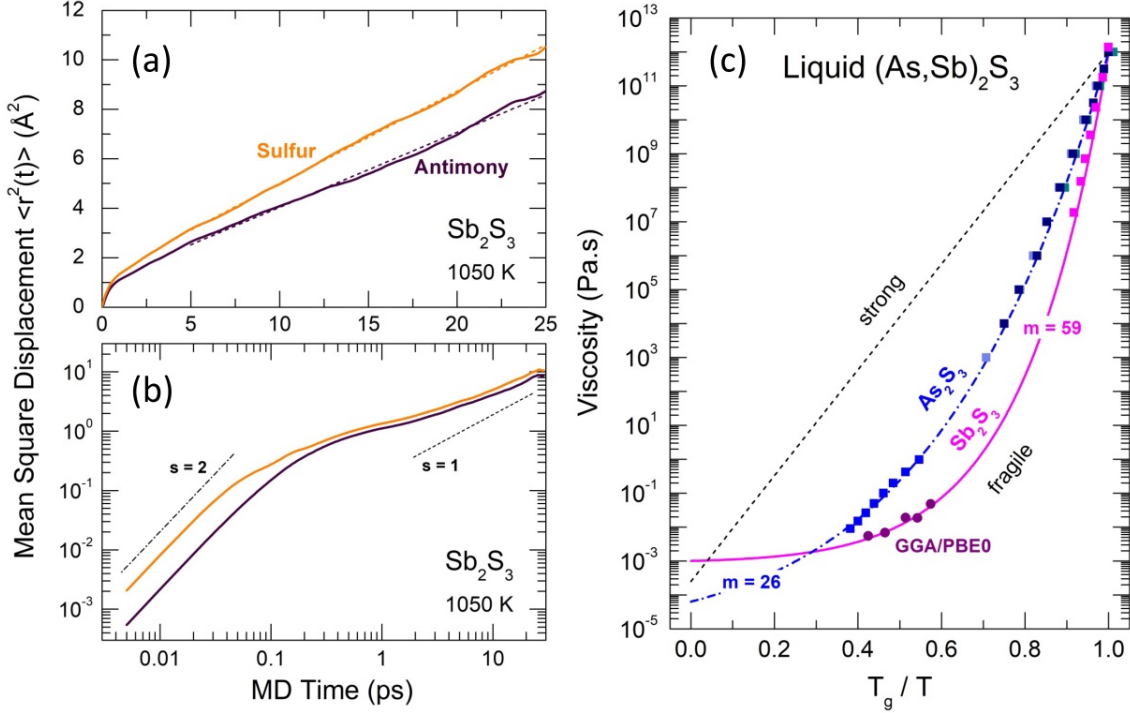

**Figure 14.** Mean-square displacements  $\langle r^2(t) \rangle$  and viscosity of  $\text{Sb}_2\text{S}_3$ . Antimony (dark purple) and sulfur (yellow)  $\langle r^2(t) \rangle$  on (a) linear and (b) log-log scales. The dashed lines in (a) represent least-square fits of the  $\langle r^2(t) \rangle$  data. The ballistic ( $s = 2$ ) and diffusion ( $s = 1$ ) regimes in (b) are shown by the dash-dotted and dashed lines, respectively. (c) Angell plot for the temperature dependence of viscosity  $\eta(T)$  for  $\text{As}_2\text{S}_3$  (blue) and  $\text{Sb}_2\text{S}_3$  (magenta). The experimental viscosity data<sup>118-123</sup> are shown by the solid squares of different shades of blue for  $\text{As}_2\text{S}_3$ , and by the magenta squares for  $\text{Sb}_2\text{S}_3$ . The FPMD viscosity calculated using the Stokes–Einstein relation (eq 9) is shown by the purple circles (this work). The dashed-dotted and solid lines represent the MYEGA<sup>124</sup> viscosity (eq 10) for the two sesquisulfides. The derived fragility indices  $m$  are also shown. See the text for further details.

Above 5 ps, a diffusive motion is visible

$$\langle r^2(t) \rangle \propto D_i t, \quad (7)$$

where  $D_i$  is the average diffusion coefficient of particles  $i$ , approaching the slope  $s = 1$ . The diffusion coefficients  $D_{\text{Sb}}$  and  $D_{\text{S}}$  were calculated using the Einstein equation

$$D_i = \frac{1}{6} \lim_{t \rightarrow \infty} \frac{\partial \langle r_i^2(t) \rangle}{\partial t}. \quad (8)$$

The derived  $D_{\text{Sb}}(T)$  and  $D_{\text{S}}(T)$  are shown in Figure S11, plotted on Arrhenius scale and following thermally activated motion with temperature-dependent activation energy,  $0.37 \leq E_d \leq 1.02$  eV in the vicinity of 1150 and 850 K, respectively.

The Stokes-Einstein relation was used to calculate the FPMD viscosity

$$\eta^{\text{FPMD}}(T) = \frac{k_B T}{6\pi D_{\text{eff}}(T) r_H}, \quad (9)$$

where the effective atomic diffusion coefficient  $D_{\text{eff}}(T) = 0.4D_{\text{Sb}}(T) + 0.6D_{\text{S}}(T)$ , and the effective temperature-dependent hydrodynamic radius  $r_H$  was determined using a Wigner-Seitz approach  $r_{\text{WS}}(T) = \sqrt[3]{(3/4\pi)V_m(T)N_A^{-1}}$ , where  $V_m(T)$  is the melt molar volume and  $N_A$  the Avogadro constant.

The derived viscosity is shown using an Angell plot,  $\log \eta$  vs.  $T_g/T$  (Figure 14c), together with experimental viscosity data of different research groups for canonical  $\text{As}_2\text{S}_3$  and  $\text{Sb}_2\text{S}_3$ .<sup>118-123</sup> The antimony sesquisulfide viscosity was obtained by extrapolation of the  $(\text{GeS}_2)_x(\text{Sb}_2\text{S}_3)_{1-x}$  data,  $0.1 \leq x \leq 0.9$ .<sup>123</sup> At low  $x \leq 0.5$ , the  $\log \eta(T, x)$  composition dependence is changing smoothly, enabling a reliable extrapolation of  $\log \eta(T, x)$  to  $x = 0$ .

The both viscosities,  $\eta(\text{As}_2\text{S}_3)$  and  $\eta(\text{Sb}_2\text{S}_3)$ , follow the Mauro–Yue–Ellison–Gupta–Allan (MYEGA) relationship<sup>124</sup> but with different fragilities

$$\log \eta(T) = \log \eta_0 + [\log \eta(T_g) - \log \eta_0] \frac{T_g}{T} \exp \left[ \left( \frac{m}{\log \eta(T_g) - \log \eta_0} \right) \left( \frac{T_g}{T} - 1 \right) \right], \quad (10)$$

where the fragility index  $m = [\partial \log \eta / \partial (T_g/T)]_{T=T_g}$ ,  $\eta_0$  and  $\eta(T_g) = 10^{12}$  Pa·s are the viscosity values at  $T = \infty$  and  $T_g$ , respectively. The  $m(\text{As}_2\text{S}_3) = 26$  is typical for canonical chalcogenide glasses with a network structure.<sup>113-116,125,126</sup> Antimony sesquisulfide exhibits a higher fragility,  $m(\text{Sb}_2\text{S}_3) = 59$ , approaching that of telluride PCMs.<sup>113-116</sup> We should also note a good agreement between experimental  $\eta(T)$  and calculated  $\eta^{\text{FPMD}}(T)$  viscosity.


We do not expect for  $\text{Sb}_2\text{S}_3$  either a fragile-to-strong transition<sup>112-115</sup> or mesoscopic immiscibility accompanied by a viscosity anomaly<sup>116,127</sup> since both the experimental conductivity (Figure 2) and FPMD simulations (Figure 13) reveal a semiconducting behavior over the studied temperature range.

**3.7.  $\text{Sb}_2\text{S}_3$  and Other Sulfides of Group 15.** The comparison with phosphorus, arsenic and bismuth sulfides allows better the atomic structure and dynamics of liquid and glassy  $\text{Sb}_2\text{S}_3$  to be understood. Vitreous sulfides of group 15 reveal a distinct loss of molecular-like atomic structure with increasing atomic number. Phosphorus sulfides mostly exist in the form of cages  $\text{P}_4\text{S}_n$ ,  $3 \leq n \leq 10$  (see, for example, Ref 128 and references therein), and glasses in the system  $\text{P}_x\text{S}_{1-x}$  have a network structure essentially below  $x \lesssim 0.20$  as a mixture of polymerized  $\text{S}=\text{PS}_3$  tetrahedra (main entities),  $\text{P}_4\text{S}_{10}$  and  $\text{P}_4\text{S}_9$  cages, sulfur rings and chains.<sup>129,130</sup> Above this limit, the structure of glasses or viscous liquids at room temperature becomes increasingly dominated by  $\text{P}_4\text{S}_{10}$  ( $x = 0.2857$ ),  $\text{P}_4\text{S}_9$ ,  $\text{P}_4\text{S}_7$  and other P-rich cages,<sup>130-132</sup> that is, appears to be mostly molecular. The network-forming  $\text{PS}_3$  trigonal pyramids possibly exist but as a minor contribution.

Arsenic sesquisulfide has a network structure both in crystalline<sup>100,101</sup> and glassy forms. Nevertheless, the vapor over  $\text{As}_2\text{S}_3$ , albeit quite complex,<sup>133,134</sup> basically consists of  $\text{As}_4\text{S}_4$  and other cages, which are also frozen in amorphous thin films obtained by thermal evaporation.<sup>135-137</sup> Annealed evaporated  $\text{As}_2\text{S}_3$  evolves into a polymeric structure similar to that in bulk  $g$ -

As<sub>2</sub>S<sub>3</sub>.<sup>135-139</sup> In contrast, antimony and bismuth sulfide cages are unknown,<sup>140</sup> and Sb<sub>2</sub>S<sub>3</sub> or Bi<sub>2</sub>S<sub>3</sub> have a network structure composed of 1D-(Pn<sub>4</sub>S<sub>6</sub>)<sub>∞</sub> ribbons, where Pn = Sb, Bi.<sup>16,17,141</sup>

The FSDP trends for arsenic and antimony sesquisulfides show a distinct difference, Figure 6d,e. In liquid Sb<sub>2</sub>S<sub>3</sub>, the FSDP position  $Q_0(T)$  follows the thermal expansion, while  $Q_0(T)$  in supercooled and normal liquid As<sub>2</sub>S<sub>3</sub> reveals a strong deviation from the expected behavior going to much lower  $Q_0$  values, Figure 15. The observed trend is reminiscent of that in amorphous evaporated As<sub>2</sub>S<sub>3</sub> on annealing at  $T_g$ <sup>138,139</sup> but occurring in the opposite direction. The latter phenomenon was attributed to a polymerization of As<sub>4</sub>S<sub>4</sub> cages in the as-deposited As<sub>2</sub>S<sub>3</sub> films, confirmed also by Raman scattering,<sup>135-137</sup> whereas in *L*-As<sub>2</sub>S<sub>3</sub>, there is a dissociation reaction  $2As-S \rightleftharpoons As-As + S-S$  with a possible network fragmentation and changes in the intermediate range order. Tanaka<sup>142</sup> was first to observe changes in the chemical and intermediate range order in *g*-As<sub>2</sub>S<sub>3</sub> quenched from different temperatures, which are consistent with the observed trend in  $Q_0(T)$ , but also with an increasing FSDP amplitude  $A_0(Q_0)$ , Figure 6e.

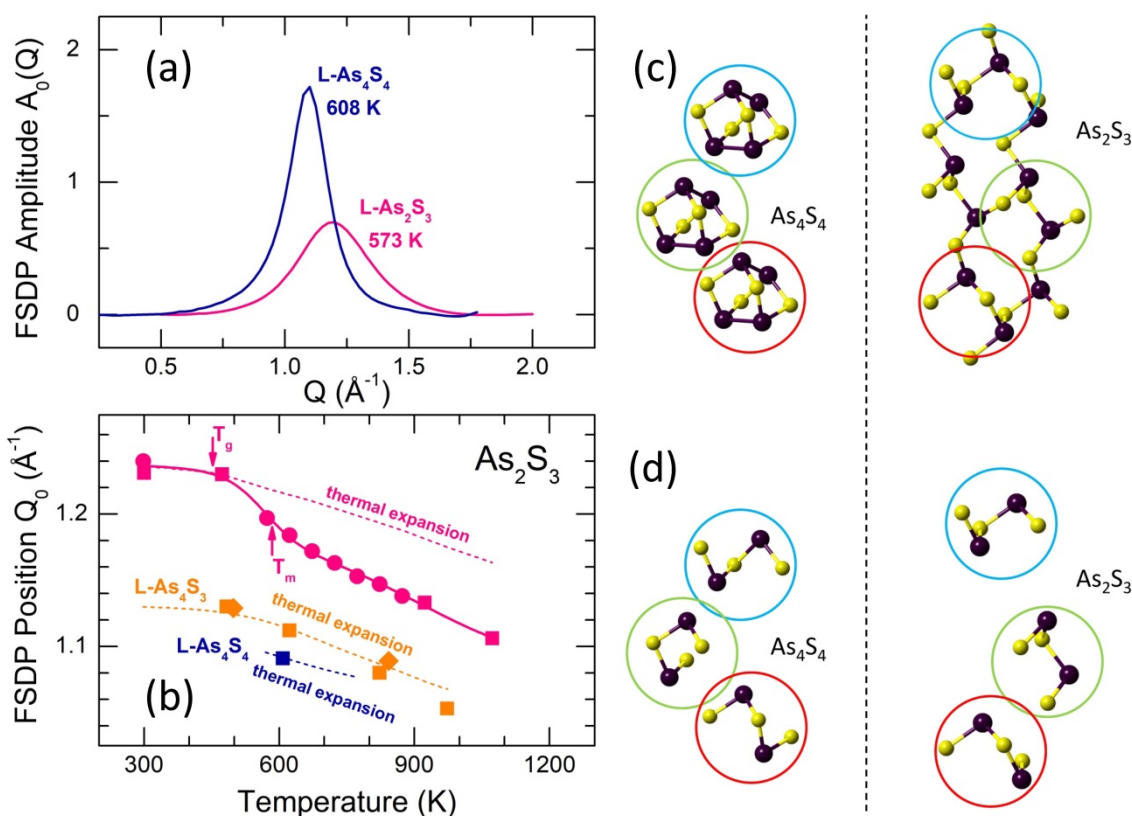


**Figure 15.** FSDP trends in liquid As<sub>2</sub>S<sub>3</sub>, As<sub>4</sub>S<sub>4</sub> and As<sub>4</sub>S<sub>3</sub>; (a) isolated FSDPs in *L*-As<sub>2</sub>S<sub>3</sub> at 573 K and *L*-As<sub>4</sub>S<sub>4</sub> at 608 K; (b) FSDP positions  $Q_0(T)$  for As<sub>2</sub>S<sub>3</sub>, As<sub>4</sub>S<sub>4</sub> and As<sub>4</sub>S<sub>3</sub> as a function of temperature; the dashed lines show the expected behavior taking into account the thermal expansion of arsenic sulfides; (c) specific projections of monoclinic orpiment As<sub>2</sub>S<sub>3</sub> and realgar As<sub>4</sub>S<sub>4</sub> to show their structural similarities; (d) nearly identical structural fragments are highlighted by the red, light green and light cyan circles for the two compounds.<sup>100</sup>


Our preliminary high-temperature Raman measurements and FPMD modeling are also coherent with these observations as well as the FSDP parameters for liquid As<sub>4</sub>S<sub>3</sub> and As<sub>4</sub>S<sub>4</sub> as a function of temperature, Figure 15b. Reversible polymerization or depolymerization seems to be related to a striking resemblance of the interatomic distances and bond angles in the realgar As<sub>4</sub>S<sub>4</sub> and

orpiment  $\text{As}_2\text{S}_3$  crystal structures, noted by Ito<sup>143</sup>, despite an apparent dissimilarity between the  $\text{As}_4\text{S}_4$  cages and the  $\text{As}_2\text{S}_3$  layered network.<sup>100,143</sup> Schematically, the elements of conversion are shown in Figure 15cd, illustrating the idea that the two structures are built by nearly identical structural fragments connected differently.<sup>143</sup>

Usually, the electronic conductivity increases and bandgap decreases going down on the Periodic Table. Vitreous, crystalline and liquid  $\text{As}_2\text{S}_3$  and  $\text{Sb}_2\text{S}_3$  are consistent with this trend. The room temperature conductivity of  $g\text{-Sb}_2\text{S}_3$  is higher by three orders of magnitude compared to arsenic sesquisulfide, and the difference in  $E_g$  is about  $\Delta E_g \approx 0.3$  eV. A semiconductor – metal (SC–M) transition is suggested to occur in these two high- $T$  liquids. Using the extrapolation of the optical absorption data,<sup>144</sup> the SC–M transition is expected at  $T_{\text{SC-M}} = 1600 \pm 150$  K for  $L\text{-As}_2\text{S}_3$ <sup>114</sup> and between 1250 and 1550 K for its antimony counterpart. The last estimation was based on FPMD modeling of the bandgap as a function of temperature or derived from the computed atomic diffusion coefficients, Figure 16.

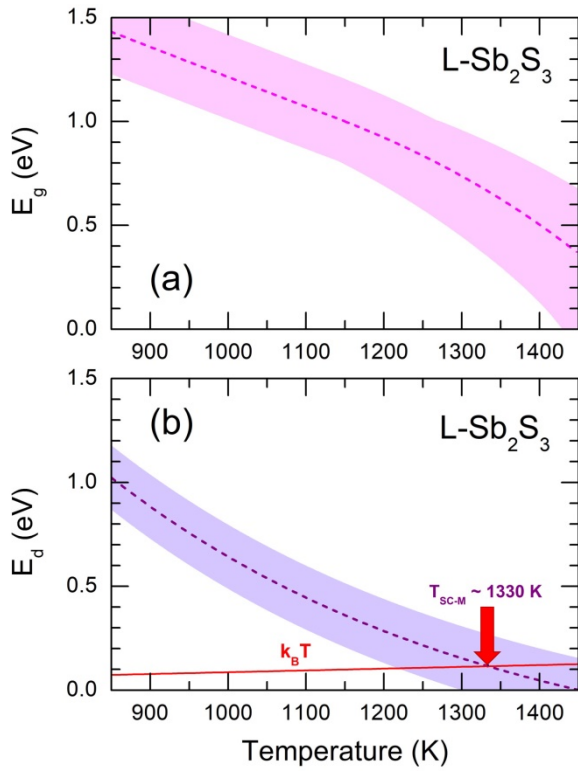

**Figure 16.** FPMD estimation of the SC-M transition temperature  $T_{\text{SC-M}}$  for liquid  $\text{Sb}_2\text{S}_3$ ; (a) bandgap  $E_g$  as a function of temperature; (b) atomic diffusion activation energy  $E_d$  as a function of temperature. The average thermal energy  $k_B T$  is also shown in (b). The effective diffusion coefficient  $D_{\text{eff}} = 0.4D_{\text{Sb}} + 0.6D_{\text{S}}$  was taken for these calculations.

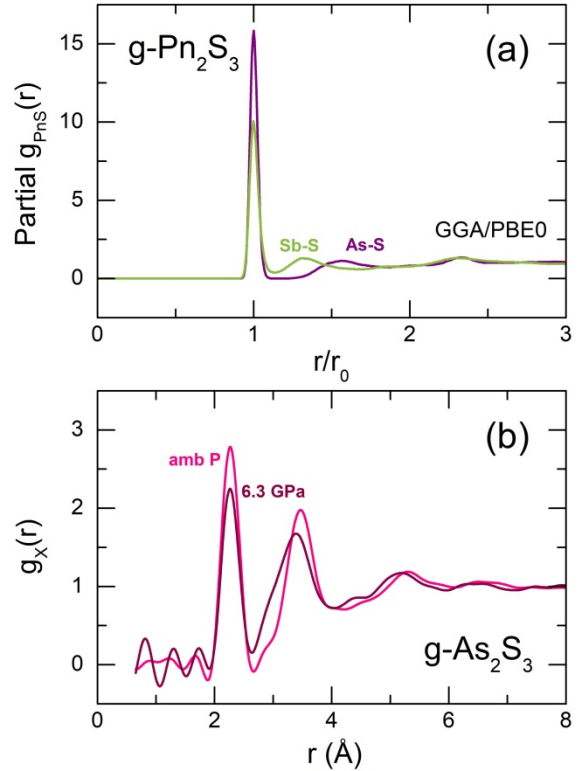

**Figure 17.** (a) FPMD partial pair-distribution functions  $g_{\text{PnS}}(r)$  for  $g\text{-Pn}_2\text{S}_3$ , Pn = As, Sb; (b) experimental  $g_X(r)$  for  $g\text{-As}_2\text{S}_3$  at ambient pressure and 6.3 GPa;<sup>150</sup> broader NN and 2<sup>nd</sup>N peaks of  $g_X(r)$  are related to a smaller accessible  $Q$ -range in a diamond anvil cell experiment,  $Q_{\text{max}} = 16 \text{ \AA}^{-1}$  instead of usual 25-30  $\text{ \AA}^{-1}$ .

The bandgap calculations using the hybrid functional GGA/PBE0 in the metallic limit yields a significant uncertainty in  $T_{\text{SC-M}} = 1550 \pm 120$  K. As expected, the modeling with the standard functional GGA/PBE reveals a metallic liquid at lower temperature,  $1250 \pm 75$  K. The derived  $T_{\text{SC-M}}$  values seem to be the two extremes for estimation of a SC–M transition using the electronic properties. Another alternative gives the atomic dynamics suggesting that the diffusion activation energy  $E_d$  in the metallic fluid appears to be comparable with the average

thermal energy,  $E_d \approx k_B T$ . This alternative yields  $T_{SC-M} = 1330 \pm 100$  K, which corresponds to a change in the slope of  $E_g(\text{PBE0})$ , Figure 16a. Finally, liquid  $\text{Sb}_2\text{S}_3$  exhibits the metallic conductivity above approximately 1300-1500 K.<sup>145</sup>

We should also note a lower SC-M transition temperature,  $900 \text{ K} \lesssim T_{SC-M} \lesssim 1100 \text{ K}$ , for liquid antimony selenides.<sup>114,145</sup> In addition, anionic (Se) or cationic (Bi) substitution can be used for bandgap engineering, since  $E_g(\text{Sb}_2\text{Se}_3) = 1.0\text{--}1.3 \text{ eV}$ <sup>12,146</sup> and  $E_g(\text{Bi}_2\text{S}_3) = 1.2\text{--}1.4 \text{ eV}$ ,<sup>147,148</sup> remaining within the wider gap materials compared to tellurides,  $E_g(\text{Sb}_2\text{Te}_3) = 0.5 \text{ eV}$ .<sup>149</sup>

Another general trend resides in a more compact or densified network for vitreous sulfides with increasing atomic number. We have already mentioned that the bond angle distributions  $B_{\text{SSbS}}(\theta)$  and  $B_{\text{SbSSb}}(\theta)$  as well as the lower fraction of microscopic voids and cavities in  $g\text{-Sb}_2\text{S}_3$ , Figures 10 and 12, are illustrating this trend. A comparison of the two partial pair-distribution functions  $g_{\text{PnS}}(r)$  for  $g\text{-As}_2\text{S}_3/\text{Sb}_2\text{S}_3$  seems to be even more convincing. Plotted on the normalized  $r/r_0$  scale, where  $r_0$  is the Pn-S NN distance, the  $g_{\text{SbS}}(r)$  shows a remarkable shift of the Sb-S second neighbors to shorter distances, approaching the NN shell, Figure 17a. The observed more compact network compared to  $g\text{-As}_2\text{S}_3$  at ambient conditions can be reproduced under high pressure. Figure 17b reveals a similar shift of the second neighbors for  $g\text{-As}_2\text{S}_3$  in a diamond anvil cell at 6.3 GPa.<sup>150</sup> Comparable trends are observed in other groups of the Periodic Table, e.g. amorphous and liquid Se and Te, Figure S12.<sup>95,151-153</sup> For liquid tellurium, a densification of the Te network is amplified by the SC-M transition in supercooled tellurium.<sup>75,114</sup>

#### 4. CONCLUDING REMARKS

Summarizing the above observations, we can emphasize favorable features in the atomic structure and dynamics of vitreous and liquid  $\text{Sb}_2\text{S}_3$  as a promising next-generation PCM for integrated smart photonics from the visible to telecom window. A high optical and electric contrast between the SET and RESET logic states in antimony sesquisulfide is based on a different short and intermediate range order in orthorhombic and amorphous  $\text{Sb}_2\text{S}_3$ . The orthorhombic polymorph is composed of quasi 1D- $(\text{Sb}_4\text{S}_6)_\infty$  ribbons with a strong asymmetry of the Sb-S nearest neighbor distances for three-fold and 5-fold antimony species ( $2.46 \leq r_{\text{Sb-S}}^{\text{NN}} \leq 2.85 \text{ \AA}$ ) and significant inter-ribbon interactions. Glassy  $\text{Sb}_2\text{S}_3$  reveals a 2D-disordered network built by defect octahedral entities  $\text{SbS}_3$  ( $r_{\text{Sb-S}}^{\text{NN}} = 2.48 \pm 0.01 \text{ \AA}$ ), whose three missing Sb-S bonds became excessively long, and the respective sulfur atoms were transformed into the second neighbors at  $\approx 3.4 \text{ \AA}$ . More compact network structure of  $g\text{-Sb}_2\text{S}_3$  compared to canonical  $\text{As}_2\text{S}_3$ , evidenced by the bond angle distributions, shorter Sb-S second neighbor distances and a lower population of microscopic voids and cavities, appears to be a good compromise between the stability of the amorphous state and the ability to fast crystallization. An additional positive feature is related to the intermediate range structure of liquid  $\text{Sb}_2\text{S}_3$ , predominantly composed of  $ABAB$  squares, which are speeding up the crystallization phenomena. Another favorable aspect for the rapid SET-RESET transition is an enhanced fragility of liquid  $\text{Sb}_2\text{S}_3$ . The fragility index  $m = 59$  is approaching those of the benchmark telluride PCMs and enables fast crystallization processes at elevated temperatures and simultaneously a remarkable slowdown in the vicinity of  $T_g$ , ensuring a good retention of the amorphous phase. Furthermore, anionic (Se) and/or cationic (Bi) substitution maybe used to decrease the temperature of a SC-M transition, thus



improving the dynamics of the SET-RESET change, and allowing bandgap engineering equally important for photonics and photovoltaics.

## ASSOCIATED CONTENT

### Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi>

Raman spectrum of amorphous antimony, evolution of Raman spectra for  $\text{Sb}_2\text{S}_3$  as a function of temperature, DFT Raman spectra of size-limited clusters, S-Sb-S bond angle distributions for DFT-optimized clusters, distributions of Sb-S interatomic distances in DFT-optimized clusters, comparison of FPMD modeling with standard PBE and hybrid PBE0 functionals, FPMD modeling of glassy  $\text{As}_2\text{S}_3$  under high-pressure, fitting Sb-S partials with asymmetric functions, coordination distributions of sulfur and antimony, bond angle distributions in glassy and liquid  $\text{Sb}_2\text{S}_3$ , derived Sb and S diffusion coefficients plotted on Arrhenius scale, pair-distribution functions of liquid and amorphous selenium and tellurium, and supporting references (PDF)

## AUTHOR INFORMATION

### Corresponding Author

**Eugene Bychkov** – Laboratoire de Physico-Chimie de l'Atmosphère, Université du Littoral Côte d'Opale, 59140 Dunkerque, France; orcid.org/0000-0002-3292-1205; Phone: +33 328 658250; Email: Eugene.Bychkov@univ-littoral.fr; Fax: +33 328 658244

### Authors

**Mohammad Kassem** – Laboratoire de Physico-Chimie de l'Atmosphère, Université du Littoral Côte d'Opale, 59140 Dunkerque, France; orcid.org/0000-0003-0512-0004

**Chris J. Benmore** – X-ray Science Division, Advanced Photon Source, Argonne National Laboratory, Argonne, Illinois 60439, United States; orcid.org/0000-0001-7007-7749

**Andrey Tverjanovich** – Institute of Chemistry, St. Petersburg State University, St. Petersburg 198504, Russia; orcid.org/0000-0002-0795-8188

**Takeshi Usuki** – Faculty of Science, Yamagata University, Yamagata 990-8560, Japan; orcid.org/0000-0002-4737-7708

**Maxim Khomenko** – ILIT RAS – Branch of the FSRC “Crystallography and Photonics” RAS, 140700 Shatura, Moscow Region, Russia

**Daniele Fontanari** – Laboratoire de Physico-Chimie de l'Atmosphère, Université du Littoral Côte d'Opale, 59140 Dunkerque, France

**Anton Sokolov** – Laboratoire de Physico-Chimie de l'Atmosphère, Université du Littoral Côte d'Opale, 59140 Dunkerque, France

**Koji Ohara** – Research and Utilization Division, Japan Synchrotron Radiation Research Institute, Sayo, Hyogo 679-5198, Japan; orcid.org/0000-0002-3134-512X

**Maria Bokova** – Laboratoire de Physico-Chimie de l’Atmosphère, Université du Littoral Côte d’Opale, 59140 Dunkerque, France

**Shinji Kohara** – Quantum Beam Field, Research Center for Advanced Measurement and Characterization, National Institute for Materials Science, 1-2-1 Sengen, Tsukuba, Ibaraki 305-0047, Japan; orcid.org/0000-0001-9596-2680

Complete contact information is available at: <https://pubs.acs.org/10.1021>

## **Author Contributions**

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

## **Notes**

The authors declare no competing financial interest.

## **ACKNOWLEDGMENTS**

This work was supported by the Région Hauts de France and the Ministère de l’Enseignement Supérieur et de la Recherche (CPER Climibio), as well as by the European Fund for Regional Economic Development. Work at the Advanced Photon Source, Argonne National Laboratory, was supported in part by the Office of Basic Energy Sciences, US Department of Energy, under Contract No. DE-AC02-06CH1135. The experiments at SPring-8 were approved by the Japan Synchrotron Radiation Research Institute (proposal Nos. 2021A1432 and 2022A1418) and supported by the Centre for Advanced Science and Technology (Japan). MKh work at ILIT RAS was supported by state assignment FSRC “Crystallography and Photonics”, Russian Academy of Sciences. This work was granted access to the HPC resources of IDRIS (France) under the allocation 2022-A0130910639 made by Grand Equipement National de Calcul Intensif (GENCI) and to use the CALCULCO computing platform, supported by Service COmmun du Système d’Information de l’Université du Littoral Côte d’Opale (SCoSI/ULCO). The FPMD simulations were also carried out using the equipment of the shared research facilities of HPC computing resources at Lomonosov Moscow State University.

## REFERENCES

- (1) Dong, W.; Liu, H.; Behera, J. K.; Lu, L.; Ng, R. J. H.; Sreekanth, K. V.; Zhou, X.; Yang, J. K. W.; Simpson, R. E. Wide Bandgap Phase Change Material Tuned Visible Photonics. *Adv. Funct. Mater.* **2018**, 1806181.
- (2) Delaney, M.; Zeimpekis, I.; Lawson, D.; Hewak, D. W.; Muskens, O. L. A New Family of Ultralow Loss Reversible Phase-Change Materials for Photonic Integrated Circuits:  $\text{Sb}_2\text{S}_3$  and  $\text{Sb}_2\text{Se}_3$ . *Adv. Funct. Mater.* **2020**, 2002447.
- (3) Liu, H.; Dong, W.; Wang, H.; Lu, L.; Ruan, Q.; Tan, Y. S.; Simpson, R. E.; Yang, J. K. W. Rewritable Color Nanoprints in Antimony Trisulfide Films. *Sci. Adv.* **2020**, 6, eabb7171.
- (4) Qin, S.; Xu, N.; Huang, H.; Jie, K.; Liu, H.; Guo, J.; Meng, H.; Wang, F.; Yang, X.; Wei, Z. Near-Infrared Thermally Modulated Varifocal Metalens Based on the Phase Change Material  $\text{Sb}_2\text{S}_3$ . *Opt. Express* **2021**, 29, 7925–7934.
- (5) Lu, L.; Dong, Z.; Tijptoharsono, F.; Ng, R. J. H.; Wang, H.; Rezaei, S. D.; Wang, Y.; Leong, H. S.; Lim, P. C.; Yang, J. K. W.; Simpson, R. E. Reversible Tuning of Mie Resonances in the Visible Spectrum. *ACS Nano* **2021**, 15, 19722–19732.
- (6) Jia, W.; Menon, R.; Sensale-Rodriguez, B. Visible and Near-Infrared Programmable Multi-Level Diffractive Lenses with Phase Change Material  $\text{Sb}_2\text{S}_3$ . *Opt. Express* **2022**, 30, 6808–6817.
- (7) Cao, L.; Gao, X.; Zhang, B.; Ou, X.; Zhang, J.; Luo, W.-B. Bimetallic Sulfide  $\text{Sb}_2\text{S}_3@FeS_2$  Hollow Nanorods as High-Performance Anode Materials for Sodium-Ion Batteries. *ACS Nano* **2020**, 14, 3610–3620.
- (8) Wang, S.; Cheng, Y.; Xue, H.; Liu, W.; Yi, Z.; Chang, L.; Wang, L. Multifunctional Sulfur-Mediated Strategy Enabling Fast-Charging  $\text{Sb}_2\text{S}_3$  Micro-Package Anode for Lithium-Ion Storage. *J. Mater. Chem. A* **2021**, 9, 7838–7847.
- (9) Chen, R.; Lu, X.; He, Q.; Yao, M.; Yao, T.; Gao, A.; Ding, S.; Cheng, Y.; Wang, H.  $\text{Sb}_2\text{S}_3$  Nanorod Hierarchies Enabling Homogeneous Sodium Deposition for Dendrite-Free Sodium-Metal Batteries. *ACS Appl. Energy Mater.* **2022**, 5, 10952–10960.
- (10) Du, Y.; Liu, F.; Jiang, L.; Jia, M.; Zhang, Z. Ultra-Fine  $\text{Sb}_2\text{S}_3$  Particles Encapsulated in Activated-Carbon: A High-Performance Anode for Li-ion Batteries. *J. Alloys Compd.* **2022**, 907, 164469.
- (11) Lian, W.; Jiang, C.; Yin, Y.; Tang, R.; Li, G.; Zhang, L.; Che, B.; Chen, T. Revealing Composition and Structure Dependent Deep-Level Defect in Antimony Trisulfide Photovoltaics. *Nat. Commun.* **2021**, 12, 3260.
- (12) Barthwal, S.; Kumar, R.; Pathak, S. Present Status and Future Perspective of Antimony Chalcogenide ( $\text{Sb}_2\text{X}_3$ ) Photovoltaics. *ACS Appl. Energy Mater.* **2022**, 5, 6545–6585.
- (13) Roy, B.; Chakraborty, B. R.; Bhattacharya, R.; Dutta, A. K. Electrical and Magnetic Properties of Antimony Sulphide ( $\text{Sb}_2\text{S}_3$ ) Crystals and the Mechanism of Carrier Transport in It. *Solid State Commun.* **1978**, 25, 937–940.
- (14) Chang, C.; Xiao, Y.; Zhang, X.; Pei, Y.; Li, F.; Ma, S.; Yuan, B.; Liu, Y.; Gong, S.; Zhao, L.-D. High Performance Thermoelectrics from Earth-Abundant Materials: Enhanced Figure of Merit in PbS through Nanostructuring Grain Size. *J. Alloys Compd.* **2016**, 664, 411–416.
- (15) Bao, D.; Sun, Q.; Huang, L.; Chen, J.; Tang, J.; Zhou, D.; Hong, M.; Yang, L.; Chen, Z.-G. Thermoelectric Performance of p-Type  $(\text{Bi,Sb})_2\text{Te}_3$  Incorporating Amorphous  $\text{Sb}_2\text{S}_3$  Nanospheres. *Chem. Eng. J.* **2022**, 430, 132738.
- (16) Bayliss, P.; Nowacki, W. Refinement of the Crystal Structure of Stibnite,  $\text{Sb}_2\text{S}_3$ . *Z. Kristallogr.* **1972**, 135, 308–315.
- (17) McKee, D. O.; McMullan, J. T. Comment on the Structure of Antimony Trisulfide. *Z. Kristallogr.* **1975**, 142, 447–449.
- (18) Swinnea, J. S.; Tenorio, A. J.; Steinfink, H.  $\text{Sb}_{10}\text{S}_{15}$ , a Pb-free Analogue of Fülöppite,  $\text{Pb}_3\text{Sb}_8\text{S}_{15}$ . *Am. Mineral.* **1985**, 70, 1056–1058.
- (19) Lundegaard, L. F.; Miletich, R.; Balic-Zunic, T.; Makovicky, E. Equation of State and Crystal Structure of  $\text{Sb}_2\text{S}_3$  between 0 and 10 GPa. *Phys. Chem. Minerals* **2003**, 30, 463–468.

- (20) Ibáñez, J.; Sans, J. A.; Popescu, C.; López-Vidrier, J.; Elvira-Betanzos, J. J.; Cuenca-Gotor, V. P.; Gomis, O.; Manjón, F. J.; Rodríguez-Hernández, P.; Muñoz, A. Structural, Vibrational, and Electronic Study of Sb<sub>2</sub>S<sub>3</sub> at High Pressure. *J. Phys. Chem. C* **2016**, *120*, 10547–10558.
- (21) Efthimiopoulos, I.; Buchan, C.; Wang, Y. Structural Properties of Sb<sub>2</sub>S<sub>3</sub> under Pressure: Evidence of an Electronic Topological Transition. *Sci. Reports* **2016**, *6*, 24246.
- (22) Dai, L.; Liu, K.; Li, H.; Wu, L.; Hu, H.; Zhuang, Y.; Yang, L.; Pu, C.; Liu, P. Pressure-Induced Irreversible Metallization Accompanying the Phase Transitions in Sb<sub>2</sub>S<sub>3</sub>. *Phys. Rev. B* **2018**, *97*, 024103.
- (23) Wang, Y.; Ma, Y.; Liu, G.; Wang, J.; Li, Y.; Li, Q.; Zhang, J.; Ma, Y.; Zou, G. Experimental Observation of the High Pressure Induced Substitutional Solid Solution and Phase Transformation in Sb<sub>2</sub>S<sub>3</sub>. *Sci. Reports* **2018**, *8*, 14795.
- (24) Cui, Z.; Bu, K.; Zhuang, Y.; Donnelly, M.-E.; Zhang, D.; Dalladay-Simpson, P.; Howie, R. T.; Zhang, J.; Lü, X.; Hu, Q. Phase Transition Mechanism and Bandgap Engineering of Sb<sub>2</sub>S<sub>3</sub> at Gigapascal Pressures. *Commun. Chem.* **2021**, *4*, 125.
- (25) Ali, M. M. E.; Kong, P.; Ni, Y.; Wang, H.; Chen, Y. High Pressure Induced Decomposition of Antimony Trisulfide. *Mater. Today Commun.* **2021**, *29*, 102828.
- (26) Hu, C.; Xu, Y.; Gong, Y.; Yang, D.; Li, X.; Li, Y. Pressure-Induced Phase Transitions, Amorphization and Alloying in Sb<sub>2</sub>S<sub>3</sub>. *Phys. Chem. Chem. Phys.* **2022**, *24*, 10053–10061.
- (27) Červinka, L.; Hrubý, A. Structure of Amorphous and Glassy Sb<sub>2</sub>S<sub>3</sub> and its Connection with the Structure of As<sub>2</sub>X<sub>3</sub> Arsenic – Chalcogenide Glasses. *J. Non-Cryst. Solids* **1982**, *48*, 231–264.
- (28) Dalba, G.; Fornasini, P.; Giunta, G. Short Range Order of Amorphous Sb<sub>2</sub>S<sub>3</sub> Thin Films: An X-ray Diffraction Study. *Solid State Commun.* **1987**, *62*, 773–776.
- (29) Dalba, G.; Fornasini, P.; Giunta, G.; Burattini, E. XRD and EXAFS Study of the Local Structure in Some Non-Crystalline Sb-S Compounds. *J. Non-Cryst. Solids* **1989**, *107*, 261–270.
- (30) Wuttig, M.; Yamada, N. Phase-Change Materials for Rewriteable Data Storage. *Nat. Mater.* **2007**, *6*, 824–832.
- (31) Raoux, S.; Wełnic, W.; Ielmini, D. Phase Change Materials and Their Application to Nonvolatile Memories. *Chem. Rev.* **2010**, *110*, 240–267.
- (32) Zhang, W.; Mazzarello, R.; Wuttig, M.; Ma, E. Designing Crystallization in Phase-Change Materials for Universal Memory and Neuro-Inspired Computing. *Nat. Rev. Mater.* **2019**, *4*, 150–168.
- (33) Kooi, B. J.; Wuttig, M. Chalcogenides by Design: Functionality through Metavalent Bonding and Confinement. *Adv. Mater.* **2020**, *32*, 1908302.
- (34) Akola, J.; Jones, R. O.; Kohara, S.; Kimura, S.; Kobayashi, K.; Takata, M.; Matsunaga, T.; Kojima, R.; Yamada, N. Experimentally Constrained Density-Functional Calculations of the Amorphous Structure of the Prototypical Phase-Change Material Ge<sub>2</sub>Sb<sub>2</sub>Te<sub>5</sub>. *Phys. Rev. B* **2009**, *80*, 020201.
- (35) S. Caravati, M. Bernasconi and M. Parrinello, First-principles study of liquid and amorphous Sb<sub>2</sub>Te<sub>3</sub>, *Phys. Rev. B* **2010**, *81*, 014201.
- (36) Kolobov, A. V.; Tominaga, J. *Chalcogenides: Metastability and Phase Change Phenomena*; Springer: Berlin, 2012; pp 183–208.
- (37) Ahmed, S.; Wang, X.; Li, H.; Zhou, Y.; Chen, Y.; Sun, L.; Zhang, W.; Mazzarello, R. Change in Structure of Amorphous Sb–Te Phase-Change Materials as a Function of Stoichiometry. *Phys. Status Solidi RRL* **2021**, 2100064.
- (38) Hammersley, A. P.; Svensson, S. O.; Hanfland, M.; Fitch, A. N.; Häusermann, D. Two-Dimensional Detector Software: From Real Detector to Idealised Image or Two-Theta Scan. *High Pressure Res.* **1996**, *14*, 235–248.
- (39) Skinner, L. B.; Benmore, C. J.; Parise, J. B. Area Detector Corrections for High Quality Synchrotron X-ray Structure Factor Measurements. *Nucl. Instrum. Methods Phys. Res.* **2012**, *662*, 61–70.
- (40) Ohara, K.; Onodera, Y.; Kohara, S.; Koyama, C.; Masuno, A.; Mizuno, A.; Okada, J. T.; Tahara, S.; Watanabe, Y.; Oda, H.; Nakata, Y.; Tamaru, H.; Ishikawa, T.; Sakata, O. Accurate Synchrotron Hard X-ray Diffraction Measurements on High-Temperature Liquid Oxides. *Intern. J. Microgravity Sci. Appl.* **2020**, *37*, 370202.

- (41) Kohara, S.; Itou, M.; Suzuya, K.; Inamura, Y.; Sakurai, Y.; Ohishi, Y.; Takata, M. Structural Studies of Disordered Materials using High-Energy X-ray Diffraction from Ambient to Extreme Conditions. *J. Phys. Condens. Matter* **2007**, *19*, 506101.
- (42) Usuki, T.; Bokova, M.; Kassem, M.; Ohara, K.; Hannon, A. C.; Bychkov, E. Dimeric Molecular Structure of Molten Gallium Trichloride and a Hidden Evolution toward a Possible Liquid-Liquid Transition. *J. Phys. Chem. B* **2019**, *123*, 10260–10266.
- (43) Tverjanovich, A.; Khomenko, M.; Bereznev, S.; Fontanari, D.; Sokolov, A.; Usuki, T.; Ohara, K.; Le Coq, D.; Masselin, P.; Bychkov, E. Glassy GaS: Transparent and Unusually Rigid Thin Films for Visible to Mid-IR Memory Applications. *Phys. Chem. Chem. Phys.* **2020**, *22*, 25560–25573.
- (44) Frisch, M. J.; Trucks, G. W.; Schlegel, H. B.; Scuseria, G. E.; Robb, M. A.; Cheeseman, J. R.; Scalmani, G.; Barone, V.; Petersson, G. A.; Nakatsuji, H.; Li, X.; Caricato, M.; Marenich, A. V.; Bloino, J.; Janesko, B. G.; Gomperts, R.; Mennucci, B.; Hratchian, H. P.; Ortiz, J. V.; Izmaylov, A. F.; Sonnenberg, J. L.; Williams-Young, D.; Ding, F.; Lipparini, F.; Egidi, F.; Goings, J.; Peng, B.; Petrone, A.; Henderson, T.; Ranasinghe, D.; Zakrzewski, V. G.; Gao, J.; Rega, N.; Zheng, G.; Liang, W.; Hada, M.; Ehara, M.; Toyota, K.; Fukuda, R.; Hasegawa, J.; Ishida, M.; Nakajima, T.; Honda, Y.; Kitao, O.; Nakai, H.; Vreven, T.; Throssell, K.; Montgomery, J. A.; Peralta, J. E.; Ogliaro, F.; Bearpark, M. J.; Heyd, J. J.; Brothers, E. N.; Kudin, K. N.; Staroverov, V. N.; Keith, T. A.; Kobayashi, R.; Normand, J.; Raghavachari, K.; Rendell, A. P.; Burant, J. C.; Iyengar, S. S.; Tomasi, J.; Cossi, M.; Millam, J. M.; Klene, M.; Adamo, C.; Cammi, R.; Ochterski, J. W.; Martin, R. L.; Morokuma, K.; Farkas, O.; Foresman, J. B.; Fox, D. J. *Gaussian 16*, revision B.01; Gaussian, Inc.: Wallingford, CT, 2016.
- (45) Becke, A. D. Density-Functional Thermochemistry. III. The Role of Exact Exchange. *J. Chem. Phys.* **1993**, *98*, 5648–5653.
- (46) Lee, C.; Yang, W.; Parr, R. G. Development of the Colle-Salvetti Correlation-Energy Formula into a Functional of the Electron Density. *Phys. Rev. B* **1988**, *37*, 785.
- (47) Feller, D. The Role of Databases in Support of Computational Chemistry Calculations. *J. Comput. Chem.* **1996**, *17*, 1571–1586.
- (48) Peterson, K. A.; Figgen, D.; Goll, E.; Stoll, H.; Dolg, M. Systematically Convergent Basis Sets with Relativistic Pseudopotentials. II. Small-Core Pseudopotentials and Correlation Consistent Basis Sets for the Post-d Group 16–18 Elements. *J. Chem. Phys.* **2003**, *119*, 11113–11123.
- (49) Bacskay, G. B. A Quadratically Convergent Hartree-Fock (QCSCF) Method. Application to Closed Shell Systems. *Chem. Phys.* **1981**, *61*, 385–404.
- (50) Masselin, P.; Le Coq, D.; Cuisset, A.; Bychkov, E. Spatially Resolved Raman Analysis of Laser Induced Refractive Index Variation in Chalcogenide Glass. *Opt. Mater. Express* **2012**, *2*, 1768–1775.
- (51) Tverjanovich, A.; Cuisset, A.; Fontanari, D.; Bychkov, E. Structure of Se-Te Glasses by Raman Spectroscopy and DFT Modelling. *J. Am. Ceram. Soc.* **2018**, *101*, 5188–5197.
- (52) Kassem, M.; Bokova, M.; Tverjanovich, A. S.; Fontanari, D.; Le Coq, D.; Sokolov, A.; Masselin, P.; Kohara, S.; Usuki, T.; Hannon, A. C.; Benmore, C. J.; Bychkov, E. Bent HgI<sub>2</sub> Molecules in the Melt and Sulfide Glasses: Implications for Nonlinear Optics. *Chem. Mater.* **2019**, *31*, 4103–4112.
- (53) Kühne, T. D.; Iannuzzi, M.; Del Ben, M.; Rybkin, V. V.; Seewald, P.; Stein, F.; Laino, T.; Khaliullin, R. Z.; Schütt, O.; Schiffmann, F.; Golze, D.; Wilhelm, J.; Chulkov, S.; Bani-Hashemian, M. H.; Weber, V.; Borštnik, U.; Taillefumier, M.; Jakobovits, A. S.; Lazzaro, A.; Pabst, H.; Müller, T.; Schade, R.; Guidon, M.; Andermatt, S.; Holmberg, N.; Schenter, G. K.; Hehn, A.; Bussy, A.; Belleflamme, F.; Tabacchi, G.; Glöß, A.; Lass, M.; Bethune, I.; Mundy, C. J.; Plessl, C.; Watkins, M.; VandeVondele, J.; Krack, M.; Hutter, J. CP2K: An Electronic Structure and Molecular Dynamics Software Package – Quickstep: Efficient and Accurate Electronic Structure Calculations. *J. Chem. Phys.* **2020**, *152*, 194103.
- (54) Perdew, J. P.; Ernzerhof, M.; Burke, K. Rationale for Mixing Exact Exchange with Density Functional Approximations. *J. Chem. Phys.* **1996**, *105*, 9982–9985.
- (55) Adamo, C.; Barone, V. Toward Reliable Density Functional Methods without Adjustable Parameters: The PBE0 Model. *J. Chem. Phys.* **1999**, *110*, 6158–6170.

- (56) Tverjanovich, A.; Khomenko, M.; Benmore, C. J.; Bokova, M.; Sokolov, A.; Fontanari, D.; Kassem, M.; Usuki, T.; Bychkov, E. Bulk Glassy GeTe<sub>2</sub>: A Missing Member of the Tetrahedral GeX<sub>2</sub> Family and a Precursor for the Next Generation of Phase-Change Materials. *Chem. Mater.* **2021**, *33*, 1031–1045.
- (57) Bokova, M.; Tverjanovich, A.; Benmore, C. J.; Fontanari, D.; Sokolov, A.; Khomenko, M.; Kassem, M.; Ozheredov, I.; Bychkov, E. Unraveling the Atomic Structure of Bulk Binary Ga–Te Glasses with Surprising Nanotectonic Features for Phase-Change Memory Applications. *ACS Appl. Mater. Interfaces* **2021**, *13*, 37363–37379.
- (58) Tverjanovich, A.; Khomenko, M.; Benmore, C. J.; Bereznev, S.; Sokolov, A.; Fontanari, D.; Kiselev, A.; Lotin, A.; Bychkov, E. Atypical Phase-Change Alloy Ga<sub>2</sub>Te<sub>3</sub>: Atomic Structure, Incipient Nanotectonic Nuclei, and Multilevel Writing. *J. Mater. Chem. C* **2021**, *9*, 17019–17032.
- (59) Kassem, M.; Bounazef, T.; Sokolov, A.; Bokova, M.; Fontanari, D.; Hannon, A. C.; Alekseev, I.; Bychkov, E. Deciphering Fast Ion Transport in Glasses: A Case Study of Sodium and Silver Vitreous Sulfides. *Inorg. Chem.* **2022**, *61*, 12870–12885.
- (60) Grimme, S.; Ehrlich, S.; Goerigk, L. Effect of the Damping Function in Dispersion Corrected Density Functional Theory. *J. Comput. Chem.* **2011**, *32*, 1456–1465.
- (61) Micoulaut, M. Communication: Van der Waals Corrections for an Improved Structural Description of Telluride Based Materials. *J. Chem. Phys.* **2013**, *138*, 061103.
- (62) Bouzid, A.; Massobrio, C.; Boero, M.; Ori, G.; Sykina, K.; Furet, E. Role of the van der Waals Interactions and Impact of the Exchange-Correlation Functional in Determining the Structure of Glassy GeTe<sub>4</sub>. *Phys. Rev. B* **2015**, *92*, 134208.
- (63) Matsunaga, T.; Akola, J.; Kohara, S.; Honma, T.; Kobayashi, K.; Ikenaga, E.; Jones, R. O.; Yamada, N.; Takata, M.; Kojima, R. From Local Structure to Nanosecond Recrystallization Dynamics in AgInSbTe Phase-Change Materials. *Nat. Mater.* **2011**, *10*, 129–134.
- (64) Gereben, O.; Pusztai, L. RMC\_POT, a Computer Code for Reverse Monte Carlo Modeling the Structure of Disordered Systems Containing Molecules of Arbitrary Complexity. *J. Comput. Chem.* **2012**, *33*, 2285–2291.
- (65) Hartwigsen, C.; Goedecker, S.; Hutter, J. Relativistic Separable Dual-Space Gaussian Pseudopotentials from H to Rn. *Phys. Rev. B* **1998**, *58*, 3641.
- (66) Nosé, S. A Molecular Dynamics Method for Simulations in the Canonical Ensemble. *Mol. Phys.* **1984**, *52*, 255–268.
- (67) Hoover, W. G. Canonical Dynamics: Equilibrium Phase-Space Distributions. *Phys. Rev. A* **1985**, *31*, 1695.
- (68) Le Roux, S.; Jund, P. Ring Statistics Analysis of Topological Networks: New Approach and Application to Amorphous GeS<sub>2</sub> and SiO<sub>2</sub> Systems. *Comput. Mater. Sci.* **2010**, *49*, 70–83.
- (69) Kohara, S.; Ohno, H.; Takata, M.; Usuki, T.; Morita, H.; Suzuya, K.; Akola, J.; Pusztai, L. Lead Silicate Glasses: Binary Network-Former Glasses with Large Amounts of Free Volume. *Phys. Rev. B* **2010**, *82*, 134209.
- (70) Heimbach, I.; Rhiem, F.; Beule, F.; Knodt, D.; Heinen, J.; Jones, R. O. pyMolDyn: Identification, Structure, and Properties of Cavities/Vacancies in Condensed Matter and Molecules. *J. Comput. Chem.* **2017**, *38*, 389–394.
- (71) Kawamoto, Y.; Tsuchihashi, S. The Properties and Structure of Glasses in the System As<sub>2</sub>S<sub>3</sub>-Sb<sub>2</sub>S<sub>3</sub>. *Yogyo-Kyokai-Shi* **1969**, *77*, 12–19.
- (72) N'Dri, K.; Sei, J.; Houphouet-Boigny, D.; Kra, G.; Jumas, J.-C. Estimation of Glass-Forming Ability and Glass Stability of Sb<sub>2</sub>S<sub>3</sub>-As<sub>2</sub>S<sub>3</sub>-Sb<sub>2</sub>Te<sub>3</sub> Glasses by Thermal Properties. *J. Appl. Sci.* **2007**, *7*, 3167–3176.
- (73) N'Dri, K.; Houphouet-Boigny, D.; Jumas, J.-C.; Olivier-Fourcade, J. Electronegativity Difference, Atomic Size Parameter and Widths of Supercooled Liquid Regions of Sb<sub>2</sub>S<sub>3</sub>-As<sub>2</sub>S<sub>3</sub>-Sb<sub>2</sub>Te<sub>3</sub> glasses. *J. Non-Cryst. Solids* **2011**, *357*, 145–149.
- (74) Janz, G. J.; Dampier, F. W.; Lakshminarayanan, G. R.; Lorenz, P. K.; Tomkins, R. P. T. *Molten Salts: Volume 1, Electrical Conductance, Density, and Viscosity Data*; National Standard Reference Data Series; NBS 15: Washington D.C., 1968; p. 98.

- (75) Mott, N. F.; Davis, E. A. *Electronic Processes in Non-Crystalline Materials*, 2nd ed.; Clarendon Press: Oxford, 1979; pp 28–37, 194–197, 491–497.
- (76) Guo, L.; Zhang, B.; Li, S.; Zhang, Q.; Buettner, M.; Li, L.; Qian, X.; Yan, F. Scalable and Efficient Sb<sub>2</sub>S<sub>3</sub> Thin-Film Solar Cells Fabricated by Close Space Sublimation. *APL Mater.* **2019**, *7*, 041105.
- (77) Chen, J.; Qi, J.; Liu, R.; Zhu, X.; Wan, Z.; Zhao, Q.; Tao, S.; Dong, C.; Ashebir, G. Y.; Chen, W.; Peng, R.; Zhang, F.; Yang, S.; Tian, X.; Wang, M. Preferentially Oriented Large Antimony Trisulfide Single-Crystalline Cuboids Grown on Polycrystalline Titania Film for Solar Cells. *Commun. Chem.* **2019**, *2*, 121.
- (78) Guo, C.; Chen, J.; Li, G.; Liang, X.; Lai, W.; Yang, L.; Mai, Y.; Li, Z. Enhanced Electrical Conductivity of Sb<sub>2</sub>S<sub>3</sub> Thin Film via C<sub>60</sub> Modification and Improvement in Solar Cell Efficiency. *Global Challenges* **2019**, 1800108.
- (79) Lojpur, V.; Joschko, M.; Graf, C.; Radmilović, N.; Novaković, M.; Validžić, I. Structural, Morphological, Optical, and Electronic properties of Amorphous Non-Doped and I and Sn Doped Sb<sub>2</sub>S<sub>3</sub> Nanoparticles. *Mater. Sci. Semicond. Processing* **2022**, *137*, 106196.
- (80) Batsanov, S. S. Van der Waals Radii of Elements. *Inorg. Mater.* **2001**, *37*, 871–885.
- (81) Liu, Y.; Chua, K. T. E.; Sum, T. C.; Gan, C. K. First-Principles Study of the Lattice Dynamics of Sb<sub>2</sub>S<sub>3</sub>. *Phys. Chem. Chem. Phys.* **2014**, *16*, 345–350.
- (82) Lannin, J. S. Raman Scattering Properties of Amorphous As and Sb. *Phys. Rev. B* **1977**, *15*, 3863–3871.
- (83) Cheng, Z.; Milne, T.; Salter, P.; Kim, J. S.; Humphrey, S.; Booth, M.; Bhaskaran, H. Antimony Thin Films Demonstrate Programmable Optical Nonlinearity. *Sci. Adv.* **2021**, *7*, eabd7097.
- (84) Perales, F.; Lifante, G.; Agulló-Rueda, F.; de las Heras, C. Optical and Structural properties in the Amorphous to Polycrystalline Transition in Sb<sub>2</sub>S<sub>3</sub> Thin Films. *J. Phys. D: Appl. Phys.* **2007**, *40*, 2440–2444.
- (85) Makreski, P.; Petruševski, G.; Ugarković, S.; Jovanovskic, G. Laser-Induced Transformation of Stibnite (Sb<sub>2</sub>S<sub>3</sub>) and Other Structurally Related Salts. *Vib. Spectrosc.* **2013**, *68*, 177–182.
- (86) Parize, R.; Cossuet, T.; Chaix-Pluchery, O.; Roussel, H.; Appert, E.; Consonni, V. In Situ Analysis of the Crystallization Process of Sb<sub>2</sub>S<sub>3</sub> Thin Films by Raman Scattering and X-ray Diffraction. *Mater. Design* **2017**, *121*, 1–10.
- (87) Wang, J.; Qiao, Y.; Wang, T.; Yu, H.; Feng, Y.; Li, L. Two-Dimensional (2D) Amorphous Antimony (III) Trisulfide Nanosheets: Synthesis, Photoelectronic Property and their Transformation to Crystalline 1D Micro/Nanorods. *Inorg. Chem. Comm.* **2018**, *92*, 110–114.
- (88) Watanabe, I.; Noguchi, S.; Shimizu, T. Study on Local Structure in Amorphous Sb-S Films by Raman Scattering. *J. Non-Cryst. Solids* **1983**, *58*, 35–40.
- (89) Gutiérrez, Y.; Fernández-Pérez, A.; Rosales, S. A.; Cobianu, C.; Gheorghe, M.; Modreanu, M.; Saiz, J. M.; Moreno, F.; Losurdo, M. Polarimetry Analysis and Optical Contrast of Sb<sub>2</sub>S<sub>3</sub> Phase Change Material. *Opt. Mater. Express* **2022**, *12*, 1531–1541.
- (90) Holubová, J.; Liška, M.; Chromčíková, M.; Černošková, E.; Černošek, Z. Structure of As<sub>2</sub>S<sub>3</sub>-Sb<sub>2</sub>S<sub>3</sub> Glasses by Combined Raman Spectroscopy and a Thermodynamic Modelling Approach. *Phys. Chem. Glasses* **2012**, *53*, 31–36.
- (91) Pethes, I.; Nazabal, V.; Arib, J.; Kaban, I.; Darpentigny, J.; Welter, E.; Gutowski, O.; Bureau, B.; Messaddeq, Y.; Jóvári, P. Atomic Level Structure of Ge-Sb-S Glasses: Chemical Short Range Order and Long Sb-S Bonds. *J. Alloys Compd.* **2019**, *774*, 1009–1016.
- (92) Guan, S.; Sun, S.; Chen, D.; Zhang, J.; Kang, S.; Xu, T.; Lin, C. Formation and Physical and Structural Properties of Sb<sub>2</sub>S<sub>3</sub>-PbI<sub>2</sub> Chalcogenide Glasses. *J. Non-Cryst. Solids* **2021**, *570*, 120993.
- (93) Krebs, H.; Steffen, R. Neubestimmung der Nahordnung im Glasigen Selen, im Explosiven Antimon und im β- und γ-Arsen. *Z. Anorg. Allg. Chem.* **1964**, *327*, 224–237.
- (94) Winter, R.; Pilgrim, W.-C.; Egelstaff, P. A.; Chieux, P.; Anlauf, S.; Hensel, F. Neutron Scattering Study on Amorphous Sulphur. *Europhys. Lett.* **1990**, *11*, 225–228.
- (95) Bychkov, E.; Benmore, C. J.; Price, D. L. Compositional Changes of the First Sharp Diffraction Peak in Binary Selenide Glasses. *Phys. Rev. B* **2005**, *72*, 172107.

- (96) Bychkov, A.; Cuello, G. J.; Kohara, S.; Benmore, C. J.; Price, D. L.; Bychkov, E. Unraveling the Atomic Structure of Ge-Rich Sulfide Glasses. *Phys. Chem. Chem. Phys.* **2013**, *15*, 8487–8494.
- (97) Moss, S. C.; Price, D. L. Random Packing of Structural Units and the First Sharp Diffraction Peak in Glasses. In *Physics of Disordered Materials*; Adler, D., Fritzsche, H., Ovshinsky, S., Eds.; Plenum: New York, 1985; pp 77–95.
- (98) Barrett, C. S.; Cucka, P.; Haffner, K. The Crystal Structure of Antimony at 4.2, 78 and 298 °K. *Acta Cryst.* **1963**, *16*, 451–453.
- (99) Simdyankin, S. I.; Elliott, S. R.; Hajnal, Z.; Niehaus, T. A.; Frauenheim, Th. Simulation of Physical Properties of the Chalcogenide Glass As<sub>2</sub>S<sub>3</sub> using a Density-Functional-Based Tight-Binding Method. *Phys. Rev. B* **2004**, *69*, 144202.
- (100) Mullen, D. J. E.; Nowacki, W. Refinement of the Crystal Structures of Realgar, AsS and Orpiment, As<sub>2</sub>S<sub>3</sub>. *Z. Kristallogr.* **1972**, *136*, 48–65.
- (101) Kampf, A. R.; Downs, R. T.; Housley, R. M.; Jenkins, R. A.; Hyrsl, J. Anorpiment, As<sub>2</sub>S<sub>3</sub>, the Triclinic Dimorph of Orpiment. *Mineralog. Mag.* **2011**, *75*, 2857–2867.
- (102) Bychkov, E.; Wortmann, G. <sup>121</sup>Sb-Mössbauer Study of Insulating and Ion-Conducting Antimony Chalcogenide-Based Glasses. *J. Non-Cryst. Solids* **1993**, *159*, 162–172.
- (103) Ruby, S. L.; Kalvius, G. M.; Beard, G. B.; Snyder, R. E. Interpretation of Mössbauer Measurements in Tin and Antimony. *Phys. Rev.* **1967**, *159*, 239–245.
- (104) Caravati, S.; Bernasconi, M.; Parrinello, M. First-Principles Study of Liquid and Amorphous Sb<sub>2</sub>Te<sub>3</sub>. *Phys. Rev. B* **2010**, *81*, 014201.
- (105) Akola, J.; Jónvári, P.; Kaban, I.; Voleská, I.; Kolář, J.; Wágner, T.; Jones, R. O. Structure, Electronic, and Vibrational Properties of Amorphous AsS<sub>2</sub> and AgAsS<sub>2</sub>: Experimentally Constrained Density Functional Study. *Phys. Rev. B* **2014**, *89*, 064202.
- (106) Wang, X.; Li, Z.; Kavanagh, S. R.; Ganose, A. M.; Walsh, A. Lone Pair Driven Anisotropy in Antimony Chalcogenide Semiconductors. *Phys. Chem. Chem. Phys.* **2022**, *24*, 7195–7202.
- (107) Grigas, J.; Talik, E.; Lazauskas, V. X-ray Photoelectron Spectroscopy of Sb<sub>2</sub>S<sub>3</sub> Crystals. *Phase Transitions* **2002**, *75*, 323–337.
- (108) Ben Nasr, T.; Maghraoui-Meherzi, H.; Ben Abdallah, H.; Bennaceur, R. Electronic Structure and Optical Properties of Sb<sub>2</sub>S<sub>3</sub> crystal. *Physica B* **2011**, *406*, 287–292.
- (109) Xu, M.; Gu, R.; Qiao, C.; Tong, H.; Cheng, X.; Wang, C.-Z.; Ho, K.-M.; Wang, S.; Miao, X.; Xu, M. Unraveling the Structural and Bonding Nature of Antimony Sesquichalcogenide Glass for Electronic and Photonic Applications. *J. Mater. Chem. C* **2021**, *9*, 8057–8065.
- (110) Gutiérrez, Y.; Ovvyan, A. P.; Santos, G.; Juan, D.; Rosales, S. A.; Junquera, J.; García-Fernández, P.; Dicorato, S.; Giangregorio, M. M.; Dilonardo, E.; Palumbo, P.; Modreanu, M.; Resl, J.; Ishchenko, O.; Garry, G.; Jonuzi, T.; Georghe, M.; Cobianu, C.; Hingerl, K.; Cobet, C.; Moreno, F.; Pernice, W. H. P.; Losurdo, M. Interlaboratory Study on Sb<sub>2</sub>S<sub>3</sub> Interplay between Structure, Dielectric Function, and Amorphous-to-Crystalline Phase Change for Photonics. *iScience* **2022**, *25*, 104377.
- (111) Kalikka, J.; Akola, J.; Jones, R.O.; Kohara, S.; Usuki, T. Amorphous Ge<sub>15</sub>Te<sub>85</sub>: density functional, high-energy X-ray and neutron diffraction study. *J. Phys.: Condens. Matter.* **2012**, *24*, 015802.
- (112) Orava, J.; Hewak, D. W.; Greer, A. L. Fragile-to-Strong Crossover in Supercooled Liquid Ag-In-Sb-Te Studied by Ultrafast Calorimetry. *Adv. Funct. Mater.* **2015**, *25*, 4851–4858.
- (113) Wei, S.; Lucas, P.; Angell, C. A. Phase Change Alloy Viscosities down to  $T_g$  using Adam-Gibbs-Equation Fittings to Excess Entropy Data: A Fragile-to-Strong Transition. *J. Appl. Phys.* **2015**, *118*, 034903.
- (114) Wei, S.; Lucas, P.; Angell, C. A. Phase-Change Materials: The View from the Liquid Phase and the Metallicity Parameter. *MRC Bull.* **2019**, *44*, 691-698.
- (115) Pries, J.; Weber, H.; Benke-Jacob, J.; Kaban, I.; Wei, S.; Wuttig, M.; Lucas, P. Fragile-to-Strong Transition in Phase-Change Material Ge<sub>3</sub>Sb<sub>6</sub>Te<sub>5</sub>. *Adv. Funct. Mater.* **2022**, 2202714.
- (116) Zhu, W.; Gulbiten, O.; Aitken, B.; Sen, S. Viscosity, Enthalpy Relaxation and Liquid-Liquid Transition of the Eutectic Liquid Ge<sub>15</sub>Te<sub>85</sub>. *J. Non-Cryst. Solids* **2021**, *554*, 120601.



- (117) Huang, R.; Chavez, I.; Taute, K. M.; Lukić, B.; Jeney, S.; Raizen, M. G.; Florin, E.-L. Direct Observation of the Full Transition from Ballistic to Diffusive Brownian Motion in a Liquid. *Nat. Phys.* **2011**, *7*, 576–580.
- (118) Chernov, A. P.; Dembovsky, S. A.; Makhova, V. M. Viscosity and Structure of Glasses in the  $As_2X_3-AsI_3$  System. *Izv. Akad. Nauk SSSR, Neorg. Mater.* **1970**, *6*, 823–825.
- (119) Shchukina, N. E.; Orlova, G. M.; Chalabyan, G. A. The Viscosity and Elastic Properties of Glasses in the Arsenic–Sulfur–Thallium System. *Fiz. Khim. Stekla* **1979**, *5*, 223–228.
- (120) Nemilov, S. V. The Viscosity and Elastic Properties of Melts and Glasses in the As–S System and their Valence-Bond Structure. *Fiz. Khim. Stekla* **1979**, *5*, 398–409.
- (121) Chaussemy, G.; Fornazero, J.; Mackowski, J.-M. Relationship between Viscosity and Structure in  $As_xS_{1-x}$  Molten Materials. *J. Non-Cryst. Solids* **1983**, *58*, 219–234.
- (122) Tverjanovich, A. S. Temperature Dependence of the Viscosity of Chalcogenide Glass-Forming Melts. *Glass Phys. Chem.* **2003**, *29*, 532–536.
- (123) Shánělová, J.; Košťál, P.; Málek, J. Viscosity of  $(GeS_2)_x(Sb_2S_3)_{1-x}$  Supercooled Melts. *J. Non-Cryst. Solids* **2006**, *352*, 3952–3955.
- (124) Mauro, J. C.; Yue, Y.; Ellison, A. J.; Gupta, P. K.; Allan, D. C. Viscosity of Glass-Forming Liquids. *Proc. Natl. Acad. Sci. U.S.A.* **2009**, *106*, 19780–19784.
- (125) Košťál, P.; Shánělová, J.; Málek, J. Viscosity of Chalcogenide Glass-Formers. *Int. Mater. Rev.* **2019**, *65*, 63–101.
- (126) Yuan, B.; Aitken, B. G.; Sen, S. Viscoelastic Behavior and Fragility of Se-deficient Chalcogenide Liquids in As–P–Se System. *J. Non-Cryst. Solids X* **2022**, *16*, 100128.
- (127) Kassem, M.; Benmore, C. J.; Usuki, T.; Ohara, K.; Tverjanovich, A.; Bokova, M.; Brazhkin, V. V.; Bychkov, E. Transient Mesoscopic Immiscibility, Viscosity Anomaly and High Internal Pressure at the Semiconductor–Metal Transition in Liquid  $Ga_2Te_3$ . *J. Phys. Chem. Lett.* **2022**, *13*, 10843–10850.
- (128) Rödl, T.; Weihrich, R.; Wack, J.; Senker, J.; Pfitzner, A. Rational Syntheses and Structural Characterization of Sulfur-Rich Phosphorus Polysulfides:  $\alpha$ - $P_2S_7$  and  $\beta$ - $P_2S_7$ . *Angew. Chem. Int. Ed.* **2011**, *50*, 10996–11000.
- (129) Koudelka, L.; Pisárčik, M.; Gutenov, M. S.; Blinov, L. N. Raman Spectra and Short-Range Order in  $P_xS_{1-x}$  Glasses. *J. Mater. Sci. Lett.* **1989**, *8*, 933–934.
- (130) Tullius, M.; Lathrop, D. A.; Eckert, H. Glasses in the System Phosphorus-Sulfur: A  $^{31}P$  Spin-Echo and High-speed MAS-NMR Study of Atomic Distribution and Local Order. *J. Phys. Chem.* **1990**, *94*, 2145–2150.
- (131) Lyda, C. M.; Leone, J. M.; Bankert, M. A.; Xia, Y.; Eckert, H. Structural Studies of Phosphorus-Sulfur-Tellurium Glasses by  $^{31}P$  MAS NMR and Vibrational Spectroscopies. *Chem. Mater.* **1994**, *6*, 1934–1939.
- (132) Shiba, R. K.; Xia, Y.; Srdanov, V. I.; Eckert, H. Plasma-Enhanced Chemical Vapor Deposited Phosphorus Sulfide Films. Characterization by Raman and Solid-State NMR Spectroscopies and Comparison to Melt-Quenched Glassy Materials. *Chem. Mater.* **1995**, *7*, 1631–1638.
- (133) Novoselova, A.V.; Pashinkin, A.S. *Vapor Pressures of Volatile Metal Chalcogenides*; Nauka: Moscow, 1978; pp 78–83.
- (134) Lau, K. H.; Brittain, R. D.; Hildenbrand, D. L. Vaporization of  $As_2S_3$ , and the Dissociation Energy of  $AsS$ . *J. Phys. Chem.* **1982**, *86*, 4429–4432.
- (135) Solin, S. A.; Papatheodorou, G. N. Irreversible Thermostructural Transformations in Amorphous  $As_2S_3$  Films: A Light-Scattering Study. *Phys. Rev. B* **1977**, *15*, 2084–2090.
- (136) Nemanich, R. J.; Connell, G. A. N.; Hayes, T. M.; Street, R. A. Thermally Induced Effects in Evaporated Chalcogenide Films. I. Structure. *Phys. Rev. B* **1978**, *18*, 6900–6914.
- (137) Slade, M.L.; Zallen, R. Raman Spectra of  $As_4S_4$  Polymorphs: Structural Implications for Amorphous  $As_2S_3$  Films. *Solid State Commun.* **1979**, *30*, 357–360.
- (138) De Neufville, J. P.; Moss, S. C.; Ovshinsky, S. R. Photostructural Transformations in Amorphous  $As_2Se_3$  and  $As_2S_3$  Films. *J. Non-Cryst. Solids*, **1973**, *13*, 191–223.
- (139) Daniel, M. F.; Leadbetter, A. J.; Wright, A. C.; Sinclair, R. N. The Structure of Vapour-Deposited Arsenic Sulphides. *J. Non-Cryst. Solids* **1979**, *32*, 271–293.

- (140) Greenwood, N.N.; Earnshaw, A. *Chemistry of the Elements*, 2nd ed.; Butterworth-Heinemann: Oxford, 1997; pp 578–583.
- (141) Lukaszewicz, K.; Stepen-Damm, Yu.; Pietraszko, A.; Kajokas, A.; Grigas, J. Crystal Structure, Thermal Expansion, Dielectric Permittivity and Phase Transitions of Bi<sub>2</sub>S<sub>3</sub>. *Polish J. Chem.* **1999**, *73*, 541–546.
- (142) Tanaka, K. Chemical and Medium-Range Orders in As<sub>2</sub>S<sub>3</sub> Glass. *Phys. Rev. B* **1987**, *36*, 9746–9752.
- (143) Ito, T.; Morimoto, N.; Sadanaga, R. The Crystal Structure of Realgar. *Acta Crystallogr.* **1952**, *5*, 775–782.
- (144) Hosokawa, S.; Sakaguchi, Y.; Hiasa, H.; Tamura, K. Optical Absorption Spectra of Liquid As<sub>2</sub>S<sub>3</sub> and As<sub>2</sub>Se<sub>3</sub> over a Wide Temperature Range. *J. Phys.: Condens. Matter* **1991**, *3*, 6673–6677.
- (145) Alekseev, V. A.; Andreev, A. A.; Sadovskii, M. V. Semiconductor-Metal Transition in Liquid Semiconductors. *Sov. Phys. Usp.* **1980**, *23*, 551–575.
- (146) Liang, X.; Feng, Y.; Dang, W.; Huang, H.; Wang, X.; Guo, Y.; Shen, K.; Schropp, R. E. I.; Li, Z.; Mai, Y. High-Efficiency Flexible Sb<sub>2</sub>Se<sub>3</sub> Solar Cells by Back Interface and Absorber Bulk Deep-Level Trap Engineering. *ACS Energy Lett.* **2023**, *8*, 213–221.
- (147) Linhart, W. M.; Zelewski, S. J.; Scharoch, P.; Dybała, F.; Kudrawiec, R. Nesting-Like Band Gap in Bismuth Sulfide Bi<sub>2</sub>S<sub>3</sub>. *J. Mater. Chem. C* **2021**, *9*, 13733–13738.
- (148) Lan, M.; Wang, Y.; Dong, X.; Yang, F.; Zheng, N.; Wang, Y.; Ma, H.; Zhang, X. Controllable Fabrication of Sulfur-Vacancy-Rich Bi<sub>2</sub>S<sub>3</sub> Nanorods with Efficient Near-Infrared Light Photocatalytic for Nitrogen Fixation. *Appl. Surf. Sci.* **2022**, *591*, 153205.
- (149) Park, J.-W.; Baek, S. H.; Kang, T. D.; Lee, H.; Kang, Y.-S.; Lee, T.-Y.; Suh, D.-S.; Kim, K. J.; Kim, C. K.; Khang, Y. H.; Da Silva, J. L. F.; Wei, S.-H. Optical Properties of (GeTe, Sb<sub>2</sub>Te<sub>3</sub>) Pseudobinary Thin Films Studied with Spectroscopic Ellipsometry. *Appl. Phys. Lett.* **2008**, *93*, 021914.
- (150) Soignard, E.; Tsiok, O. B.; Tverjanovich, A. S.; Bychkov, A.; Sokolov, A.; Brazhkin, V. V.; Benmore, C. J.; Bychkov, E. Pressure-Driven Chemical Disorder in Glassy As<sub>2</sub>S<sub>3</sub> up to 14.7 GPa, Post-densification Effects, and Applications in Materials Design. *J. Phys. Chem. B* **2020**, *124*, 430–442.
- (151) Ichikawa, T. Electron Diffraction Study of the Local Atomic Arrangement in Amorphous Tellurium Films. *Phys. Stat. Solidi B* **1973**, *56*, 707–715.
- (152) Suzuki, S.; Maruyama, K.; Misawa, M. Structural Analysis of Liquid Chalcogen by RMC Modeling with a Dimer Molecule Model. *J. Phys. Soc. Japan* **2000**, *69*, 3576–3580.
- (153) Akola, J.; Jones, R. O.; Kohara, S.; Usuki, T.; Bychkov, E. Density Variations in Liquid Tellurium: Roles of Rings, Chains, and Cavities. *Phys. Rev. B* **2010**, *81*, 094202.