



HAL
open science

Nanotubule inclusion in the channels formed by a six-fold interpenetrated, triperiodic framework

Sotaro Kusumoto, Youssef Atoini, Yoshihiro Koide, Kittipong Chainok, Shinya Hayami, Yang Kim, Jack Harrowfield, Pierre Thuéry

► To cite this version:

Sotaro Kusumoto, Youssef Atoini, Yoshihiro Koide, Kittipong Chainok, Shinya Hayami, et al.. Nanotubule inclusion in the channels formed by a six-fold interpenetrated, triperiodic framework. Chemical Communications, inPress, 10.1039/D3CC02636A . hal-04170568

HAL Id: hal-04170568

<https://hal.science/hal-04170568>

Submitted on 25 Jul 2023

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.


Nanotubule inclusion in the channels formed by a six-fold interpenetrated, triperiodic framework†

Sotaro Kusumoto,^a Youssef Atoini,^b Yoshihiro Koide,^a Kittipong Chainok,^{*c} Shinya Hayami,^{*d}
Yang Kim,^{*c,d} Jack Harrowfield^{*e} and Pierre Thuéry^{*f}

When reacted together with uranyl ion under solvo-hydrothermal conditions, a bis(pyridiniumcarboxylate) zwitterion (L) and tricarballic acid (H₃tca) give the complex [NH₄]₂[UO₂(L)₂][UO₂(tca)]₄·2H₂O (1). The two ligands are segregated into different units, an anionic nanotubule for tca³⁻ and a six-fold interpenetrated cationic framework for L. The entangled framework defines large channels which contain the square-profile nanotubules. Complex 1 has a photoluminescence quantum yield of 19% and its emission spectrum shows the superposition of the signals due to the two independent species.

The use of zwitterionic dicarboxylates with a large spatial separation between the two complexing sites, in association with diverse anionic dicarboxylates, has provided an efficient way to synthesize uranyl ion complexes with original features, among which the more remarkable are mixed-ligand ring- or cage-like molecular species, and woven, interpenetrated or polycatenated polymeric structures.^{1,2} This strategy thus appears as a promising development in the area of uranyl-organic coordination polymers and frameworks.³ A complication, however, is that even where a single product with the desired mixed-ligand composition is obtained, true heteroleptic metal ion centres where both ligands are bound to any one cation are not necessarily present. This we have observed in our work concerning uranyl ion coordination polymers derived from mixtures of poly-zwitterionic and poly-anionic carboxylate-donor ligands which, on the basis of extensive studies of simpler species,⁴ are assumed to have essentially identical binding capacity of their carboxylate units. This work,^{2,5} although first seeming to confirm the validity of this assumption, subsequently provided examples of single crystals containing independent cationic polymer units involving principally or solely the polyzwitterion and anionic polymer units involving just the polycarboxylate.^{2b,d,5b} While considerable progress has been made in the development of rational procedures providing mixed-ligand species with desired properties,⁶ the isolation of mixed-ligand complexes of labile metal ions is complicated by the fact that it depends not only on solution equilibria but also upon solubility. The present work provides a further example of the remarkable structures that can result from such “aberrant” behaviour.

The complex [NH₄]₂[UO₂(L)₂][UO₂(tca)]₄·2H₂O (1), where L is 1,1'-[(benzene-1,4-diyl)bis(methylene)]bis(pyridin-1-ium-4-carboxylate) and H₃tca is tricarballic acid (Scheme 1), has been synthesized† under solvo-hydrothermal conditions and its crystal structure determined.§ 1 crystallizes in the tetragonal space group

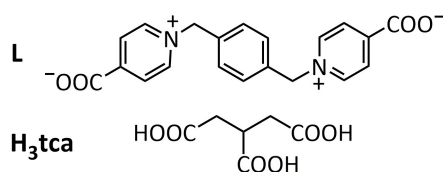

Scheme 1 The ligands L and H₃tca.

*P*4₂/*n*, with three independent uranium atoms, one of them on an inversion centre (Fig. 1). From previous work on uranyl ion

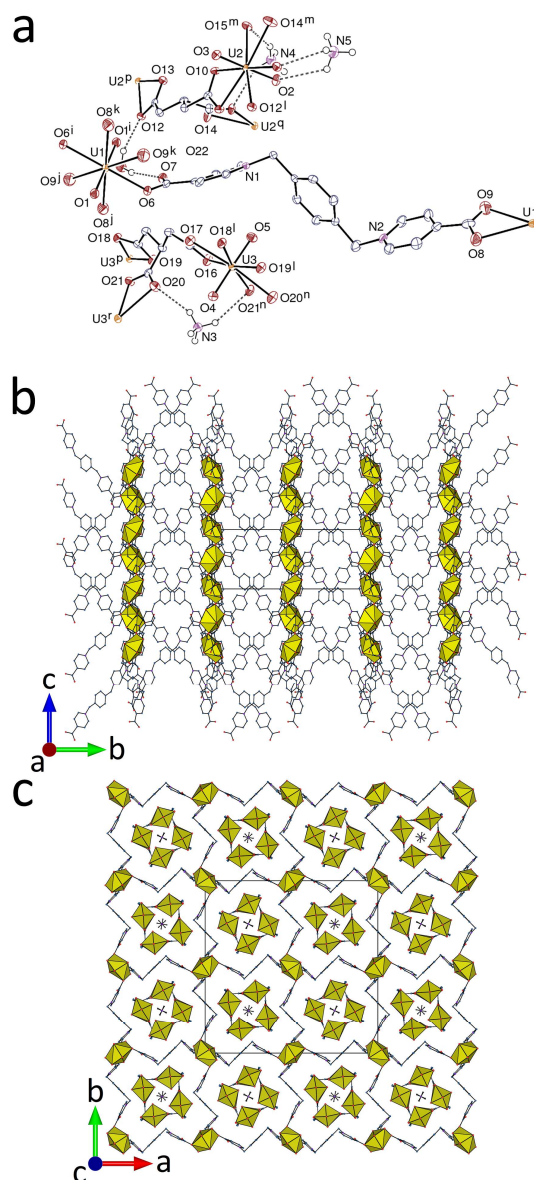


Fig. 1 (a) View of complex 1. Displacement ellipsoids are drawn at the 50% probability level and carbon-bound hydrogen atoms are omitted. Hydrogen bonds are shown as dashed lines. Symmetry codes: $i = -x, 1 - y, 2 - z$; $j = y - 1/2, 1 - x, z + 3/2$; $k = 1/2 - y, x, 1/2 - z$; $l = x, y, z - 1$; $m = 1/2 - y, x, 3/2 - z$; $n = 1 - y, x + 1/2, z - 1/2$; $o = 1 - y, x + 1/2, z - 3/2$; $p = x, y, z + 1$; $q = y, 1/2 - x, 3/2 - z$; $r = y - 1/2, 1 - x, z + 1/2$. (b) View of the six-fold interpenetrated, cationic framework with uranium coordination polyhedra shown in yellow. (c) View of the packing down the channel axis, with ammonium-containing nanotubes included.

complexes of tca^{3-} ,^{2b,7} it is known that this ligand has a tendency to generate tubular coordination polymers,^{2b,7b,d} and that with the metalladizwitterion $[\text{Ni}(\text{tpyc})_2]$ ($\text{tpyc}^- = 4'$ -carboxylato-2,2';6',2"-terpyridine) it can form a true mixed-ligand species (in the sense that both of the inequivalent U^{VI} centres are bound to both zwitterion and anionic carboxylate groups) which is tubular,^{2b} though of a rather different profile to the tubular species formed with tca^{3-} alone.^{7b,d} In the present case, the trianion forms two inequivalent but very similar monoperiodic, tubular coordination polymer units directed along [001], containing atoms U2 and U3, which are both dimensionally almost identical with that found in $[\text{NH}_4][(\text{UO}_2)_2\text{Pb}(\text{tca})_2(\text{NO}_3)(\text{bipy})]$ ($\text{bipy} = 2,2'$ -bipyridine),^{7b} involving the ligand as a *tris*($\kappa^2\text{O},\text{O}'$) chelate linking hexagonal-bipyramidal U^{VI} centres [$\text{U}-\text{O}(\text{oxo}), 1.769(3)-1.790(4)$ Å; $\text{U}-\text{O}(\text{carboxylato}), 2.439(3)-2.478(3)$ Å in **1**]. As in the $\text{U}-\text{Pb}$ species, the tubes enclose ammonium cations, either one located on a two-fold rotation axis (Wyckoff position 4e) or two located on a four-fold rotoinversion axis (2a and 2b). All are involved in $\text{NH}\cdots\text{O}$ hydrogen bonding to carboxylato (and one oxo) oxygen atoms [$\text{N}\cdots\text{O}, 2.986(5)-3.242(3)$ Å; $\text{N}-\text{H}\cdots\text{O}, 125-152^\circ$]. $\text{N}\cdots\text{N}$ separations are, however, close to 5.0 Å for all ammonium cations both here and in the previous complex. While these ammonium cations presumably arised from complete oxidative decomposition of acetonitrile under solvothermal conditions in the former case, they are most probably a remainder of the NH_4PF_6 reactant used during the synthesis of the ligand here. That the square-profile, tubular $\{[\text{UO}_2(\text{tca})]_n\}$ unit might act as an ammonium ion scavenger is a prospect to be investigated.

In the cationic part of the complex, $[\text{UO}_2(\text{L})_2]^{2+}$, the uranium atom U1 is in a centrosymmetric hexagonal bipyramidal environment, being $\kappa^2\text{O},\text{O}'$ -chelated by two carboxylate groups and bound to two more monodentate carboxylate donors [$\text{U}-\text{O}(\text{oxo}), 1.775(4)$ Å; $\text{U}-\text{O}(\text{carboxylato}), 2.324(3)$ Å for the monodentate group, 2.598(4) and 2.602(4) Å for the chelating group]. L adopts a divergent, S-shaped conformation and it bridges two uranyl cations, a situation most common with such flexible, zwitterionic dicarboxylates.^{2c,d,5b} U1 is thus a four-coordinated (4-c) node and L is a simple edge in the uninodal, triperiodic framework formed, which has the point symbol $\{4^2.8^4\}$ and the **1vt** topological type. The L edges are sufficiently elongated (separation of 20.3366(4) Å between the bridged uranium centres) to allow for six-fold interpenetration to occur (Fig. 2). The entanglement pertains to class Ia (one translation only), and the full interpenetration vector is [001].⁸ Framework interpenetration with high multiplicity is not frequent in uranyl chemistry, but another six-fold⁹ and one eight-fold¹⁰ cases are known. When viewed down [100] (Fig. 1b), the structure displays alternate layers of uranyl cations and organic chains, with no π -stacking interactions being apparent in the latter. The presence of large voids in the interpenetrated structure is shown by the value of 0.34 for the Kitaigorodsky packing index (KPI) calculated for the cationic polymer alone.

The most original feature of this structure is related to the association of the anionic and cationic polymers. The six interpenetrated networks define two sets of slightly different channels running along [001], centered on two-fold rotation or four-fold rotoinversion axes, with the oxo atoms of the corner-defining uranyl ions either directed toward the centre of the channel or away from it (Fig. 1c). The section of both channels is roughly square, with a side length of ~ 14 Å and a diagonal of ~ 19.8 Å. One of the two independent anionic tubules is included in each of these two channels, with an orientation slightly different when viewed down [001] (Figs. 1c and 2d). Apart from electrostatic interactions, it is notable that two $\text{CH}\cdots\pi$ contacts involve one methylene proton in each of the two tca^{3-} anions [$\text{H}\cdots\text{centroid}, 2.88$ and 2.82 Å; $\text{C}-\text{H}\cdots\text{centroid}, 144^\circ$ for both]; one $\text{U}=\text{O}\cdots\pi$ interaction may also be present [$\text{O5}\cdots\text{centroid}, 3.755(4)$ Å; $\text{U3}-\text{O5}\cdots\text{centroid}, 107.61(15)^\circ$]. As usual, several $\text{CH}\cdots\text{O}$ hydrogen bonds are also formed between the two polymeric motifs

[$\text{C}\cdots\text{O}, 2.993(6)-3.455(7)$ Å; $\text{C}-\text{H}\cdots\text{O}, 114-156^\circ$]. The packing is quite compact, as shown by the KPI of 0.74.

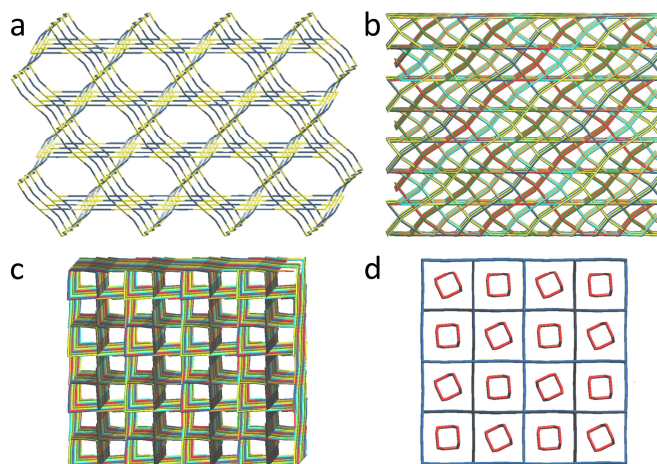


Fig. 2 (a) Nodal representation of a single network with **1vt** topology in **1** down a direction slightly rotated from [103] (yellow, U nodes; blue, L edges). (b) and (c) Two views of the six-fold interpenetrated networks, down a direction slightly rotated from [100] or [001], respectively. (d) Nanotubes (red) included in the channels of the framework (blue), viewed down [001].

Since the cationic and anionic polymers can in principle be separated without breaking of bonds, this arrangement is different from true 1D + 3D interpenetration, of which examples are known,¹¹ and it may more properly be termed “semi-interpenetration”. Some simpler cases have previously been found in uranyl ion complexes, such as the inclusion of linear, dinuclear anions in the channels formed by the packing of diperiodic cations, both formed with a zwitterionic dicarboxylate,^{2d} and that of uranyl citrate anionic chains in the channels formed by layers of uranyl complexes with the zwitterion $[\text{Ni}(\text{tpyc})_2]$.^{2b} The use of large zwitterionic dicarboxylates thus appears to be of interest for the synthesis of complexes displaying original entangled structures, as shown also by a case of 2D + 3D heterointerpenetration.^{2d}

An interesting point concerns the presence of template effects in the formation of **1**. Ammonium cations probably play a structure-directing role in the formation of the nanotubules with square cross-section as observed here and in $[\text{NH}_4][(\text{UO}_2)_2\text{Pb}(\text{tca})_2(\text{NO}_3)(\text{bipy})]$, as indicated by larger nanotubules, with a hexagonal cross-section, being formed in the presence of the $[\text{Co}(\text{en})_3]^{3+}$ counterion, also an efficient hydrogen bond donor.^{7d} In a second step, the nanotubules themselves could be necessary for the formation of the six-fold interpenetrated framework, although further investigation of uranyl ion complexes containing the ligand L will be needed to specify the possible range of different structures attainable (preliminary results show that a completely different structure is obtained with the ketopimelate coligand). If such a structure-directing effect were real, the formation of **1** would entail a nested, two-fold templating phenomenon, with ammonium as a sort of “second-sphere” structure-directing species for the framework.

The emission spectrum of **1** was measured in the solid state under excitation at 420 nm. The photoluminescence quantum yield (PLQY) reaches 19%, a high value for a carboxylate uranyl ion complex. The spectrum displays the broad envelope of several emission peaks which can be separated by Gaussian deconvolution (Fig. 3). The first six intense peaks after deconvolution are easily identified as pertaining to two families (green and orange in Fig. 3), while the two weaker, very broad and most red-shifted peaks are presumed due to unresolved

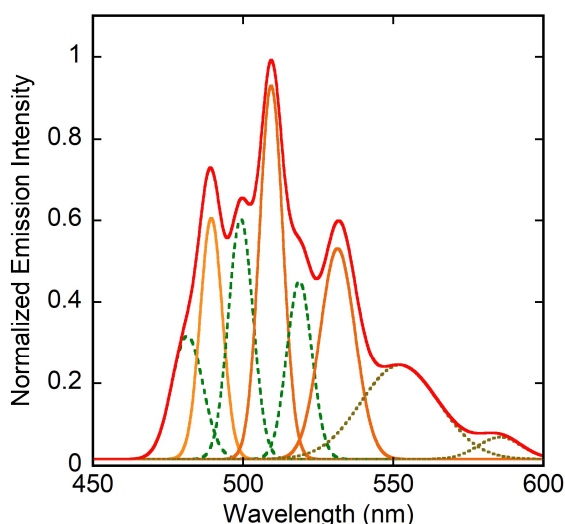


Fig. 3 Emission spectrum of complex **1** (red) and deconvoluted components, measured in the crystalline state upon excitation at 420 nm.

minor components. Each set shows the usual vibronic fine structure typical of uranyl ion emission ($S_{11} \rightarrow S_{00}$ and $S_{10} \rightarrow S_{0\nu}$ ($\nu = 0-4$) electronic transitions),¹² with average splitting energies of $\sim 800-900$ cm^{-1} . The first series (dashed green) has maxima at 479, 501 and 521 nm, and the second (full orange) at 489, 509 and 531 nm. Both sets of values are within the range usually observed for six-coordinate carboxylate uranyl ion complexes.¹³ Although the relative emissive powers of the cation and anion are unknown, it seems reasonable to attribute the most intense peaks to the nanotubules, which contain four times as many emitters as the framework; as further corroboration of this attribution, it can be remarked that the three main peaks of other uranyl tricarballylate complexes, measured under the same conditions, are at 484/495, 504/516 and 526/539 nm,^{7d} i.e. values which flank the present ones. If so, the nanotubules would correspond to the most red-shifted signals. This would indicate that the donor strength in the equatorial plane is greater in the anionic than in the zwitterionic complex, since it is known to induce a decrease in the bond order of oxo groups to uranyl.¹⁴ Evaluation of bond strengths from bond lengths as provided by calculation of bond valence parameters¹⁵ confirms this trend, with values for axial/equatorial components of 3.436/2.532 for U1, 3.406/2.694 for U2 and 3.393/2.726 for U3, indicating greater strength of the oxo bonds in zwitterion-bound U1 than in anionic carboxylate-bound U2 and U3 (overall bond valence parameters, 5.97, 6.10 and 6.12, respectively).

The structure of complex **1** provides another remarkable example of the variations possible in mixed-ligand coordination polymers, one where the dizwitterion and the anionic carboxylate have independent roles. Although many interpenetrated or polycatenated uranyl ion-containing systems are presently known, with even instances of heterointerpenetration of motifs with different chemical nature and periodicity,^{2d} the present inclusion of a monophasic nanotubular structure into the intricate scaffold formed by a six-fold interpenetrated framework is unprecedented. Another novel feature of the complex is the apparently clear distinction of the two emissive uranyl centres, raising the prospect of site-selective excitation given that only the interpenetrated polymers contain aromatic moieties possibly acting as antennae. More generally, this result is an example of the unusual supramolecular architectures which can be built through use of the peculiar coordination preferences of the uranyl cation, other fascinating cases ranging from cages to porous frameworks and quasicrystals having been reported lately.¹⁶

Acknowledgements

This work was supported by Iketani Science and Technology Foundation, and KAKENHI Grant-in-Aid for Early-Career Scientists JP22K14698 for S. Kusumoto, and Thammasat University Research Fund, Contract No. TUFF02/2564 for K. Chainok.

Conflicts of interest

There are no conflicts of interest to declare.

Notes and References

‡ Synthesis of $\text{L} \cdot \text{LH}_2(\text{PF}_6)_2$ was prepared by slight modifications of the method reported in the literature.¹⁷ 1,4-Bis(bromomethyl)benzene (2.6 g, 10 mmol) and ethyl isonicotinate (3.3 g, 22 mmol) were dissolved in acetonitrile (50 mL) and heated under reflux for 48 h, then cooled to room temperature. The solid was filtered and washed with acetonitrile, then dissolved in 5% HCl (50 mL) and refluxed for 5 h. The white product formed was filtered and washed with a small amount of cold water, then dissolved in a minimum amount of water before adding NH_4PF_6 until no further precipitate was formed. The resulting white precipitate was filtered and recrystallized three times before being filtered again, washed with a small amount of cold water, and dried under vacuum. Yield, 48%. ^1H NMR (400 MHz) in D_2O : δ 8.94 (d, 4H), 8.31 (d, 4H), 7.46 (s, 4H), 5.81 (s, 4H) (Fig. S1†).

Synthesis of complex **1**. $\text{LH}_2(\text{PF}_6)_2$ (26 mg, 0.04 mmol), H_3tca (9 mg, 0.05 mmol), $[\text{UO}_2(\text{NO}_3)_2(\text{H}_2\text{O})_2] \cdot 4\text{H}_2\text{O}$ (25 mg, 0.05 mmol), N,N -dimethylacetamide (0.2 mL), and demineralized water (0.7 mL) were placed in a 10 mL tightly closed glass vessel and heated at 140 °C under autogenous pressure in a sand bath, giving light yellow crystals of complex **1** within three days (19 mg, 68%). Anal. Calcd for $\text{C}_{64}\text{H}_{64}\text{N}_6\text{O}_{44}\text{U}_5$: C, 27.34; H, 2.29; N, 2.99. Found: C, 27.16; H, 2.38; N, 3.04%.

§ The data were collected at 100(2) K on a Bruker D8 Quest diffractometer using an Incoatec Microfocus Source ($\lambda = 3.0$ Mo) and a PHOTON III area detector, and operated with APEX3.¹⁸ The data were processed with SAINT,¹⁹ and empirical absorption corrections were made with SADABS.²⁰ The structure was solved by intrinsic phasing with SHELXT,²¹ and refined by full-matrix least-squares on F^2 with SHELXL,²² using the ShelXle interface.²³ The hydrogen atoms of the ammonium cations were found on a residual electron density map, displaced to the proper distance, then treated as riding atoms since they were somewhat unstable upon refinement. A restraint was applied on the displacement parameter of the nitrogen atom of one of the three independent ammonium cations, which is possibly slightly disordered. Drawings were made with ORTEP-3²⁴ and VESTA,²⁵ and the topological analysis with ToposPro.²⁶ Crystal data for **1**: $\text{C}_{64}\text{H}_{64}\text{N}_6\text{O}_{44}\text{U}_5$, $M = 2811.36$, tetragonal, space group $P4_2/n$, $a = 27.1130(9)$, $c = 10.1061(3)$ Å, $V = 7429.1(5)$ Å³, $Z = 4$. Refinement of 544 parameters on 7056 independent reflections out of 107845 measured reflections ($R_{\text{int}} = 0.061$) led to $R1 = 0.026$, $wR2 = 0.059$, $\Delta\rho_{\text{min}} = -1.46$, $\Delta\rho_{\text{max}} = 1.09$ e Å⁻³.

- (a) L. Mei, Z. N. Xie, K. Q. Hu, L. Y. Yuan, Z. Q. Gao, Z. F. Chai and W. Q. Shi, *Chem. Eur. J.*, 2017, **23**, 13995; (b) S. Wu, L. Mei, K. Q. Hu, Z. F. Chai, C. M. Nie and W. Q. Shi, *J. Inorg. Mater.*, 2020, **35**, 243.
- (a) P. Thuéry and J. Harrowfield, *CrystEngComm*, 2021, **23**, 7305; (b) P. Thuéry and J. Harrowfield, *Inorg. Chem.*, 2022, **61**, 9725; (c) S. Kusumoto, Y. Atoini, S. Masuda, J. Y. Kim, S. Hayami, Y. Kim, J. Harrowfield and P. Thuéry, *Inorg. Chem.*, 2022, **61**, 15182; (d) S. Kusumoto, Y. Atoini, S. Masuda, Y. Koide, J. Y. Kim, S. Hayami, Y. Kim, J. Harrowfield and P.

- Thuéry, *Inorg. Chem.*, 2023, **62**, 3929; (e) S. Kusumoto, Y. Atoini, S. Masuda, Y. Koide, K. Chainok, Y. Kim, J. Harrowfield and P. Thuéry, *Inorg. Chem.*, 2023, **62**, 7803; (f) L. Baklouti and J. Harrowfield, *Dalton Trans.*, 2023, **52**, 7772.
- 3 (a) M. B. Andrews and C. L. Cahill, *Chem. Rev.*, 2013, **113**, 1121; (b) T. Loiseau, I. Mihalcea, N. Henry and C. Volkringer, *Coord. Chem. Rev.*, 2014, **266–267**, 69; (c) J. Su and J. S. Chen, *Struct. Bond.*, 2015, **163**, 265; (d) P. Thuéry and J. Harrowfield, *Dalton Trans.*, 2017, **46**, 13660; (e) K. Lv, S. Fichter, M. Gu, J. März and M. Schmidt, *Coord. Chem. Rev.*, 2021, **446**, 214011.
- 4 X. M. Chen and T. C. W. Mak, *J. Cryst. Spectr. Res.*, 1993, **23**, 291.
- 5 (a) P. Thuéry and J. Harrowfield, *Eur. J. Inorg. Chem.*, 2022, e202200011; (b) S. Kusumoto, Y. Atoini, S. Masuda, Y. Koide, J. Y. Kim, S. Hayami, Y. Kim, J. Harrowfield and P. Thuéry, *CrystEngComm*, 2022, **24**, 7833.
- 6 (a) Y. R. Zheng, Z. Zhao, M. Wang, K. Ghosh, J. B. Pollock, T. R. Cook and P. J. Stang, *J. Am. Chem. Soc.*, 2010, **132**, 16873; (b) M. L. Saha, S. Neogi and M. Schmittel, *Dalton Trans.*, 2014, **43**, 3815; (c) H. Furukawa, U. Müller and O. M. Yaghi, *Angew. Chem. Int. Ed.*, 2015, **54**, 3417; (d) W. M. Bloch and G. H. Clever, *Chem. Commun.*, 2017, **53**, 8506; (e) S. Pullen and G. H. Clever, *Acc. Chem. Res.*, 2018, **51**, 3052; (f) M. Viciano-Chumillas, X. Liu, A. Leyva-Pérez, D. Armentano, J. Ferrando-Soria and E. Pardo, *Coord. Chem. Rev.*, 2022, **451**, 214273.
- 7 (a) P. Thuéry, *Chem. Commun.*, 2006, 853; (b) P. Thuéry and J. Harrowfield, *Cryst. Growth Des.*, 2017, **17**, 963; (c) P. Thuéry and J. Harrowfield, *Eur. J. Inorg. Chem.*, 2018, 1016; (d) P. Thuéry, Y. Atoini and J. Harrowfield, *Inorg. Chem.*, 2020, **59**, 6953.
- 8 V. A. Blatov, L. Carlucci, G. Ciani and D. M. Proserpio, *CrystEngComm*, 2004, **6**, 377.
- 9 P. Thuéry and J. Harrowfield, *Cryst. Growth Des.*, 2020, **20**, 262.
- 10 X. Hou and S. F. Tang, *Inorg. Chem.*, 2020, **59**, 15824.
- 11 L. Carlucci, G. Ciani and D. M. Proserpio, *Chem. Commun.*, 2004, 380.
- 12 (a) A. Brachmann, G. Geipel, G. Bernhard and H. Nitsche, *Radiochim. Acta*, 2002, **90**, 147; (b) M. Demnitz, S. Hilpmann, H. Lösch, F. Bok, R. Steudtner, M. Patzschke, T. Stumpf and N. Huittinen, *Dalton Trans.*, 2020, **49**, 7109.
- 13 P. Thuéry and J. Harrowfield, *Inorg. Chem.*, 2017, **56**, 13464.
- 14 (a) M. P. Redmond, S. M. Cornet, S. D. Woodall, D. Whittaker, D. Collison, M. Helliwell and L. S. Natrajan, *Dalton Trans.*, 2011, **40**, 3914; (b) L. S. Natrajan, *Coord. Chem. Rev.*, 2012, **256**, 1583.
- 15 (a) N. E. Brese and M. O’Keeffe, *Acta Crystallogr., Sect. B*, 1991, **47**, 192; (b) A. L. Spek, *Acta Crystallogr., Sect. D*, 2009, **65**, 148.
- 16 (a) P. C. Burns and M. Nyman, *Dalton Trans.*, 2018, **47**, 5916; (b) P. Li, N. A. Vermeulen, C. D. Malliakas, D. A. Gómez-Gualdrón, A. J. Howarth, B. L. Mehdi, A. Dohnalkova, N. D. Browning, M. O’Keeffe and O. K. Farha, *Science*, 2017, **356**, 624; (c) V. Smetana, S. P. Kelley, A. V. Mudring and R. D. Rogers, *Sci. Adv.*, 2020, **6**, eaay7685; (d) J. C. Wu, E. C. Escudero-Adán, M. Martínez-Belmonte and J. de Mendoza, *Front. Chem.*, 2023, **11**, 1163178.
- 17 F. Huang, C. Slobodnick, E. J. Mahan and H. W. Gibson, *Tetrahedron*, 2007, **63**, 2875.
- 18 APEX3, ver. 2019.1-0; Bruker AXS: Madison, WI, 2019.
- 19 SAINT, ver. 8.40A; Bruker Nano: Madison, WI, 2019.
- 20 SADABS, ver. 2016/2; Bruker AXS: Madison, WI, 2016.
- 21 G. M. Sheldrick, *Acta Crystallogr., Sect. A*, 2015, **71**, 3.
- 22 G. M. Sheldrick, *Acta Crystallogr., Sect. C*, 2015, **71**, 3.
- 23 C. B. Hübschle, G. M. Sheldrick and B. Dittrich, *J. Appl. Crystallogr.*, 2011, **44**, 1281.
- 24 (a) M. N. Burnett and C. K. Johnson, *ORTEPIII*, Report ORNL-6895; Oak Ridge National Laboratory: TN, 1996; (b) L. J. Farrugia, *J. Appl. Crystallogr.*, 2012, **45**, 849.
- 25 K. Momma and F. Izumi, *J. Appl. Crystallogr.*, 2011, **44**, 1272.
- 26 V. A. Blatov, A. P. Shevchenko and D. M. Proserpio, *Cryst. Growth Des.*, 2014, **14**, 3576.

Table of Contents:

Anionic uranyl tricarballylate nanotubules are included within the cationic, six-fold interpenetrated framework formed by uranyl with a zwitterionic dicarboxylate ligand.

