



**HAL**  
open science

## Superconductivity in null-scattering Ti:Zr alloy

S. Klotz, D. Hrabovski, E. Lelièvre-Berna, B. Baptiste

► **To cite this version:**

S. Klotz, D. Hrabovski, E. Lelièvre-Berna, B. Baptiste. Superconductivity in null-scattering Ti:Zr alloy. *Journal of Neutron Research*, 2023, 25 (2), pp.61-64. 10.3233/JNR-230002. hal-04178167

**HAL Id: hal-04178167**

**<https://hal.science/hal-04178167>**

Submitted on 7 Aug 2023

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# 1 Superconductivity in null-scattering Ti:Zr 2 alloy

3 S. Klotz<sup>a,\*</sup>, D. Hrabovskí<sup>b</sup>, E. Lelièvre-Berna<sup>c</sup> and B. Baptiste<sup>a</sup>

4 <sup>a</sup>*Sorbonne Université, IMPMC, UMR 7590, 4 Place Jussieu, 75252 Paris, France*

5 *E-mail: [Stefan.Klotz@upmc.fr](mailto:Stefan.Klotz@upmc.fr)*

6 <sup>b</sup>*Sorbonne Université, MPBT Platform, 4 Place Jussieu, 75252 Paris, France*

7 <sup>c</sup>*Institut Laue Langevin, 71 Avenue des Martyrs, 38042 Grenoble, France*

8 *E-mails: [david.hrabovsky@sorbonne-universite.fr](mailto:david.hrabovsky@sorbonne-universite.fr), [lelievre@ill.eu](mailto:lelievre@ill.eu), [benoit.baptiste@sorbonne-universite.fr](mailto:benoit.baptiste@sorbonne-universite.fr)*

10 **Abstract.** Null-scattering Ti:Zr alloy ( $\text{Ti}_{67.6}\text{Zr}_{32.4}$ ) is widely used in neutron scattering for sample containers, pressure cells and  
11 gaskets since it does not produce contaminant Bragg reflections from the sample environment. Here we report  
12 superconductivity in this material with critical temperature  $T_c=1.4$  K, lower critical field  $H_{c1}\approx 100$  Oe and upper critical field  
13  $H_{c2}\approx 4500$  Oe. These properties are largely independent of the amount of a small quantity of ferromagnetic iron found in  
14 materials of all providers. Our findings bear on the use of Ti:Zr in neutron scattering experiments at applied field and low  
15 temperatures.

## 16 1. Introduction

17 Titanium and zirconium crystallize at 300 K both in a hexagonal close-packed structure and the two  
18 elements are fully miscible. In 1956, Sidhu et al. [1] have found that the negative and positive scattering  
19 amplitudes of Ti and Zr could be exploited to cancel the coherent scattering length of a Ti:Zr alloy  
20 containing 62 atomic% of Ti and 38 atomic% of Zr. From scattering lengths published in 1992 [2], with  
21 52.2 mass% Ti and 47.8 mass% Zr; i.e., 67.6 mole% Ti and 32.4 mole% Zr,  $\text{Ti}_{67.6}\text{Zr}_{32.4}$  is “null  
22 scattering”, i.e., does not produce Bragg reflections in a neutron diffraction (the term “null-scattering”  
23 is somewhat misleading since the material indeed scatters neutrons, but only incoherently, resulting in a  
24 diffuse “background” with a weak  $Q$ -dependence). This alloy has relatively high neutron transparency,  
25 good mechanical properties, and is easily machinable provided there is a continuous supply of coolant  
26 to prevent self-ignition [3]. For all these reasons it is widely used for sample containers, in particular  
27 those with thick walls such as high-pressure cells [4]. It is also extensively used as gasket materials in  
28 opposed-anvil pressure devices such as the Paris-Edinburgh cell [5], and is often simply referred to as  
29 “titanium-zirconium” (“Ti:Zr”) in the neutron community.

30 Whereas the mechanical properties of Ti:Zr have been investigated in much detail [5], both at high  
31 and low temperatures, its magnetic properties appear to be rather unknown. Both Ti and Zr are  
32 superconducting with critical temperatures of 0.49 K and 0.61 K, respectively, and it appears hence  
33 likely that Ti:Zr is superconducting as well. Indeed, it was demonstrated that the critical temperature of  
34 this alloy has a maximum of 1.5 K at approximately equimolar composition [6]. But so far, no further  
35 details have been published, for example values of the critical fields are unknown. More specifically, no  
36 data on the null-scattering alloy Ti:Zr are known at all, as far as we are aware of.

---

\*Corresponding author. E-mail: [Stefan.Klotz@upmc.fr](mailto:Stefan.Klotz@upmc.fr)

1 Here we present magnetization measurements on Ti:Zr showing that it is superconducting and giving  
2 properties such as lower and upper critical fields and the influence of minor amount of iron in ingots of  
3 different producers. These result bear on the use of null-scattering Ti:Zr for sample containers in  
4 neutron scattering experiments under applied field.

## 5 2. Experimental details

6 Magnetization measurements were carried out on five different samples from at least two different  
7 providers. The first sample was cut off from a bar of 30 mm diameter provided to the ILL in 1988. The  
8 producer is believed to be UGITEC (Ugine, France). The second sample was cut-off a toroidal gasket  
9 made for use in a Paris-Edinburgh cell. The producer is either IMI Titanium Ltd. (Birmingham, U.K.)  
10 or TIMET (Henderson, USA). The three other sample are all from the TIMET Henderson Technical  
11 Laboratory, an entity working with the UGITEC research center. They were cut-off from 3 different  
12 billets of ~20 cm (8 inch) diameter purchased in 2010 and 2019. A significant difference in these  
13 samples is the amount of a small ferromagnetic component as revealed by magnetization measurements  
14 at 300 K. X-ray fluorescence measurements using a Mo-source ( $\lambda = 0.71 \text{ \AA}$ ) show that it is iron, and,  
15 based on the magnetization signal, correspond to 85 ppm in sample 1, 25 ppm in sample 2, and less than  
16 3 ppm in the three samples from TIMET. The superconducting properties appear to be largely  
17 independent of this small ferromagnetic impurity, as discussed further below. We therefore show in the  
18 following only magnetization data of one of the 3 TIMET samples. Chemical analysis by ICP mass  
19 spectroscopy of the provider quotes a Zr content between 45.065 mass% and 45.96 mass% (depending  
20 on the billet) but remarks that the accuracy in this number is uncertain because the analysis was run for  
21 a Ti matrix and not reliable for high Zr concentrations. From the sponge weights, the Zr content was of  
22 47.58 mass%. As for the minor impurities, the quoted values are 0.116-0.129 mass% for oxygen (0.10-  
23 0.14 mass% requested for getting high tensile strength), 0.002-0.005 mass% for nitrogen (<0.01 mass%  
24 requested), 0.005-0.007 mass% for carbon and less than 50 ppm for hafnium (<0.005 mass% requested).

25 The magnetic measurements were performed with a SQUID-VSM magnetometer (Quantum Design,  
26 USA) with a  $^3\text{He}$  option. The sample with a mass of 308.4 mg ( $58.3 \text{ mm}^3$ ) had an ellipsoidal shape with  
27 approximately 8 mm high and a 3.3 mm width. It was mounted in a plastic straw and suspended on a  
28 sample rod in the cold gas above the  $^3\text{He}$  bath. At each measurement the sample scans through detection  
29 coils (over a length of 25 mm) and the measured signal is fitted to the theoretical response function for a  
30 small magnetic dipole from which the magnetization is determined.


## 31 3. Results and Discussion

32 Figure 1 shows susceptibility data as a function of temperature, at three different applied fields. In all  
33 cases onset of superconductivity is found at temperatures slightly above 1.4 K and full field expulsion  
34 (Meissner effect, susceptibility reaches -1 in SI system) is seen below 1 K. Figure 2 displays a full  
35 magnetization versus field cycle recorded at 0.42 K and starting at zero field. It is seen that Ti:Zr is a  
36 type-II superconductor with a lower critical field  $H_{c1}$  of approximately 100 Oe, i.e., 0.01 Tesla, if we  
37 define  $H_{c1}$  as the field where the  $M(H)$  relation starts to deviate from being linear. Above this field, in  
38 the Shubnikov phase, flux-lines enter the sample and reduce the magnetization. The upper critical field  
39 is approximately 4500 Oe (0.45 Tesla), above which the magnetization is zero and the sample is fully  
40 normal-conducting.

41 We have repeated the same measurements with samples from other providers, i.e., those with the  
42 higher ferromagnetic impurities (85 and 25 ppm, see above). The critical temperatures are found to be

1 exactly the same in both samples, but in the first specimen the lower and upper critical field are  
 2 significantly higher (i.e., approximately 300 Oe and 6000 Oe, respectively). This leads naturally to a  
 3 somewhat smaller field dependence of the susceptibility data as a function of temperature (Fig. 1).  
 4 Whilst this reflects most likely an increased flux-pinning, it may not be related to the ferromagnetic  
 5 impurity but rather on other factors, such as a different microstructure due to a different thermal or  
 6 mechanical treatment.

7 Apart from the academic value of our data related to superconductivity, these findings have some  
 8 practical importance for neutron scattering experiments which investigate materials under applied field  
 9 and using Ti:Zr as a sample container. Typical examples are chiral magnets like MnSi where skyrmions  
 10 and spirals are investigated with polarized beams under hydrostatic pressure [7-8]. An investigation of  
 11 the pressure dependence of such phases below 1.4 K would be seriously hampered if the pressure cell is  
 12 made of Ti:Zr, at least for applied field below 0.45 T.  
 13

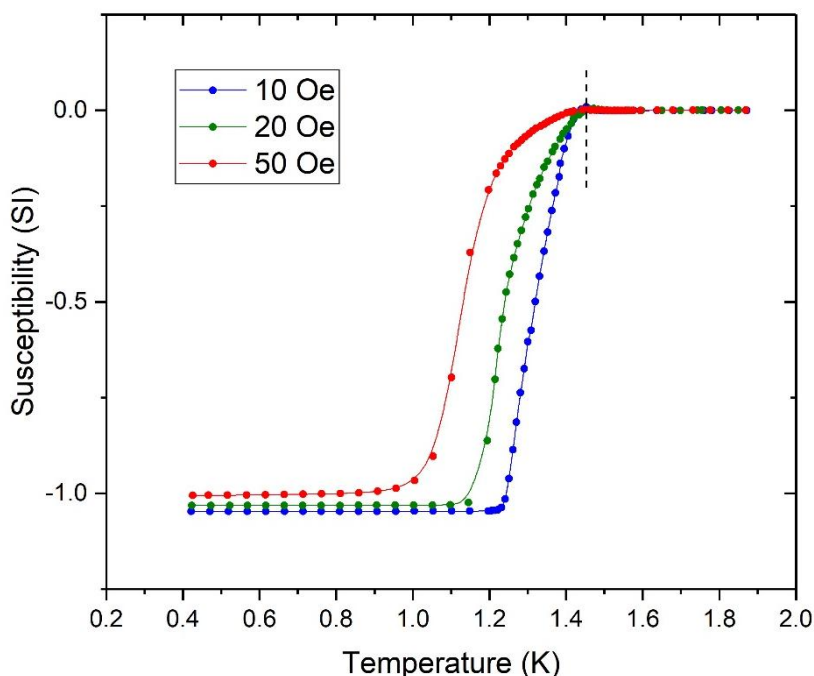

14  
 15  
 16 Figure 1: Meissner effect in Ti:Zr, at three different applied fields. Note that in SI units, a  
 17 susceptibility value of -1 corresponds to full field expulsion.  
 18  
 19

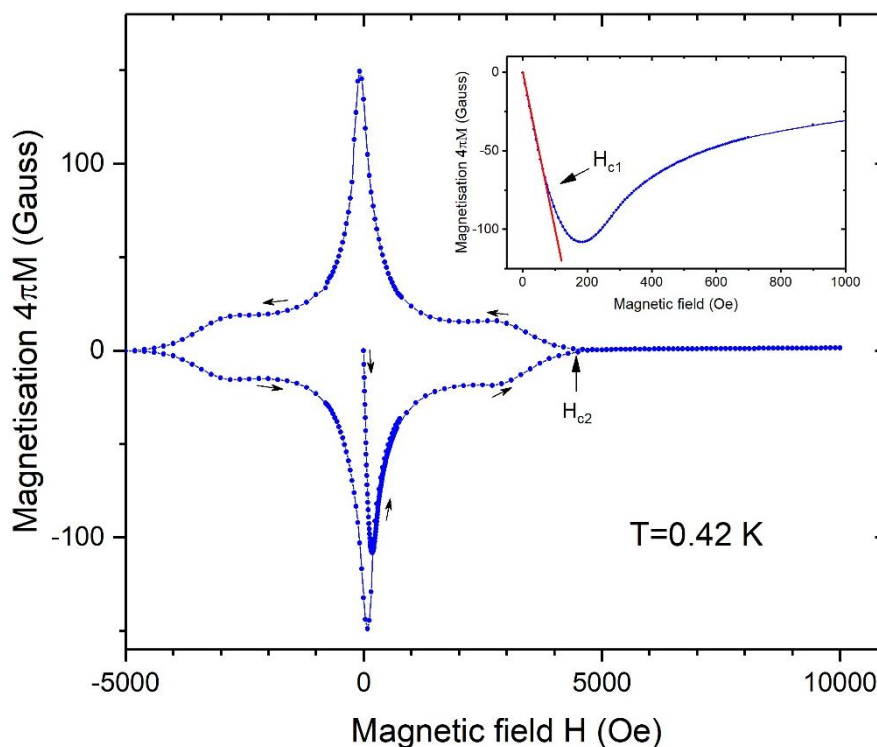


Figure 2: Magnetization  $M$  versus field  $H$  at 0.42 K, over a full  $M$ - $H$  cycle. The inset shows an enlarged view of the low-field region. The red line corresponds to a susceptibility  $\chi=4\pi M/H = -1$  (in SI units), i.e., full field expulsion. Lower and upper critical fields  $H_{c1}$  and  $H_{c2}$  are indicated.

#### References

- [1] S.S. Sidhu, LeRoy Heaton, D.D. Zaubers, F.P. Campos, *J. Appl. Phys.* **27** (1956), 1040-1042; doi:[10.1063/1.1722538](https://doi.org/10.1063/1.1722538)
- [2] V. F. Sears, *Neutron News* **3** (1992) 26-37; doi:[10.1080/10448639208218770](https://doi.org/10.1080/10448639208218770)
- [3] <https://www.ill.eu/users/support-labs-infrastructure/sample-environment/equipment/high-pressures/tizr-null-matrix-alloy>
- [4] <https://www.ill.eu/users/support-labs-infrastructure/sample-environment/equipment/high-pressures>
- [5] S. Klotz: *Techniques in High Pressure Neutron Scattering*, CRC Press, Taylor and Francis, Boca Raton, 2013.
- [6] J.K. Hulm and R.D. Blaugher, *Phys. Rev.* **123** (1961), 1569-1580 doi:[10.1234/JN-2005-102-203](https://doi.org/10.1234/JN-2005-102-203).
- [7] L. J. Bannenberg, R. Sadykov, R. M. Dalglish et al., *Phys. Rev. B* **100** (2019) 054447; doi:[10.1103/PhysRevB.100.054447](https://doi.org/10.1103/PhysRevB.100.054447)
- [8] R. Sadykov, C. Pappas, L. J. Bannenberg et al., *J. Neutron Res.* **20** (2018) 25-23; doi:[10.3233/JNR-180056](https://doi.org/10.3233/JNR-180056)