



HAL
open science

Control of the colossal magnetoresistance by strain effect in Nd_{0.5}Ca_{0.5}MnO₃ thin films

E. Rauwel Buzin, W. Prellier, Ch H Simon, S. Mercone, B. Mercery, B. Raveau, J. Sebek, J. Hejtmanek

► **To cite this version:**

E. Rauwel Buzin, W. Prellier, Ch H Simon, S. Mercone, B. Mercery, et al.. Control of the colossal magnetoresistance by strain effect in Nd_{0.5}Ca_{0.5}MnO₃ thin films. Applied Physics Letters, 2001, 79 (5), pp.647 - 649. 10.1063/1.1390313 . hal-04183133

HAL Id: hal-04183133

<https://hal.science/hal-04183133v1>

Submitted on 18 Aug 2023

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Control of the colossal magnetoresistance by strain effect in Nd 0.5 Ca 0.5 MnO 3 thin films

E. Rauwel Buzin, W. Prellier, Ch. Simon, S. Mercone, B. Mercey, B. Raveau, J. Sebek, and J. Hejtmanek

Citation: [Applied Physics Letters](#) **79**, 647 (2001); doi: 10.1063/1.1390313

View online: <http://dx.doi.org/10.1063/1.1390313>

View Table of Contents: <http://scitation.aip.org/content/aip/journal/apl/79/5?ver=pdfcov>

Published by the [AIP Publishing](#)

Articles you may be interested in

[Stress deformations and structural quenching in charge-ordered Sm 0.5 Ca 0.5 MnO 3 thin films](#)

J. Appl. Phys. **98**, 093903 (2005); 10.1063/1.2126157

[Enhancement of magnetoresistance in the intermediate state of Pr 0.5 Sr 0.3 Ca 0.2 MnO 3](#)

J. Appl. Phys. **90**, 4874 (2001); 10.1063/1.1408263

[Strain-stabilized charge ordering and magnetorelaxor behaviors in Cr-doped Pr 0.5 Ca 0.5 MnO 3 epitaxial thin films](#)

Appl. Phys. Lett. **78**, 3505 (2001); 10.1063/1.1376146

[Time dependent effects and transport evidence for phase separation in La 0.5 Ca 0.5 MnO 3](#)

J. Appl. Phys. **87**, 5831 (2000); 10.1063/1.372537

[Nonlinear electrical conduction and broad band noise in the charge-ordered rare earth manganate Nd 0.5 Ca 0.5 MnO 3](#)

Appl. Phys. Lett. **75**, 3381 (1999); 10.1063/1.125358

The logo for AIP Chaos is displayed on a red background with a geometric pattern. The letters 'AIP' are in a large, white, sans-serif font, followed by a vertical bar and the word 'Chaos' in a smaller, white, sans-serif font.

AIP | Chaos

CALL FOR APPLICANTS

Seeking new Editor-in-Chief

Control of the colossal magnetoresistance by strain effect in $\text{Nd}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ thin films

E. Rauwel Buzin, W. Prellier,^{a)} Ch. Simon, S. Mercone, B. Mercey, and B. Raveau
Laboratoire CRISMAT, CNRS UMR 6508, Bd. du Maréchal Juin, 14050 Caen Cedex, France

J. Sebek and J. Hejtmanek
Institute of Physics, Na Slovance 2, 182 21 Praha 8, Czech Republic

(Received 22 March 2001; accepted for publication 5 June 2001)

Thin films of $\text{Nd}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ manganites with colossal magnetoresistance (CMR) properties have been synthesized by the pulsed-laser deposition technique on (100)-(SrTiO₃). The lattice parameters of these manganites and correlatively their CMR properties can be controlled by the substrate temperature T_S . The maximum CMR effect at 50 K, calculated as the ratio $\rho(H=0T)/\rho(H=7T)$ is 10^{11} for a deposition temperature of $T_S=680^\circ\text{C}$. Structural studies show that the $\text{Nd}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ film is single phase, [010]-oriented and has a pseudocubic symmetry of the perovskite subcell with $a=3.77\text{ \AA}$ at room temperature. We suggest that correlation between lattice parameters, CMR, and substrate temperature T_S result mainly from substrate-induced strains which can weaken the charge-ordered state at low temperature. © 2001 American Institute of Physics. [DOI: 10.1063/1.1390313]

Numerous investigations of the manganites $\text{Ln}_{1-x}\text{Ca}_x\text{MnO}_3$ (Ln=lanthanides) have been performed on bulk ceramics, showing that the colossal magnetoresistance (CMR) in these materials originates from a competition between metallic ferromagnetism (FM) and charge-ordered (CO) insulating antiferromagnetism (AFM).^{1,2} The magnetotransport properties of these compounds are sensitive to the sample nature, i.e., single crystal, ceramic, thin film; the studies of manganite thin films³⁻⁹ and their properties often being different from the bulk ceramics or single crystals.

The great potentiality of thin films for device applications ensures that their magnetotransport properties need to be investigated in detail in the future. In this respect, our recent studies of $\text{Pr}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ thin films^{8,9} have shown that the substrate-induced strains play a key role in the appearance of CMR by decreasing the stability of the charge-ordered (CO) state. Keeping in mind the key effect of the A-site cation size observed for bulk manganites,¹⁰ it is of great interest to extend previous studies to $\text{Nd}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ (NCMO) thin films despite the unreasonably large magnetic field (>20 T) reported to melt the AFM charge ordered state below 200 K in bulk samples.¹¹ Moreover no direct confirmation of a complete conversion to FM metallic state was claimed.

In this letter, we show that $\text{Nd}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ thin films, grown on SrTiO₃ by pulsed laser deposition (PLD), exhibit spectacular CMR effect at 7 T, involving an insulator-to-metal transition around 100 K. We demonstrate that the perovskite subcell at room temperature (RT) varies with the temperature of the substrate during deposition, and correlatively, the CMR effect is controlled by the growth conditions. The correlations between CMR and lattice parameters are interpreted in terms of strain effects due to the substrate and oxygen nonstoichiometry.

Dense targets of $\text{Nd}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ were synthesized via the standard ceramic methods. The PLD apparatus has been described in detail elsewhere.^{8,9} 1200 Å thick films were deposited on (100)-SrTiO₃ (STO) substrates heated during deposition at constant temperatures ranging from 590 to 770 °C under an oxygen pressure of about 300 mTorr. Details of the growth parameters will be discussed. Structural characterizations were done using an x-ray diffraction (XRD) facility (Seifert 3000 P for $\Theta-2\Theta$ and Philips X'Pert MRD for in-plane measurements, Cu $K\alpha$ with $\lambda=1.5406\text{ \AA}$). Resistivity (ρ) of NCMO films was measured with a PPMS Quantum Design as a function of magnetic field (H) and temperature (T) using four-probe contact. The energy dispersive spectroscopy analyses have shown that the cationic composition of the film is homogeneous and remains very close to the nominal one " $\text{Nd}_{0.5\pm 0.02}\text{Ca}_{0.5\pm 0.02}\text{MnO}_x$ " within experimental error.

In order to obtain simultaneously good crystallization and full oxidized films, we have performed the synthesis under 400 mTorr of O₂ since the preparation of manganites with high Mn valency usually require a high oxygen pressure, or a postannealed treatment.¹² The best results concerning CMR were obtained for a substrate temperature (T_S) of 680 °C and, consequently, the following study was focused on this sample. The corresponding XRD patterns confirm a single phase (Fig. 1) with an out-of-plane parameter multiple of a_C (where a_C refers to the ideal cubic parameter 3.9 Å). The high intensity of the peak indicating a good crystallization for the film is independently confirmed by the full width at half maximum of the rocking-curve equal to 0.25° (not shown). The sharp peaks 90° separated in the Φ -scan of the NCMO film (see inset of Fig. 1) make evident the existence of a complete in-plane orientation of the film. For the sake of clarity the diffraction peak around $2\Theta=47^\circ$ (see Fig. 1) has been indexed in the perovskite cell as a (002)_C (where c refers to the cubic perovskite cell). In fact, the electron dif-

^{a)}Electronic mail: prellier@ismra.fr

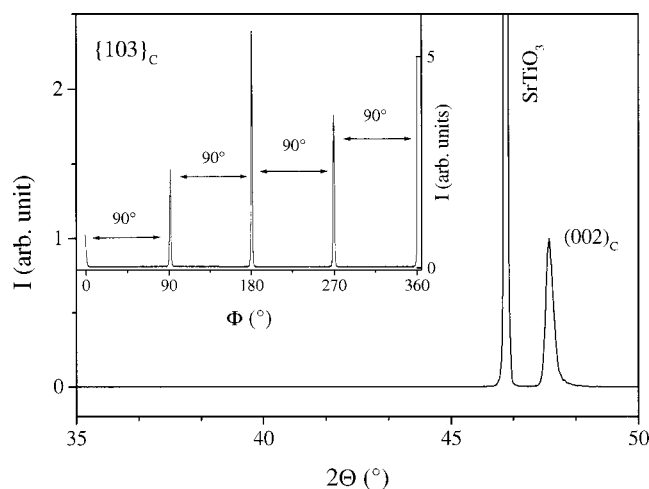


FIG. 1. Room temperature Θ - 2Θ XRD pattern in the range 35° - 50° of NCMO/STO. The inset depicts the Φ scan recorded around the $\{103\}_c$.

fraction study of selected NCMO films confirmed that they are single phase. We have found that they are $[010]$ -oriented referring to the $Pnma$ space group¹³ as previously reported for $\text{Pr}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ thin films grown on (100) - SrTiO_3 substrates.⁸ The details of the transmission electron microscopy study are currently undertaken and will be published elsewhere. The in-plane parameter has been evaluated by considering the $(103)_c$ reflection. It is remarkable that the parameters of the perovskite subcell are very close to each other, i.e., 3.775 and 3.765 Å for the in-plane and out of plane parameters, respectively. This indicates a pseudocubic symmetry which is similar to the bulk $\text{Nd}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$, but the latter exhibits significantly larger cell parameters at RT ($a/\sqrt{2}=3.821$, $b/2=3.797$, and $c/\sqrt{2}=3.805$ Å¹³) but more importantly we emphasize the substantial variation of RT lattice parameters with the deposition temperature T_S , in the range 620 - 780°C [Fig. 2(a)]. Indeed for T_S ranging from 620° to 680°C the symmetry remains pseudocubic and the cell parameters decrease almost linearly with increasing T_S . Contrary to that for $T_S > 680^\circ\text{C}$, a sudden distortion of the perovskite subcell appears, the in-plane and out of plane parameters being very different, and further increase with T_S . From these observations we deduce that the strains induced by the substrate are not the only factor which governs the crystallographic nature of the film and we presume that the oxygen stoichiometry of NCMO thin film varies with the deposition temperature. This general statement is reinforced by the evolution of the cell volume versus T_S [Fig. 2(a)] when below 680°C the volume decrease likely suggests an oxygen uptake with increasing T_S due to increasing Mn valency (Mn^{4+} for Mn^{3+} substitution), whereas above 680°C the volume increase can be explained by an oxygen departure, i.e., Mn^{3+} for Mn^{4+} substitution.

Keeping in mind that the substrate-induced strains may crucially affect the temperature and stability of phase transitions, we may expect that the CMR properties of films will depend upon the crystallographic nature of the RT form and, consequently, upon the deposition temperature T_S . We have focused our study on the best crystallized films deposited under 400 mTorr of O_2 in the temperature range of 620 - 680°C (below 620°C , the crystallization of the film is poor). As stated above, the best result was observed for the film

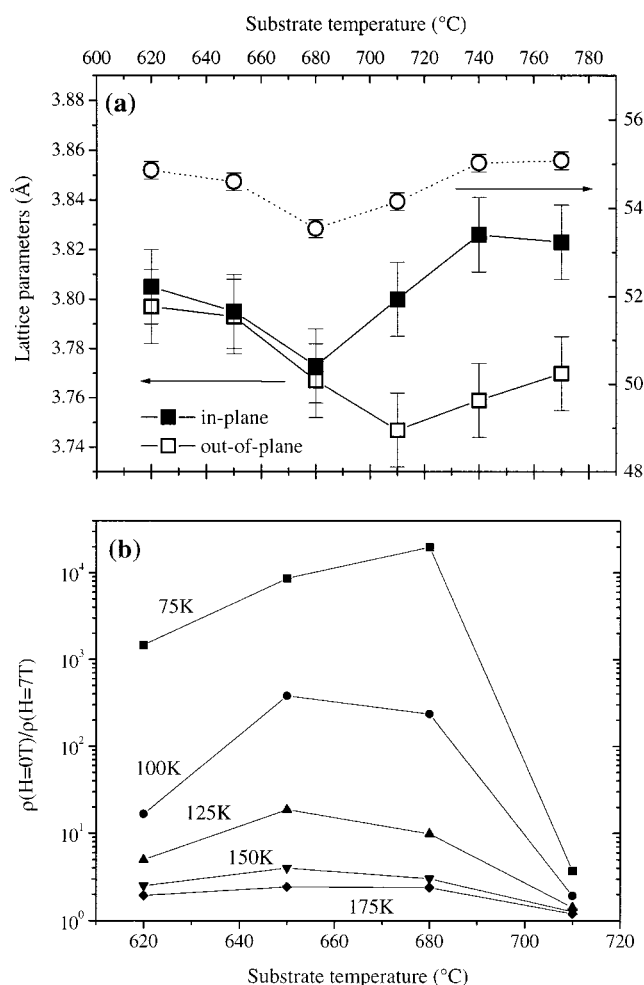


FIG. 2. (a) Evolution of the lattice parameters and the volume of the cell vs deposition temperature for films grown under 400 mTorr of O_2 . (b) CMR effect calculated as $\rho(H=0)/\rho(H=7\text{T})$ vs the deposition temperature.

grown at 680°C . The $\rho(T)$ curves registered in the absence of magnetic field and at 7 T are shown in Fig. 3(a) first order insulator-to-metal transitions, characterized by a hysteretic resistivity jump of several orders of magnitude [see also $\rho(H)$ in Fig. 3(a)]. Such a sharp transition has never been detected before in thin films. In context to the metallic ground state at low temperatures, let us underline the very low value of residual resistivity ($\sim 30 \mu\Omega\text{cm}$) which independently confirms both the high quality of the film and the complete transformation to FM metallic phase.

Thus, based on resistivity measurements we deduce a phase diagram [see Fig. 3(b)]. Using the hysteresis cycles in the field ramping up (H_C^+) and ramping down (H_C^-), we define the thermodynamic field (H_C) as the average of (H_C^+) and (H_C^-). In Fig. 3(b) H_C shows a monotonous increase with temperature when $T < 150\text{K}$. H_C is estimated to be 3 T at 25 K, which is 6-7 times lower than the 25 T found in the bulk material with the same chemical composition.¹¹ In fact, our phase diagram of 680°C deposited NCMO film is very different from the bulk where the magnetic field required to melt the charge ordered state is much higher at each temperature.¹¹

The second important point of the letter concerns the influence of the deposition temperature T_S of NCMO films up on the CMR effect. The evolution of the resistance ratio

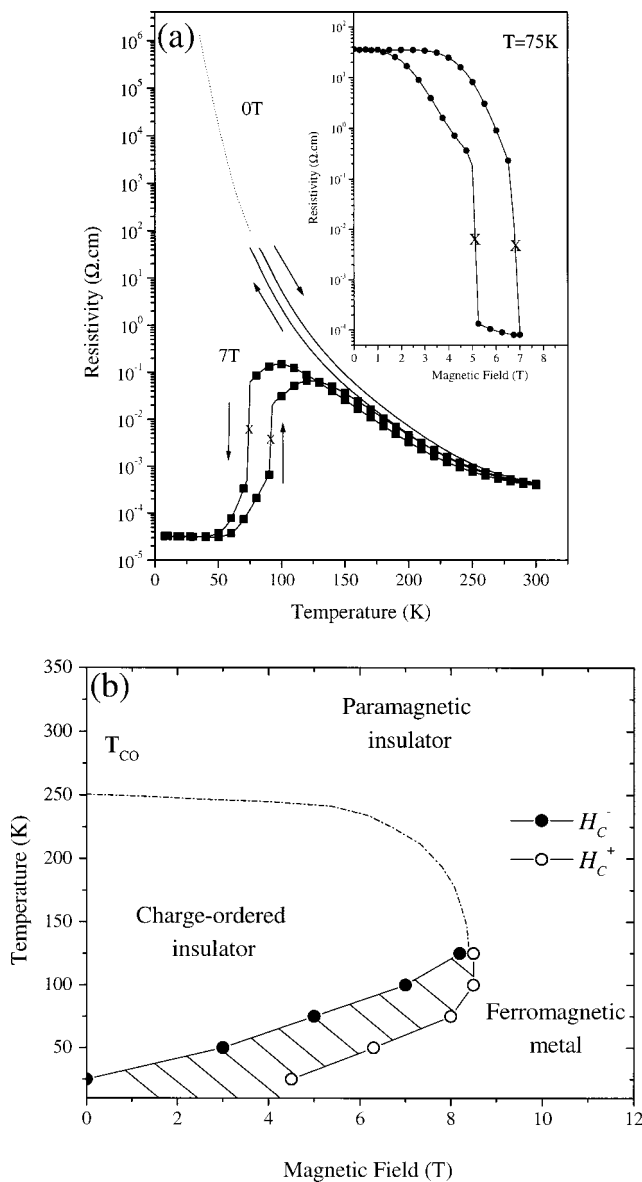


FIG. 3. (a) $\rho(T)$ under different applied magnetic fields for an optimized film ($T_S=680^\circ\text{C}$). The inset shows the $\rho(H)$ at 75 K. Note the sharp transition and the CMR effect of 11 orders of magnitude at 7 T. Field is applied parallel to the substrate plane. The arrows indicate the increase and the decrease in T . (b) Corresponding $T-H$ phase diagram. The dashed area indicates the hysteresis region where CO and FM phases coexist.

$RR = \rho(H=0\text{ T})/\rho(H=7\text{ T})$ vs T_S [Fig. 2(b)] shows that the RR increase as T_S increases up to $T_S=680^\circ\text{C}$ and suddenly decreases for $T_S>680^\circ\text{C}$. It is straightforward to correlate this evolution to the lattice parameters:

(i) the CMR effect increases in the pseudocubic region as the lattice parameters at room temperature decrease reaching a maximum value of 10^4 for a minimum average lattice parameter of 3.77 \AA (corresponding to $T_S=680^\circ\text{C}$).

(ii) then it drops abruptly in the distorted lattice region as the parameters increase. Similar evolutions are observed for RR measured at $T=100$ and 125 K , while the maximum RR value rapidly decreases, as one approaches T_{CO} ($T_{CO}=250\text{ K}$).

The dramatic influence of T_S upon both lattice parameters and CMR properties of $\text{Nd}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ thin films sug-

gests that two factors influence their properties, the oxygen stoichiometry and the strains induced by the substrate. Concerning the influence of the oxygen stoichiometry, the study on bulk ceramics by Frontera *et al.*¹⁴ has shown, that an oxygen overstoichiometry in $\text{Nd}_{0.5}\text{Ca}_{0.5}\text{MnO}_{3+\delta}$ leads to a significant variation of the structural and magnetic properties, namely the formally excess oxygen δ induces the increase of ferromagnetic interactions at low temperatures. Nevertheless, the lattice and CMR effects encountered for our NCMO films are huge compared to the $\text{Nd}_{0.5}\text{Ca}_{0.5}\text{MnO}_{3+\delta}$ ceramics, so we do not suppose that oxygen nonstoichiometry is the only factor controlling the properties of our films. The second factor dealing with the strains induced by the substrate, previously observed for other CO manganites,^{8,9,15} has at least the same prominence since, as previously observed, the substrate-layer strain is susceptible, e.g., weakening the CO state, by blocking the variation of the in-plane lattice parameters with increasing temperature,⁹ thus favoring the CMR effect.

To conclude, high quality $\text{Nd}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ thin films, with exceptional CMR properties have been grown using pulsed laser deposition. The room temperature lattice parameters and their CMR properties of films are correlated and can be controlled by the deposition temperature T_S . We suggest that observed correlations between structural and transport properties in NCMO films result predominantly from substrate-induced strains which can destabilize the charge-ordered state.

One author (W. P.) thanks Dr. C. Frontera for helpful discussions.

- ¹ *Colossal Magnetoresistance Oxides*, edited by Y. Tokura (Gordon and Breach, London, 1999).
- ² *Colossal Magnetoresistance, Charge Ordering and Related Properties of Manganese Oxides*, edited by C. N. R. Rao and B. Raveau (World Scientific, Singapore, 1998).
- ³ T. Venkatesan, M. Rajeswari, Z.-W. Dong, S. B. Ogale, and R. Ramesh, *Philos. Trans. R. Soc. London* **356**, 1661 (1998).
- ⁴ R. Von Helmolt, J. Wecker, R. Holzapfel, L. Schultz, and K. Samwer, *Phys. Rev. Lett.* **71**, 2331 (1993).
- ⁵ H. L. Ju, C. Kwon, Q. Li, R. L. Greene, and T. Venkatesan, *Appl. Phys. Lett.* **65**, 2108 (1994).
- ⁶ S. Jin, T. H. Tiefel, M. McCormack, R. A. Fastnacht, R. Ramesh, and L. H. Chen, *Science* **264**, 413 (1994).
- ⁷ G. C. Xiong, Q. Li, H. L. Mao, S. N. Senapati, X. X. Xi, R. L. Greene, and T. Venkatesan, *Appl. Phys. Lett.* **66**, 1427 (1995).
- ⁸ W. Prellier, A. M. Haghiri-Gosnet, B. Mercey, Ph. Lecoq, M. Hervieu, and B. Raveau, *Appl. Phys. Lett.* **77**, 1023 (2000); W. Prellier, Ch. Simon, A. M. Haghiri-Gosnet, B. Mercey, and B. Raveau, *Phys. Rev. B* **62**, 16337 (2000).
- ⁹ A. M. Haghiri-Gosnet, M. Hervieu, Ch. Simon, B. Mercey, and B. Raveau, *J. Appl. Phys.* **88**, 3545 (2000).
- ¹⁰ A. Sundaresan, A. Maignan, and B. Raveau, *Phys. Rev. B* **56**, 5092 (1997); F. Millange, A. Maignan, V. Caignert, Ch. Simon, and B. Raveau, *Z. Phys. B: Condens. Matter* **101**, 169 (1996).
- ¹¹ M. Tokunaga, N. Miura, Y. Tomioka, and Y. Tokura, *Phys. Rev. B* **57**, 5259 (1998).
- ¹² W. Prellier, M. Rajeswari, T. Venkatesan, and R. L. Greene, *Appl. Phys. Lett.* **75**, 1446 (1999).
- ¹³ F. Millange, S. de Brion, and G. Chouteau, *Phys. Rev. B* **62**, 5619 (2000).
- ¹⁴ C. Frontera, J. G. Garcia-Munoz, A. Llobet, C. Ritter, J. A. Alonso, and J. Rodriguez-Carvajal, *Phys. Rev. B* **62**, 3002 (2000).
- ¹⁵ B. Mercey, M. Hervieu, W. Prellier, J. Wolfman, Ch. Simon, and B. Raveau, *Appl. Phys. Lett.* **78**, 3857 (2001).