



HAL
open science

Interaction between nanoparticles, membranes and proteins: A surface plasmon resonance study

Erenildo Ferreira de Macedo, Nivia Salles Santos, Lucca Silva Nascimento, Raphaël Mathey, Sophie Brenet, Matheus Sacilotto de Moura, Yanxia Hou, Dayane Batista Tada

► To cite this version:

Erenildo Ferreira de Macedo, Nivia Salles Santos, Lucca Silva Nascimento, Raphaël Mathey, Sophie Brenet, et al.. Interaction between nanoparticles, membranes and proteins: A surface plasmon resonance study. *International Journal of Molecular Sciences*, 2023, 24, pp.591. 10.3390/ijms24010591 . hal-04229980

HAL Id: hal-04229980

<https://hal.science/hal-04229980v1>

Submitted on 5 Oct 2023

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution 4.0 International License



1 Article

2 Interaction between Nanoparticles, Membranes and Proteins: A 3 Surface Plasmon Resonance Study

4 Erenildo Ferreira de Macedo ^{1,2}, Nivia Salles Santos ^{1,2}, Lucca Silva Nascimento ¹, Raphaël Mathey ², Sophie Brenet ²,
5 Matheus Sacilotto de Moura ¹, Yanxia Hou ² and Dayane Batista Tada ^{1*}

6 ¹ Laboratory of Nanomaterials and Nanotoxicology, Federal University of São Paulo (UNIFESP), Institute of
7 science and Technology, São Paulo, Brazil, e.macedo@unifesp.br

8 ² Univ. Grenoble Alpes, CEA, CNRS, IRIG-SYMMES, 38000 Grenoble, France, yanxia.hou-broutin@cea.fr

9 * Correspondence: d.tada@unifesp.com

10 **Abstract:** Regardless of the promising use of nanoparticles (NPs) in biomedical applications, sev-
11 eral toxic effects have increased the concerns about the safety of these nanomaterials. Although the
12 pathways for NPs toxicity are diverse and dependent upon many parameters such as the nature of
13 the nanoparticle and the biochemical environment, numerous studies have provided evidence that
14 direct contact between NPs and biomolecules or cell membranes leads to cell inactivation or dam-
15 age and may be a primary mechanism for cytotoxicity. In such a context, this work was focused on
16 the development of a fast and accurate method to characterize the interaction between NPs, pro-
17 teins and lipidic membranes by surface plasmon resonance imaging (SPRi) technique. The interac-
18 tion of gold NPs with mimetic membranes was evaluated by monitoring the variation of reflectiv-
19 ity after several consecutive gold NPs injections on the lipidic membranes prepared on the SPRi
20 biochip. The interaction on the membranes with varied lipidic composition was compared re-
21 garding the total surface concentration density of gold NPs adsorbed on them. Then, the interaction
22 of gold and silver NPs with blood proteins was analyzed regarding their kinetic profile of the as-
23 sociation/dissociation and dissociation constants (k_{off}). The surface concentration density on mem-
24 brane composed of 1-palmitoyl-2-oleoyl-glycero-3-phosphocholine and cholesterol
25 (POPC/cholesterol) was 2.5 times higher than the value found after the injections of gold NPs on
26 POPC only or with dimethyldioctadecylammonium (POPC/DDAB). Regarding the proteins, gold
27 NPs showed a preferential binding to fibrinogen resulting in a value of variation of reflectivity 8
28 times higher than the value found for the other proteins. Differently, silver NPs showed similar
29 interaction on all the tested proteins but with a variation of reflectivity on immunoglobulin G (IgG)
30 2 times higher than the value found for the other tested proteins.

Citation: Lastname, F.; Lastname, F. Title. *Int. J. Mol. Sci.* 2022, 23, x.
<https://doi.org/10.3390/xxxxx>

Academic Editor: Firstname
Lastname

Received: date

Accepted: date

Published: date

31 **Keywords:** nanoparticles; protein corona; membranes; surface plasmon resonance imaging ;
32 biomolecular) interactions, blood serum proteins, nanocomplex dissociation rate ; affinity.

33
34 **Publisher's Note:** MDPI stays
35 neutral with regard to jurisdictional
36 claims in published maps and
37 institutional affiliations.



38
39 **Copyright:** © 2022 by the authors.
40 Submitted for possible open access
41 publication under the terms and
42 conditions of the Creative Commons
43 Attribution (CC BY) license
44 (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Nanoparticles (NPs) of diverse sizes, shapes and compositions have been developed for increasing applications in materials and life sciences[1], [2]. Particularly in cancer therapy, NPs physico-chemical properties allow them to target cancer cells, enhancing the penetration and accumulation of drugs in tumor tissues and reducing the systemic effects of usual therapies[3]–[5].

When NPs are used in biomedical applications they are brought in direct contact with biological fluids, wherein they assume the biological identity, that can bring new features not predicted during development process of the NPs[4], [6], [7]. It has been continuously proven that once NPs assume their biological identity, they can provide unexpected therapeutic efficiency or toxicity. For this reason, a full characterization of

45 the interaction between NPs and the biological components is crucial to evaluate NPs
46 therapeutic efficiency as well as their potential toxicity[6], [8], [9].

47 In the last years, several research groups have focused their works on the under-
48 standing of the physicochemical changes that NPs go through into the biological medi-
49 um^{5,6} and how they interact with membranes and cells. The adsorption of NPs on cell
50 membrane or microbial cell wall and how they affect the integrity of these membranes
51 have been shown to depend on the cell type, NPs size, NPs surface properties and NPs
52 colloidal state[10]–[13]. For example, gold NPs smaller than 6 nm were shown to enter
53 the nucleus whereas larger NPs could only be found in the cytoplasm which could ex-
54 plain the increased cytotoxicity of ultrasmall gold NPs[14]. The interaction between
55 cells and NPs has been also used to promote cell differentiation on the surface of scaf-
56 folds or implants improving bioactivity and tissue regeneration[15], [16]. In the blood-
57 stream, there is a high content and wide diversity of proteins and immediately after the
58 contact of NPs with the bloodstream, a coating of these proteins is formed surrounding
59 the surface of the NPs. As a result, a protein corona is formed on NPs surface, whose
60 composition depends on the NPs size, surface chemistry and medium conditions[4], [6],
61 [7], [13], [17], [18]. Much evidence has been reported on the effects of protein corona on
62 the cell targeting, intracellular fate and cell uptake process[6], [7], [13], [19]. Protein co-
63 corona can affect NPs hydrophobic character or even activate an internalization process
64 triggered by a specific bio-interaction[20]–[24].

65 Due to the aforementioned reasons, the evaluation of the interaction of NPs with
66 membranes and proteins should be a mandatory step in the development process of a
67 NP. This investigation is crucial to predict and to understand NPs' behavior in the bio-
68 logical medium and therefore, it can help to guarantee their performance *in vivo*. The
69 analysis of biological interaction of NPs also finds application in the field of materials
70 science since it can allow to associate NPs physicochemical properties, the formation of
71 protein corona and the NPs effects on membranes. Through this type of analysis, it could
72 be possible to identify which NPs properties should be controlled in order to tune NPs'
73 behavior in the biological medium.

74 It is clear that NPs surface properties mediate protein corona formation and NPs
75 interaction with membranes. Therefore, it is an important aspect to be considered in the
76 design of NPs. Different surface coating of NP can be engineered to modulate the inter-
77 action with cell membrane, bringing the possibility to target a specific membrane
78 microdomain and even to drive the NPs through a specific mechanism of cell uptake.
79 Innovative NPs coating could also control the protein corona formation and composition.
80 Gorshkov et al.[25] reported that the binding of proteins on the surface of silver NPs
81 would be observed after an unfolding of a specific site in the protein. The main compo-
82 nents of protein corona of silver NPs were identified to be proteins with tendency to
83 prefer a higher amount of β -sheet formation, and hydrophobicity. The influence of sur-
84 face chemistry of NPs on the composition of protein corona was also evidenced by sev-
85 eral groups that also pointed out the effects of medium conditions. Eigenheer et al.
86 showed that at low ion concentration, electrostatic interactions are the driving forces that
87 defines protein corona formation[26]. In other works, the composition of protein corona
88 was shown to change as a result of different binding affinity of the proteins available in
89 the medium, which could provide a strategy to change protein corona composition by
90 host-guest interaction[27]–[29].

91 NPs interaction with membranes has been extensively characterized by computa-
92 tional simulation. Additionally, experimental techniques have been used to complement
93 the computational assays such as atomic force microscopy (AFM), differential scanning
94 calorimetry and giant vesicles coupled with optical microscopy. Nevertheless, current
95 computational tools do not allow modeling the complexity of the nanoparticle-cell
96 membrane interaction. For this reason the experimental approaches must be designed as
97 simple as possible in order to be modeled[30]–[34].

98 The composition of protein corona of gold NPs and silver NPs in contact with blood
99 serum⁸ or plasma has already been characterized by mass spectrometry, liquid chroma-
100 tography and SDS-PAGE. Most reported experimental methodologies were based on a
101 combination of different techniques to indirectly identify the composition of protein co-
102 rona. These approaches detected the proteins that were left in the medium after the in-
103 cubation with NPs followed by a centrifugation step. The proteins were also identified
104 after being washed from the precipitated NPs. Despite extensive information, these
105 methods are too complex and time-consuming to be considered as a routine step in the
106 development process of NPs. Besides, as adverted by some of the researchers, the accu-
107 racy of their approaches could be compromised by the limit of detection. Gorshkov et al.
108 for example, mentioned that the dynamic range limitation of the mass spectrometer
109 would exclude the observation of very low-abundance proteins from plasma and in this
110 case enrichment step would be mandatory[25]. In addition, the mentioned methods re-
111 quired several steps such as mixing of NPs with proteins and other media, followed by
112 steps of washing out the proteins. In particular, the washing out process could be another
113 factor compromising the experimental accuracy. An incomplete composition of protein
114 corona could be identified due to the incomplete washing out process, especially for the
115 strongly bound proteins. Furthermore, centrifugation steps are known to perturb colloi-
116 dal stability of NPs and, therefore, would induce NP-protein dissociation that would not
117 occur in the biological fluids.

118 Despite the wide applications of NPs in biomedical field, the biological interaction of
119 NPs is yet to be fully understood. To make the characterization of the biological interac-
120 tion of NPs as a regular step in the development of NPs it is necessary to develop a con-
121 venient analytical tool that could provide detailed and reliable information. Herein,
122 Surface Plasmon Resonance Imaging (SPRi) is presented to be a useful technique in the
123 study of interaction of gold and silver NPs with lipid membranes and proteins. In com-
124 parison with other available techniques (AFM, mass spectrometry, UV-Vis spectroscopy)
125 that has been used in similar investigations, SPRi can be faster, more accurate and able to
126 provide a wide range of information in real-time. In fact, SPR has already been explored
127 as a technique to evaluate the adsorption of NPs on proteins biochip or as complemen-
128 tary technique in the identification of protein corona[21], [25], [35], [36]. However, in
129 these studies, immobilized NPs were used and the proteins were injected on the modi-
130 fied biochip and therefore the colloidal state of the NPs suspension was compromised in
131 comparison with the use of the NPs suspension as it would be injected *in vivo*.


132 SPRi is a well-known technique used to monitor the interactions between biomole-
133 cules (e.g. proteins, DNA, RNA, peptides) in real time based on the variation of the re-
134 fractive index of a prism coated by a thin layer of metal (SPRi biochip)[37], [38]. Due to
135 the surface plasmon effect, under the incidence of a polarized light at a specific angle on
136 the interface between the biochip surface and a dielectric medium, the energy of the light
137 is almost entirely absorbed by the plasmonic band. Under this condition, an evanescent
138 wave is generated and the electromagnetic field of a surface plasmon polarization is
139 confined between the boundaries of the metal and the dielectric environment and its in-
140 tensity decreases exponentially between these two environments. Small disturbances
141 caused in this field by the adsorption of molecules on the biochip surface are detected as
142 changes in the refractive index.

143 In the methodology presented herein, lipid membranes and proteins were immobi-
144 lized on the SPRi biochip surface and the interaction with gold and silver NPs were
145 monitored in real time by injecting these NPs on the modified biochip surface. Proteins
146 from the blood serum and plasma were chosen since most applications of these NPs
147 predicts their intravenous administration. Phospholipid composition of mimetic mem-
148 branes was varied to evidence the versatility of the technique that allows to mimic lipid
149 membranes of different cell types, organelles, cell wall of microorganisms. Therefore,
150 considering that SPRi would allow the evaluation of several different NPs in a fast and
151 standardized way, it could become a convenient step in the design process of a NP de-

152 velopment for biomedical applications. The combination of the proteins and lipids to be
 153 immobilized on the biochip can be chosen according to the target cells and medium
 154 wherein the NPs will be used.

155 2. Results

156 In this study, the interaction of gold and silver NPs with lipid membranes and pro-
 157 teins from the blood serum and plasma was investigated. For this, two types of biochips
 158 were prepared for SPRi assays, as illustrated in Figure 1.

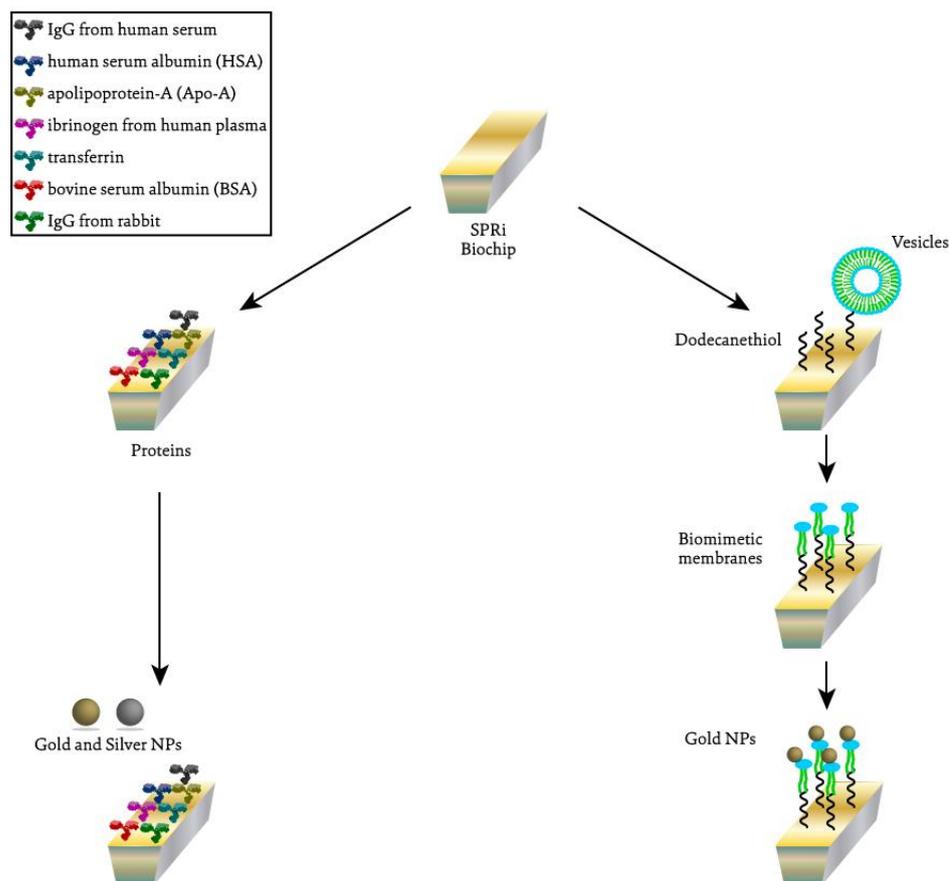


159
 160 **Figure 1.** Schematic representation of the different SPRi assays performed to evaluate the interac-
 161 tion between silver and gold NPs and proteins (on the left) and between gold NPs and lipidic
 162 membranes (on the right).

163 2.1. Gold NPs Interaction with Membrane

164 Three different lipid membranes composed of
 165 1-palmitoyl-2-oleoyl-glycero-3-phosphocholine only (POPC) or combined with choles-
 166 terol (POPC/Chol) or dimethyldioctadecylammonium (POPC/DDAB) were constructed
 167 on the SPRi biochip. These lipid compositions were chosen aiming to mimic biological
 168 membranes and cell membrane domains. POPC is the main component of cell membrane
 169 and bacteria cell wall. Chol is one of the main components of lipid-rafts, which is a type
 170 of cell membrane domain that also contains proteoglycans and forms a rigid structure
 171 that can flow throughout the cell membrane. Lipid-rafts has been associated with cell
 172 uptake mechanisms of NPs and therefore, preferential interaction of NPs with this do-
 173 main may indicate that the NP can internalize into the cells by this domain. The addition
 174 of DDAB was a strategy to evaluate the effect of positively charged lipids on the interac-
 175 tion with negatively charged NPs which could induce cell damage through its positive


176
177
178
179
180
181
182
183
184
185
186
187

moieties[39]. Successive injections of NPs at the same concentration were performed on each membrane to evaluate the NPs distribution on the membrane and the variation of reflectivity monitored in function of time (Figure 2). The changes observed after each injection of gold NPs on the three different membranes could be better evaluated by plotting the variation of reflectivity in function of the number of gold NPs injections (Figure 3). It was observed that the variation of reflectivity increased with the increasing number of NPs injections. For POPC/DDAB membrane, after the fifth injection, the reflectivity slightly changed with additional injections of NPs indicating the saturation of the membrane. When gold NPs were injected on the membrane composed of POPC/Chol or POPC, the variation of reflectivity did not reach a *plateau* and the reflectivity continued to change with the additional NPs injections, indicating that NPs continued to interact with the membrane even after the seventh injection (Figure 3).

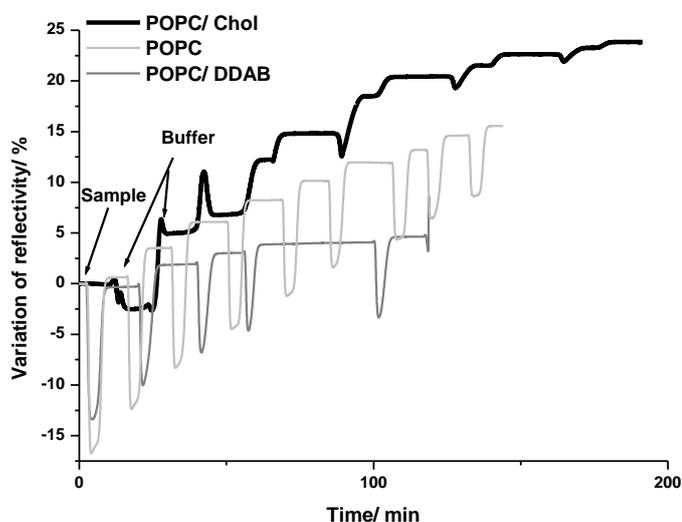

188
189
190

Figure 2. Average kinetic curves variation of reflectivity on the biochip after injections of gold NPs on POPC, POPC/DDAB and POPC/Chol membranes.

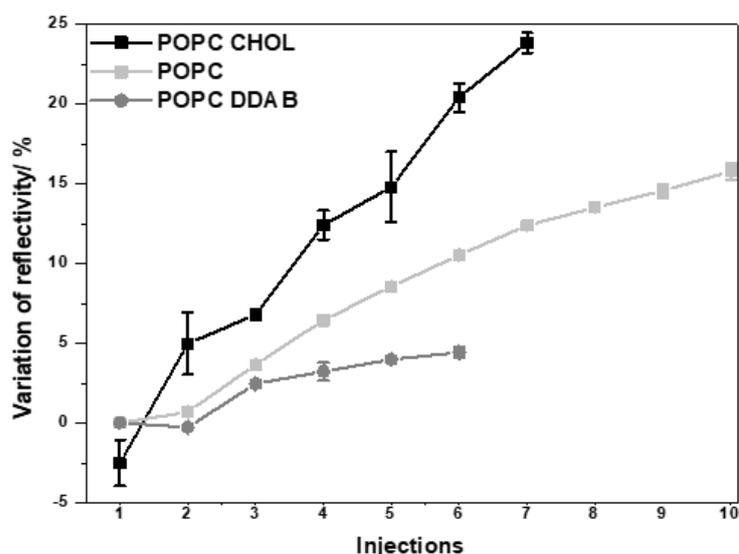


191

Figure 3. Variation of reflectivity in function of number of injections of gold NPs on POPC, POPC/DAB and PC/Chol membranes.

192 The different profiles of interaction of gold NPs could be a result of the different af-
193 finity of gold NPs with each type of membrane as well as because of the different struc-
194 turing of the membranes. The continuous adsorption of gold NPs on the POPC/Chol or
195 POPC membrane and the low adsorption of gold NPs on POPC/DDAB membrane was
196 evidenced in Figure 4. The surface concentration density of gold NPs adsorbed on
197 POPC/Chol membrane was of (9.0 ± 0.4) mg/mm² whereas the average value on the
198 POPC and POPC/DDAB membranes was of (4.0 ± 0.1) and (4.0 ± 0.3) mg/mm², respec-
199 tively.

200 The enhanced interaction between gold NPs and the POPC/Chol membrane could
201 be correlated with the results reported previously regarding the cell internalization pro-
202 cess of NPs. Cholesterol-rich domains in cellular membrane, called lipid-rafts have al-
203 ready been well characterized and mimicked *in vitro* by assays wherein giant vesicles
204 were used as membrane model [32], [33], [40], [41]. These domains have already been
205 identified as one of the main regions that promote NPs cellular internalization. Preferen-
206 tial adsorption of gold NPs on these domains could lead to the NPs accumulation in a
207 small portion of the membrane, promoting NPs agglomeration and/or aggregation.

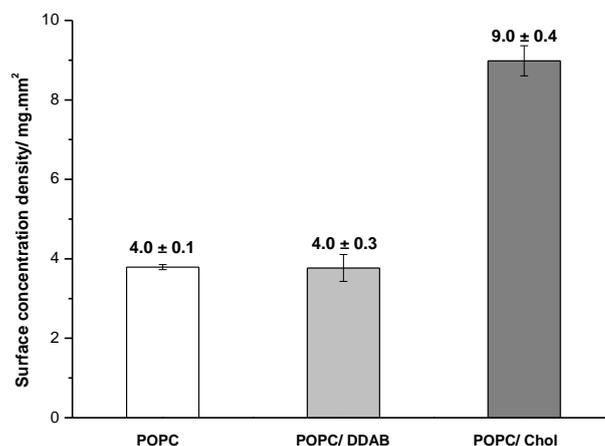

208
209 **Figure 4.** Surface concentration density of gold NPs adsorbed on the membrane of each composi-
210 tion after the SPRi assay was completed.

211 In addition to the quantitative analysis of the gold NPs adsorption on lipid mem-
212 branes of different composition, it was possible to infer how the adsorption process could
213 occur and if it could be expected the aggregation or agglomeration of NPs on each type of
214 membrane. Figure 5 describes our hypothesis on how the adsorption of gold NPs would
215 proceed on each type of membrane. The adsorption of gold NPs on membranes con-
216 taining POPC and POPC/DDAB could be a result of the electrostatic interaction between
217 the negatively charged NPs and positively charged membrane of POPC/DDAB or the
218 positive portion of POPC molecules. However, after the first injections of gold NPs on the
219 membrane, the membrane would be recovered by the NPs resulting in a negatively
220 charged surface, which hampers the continuous adsorption of gold NPs under the suc-
221 cessive injections and only low variation of reflectivity could be observed. The adsorp-
222 tion of gold NPs on POPC/Chol membrane took place on the domains containing cho-
223 lesterol rather than on the regions of POPC. The preferential and strong adsorption of
224 gold NPs in the cholesterol-rich domains, induces aggregation under successive injec-
225 tions of gold NPs on the membrane.

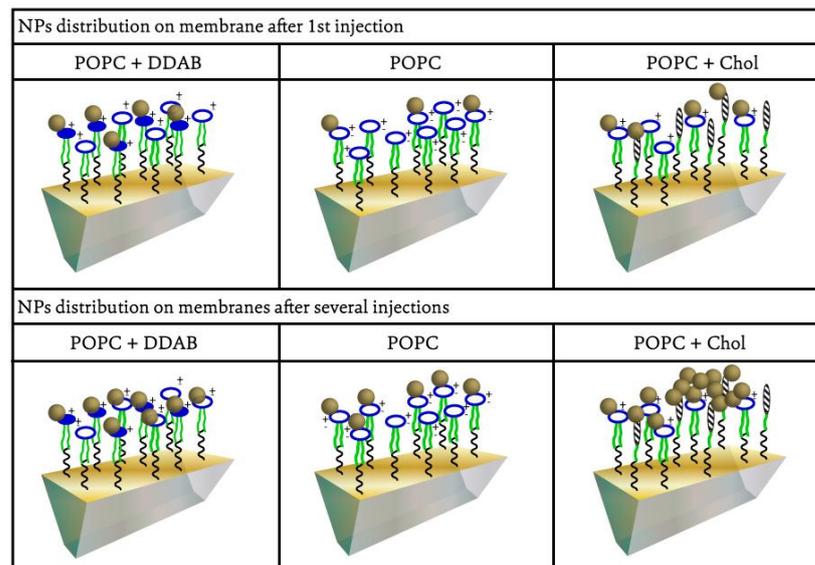


Figure 5. Schematic representation of the gold NPs adsorption on lipid membranes of different composition under successive injections on SPRi biochip.

Our hypothesis regarding the adsorption process of gold NPs on the membranes was supported by the differential images generated in the SPRi assay. Figure 6 depicts the images at the end of the SPRi assays, after the injection of gold NPs on POPC/DDAB, POPC and POPC/Chol membranes. The clearer areas indicated the regions where the adsorption took place. It was possible to note the homogenous adsorption on POPC/DDAB and POPC membranes whereas the image of POPC/Chol membrane pointed out different contrast trough the surface, which could be an indicative of NPs aggregation on the surface.

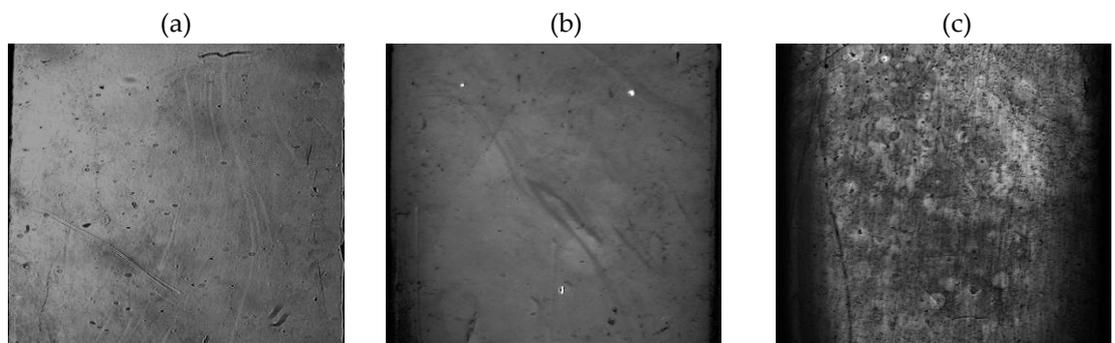


Figure 6 – Differential images of biochip surface after SPRi assays. (a) Gold NPs injected on POPC/DDAB membrane. (b) Gold NPs injected on POPC membrane. (c) Gold NPs injected on POPC/Chol membrane.

different interaction of NPs with membranes of different composition could lead to different cytotoxic and antimicrobial effects. Several groups have observed different toxicity of NPs in gram positive and gram-negative bacteria which they attributed to the different lipid composition of bacteria cell wall[41]–[45]. Herein, it is shown that by using SPRi, it could be possible to infer about the effects of a NP on membranes with varied lipid composition.

2.2. Interaction of NPs with Proteins

In this work, the interaction between gold and silver NPs and several proteins from blood serum was evaluated by SPRi. Even if the composition of protein corona of these NPs in different medium has already been reported, there is still a lack of information about the affinity of NPs to different proteins. The application of SPRi in the study of interaction between NPs and proteins provides information about the extension of the adsorption and also about the affinity between NPs and the proteins.

Herein, gold and silver NPs were injected on a biochip functionalized with 7 different proteins. The average kinetic curves of variation of the reflectivity in function of time after injection of gold NPs is presented in the Figure 7 for each kind of protein. As can be seen, the injection of gold NPs on proteins biochip resulted in different values of variation of reflectivity, depending on the identity of the protein. This result indicated that the extension of adsorption of gold NPs changed according to each blood protein immobilized on the biochip and therefore, it would be expected a different affinity of gold NPs to each protein.

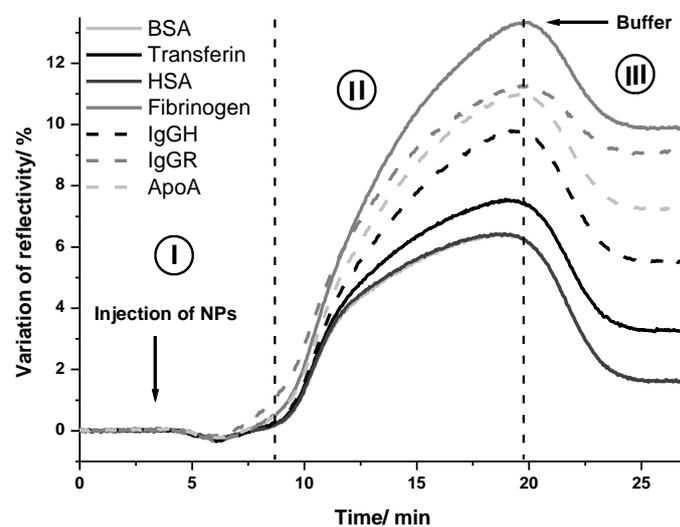


Figure 7. Kinetic curves of the interaction between gold NPs and proteins. Average of variation of reflectivity on protein spots under gold NPs injection in SPRi.

The same assay was repeated with silver NPs. The analysis of the kinetic curves allowed to infer about the affinity of each protein with gold and silver NPs. The proteins with high affinity should bind to NPs more strongly than the proteins with low affinity. Therefore, after the injection of NPs (step I; Figure 7), it was observed a variation of reflectivity when they bound to the proteins on the biochip surface (association phase shown in step II; Figure 7). Following, the reflectivity decreased due to the washing out process by the running buffer (dissociation phase shown in step III; Figure 7). Finally, it was observed a *plateau* that indicated the quantity of the bound NPs to the protein on the biochip.

The Figure 8 shows the average values and standard deviation of variation of reflectivity after the injection of gold (Figure 8a) and silver NPs (Figure 8b) on each kind of protein. These values were calculated by subtracting the initial value of reflectivity of the base line from the value of reflectivity after dissociation phase. The evaluation of the variation of reflectivity provides an insight about the extension of the adsorption of NPs on each type of protein. The higher the adsorption the higher the affinity between the protein and NPs.

It was possible to observe that among the tested blood serum proteins, fibrinogen, ApoA and IgG are the proteins that interact more with gold and silver NPs. In the assays

performed with gold NPs, the average value of variation of reflectivity was of $(10 \pm 1) \%$; $(9.2 \pm 0.5) \%$; $(7.3 \pm 0.5) \%$ and $(5.6 \pm 0.8) \%$ on the spots of fibrinogen, IgGR, ApoA and IgGH respectively, whereas on the spots of HSA and BSA the average values were 6-times lower $(1.6 \pm 0.3) \%$. The difference on the variation of reflectivity between the spots of IgGR and IgGH pointed out the higher affinity of gold NPs to the animal protein compared with the human protein.

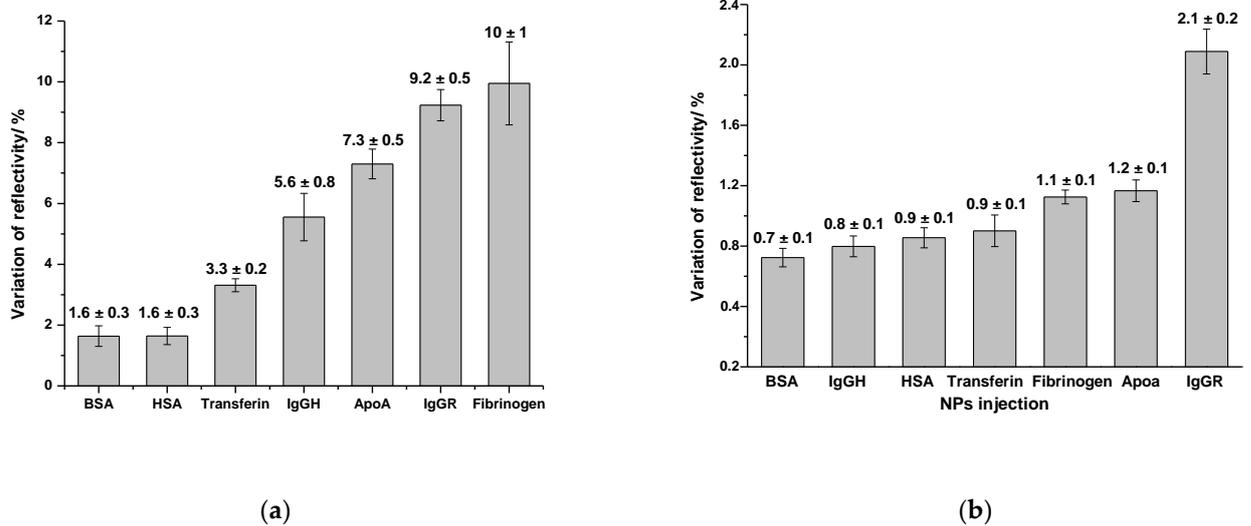


Figure 8. Average and standard deviation of the variation of reflectivity observed in the SPRi curves after the injection of gold NPs (a) and silver NPs (b) on the protein-functionalized biochip surface.

In the assays performed with silver NPs, the highest average value of variation of reflectivity was observed on IgGR spots, $(2.1 \pm 0.2) \%$ followed by ApoA $(1.7 \pm 0.1) \%$ and fibrinogen $(1.1 \pm 0.1) \%$. Differently from what was observed with gold NPs, the interaction of silver NPs did not show a high variation between the tested proteins. The interaction of silver NPs with the other proteins resulted in values of variation of reflectivity only slightly lower in range of 0.7 - 0.9 %.

In addition to the information regarding the composition of the NPs protein corona and the comparative evaluation of proteins adsorption on the NPs surface, the SPRi technique can also be applied to quantitatively evaluate the affinity between them. The kinetic curves obtained in the assays with gold and silver NPs were used to calculate the dissociation constant (k_{off}) after the interaction of NPs with proteins (see Supporting Information for detailed description of the calculus). The values are depicted in Table 1.

Table 1. Values of k_{off} calculated by using SPRi kinetics data of the interaction between AuNPs, AgNPs and proteins and values of K_{off} reported in the indicated references.

Protein	k_{off} (AuNPs)/s ⁻¹	k_{off} (AgNPs)/s ⁻¹	k_{off} (AuNPs)[25]
IgGR	$(1.10 \pm 0.02) \times 10^{-3}$	$(1.50 \pm 0.01) \times 10^{-3}$	$2.3 \times 10^{-3} \text{ s}^{-1}$
Fibrinogen	$(1.40 \pm 0.02) \times 10^{-3}$	$(1.60 \pm 0.01) \times 10^{-3}$	$2.0 \times 10^{-3} \text{ s}^{-1}$
ApoA	$(1.90 \pm 0.02) \times 10^{-3}$	$(1.40 \pm 0.01) \times 10^{-3}$	$1.6 \times 10^{-3} \text{ s}^{-1}$
IgGH	$(2.60 \pm 0.04) \times 10^{-3}$	$(1.40 \pm 0.01) \times 10^{-3}$	$2.3 \times 10^{-3} \text{ s}^{-1}$
Transferrin	$(3.60 \pm 0.05) \times 10^{-3} \text{ s}^{-1}$	$(1.50 \pm 0.01) \times 10^{-3}$	
HSA	$(5.50 \pm 0.01) \times 10^{-3} \text{ s}^{-1}$	$(1.60 \pm 0.01) \times 10^{-3}$	1.8×10^{-3}
BSA	$(5.50 \pm 0.01) \times 10^{-3} \text{ s}^{-1}$	$(1.30 \pm 0.01) \times 10^{-3}$	

The values of k_{off} reflected the same preferential interaction indicated by the values of variation of reflectivity. Since the k_{off} refers to the dissociation, the lower its value, the stronger the affinity between NPs and proteins. Therefore, the lowest values of k_{off}

amongst the interaction of gold NPs were observed with fibrinogen and IgGR ($k_{\text{off}} = 1.1 \times 10^{-3} \text{ s}^{-1}$). Notably, this value is at the same order of magnitude as the strong interaction between transferrin receptor:T7 peptide ($k_{\text{off}} = 6.8 \times 10^{-4} \text{ s}^{-1}$)[46] and flavoenzyme:NADP+ cofactor ($k_{\text{off}} = 2.0 \times 10^{-2} \text{ s}^{-1}$)[47]. Comparing with the values found for silver NPs, it was possible to observe that despite the lower adsorption of these NPs on BSA and HSA, the k_{off} was very similar among all the tested proteins, indicating the similar affinity between these proteins and silver NPs. In this case, the composition of protein corona of silver NPs would be expected to depend mainly on the concentration of the proteins in the medium which could change with time or with the conditions of the medium whereas the composition of protein corona of gold NPs would be determined by the concentration and the affinity between gold NPs and each protein.

In contrast with the numerous works that reported on the composition of protein corona formed on NPs, works reporting quantitative data of affinity between proteins and NPs are much less abundant. In the work of Gorshkov et al.[25], binding affinity of different proteins and silver NPs (citrate capped NPs of 60 nm) was inferred from the data obtained at different temperatures. In this case, the proteins that remained bound to the NP even after the temperature raising were considered strongly bound. Differently from what we observed here, their studies pointed out that protein-binding on silver NPs is selective and that the protein corona formed in the blood would contain only a very small subset of the entire plasma proteome. Their work included about 300 proteins and the persistent protein corona did not include serum albumin, apolipoprotein and immunoglobulins. Notably, the silver NPs investigated here were smaller (30 nm) and the assays were performed only at 37°C. Lai et al.[48] also reported the low content of albumin in the protein corona of 20 nm silver and gold NPs. The authors observed preferential binding of fibrinogen on gold NPs proteins and the low abundance of albumin and globulins on both gold and silver NPs protein corona. In the work of Patra et al.[49] the composition of protein corona and the affinity between plasma protein and gold NPs were evaluated by using multiplexed surface plasmon resonance. The authors found similar values of k_{off} to the interaction with IgGR, fibrinogen, ApoA and IgGH (Table 1) but the value of k_{off} found here to the interaction with HSA was higher ($5.50 \times 10^{-3} \text{ s}^{-1}$) than the value reported by them ($1.8 \times 10^{-3} \text{ s}^{-1}$)[49]. This difference may arise from the fact that in the work of Patra et al. the gold NPs were immobilized on the biochip surface whereas in our assays, the gold NPs were in suspension. Once the movement of NPs was hampered by their immobilization, the dissociation between them and the protein was slower and therefore the k_{off} was lower.

The application of SPRi in the study of proteins association to and dissociation from NPs has also been explored before with non-metallic NPs[35], [36]. Inversely to what was done herein, the NPs were immobilized on the surface of the biochip and the proteins from plasma were injected on the biochip surface. Cedervall et al. used SPR only as a complementary technique to characterize protein corona formed on 70 nm and 200 nm copolymeric NPs[35]. Although they have quantified exchange rates and binding affinities of proteins to NPs, their approach did not lay only on the SPR data but also on the data obtained by isothermal titration calorimetry, SDS-PAGE and liquid chromatography. From SPR assay, they concluded that when the whole plasma was injected on the NPs, more than one protein associated to NPs and in order to calculate dissociation constants, the SPR data were adjusted by considering two simultaneous association-dissociation events. The calculated dissociation rates revealed faster dissociation of proteins fibrinogen and HSA from hydrophobic NPs than from hydrophilic NPs. Similar to what was observed here and in the aforementioned works affinity of proteins to NPs depends on the NPs surface and the identity of protein.

2.2.1. Interaction between gold NPs and proteins studied by localized surface plasmon resonance

Gold and silver NPs can also be used as a sensitive tool for bio-sensing based on localized surface plasmon resonance (LSPR). Both local refractive index change, for example, induced by coating of chemical/biochemical molecules and self-assembly of the nanoparticles due to aggregation can lead to some spectral shifts of the LSPR extinction peak. In this study, we also utilized these phenomena to develop a very simple and straightforward approach for the evaluation of the interaction between NPs and proteins in solution.

Gold NPs have a characteristic absorbance band in the region of 500 nm whereas silver NPs have the plasmon band around 400 nm. The values of λ_{max} vary according to the size of the NPs. For example, the 20 nm gold NPs used in this work presented λ_{max} at 525 nm and the silver NPs at 431 nm. When the optical properties of these NPs change due to aggregation or due to the coating by chemical/biochemical molecules, the plasmon band become wider and shifts to higher wavelengths. Herein, interaction of gold and silver NPs with serum blood proteins was also monitored by UV-Vis spectroscopy in order to compare with the SPRI results.

The spectra were obtained immediately after mixing the proteins with the NPs and 4h after incubation. The spectra of gold NPs are depicted in Figure 9. Similar behavior were observed with silver NPs. It was possible to note there was red-shift of the spectrum after the interaction between NPs and proteins. For easier comparison purposes, the values of λ_{max} and absorbance of each spectrum were depicted in **Table 2**. Variation of absorbance and λ_{max} shifting were evaluated by comparing the spectra of gold and silver NPs mixed with proteins with the spectra of NPs stock suspension and of NPs in HEPES buffer solution. Once no changes had been observed in the spectrum of NPs suspended in HEPES solution in comparison with the spectra of NPs stock suspension, it was possible to conclude that the changes observed in the spectra of NPs mixed with the proteins were a consequence of the interaction between them.

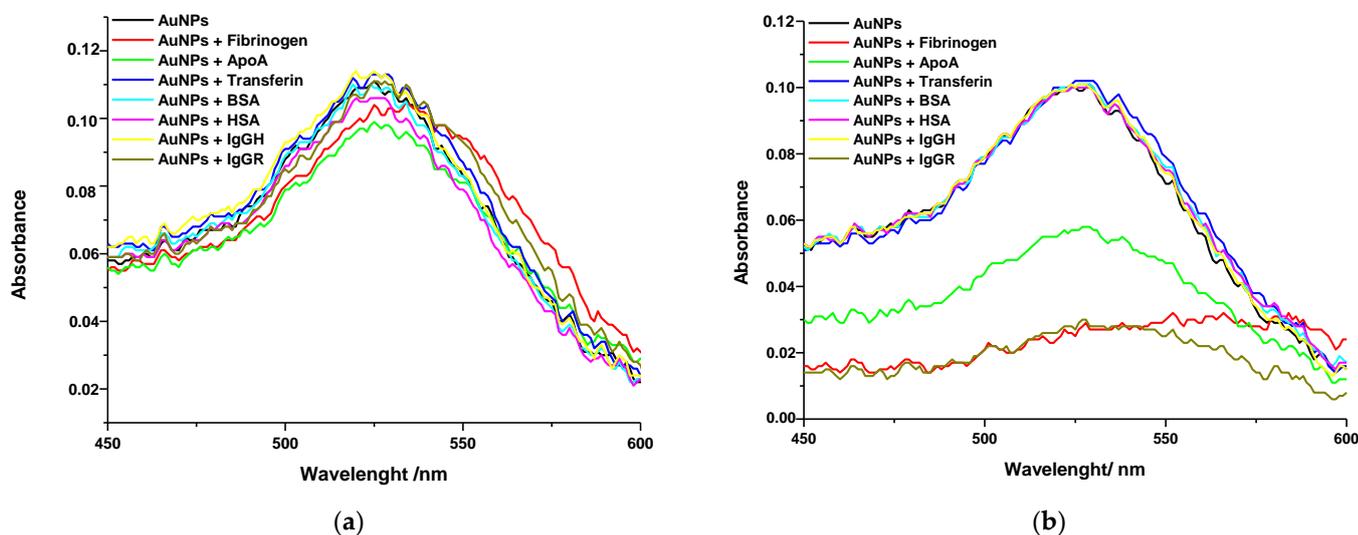


Figure 9. UV-Vis spectra of gold NPs in the presence of proteins (A) immediately after mixing and (B) after 4h of incubation.

Immediately after mixing NPs and proteins, only slight shifts of plasmon band were observed. The most prominent red-shift was observed in the spectra of gold NPs in the presence of fibrinogen, indicating that gold NPs interacted more with fibrinogen than with the other proteins. After 4h of incubation, the spectra of gold NPs incubated with fibrinogen, apoA and IgGR, became wider and significant shift of the plasmon band to higher wavelengths at the region of 570 nm was observed. Nevertheless, no difference was observed in the spectra of gold NPs incubated with transferrin, BSA, HSA and IgGH. These results suggest that subtle changes on NPs surface as for example due to low in-

410 teraction of proteins could not be detected by UV-Vis spectroscopy. In this case, SPRi was
 411 advantageous since the interaction between gold NPs and all the tested proteins were
 412 detected and monitored in real time.

413 **Table 2.** Values and variations of λ_{\max} and absorbance of gold and silver NPs immediately after
 414 mixing and after 4h of incubation with proteins.

Sample	Immediately		After 4 hours		Variation	
	λ_{\max} (nm)	Absorbance	λ_{\max} (nm)	Absorbance	$\Delta\lambda_{\max}$ (nm)	Δ absorbance
gold NPs						
gold NPs	525	0.12	528	0.12	3	-0.01
NPs + HEPES	525	0.11	528	0.10	3	-0.01
NPs + Fibr	534	0.10	584	0.04	50	-0.07
NPs + ApoA	525	0.10	529	0.06	4	-0.04
NPs + Transf	529	0.11	525	0.10	-4	-0.01
NPs + BSA	519	0.11	526	0.10	7	-0.01
NPs + IgGH	520	0.11	524	0.10	4	-0.01
NPs + IgGR	528	0.11	529	0.09	1	-0.02
silver NPs						
silver NPs	431	0.09	428	0.11	-3	0.01
NPs + HEPES	412	0.14	430	0.10	18	-0.03
NPs + Fibr	415	0.14	435	0.05	20	-0.09
NPs + ApoA	389	0.15	410	0.12	21	-0.02
NPs + Transf	408	0.17	415	0.14	7	-0.03
NPs + BSA	411	0.15	430	0.09	19	-0.06
NPs + IgGH	408	0.16	428	0.07	20	-0.09
NPs + IgGR	408	0.14	429	0.11	21	-0.04

415 The results found with silver NPs were also in agreement with the results from the
 416 SPRi assay. The most prominent shifts towards higher wavelengths were observed with
 417 the fibrinogen and ApoA proteins. In addition, as also pointed out by the SPRi results,
 418 silver NPs showed similar interaction with all the studied proteins since the λ_{\max} shift-
 419 ing were not very different among the absorption spectra.

420 The difference between the results observed immediately after the mixing gold and
 421 silver NPs with proteins and after 4h of incubation suggested that the interaction with the
 422 proteins increase with time. The decrease in absorbance is probable a result of NPs ag-
 423 gregation since the proteins with higher affinity with gold NPs could coat all the NPs
 424 surface decreasing surface charge. Although similar trend has been observed in the
 425 UV-Vis and SPRi results regarding which proteins would interact more with gold and
 426 silver NPs, the UV-Vis results were less informative and less sensitive regarding the ki-
 427 netics and affinity differences.

428 3. Discussion

429 Biological interaction of NPs has been the subject of extensive research in the last
 430 years. In particular, the interaction of NPs with lipid membranes and proteins have at-
 431 tracted more attention due to their impact on the circulation time, targeting activity, cell
 432 internalization and therapeutic efficiency of NPs. Several theoretical and experimental
 433 approaches have been developed to fully characterize the interaction of NPs with lipid
 434 membranes and proteins regarding their kinetic, mechanism and composition [18], [21],
 435 [50], [51]. Herein, we report on the use of SPRi assays aiming at a fast and accurate char-
 436 acterization of NPs protein corona and interaction with lipid membranes.

437 Although the pathways for NP's cytotoxicity are diverse and dependent upon the
438 nature of the NP and the biochemical environment, numerous studies have provided
439 evidence that direct contact between NP and cell membranes leads to cell inactivation or
440 damage and may be a primary mechanism for cytotoxicity[31], [32], [52]–[54]. Further-
441 more, the interaction between NPs and lipid membranes can also suggest a potential an-
442 timicrobial activity of the NPs. In fact, the effect of gold NPs on outer membrane of bac-
443 teria cell wall has evidenced their potential application as antimicrobial agents[45], [53],
444 [55]–[57]. Our findings have shown that it is possible to evaluate the interaction between
445 gold NPs with membranes of different composition in an easy and fast way by using
446 SPRi. The observed low affinity of gold NPs with POPC membrane was in line with the
447 observed affinity of negatively charged NPs with POPC membranes or membranes with
448 similar lipid composition. The crucial role of the electrostatic interaction between NPs
449 and membranes have been evidenced by several researchers[12], [58]–[60]. Hong et
450 al.[61] pointed out that the adsorption of NPs to membrane was a process driven by
451 electrostatic interaction, which induced an osmotic imbalance to the membrane. In the
452 work of Katz et al. the authors could prove that an amphiphilic monolayer created on the
453 NPs surface inhibited the interaction of gold NPs with plasma cell membrane and no
454 evidence of membrane poration or cell death was observed[62]. On the other hand, by
455 using gold NPs with different charges and surface densities, Lin et al.[32] could observe
456 that the NPs spontaneously adsorbed on the surface of the membrane or penetrated the
457 bilayer. Although it is expected that the surface of POPC/DDAB membrane has slightly
458 positive charge, the DDAB molecules would be homogeneously spread throughout the
459 membrane, and it was not enough to increase the adsorption of gold NPs on the mem-
460 brane in comparison with the membrane containing only POPC. Therefore, the NPs were
461 homogeneously distributed on the membrane surface and showed the saturation after
462 successive injections.

463 The continuous adsorption of gold NPs on POPC/chol membrane could be ex-
464 plained by the preferential interaction of these NPs with cholesterol-rich domains of
465 membranes. This interaction could be promoted by the instability of the cholester-
466 ol-cholesterol interaction in the POPC membrane. As reported by Dai et al.[63], choles-
467 terol clusters can pass through a conformational change to avoid water penetration be-
468 tween cholesterol headgroups. Then, the presence of gold NPs would promote the pref-
469 erential interaction between cholesterol monomers than cholesterol-cholesterol interac-
470 tion in the cluster. Under their strong interaction subsequential gold NPs injected on the
471 membrane would promote NPs agglomeration/aggregation with the gold NPs previ-
472 ously adsorbed. The agglomeration/aggregation of NPs will result in bigger structures
473 and as already evidenced before, changes in size will result in different interaction with
474 cell membranes[62], [64]–[66]. The effect of NPs size on the interaction with membrane
475 has also been pointed out to change the antimicrobial activity of NPs. In the work of
476 Hayden et al. (2012), hydrophobic cationic 2 nm gold NPs were able to lyse *B. subtilis* cell
477 wall whereas 6 nm NPs did not cause any toxic effect. The authors associated this result
478 to the different clustering of 2 nm and 6 nm NPs on bacteria outer membrane. The 2 nm
479 NPs formed big aggregates after adsorption on the cell wall whereas the 6 nm NPs were
480 homogeneously distributed on the cell wall and formed small aggregates[44].

481 Once most of the NPs under development have been focused on biomedical appli-
482 cation, the protein corona formed on different types of NPs has been mainly investigated
483 in the blood serum and plasma. The results showed that composition of protein corona
484 can be influenced by the core, surface charge and surface chemistry of NPs[17], [28], [48],
485 [67] and can also be changed by the conditions of the biological medium such as concen-
486 tration of proteins, pH and temperature[25], [27], [28]. The strategy addressed by most of
487 the researchers has been based on an indirect measurement and other procedures that
488 included the centrifugation of NPs after their incubation with the biological medium and
489 quantitative analysis of the proteins in the supernatant. However, centrifugation is

known to induce NPs aggregation and to perturb the association of biomolecules adsorbed on NPs surface. Therefore, it would compromise the accuracy of these assays.

Herein, the interaction of silver and gold NPs with proteins was evaluated by SPRi. The identification of ApoA, fibrinogen and immunoglobulins as the proteins that gold and silver NPs would have higher affinity can be considered as an indicative that these proteins would be the major components of protein-corona formed on the NPs surface when these NPs would be in blood serum (and/or) plasma. This observation is in line with several works reported before[6], [48], [49], [68]. Chan et al.[27] have reported on the composition of protein corona formed on gold NPs. The authors investigated the effect of NPs size and surface chemistry on the protein corona composition. They also showed how the composition changed with time and with media composition and cell phenotype. The composition of protein corona of 15 nm citrate-stabilized gold NPs was characterized by liquid chromatography-tandem mass spectrometry (LC-MS/MS) after incubation with a culture medium conditioned by A459 cells which contained 581 proteins. The group of proteins that composed the majority of protein corona changed with time. Although they have not identified fibrinogen, IGR or ApoA, they reported the presence of APO E, fibronectin, Beta-2 glycoprotein and thrombospondin-1 as the main components of the protein corona formed right after the incubation. In the work of Dobrovolskaia et al.[68] the protein corona formed on 30 nm gold NPs when these NPs were in contact with human serum was characterized by 2D page and mass spectrometry. They have found that the main components of protein corona were fibrinogen, albumin and ApoA. In the work of Gorshkov et al.[25], ApoA also appeared amongst the most abundant proteins in protein corona formed on 60 nm citrate-stabilized silver NPs. Interestingly, ApoA was also one of the main proteins of corona formed on metal oxide and liposomes NPs. In the protein corona formed on 50 nm silica NPs, besides ApoA, the authors also identified the presence of other apolipoproteins such as ApoB and ApoE[22]. Similarly, Yang et al.[69] indicated APO as one of the main components of protein corona formed on liposomes of different ratios of negatively charged and zwitterionic lipids. ApoC was the most abundant protein in the protein corona of liposomes composed of negatively charged lipids. Gorshkov et al.[25] reported on the selective interaction of silver NPs with plasma proteins resulting in a protein corona that included only a very small subset of the entire plasma proteome. Nevertheless, they adverted that due to dynamic range limitation of mass spectrometer, the observation of very low-abundance proteins from plasma samples could be compromised.

In comparison with the techniques already used to identify the NPs protein corona, mainly mass spectrometry, liquid chromatography and SDS-PAGE, the present work highlights the application of SPRi as a convenient and systematic technique to investigate NP-protein interaction. Most important, the informative aspect of SPRi configures its main advantage over the others available technique. Through SPRi it was possible not only to identify which proteins would be the most abundant in the protein corona formed on each type of NPs but also to perform a comparative investigation of interaction of NP with several types of protein at the same time. Notoriously, SPRi was shown to be a straightforward method that allows the calculation of dissociation constant of NPs-protein interaction with high accuracy which was pointed by the most researchers as the main difficult faced by the methods that they used. Nevertheless, one of the drawbacks of SPRi is the limitation regarding NPs size under investigation since the sensitivity decreases with the distance from the biochip surface due to the evanescent plasmon field and for this reason, the sensitivity to particles or aggregates larger than 300 nm would be compromised. Even so, SPRi has been very useful to evaluate interaction of NPs < 100 nm. In our previous work, the SPRi was successfully applied in the investigation of interaction of 30 nm NPs with membranes. In this case, SPRi allowed us to investigate how lipid coating changed the interaction of NPs with lipid membranes of different surface charges[70]. Similarly, some other groups applied SPR in order to evaluate the association of proteins with NPs[36], [49], [67]. Cedervall et al.[67] investigated the ad-

sorption of fibrinogen and HSA to 70 nm NPs composed of copolymers with different hydrophobicity[67]. Herein, SPRi was successfully applied in the study of interaction of 30 nm silver and 20 nm gold NPs with proteins and membranes.

Since protein corona changes NPs colloidal stability and interaction with cells, the prediction of its composition would be a crucial step in the NPs design and development process. The influence of NPs surface charge and chemistry on the formation of protein corona brought to light how NPs coating could be used to control the composition of protein corona. The results obtained herein showed SPRi would be a simple method to evaluate the performance of different NPs coatings as modulators of NPs interaction with proteins and lipid membranes. Innovative coatings could be developed in order to obtain a fine tune of the protein corona composition and cell targeting. Yang et al.[69] showed that the composition of protein corona could be modulated by tuning the surface charge of liposomes. Liposomes composed of higher ratios of negatively charged lipids to zwitterionic lipids recruited higher concentration of apolipoproteins (APOC, APOA-1) whereas liposomes composed mainly of 1,2-dioleoyl-sn-glycero-3-phosphocholine (DOPC) showed protein corona with higher content of immunoglobulins such as IGKC and IGMH. Following what was done in our previous work[70], lipid coating of NPs with the different phospholipids could also be a strategy to modulate the composition of protein corona. Another candidate of a stable NPs coating could be composed by proteins with high affinity to NPs surface. In this case, SPRi assays would be helpful in the identification of proteins that would strongly bind to NPs surface, hampering the exchange process once they are found in biological medium. Also with the purpose of controlling protein composition of protein corona, Mosquera et al.[28] presented an ingenious approach to induce reversible disruption of the protein corona by using external stimuli based on the host-guest interactions. Their results reinforced the changes in the protein corona composition with the conditions of the external medium.

In this context, SPRi would also be a convenient technique to investigate how NP-protein interaction would be affected by NPs coating and environmental conditions in function of time. It is important to have in mind that the environmental conditions would change through NPs pathway in the body, as they would pass from blood to several tissues. In addition, biological environments have a dynamic composition which responds to metabolism and diseases. Moreover, one should also consider that the contrary could also be true, that means, the presence of NPs and the way they interact with cell, especially with cell membrane, could alter the cell metabolism and, therefore, change the proteins and metabolites released into the extracellular environment. Considering the complexity of NPs interaction with protein and membranes and their effects on NPs behavior *in vivo*, development and design process of NPs should count on the SPRi as straightforward and systematic method to provide accurate information regarding their biological interaction. SPRi assays could also be combined to other techniques, enriching the information regarding biological behavior of NPs. For example, biomolecular interactions can be further investigated by bioluminescence resonance energy transfer (BRET)[71], fluorescence cross-correlation spectroscopy[72] and by atomic force microscopy to quantitatively assess the biomolecular dynamics and molecular recognition imaging (MRI)[73].

In order to summarize the idea, Figure 10 depicts a flowchart of how SPRi assays could be integrated in the development process of NPs for biomedical applications. Normally, aiming certain applications, the NPs are designed to present suitable size, morphology, surface charge and colloidal stability. Following the synthesis, these NPs are already applied *in vitro* which consists of time consuming and expensive assays (Figure 10; step I). Notably, once the *in vitro* results reveal unsatisfactory performance of NPs, the process must return to synthesis. However, by using SPRi (Figure 10; step II), *in vitro* results could already be predictable by evaluating biointeractions of NPs as soon as NPs synthesis is finished.

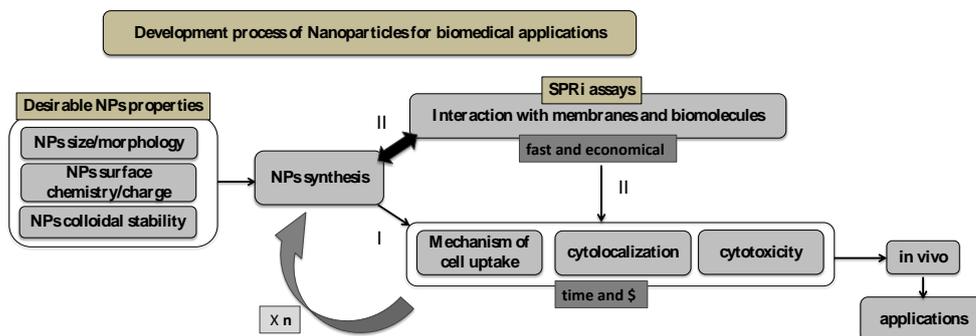
598
599

Figure 10. Flowchart of an example of how SPRi assays could be incorporated in the development process of NPs for biomedical applications providing fast and less expensive assays to predict in vitro results. As soon as NPs synthesis is finished, their biological interactions could be evaluated by SPRi (step II) instead of following direct to in vitro assays (step I) which are time consuming and expensive. SPRi assays are faster and of low cost. During the NPs development process, the synthesis has to be adjusted “n” times after the evaluation of in vitro results. SPRi assays provide a much practical technique to adjust synthesis and biological behavior of NPs.

600

601

602

603

604

605

606

607

608

609

610

611

612

613

614

615

616

617

618

619

620

621

622

623

624

625

626

4. Materials and Methods

4.1. SPRi assay with membranes

Biomimetic membranes were prepared on SPRi biochip according to the method previously described[65]. The following sections briefly describe the method with some modifications.

4.1.1. Preparation of the biochip

Before the assay the SPRi prism (SPRi-Biochips™; Horiba) was cleaned with sulfuric acid: hydrogen peroxide (4:1) solution. After washing with water and drying with N₂ the SPRi prism was immersed in a 10 mM 1-dodecanethiol (Sigma-Aldrich) ethanolic solution for 12 h. Finally, the functionalized SPRi prism was thoroughly washed with ethanol and dried with N₂.

4.1.2. Vesicles preparation

The vesicles were prepared by drying a solution of lipids in chloroform under a flow of N₂, following by solubilization of the lipidic film with warm (36°C) PBS buffer. All the lipids were acquired from Avanti Polar Lipids. Total lipid concentration was of 6.6 mM. In the POPC: Cholesterol the molar ratio was of 1:1 and the POPC/DDAB vesicles were prepared with 98% of POPC and 2% of DDAB. Then the vesicles preparation was completed by a freeze-tooling process. After about 6 repetitions of freeze-heating process, the suspension of vesicles was extruded about 11 times in Avanti polar Lipids extruder with a Millipore membrane (0.1µm). The vesicles were characterized regarding size and Zeta potential by dynamic light scattering (Delsa Nano C, Beckman Coulter).

4.1.3. SPRi assay

In the SPRi assay several spots were chosen to analyze the whole surface of the biochip. At the beginning of the experiment, a solution of SDS 1% was injected to clean the surface of the biochip and to wash-off the excess of dodecanethiol. After the stabilization of the kinetic curves, the vesicles suspension was injected for the formation of the mem-

brane on the biochip surface. After the stabilization, successive injections of gold NPs were performed to evaluate the adsorption of the NP and saturation of the membrane.

4.2. SPRi assay with proteins

4.2.1. Preparation of the protein and prism

All the SPRi assays presented in this work were performed using a SPRi Lab+ equipment (Horiba, France). At first, the SPRi prism (SPRi-Biochips™; Horiba, France) was cleaned by a plasma cleaning, in a Femto plasma cleaner (Diener Electronic, Germany) (0.6 mbar, 75% Oxygen, 25% Argon, power 40 W, 3 min) to ensure that the surface was completely free of any contaminants. Following that, the SPRi prism was immersed in a solution of N-hydroxysuccinimidyl 11-mercaptoundecanoate (Thiol-NHS; Sigma-Aldrich, France) (1 mM in ethanol) overnight. In such a way, the gold surface on the prism was covered by the self-assembled monolayer of thiols with active terminal groups for binding the proteins on the chip surface. Then, protein solutions were spotted on the SPRi prism using a non-contact spotter (sciFLEXARRAYER S3, Germany). This system enables many spots to be made on the same surface with low volume of solution (about 100 nL for drop). The following proteins were used: IgG from human serum, human serum albumin (HSA), apolipoprotein-A (Apo-A), fibrinogen from human plasma, transferrin. Two animal proteins were used for comparative purposes: bovine serum albumin (BSA) and IgG from rabbit. All of them were purchased from Sigma-Aldrich (France). The solutions of these proteins were all prepared at the concentration of 0.01 mg/mL in phosphate buffer solution (PBS) with pH 8.0. 2h after spotting, the SPRi biochip was washed carefully with PBS. Finally, the NHS-containing active surface between protein spots on the SPRi biochip was blocked with ethanolamine (Sigma-Aldrich, France) at 1 M in PBS pH 8.0, for 1h. After washing, the SPRi biochip was stored in HEPES buffer solution at 4°C.

4.2.2. SPRi experiment protocol

The SPRi biochip containing the proteins array was setup in Horiba SPRi (Lab+) equipment at 37°C. All the spots were labeled according to the respective protein and after the stabilization of the kinetic curves by using HEPES (pH = 7.4) as running solution, the NPs were then injected. The gold NPs of 20 nm at the concentration 7.00×10^{10} NPs/mL were purchased from BBI Solutions and silver NPs were previously synthesized and characterized by transmission electron microscopy as having 30 ± 8 nm of diameter and at the concentration of 1.46×10^{11} NPs/mL[74].

4.3. Data analysis

Data obtained from SPR measurements were analyzed using Origin 2018 and Matlab R2020a software. Each injection results in an interaction between the sample and the various points previously chosen on the sensor surface. The reflectivity variation values are obtained considering the interaction of at least 10 points on the sensor surface of each type of immobilized molecule and, therefore, it was possible to represent the variation values by the mean and the standard deviation. Finally, the average values of reflectivity variation were used to obtain the surface concentration density. The dissociation step represented in the kinetic curve was considered to obtain the k_{off} constant. All calculations are described in the support information.

5. Conclusions

The valuable application of SPRi in the characterization of two of the most important interaction of NPs (membranes and proteins) has been shown. It is expected that this work would motivate the application of SPRi in the most diverse investigation and design process of new NPs form biomedical applications. The authors highlight that there is still a lot to be explored in this subject, as for example, the SPRi technique also provides a

676 simple way to investigate the interaction at different conditions such as different protein
677 concentration, medium composition (e.g. presence of ions) and temperature without re-
678 quiring additional experimental steps. In this case, it would be only required to set up the
679 conditions of the running buffer or in the biochip functionalization. Therefore, SPRi will
680 be able to provide much more information in the field of nanotoxicology and
681 nanomedicine.

682 **Supplementary Materials:** The following supporting information can be downloaded at:
683 www.mdpi.com/xxx/s1, Supporting Information: Calculation of dissociation constant and surface
684 coverage density

685 **Author Contributions:** For research articles with several authors, a short paragraph specifying
686 their individual contributions must be provided. The following statements should be used Con-
687 ceptualization, D.B.T.; methodology, D.B.T., E.F.M.; N.S.S., M.S.M., Y.H.; software, E.F.M., L.S.N.;
688 validation, E.F.M., M.S.M. and L.S.N.; formal analysis, E.F.M., N.S.S., M.S.M., L.S.N.; investigation,
689 E.F.M., N.S.S., L.S.N., S.B., R.M and Y.H.; resources, D.B.T., Y.H., N.S.S., E.F.M.; data curation,
690 E.F.M., N.S.S., M.S.M., L.S.N.; writing—original draft preparation, D.B.T., E.F.M.; N.S.S., M.S.M.,
691 L.S.N.; writing—review and editing, D.B.T. and Y.H.; visualization, E.F.M. and L.S.N.; supervision,
692 D.B.T. and Y.H.; project administration, D.B.T. and Y.H.; funding acquisition, D.B.T., Y.H.. All au-
693 thors have read and agreed to the published version of the manuscript.

694 **Funding:** This research was funded by Fundação de Amparo à Pesquisa do Estado de São Paulo
695 (FAPESP) grant numbers: 2020/00807-5; 2019/06803-4; 2016/20503-5; 2016/14795-3, 2016/07354-0,
696 2017/01697-6.

697 **Institutional Review Board Statement:** Not applicable.

698 **Informed Consent Statement:** Not applicable.

699 **Data Availability Statement:** Raw data were generated at ICT-UNIFESP and UMC. Derived data
700 supporting the findings of this study are available from the corresponding authors D.B.T and
701 D.C.A. on request.

702 **Acknowledgments:** The authors would like to thank Nucleo de Apoio à Engenharia e Ciência dos
703 Materiais (NAPCEM) from UNIFESP for the use of DelsaNanoC equipment.

704 **Conflicts of Interest:** The authors declare no conflict of interest.

705 References

- 706 [1] M. R. King and Z. J. Mohamed, "Dual nanoparticle drug delivery: The future of anticancer therapies?,"
707 *Nanomedicine*, vol. 12, no. 2. Future Medicine, pp. 95–98, 2017, doi: 10.2217/nnm-2016-0378.
- 708 [2] R. X. Zhang *et al.*, "Importance of integrating nanotechnology with pharmacology and physiology for
709 innovative drug delivery and therapy - An illustration with firsthand examples," *Acta Pharmacol. Sin.*, vol. 39,
710 no. 5, pp. 825–844, 2018, doi: 10.1038/aps.2018.33.
- 711 [3] H. S. Choi *et al.*, "Design considerations for tumour-targeted nanoparticles," *Nat. Nanotechnol.*, vol. 5, no. 1, pp.
712 42–47, 2010, doi: 10.1038/nnano.2009.314.
- 713 [4] J. L. S. Au, R. A. Abbiati, M. G. Wientjes, and Z. Lu, "Target site delivery and residence of nanomedicines:
714 Application of quantitative systems pharmacology," *Pharmacol. Rev.*, vol. 71, no. 2, pp. 157–169, Apr. 2019, doi:
715 10.1124/pr.118.016816.
- 716 [5] W. H. Gmeiner and S. Ghosh, "Nanotechnology for cancer treatment," *Nanotechnol. Rev.*, vol. 3, no. 2, pp.
717 111–122, 2014.
- 718 [6] A. Albanese, C. D. Walkey, J. B. Olsen, H. Guo, A. Emili, and W. C. W. Chan, "Secreted biomolecules alter the
719 biological identity and cellular interactions of nanoparticles," *ACS Nano*, vol. 8, no. 6, pp. 5515–5526, Jun. 2014,
720 doi: 10.1021/nn4061012.
- 721 [7] S. Tenzer *et al.*, "Rapid formation of plasma protein corona critically affects nanoparticle pathophysiology,"
722 *Nat. Nanotechnol.*, vol. 8, no. 10, pp. 772–781, 2013, doi: 10.1038/nnano.2013.181.

- 723 [8] B. D. Chithrani and W. C. W. Chan, "Elucidating the mechanism of cellular uptake and removal of
724 protein-coated gold nanoparticles of different sizes and shapes," *Nano Lett.*, vol. 7, no. 6, pp. 1542–1550, 2007,
725 doi: 10.1021/nl070363y.
- 726 [9] D. Docter, D. Westmeier, M. Markiewicz, S. Stolte, S. K. Knauer, and R. H. Stauber, "The nanoparticle
727 biomolecule corona: lessons learned - challenge accepted?," *Chem. Soc. Rev.*, vol. 44, no. 17, pp. 6094–6121, Sep.
728 2015, doi: 10.1039/c5cs00217f.
- 729 [10] R. C. Van Lehn *et al.*, "Effect of particle diameter and surface composition on the spontaneous fusion of
730 monolayer-protected gold nanoparticles with lipid bilayers," *Nano Lett.*, vol. 13, no. 9, pp. 4060–4067, Sep. 2013,
731 doi: 10.1021/nl401365n.
- 732 [11] Y. Li, M. Kröger, and W. K. Liu, "Shape Effect in Cellular Uptake of PEGylated Nanopar-ticles: Comparison
733 between sphere, rod, cube and disk †," doi: 10.1039/b000000x.
- 734 [12] J. Lin, R. Dargazany, and A. Alexander-Katz, "Lipid Flip-Flop and Pore Nucleation on Zwitterionic Bilayers
735 are Asymmetric under Ionic Imbalance," *Small*, vol. 13, no. 22, Jun. 2017, doi: 10.1002/smll.201603708.
- 736 [13] L. Wang, N. Hartel, K. Ren, N. A. Graham, and N. Malmstadt, "Effect of protein corona on
737 nanoparticle-plasma membrane and nanoparticle-biomimetic membrane interactions," *Environ. Sci. Nano*, vol.
738 7, no. 3, pp. 963–974, Mar. 2020, doi: 10.1039/d0en00035c.
- 739 [14] S. Huo *et al.*, "Ultrasmall Gold Nanoparticles as Carriers for Nucleus-Based Gene Therapy Due to
740 Size-Dependent Nuclear Entry," *ACS Nano*, vol. 8, no. 6, pp. 5852–5862, Jun. 2014, doi: 10.1021/nn5008572.
- 741 [15] I. Ishmukhametov *et al.*, "DNA/Magnetic Nanoparticles Composite to Attenuate Glass Surface
742 Nanotopography for Enhanced Mesenchymal Stem Cell Differentiation," *Polymers (Basel)*, vol. 14, no. 2, p. 344,
743 Jan. 2022, doi: 10.3390/polym14020344.
- 744 [16] R. L. M. S. Oliveira *et al.*, "Bioglass-based scaffolds coated with silver nanoparticles: Synthesis, processing and
745 antimicrobial activity," *J. Biomed. Mater. Res. - Part A*, 2020, doi: 10.1002/jbm.a.36996.
- 746 [17] P. Chandran, J. E. Riviere, and N. A. Monteiro-Riviere, "Surface chemistry of gold nanoparticles determines
747 the biocorona composition impacting cellular uptake, toxicity and gene expression profiles in human
748 endothelial cells," *Nanotoxicology*, vol. 11, no. 4, pp. 507–519, 2017, doi: 10.1080/17435390.2017.1314036.
- 749 [18] C. Ge, J. Tian, Y. Zhao, C. Chen, R. Zhou, and Z. Chai, "Towards understanding of nanoparticle–protein
750 corona," *Archives of Toxicology*, vol. 89, no. 4. Springer Verlag, pp. 519–539, Mar. 11, 2015, doi:
751 10.1007/s00204-015-1458-0.
- 752 [19] M. Barbalinardo, F. Caicci, M. Cavallini, and D. Gentili, "Protein Corona Mediated Uptake and Cytotoxicity of
753 Silver Nanoparticles in Mouse Embryonic Fibroblast," *Small*, vol. 14, no. 34, pp. 1–8, 2018, doi:
754 10.1002/smll.201801219.
- 755 [20] W. Xiao and H. Gao, "The impact of protein corona on the behavior and targeting capability of
756 nanoparticle-based delivery system," *Int. J. Pharm.*, vol. 552, no. 1–2, pp. 328–339, 2018, doi:
757 10.1016/j.ijpharm.2018.10.011.
- 758 [21] T. Kopac, "Protein corona, understanding the nanoparticle–protein interactions and future perspectives: A
759 critical review," *Int. J. Biol. Macromol.*, vol. 169, pp. 290–301, 2021, doi: 10.1016/j.ijbiomac.2020.12.108.
- 760 [22] V. Francia, K. Yang, S. Deville, C. Reker-Smit, I. Nelissen, and A. Salvati, "Corona Composition Can Affect the
761 Mechanisms Cells Use to Internalize Nanoparticles," *ACS Nano*, vol. 13, no. 10, pp. 11107–11121, Oct. 2019, doi:
762 10.1021/acsnano.9b03824.
- 763 [23] G. Caracciolo, O. C. Farokhzad, and M. Mahmoudi, "Biological identity of nanoparticles in vivo: clinical
764 implications of the protein corona," *Trends Biotechnol.*, vol. 35, no. 3, pp. 257–264, 2017.

- 765 [24] S. M. Ahsan, C. M. Rao, and M. F. Ahmad, "Nanoparticle-Protein Interaction: The Significance and Role of
766 Protein Corona," 2018, pp. 175–198.
- 767 [25] V. Gorshkov, J. A. Bubis, E. M. Solovyeva, M. V. Gorshkov, and F. Kjeldsen, "Protein corona formed on silver
768 nanoparticles in blood plasma is highly selective and resistant to physicochemical changes of the solution,"
769 *Environ. Sci. Nano*, vol. 6, no. 4, pp. 1089–1098, 2019, doi: 10.1039/c8en01054d.
- 770 [26] R. Eigenheer, E. R. Castellanos, M. Y. Nakamoto, K. T. Gerner, A. M. Lampe, and K. E. Wheeler, "Silver
771 nanoparticle protein corona composition compared across engineered particle properties and environmentally
772 relevant reaction conditions," *Environ. Sci. Nano*, vol. 1, no. 3, pp. 238–247, 2014, doi: 10.1039/c4en00002a.
- 773 [27] A. Albanese, C. D. Walkey, J. B. Olsen, H. Guo, A. Emili, and W. C. W. Chan, "Secreted biomolecules alter the
774 biological identity and cellular interactions of nanoparticles," 2014.
- 775 [28] J. Mosquera *et al.*, "Reversible Control of Protein Corona Formation on Gold Nanoparticles Using Host-Guest
776 Interactions," *ACS Appl. Mater. Interfaces*, 2020, doi: 10.1021/acsnano.9b08752.
- 777 [29] A. Kumar *et al.*, "Differences in the coronal proteome acquired by particles depositing in the lungs of asthmatic
778 versus healthy humans," *Nanomedicine Nanotechnology, Biol. Med.*, vol. 13, no. 8, pp. 2517–2521, Nov. 2017, doi:
779 10.1016/j.nano.2017.06.008.
- 780 [30] R. C. Van Lehn *et al.*, "Effect of particle diameter and surface composition on the spontaneous fusion of
781 monolayer-protected gold nanoparticles with lipid bilayers," *Nano Lett.*, vol. 13, no. 9, pp. 4060–4067, 2013.
- 782 [31] J. Chen *et al.*, "Cationic nanoparticles induce nanoscale disruption in living cell plasma membranes," *J. Phys.*
783 *Chem. B*, vol. 113, no. 32, pp. 11179–11185, Aug. 2009, doi: 10.1021/jp9033936.
- 784 [32] J. Lin, H. Zhang, Z. Chen, and Y. Zheng, "Penetration of lipid membranes by gold nanoparticles: insights into
785 cellular uptake, cytotoxicity, and their relationship," *ACS Nano*, vol. 4, no. 9, pp. 5421–5429, 2010.
- 786 [33] C. Contini, M. Schneemilch, S. Gaisford, and N. Quirke, "Nanoparticle–membrane interactions," *Journal of*
787 *Experimental Nanoscience*, vol. 13, no. 1. Taylor and Francis Ltd., pp. 62–81, Jan. 01, 2018, doi:
788 10.1080/17458080.2017.1413253.
- 789 [34] Y. Li, X. Chen, and N. Gu, "Computational investigation of interaction between nanoparticles and membranes:
790 Hydrophobic/hydrophilic effect," *J. Phys. Chem. B*, vol. 112, no. 51, pp. 16647–16653, Dec. 2008, doi:
791 10.1021/jp8051906.
- 792 [35] T. Cedervall *et al.*, "Understanding the nanoparticle-protein corona using methods to quantify exchange rates
793 and affinities of proteins for nanoparticles," 2007. [Online]. Available: www.pnas.org/cgi/content/full/.
- 794 [36] M. Canovi *et al.*, "Applications of Surface Plasmon Resonance (SPR) for the characterization of nanoparticles
795 developed for biomedical purposes," *Sensors (Switzerland)*, vol. 12, no. 12, pp. 16420–16432, 2012, doi:
796 10.3390/s121216420.
- 797 [37] P. Chavel, M. Canva, P. Lecaruyer, H. Sauer, and J. Taboury, "Surface plasmon resonance imaging
798 instrumentation and data handling for biochips: review and perspectives," in *Seventh International Conference*
799 *on Correlation Optics*, 2006, pp. 62540M–62540M.
- 800 [38] J. Homola, "Present and future of surface plasmon resonance biosensors," *Anal. Bioanal. Chem.*, vol. 377, no. 3,
801 pp. 528–539, 2003.
- 802 [39] L. C. Schenkel and M. Bakovic, "Formation and Regulation of Mitochondrial Membranes," *Int. J. Cell Biol.*, vol.
803 2014, pp. 1–13, 2014, doi: 10.1155/2014/709828.
- 804 [40] N. D. Donahue, H. Acar, and S. Wilhelm, "Concepts of nanoparticle cellular uptake, intracellular trafficking,
805 and kinetics in nanomedicine," *Adv. Drug Deliv. Rev.*, vol. 143, pp. 68–96, 2019, doi: 10.1016/j.addr.2019.04.008.
- 806 [41] V. Francia, D. Montizaan, and A. Salvati, "Interactions at the cell membrane and pathways of internalization of

- 807 nano-sized materials for nanomedicine," *Beilstein J. Nanotechnol.*, vol. 11, pp. 338–353, 2020, doi:
808 10.3762/bjnano.11.25.
- 809 [42] S. Y. Ong *et al.*, "Interaction of nanodiamonds with bacteria," *Nanoscale*, vol. 10, no. 36, pp. 17117–17124, Sep.
810 2018, doi: 10.1039/c8nr05183f.
- 811 [43] Z. V. Feng *et al.*, "Impacts of gold nanoparticle charge and ligand type on surface binding and toxicity to
812 Gram-negative and Gram-positive bacteria," *Chem. Sci.*, vol. 6, no. 9, pp. 5186–5196, Jun. 2015, doi:
813 10.1039/c5sc00792e.
- 814 [44] S. C. Hayden *et al.*, "Aggregation and interaction of cationic nanoparticles on bacterial surfaces," *J. Am. Chem.*
815 *Soc.*, vol. 134, no. 16, pp. 6920–6923, Apr. 2012, doi: 10.1021/ja301167y.
- 816 [45] Y. Zhao, Y. Tian, Y. Cui, W. Liu, W. Ma, and X. Jiang, "Small molecule-capped gold nanoparticles as potent
817 antibacterial agents that target gram-negative bacteria," *J. Am. Chem. Soc.*, vol. 132, no. 35, pp. 12349–12356, Sep.
818 2010, doi: 10.1021/ja1028843.
- 819 [46] S. Li, X. Pang, J. Zhao, Q. Zhang, and Y. Shan, "Evaluating the single-molecule interactions between targeted
820 peptides and the receptors on living cell membrane," *Nanoscale*, vol. 13, no. 41, pp. 17318–17324, 2021, doi:
821 10.1039/D1NR05547J.
- 822 [47] S. Pérez-Domínguez, S. Caballero-Mancebo, C. Marcuello, M. Martínez-Júlvez, M. Medina, and A. Lostao,
823 "Nanomechanical Study of Enzyme: Coenzyme Complexes: Bipartite Sites in Plastidic Ferredoxin-NADP+
824 Reductase for the Interaction with NADP+," *Antioxidants*, vol. 11, no. 3, p. 537, Mar. 2022, doi:
825 10.3390/antiox11030537.
- 826 [48] W. Lai, Q. Wang, L. Li, Z. Hu, J. Chen, and Q. Fang, "Interaction of gold and silver nanoparticles with human
827 plasma: Analysis of protein corona reveals specific binding patterns," *Colloids Surfaces B Biointerfaces*, vol. 152,
828 pp. 317–325, 2017, doi: 10.1016/j.colsurfb.2017.01.037.
- 829 [49] A. Patra *et al.*, "Component-Specific Analysis of Plasma Protein Corona Formation on Gold Nanoparticles
830 Using Multiplexed Surface Plasmon Resonance," *Small*, vol. 12, no. 9, pp. 1174–1182, Mar. 2016, doi:
831 10.1002/sml.201501603.
- 832 [50] H. Zhao, L. Li, H. Zhan, Y. Chu, and B. Sun, "Mechanistic Understanding of the Engineered
833 Nanomaterial-Induced Toxicity on Kidney," *J. Nanomater.*, vol. 2019, 2019, doi: 10.1155/2019/2954853.
- 834 [51] C. Peetla, A. Stine, and V. Labhasetwar, "Biophysical interactions with model lipid membranes: Applications
835 in drug discovery and drug delivery," in *Molecular Pharmaceutics*, Oct. 2009, vol. 6, no. 5, pp. 1264–1276, doi:
836 10.1021/mp9000662.
- 837 [52] L. Tong, Y. Zhao, T. B. Huff, M. N. Hansen, A. Wei, and J. X. Cheng, "Gold nanorods mediate tumor cell death
838 by compromising membrane integrity," *Adv. Mater.*, vol. 19, no. 20, pp. 3136–3141, Oct. 2007, doi:
839 10.1002/adma.200701974.
- 840 [53] K. L. Chen and G. D. Bothun, "Nanoparticles meet cell membranes: Probing nonspecific interactions using
841 model membranes," *Environ. Sci. Technol.*, vol. 48, no. 2, pp. 873–880, Jan. 2014, doi: 10.1021/es403864v.
- 842 [54] A. Bhat *et al.*, "Effects of gold nanoparticles on lipid packing and membrane pore formation," *Appl. Phys. Lett.*,
843 vol. 109, no. 26, p. 263106, 2016.
- 844 [55] D. M. D. Formaggio *et al.*, "In vivo toxicity and antimicrobial activity of AuPt bimetallic nanoparticles," *J.*
845 *Nanoparticle Res.*, vol. 21, no. 11, 2019, doi: 10.1007/s11051-019-4683-2.
- 846 [56] J. Lin and A. Alexander-Katz, "Cell membranes open 'doors' for cationic nanoparticles/ biomolecules: Insights
847 into uptake kinetics," *ACS Nano*, vol. 7, no. 12, pp. 10799–10808, Dec. 2013, doi: 10.1021/nn4040553.
- 848 [57] D. Baowan, "Penetration of spherical gold nanoparticle into a lipid bilayer," *ANZIAM J.*, vol. 57, no. 1, pp.

18–28, 2015.

- 849
- 850 [58] C. W. Yong, "Study of interactions between polymer nanoparticles and cell membranes at atomistic levels,"
- 851 *Philos. Trans. R. Soc. B Biol. Sci.*, vol. 370, no. 1661, Jan. 2015, doi: 10.1098/rstb.2014.0036.
- 852 [59] C. M. Goodman, C. D. McCusker, T. Yilmaz, and V. M. Rotello, "Toxicity of gold nanoparticles functionalized
- 853 with cationic and anionic side chains," *Bioconjug. Chem.*, vol. 15, no. 4, pp. 897–900, Jul. 2004, doi:
- 854 10.1021/bc049951i.
- 855 [60] A. R. Mhashal and S. Roy, "Effect of gold nanoparticle on structure and fluidity of lipid membrane," *PLoS One*,
- 856 vol. 9, no. 12, pp. 1–18, 2014, doi: 10.1371/journal.pone.0114152.
- 857 [61] S. Hong *et al.*, "Interaction of poly(amidoamine) dendrimers with supported lipid bilayers and cells: Hole
- 858 formation and the relation to transport," *Bioconjug. Chem.*, vol. 15, no. 4, pp. 774–782, Jul. 2004, doi:
- 859 10.1021/bc049962b.
- 860 [62] R. C. Van Lehn and A. Alexander-Katz, "Membrane-embedded nanoparticles induce lipid rearrangements
- 861 similar to those exhibited by biological membrane proteins," *J. Phys. Chem. B*, vol. 118, no. 44, pp. 12586–12598,
- 862 Nov. 2014, doi: 10.1021/jp506239p.
- 863 [63] J. Dai, M. Alwarawrah, and J. Huang, "Instability of Cholesterol Clusters in Lipid Bilayers and The
- 864 Cholesterol's Umbrella Effect," *J. Phys. Chem. B*, vol. 114, no. 2, pp. 840–848, Jan. 2010, doi: 10.1021/jp909061h.
- 865 [64] H. Zhang *et al.*, "Cooperative transmembrane penetration of nanoparticles," *Sci. Rep.*, vol. 5, May 2015, doi:
- 866 10.1038/srep10525.
- 867 [65] D. B. Tada *et al.*, "Effect of lipid coating on the interaction between silica nanoparticles and membranes," *J.*
- 868 *Biomed. Nanotechnol.*, vol. 10, no. 3, 2014, doi: 10.1166/jbn.2014.1723.
- 869 [66] S. R. Hemelaar *et al.*, "The interaction of fluorescent nanodiamond probes with cellular media," *Microchim. Acta*,
- 870 vol. 184, no. 4, pp. 1001–1009, Apr. 2017, doi: 10.1007/s00604-017-2086-6.
- 871 [67] T. Cedervall *et al.*, "Understanding the nanoparticle--protein corona using methods to quantify exchange rates
- 872 and affinities of proteins for nanoparticles," *Proc. Natl. Acad. Sci.*, vol. 104, no. 7, pp. 2050–2055, 2007.
- 873 [68] M. A. Dobrovolskaia *et al.*, "Interaction of colloidal gold nanoparticles with human blood: effects on particle
- 874 size and analysis of plasma protein binding profiles," *Nanomedicine Nanotechnology, Biol. Med.*, vol. 5, no. 2, pp.
- 875 106–117, 2009.
- 876 [69] K. Yang, B. Mesquita, P. Horvatovich, and A. Salvati, "Tuning liposome composition to modulate corona
- 877 formation in human serum and cellular uptake," *Acta Biomater.*, vol. 106, pp. 314–327, Apr. 2020, doi:
- 878 10.1016/j.actbio.2020.02.018.
- 879 [70] D. B. Tada *et al.*, "Effect of Lipid Coating on the Interaction Between Silica Nanoparticles and Membranes,"
- 880 2014, doi: 10.1166/jbn.2014.1723.
- 881 [71] E. W. E. Verweij *et al.*, "BRET-Based Biosensors to Measure Agonist Efficacies in Histamine H1
- 882 Receptor-Mediated G Protein Activation, Signaling and Interactions with GRKs and β -Arrestins," *Int. J. Mol.*
- 883 *Sci.*, vol. 23, no. 6, p. 3184, Mar. 2022, doi: 10.3390/ijms23063184.
- 884 [72] I. Jakobowska *et al.*, "Fluorescence Cross-Correlation Spectroscopy Yields True Affinity and Binding Kinetics of
- 885 Plasmodium Lactate Transport Inhibitors," *Pharmaceuticals*, vol. 14, no. 8, p. 757, Aug. 2021, doi:
- 886 10.3390/ph14080757.
- 887 [73] C. Marcuello, R. de Miguel, and A. Lostao, "Molecular Recognition of Proteins through Quantitative Force
- 888 Maps at Single Molecule Level," *Biomolecules*, vol. 12, no. 4, p. 594, Apr. 2022, doi: 10.3390/biom12040594.
- 889 [74] R. L. M. S. Oliveira *et al.*, "Bioglass-based scaffolds coated with silver nanoparticles: Synthesis, processing and
- 890 antimicrobial activity," *J. Biomed. Mater. Res. Part A*, vol. 108, no. 12, pp. 2447–2459, Dec. 2020, doi:

10.1002/jbm.a.36996.

891

892