



**HAL**  
open science

## A Parametric Study of the Crystal Phases on Au/TiO<sub>2</sub> Photocatalysts for CO<sub>2</sub> Gas-Phase Reduction in the Presence of Water

Clément Marchal, Caroline Mary, Leila Hammoud, Qingyang Xi, Joumana Toufaily, Tayssir Hamieh, Luka Suhadolnik, Paolo Fornasiero, Christophe Colbeau-Justin, Valérie Caps, et al.

► **To cite this version:**

Clément Marchal, Caroline Mary, Leila Hammoud, Qingyang Xi, Joumana Toufaily, et al.. A Parametric Study of the Crystal Phases on Au/TiO<sub>2</sub> Photocatalysts for CO<sub>2</sub> Gas-Phase Reduction in the Presence of Water. *Catalysts*, 2022, 12 (12), pp.1623. 10.3390/catal12121623 . hal-04245739

**HAL Id: hal-04245739**

**<https://hal.science/hal-04245739>**

Submitted on 17 Oct 2023

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution 4.0 International License

## Article

# A Parametric Study of the Crystal Phases on Au/TiO<sub>2</sub> Photocatalysts for CO<sub>2</sub> Gas-Phase Reduction in the Presence of Water

Clément Marchal <sup>1,\*</sup> , Caroline Mary <sup>1</sup>, Leila Hammoud <sup>1</sup>, Qingyang Xi <sup>1</sup>, Joumana Toufaily <sup>2</sup> , Tayssir Hamieh <sup>2,3</sup> , Luka Suhadolnik <sup>4</sup> , Paolo Fornasiero <sup>4</sup> , Christophe Colbeau-Justin <sup>5</sup>, Valérie Caps <sup>1</sup> , Thomas Cottineau <sup>1</sup>  and Valérie Keller <sup>1,\*</sup> 

- <sup>1</sup> ICPEES—Institute of Chemistry and Processes for Energy, Environment and Health, UMR 7515, CNRS/University of Strasbourg, 25, Rue Becquerel, CEDEX 2, 67087 Strasbourg, France
- <sup>2</sup> Laboratory of Materials, Catalysis, Environment and Analytical Methods Laboratory (MCEMA), Faculty of Sciences, Lebanese University, Hadath P.O. Box 11-2806, Lebanon
- <sup>3</sup> Faculty of Science and Engineering, Maastricht University, P.O. Box 616, 6200 MD Maastricht, The Netherlands
- <sup>4</sup> Department of Chemical and Pharmaceutical Sciences, INSTM and ICCOM-CNR Research Units, University of Trieste, via L. Giorgieri 1, 34127 Trieste, Italy
- <sup>5</sup> ICP, Institut de Chimie Physique, CNRS UMR 8000, Université Paris-Saclay, Bâtiment 349, CEDEX, 91405 Orsay, France
- \* Correspondence: cle.marchal@unistra.fr (C.M.); vkeller@unistra.fr (V.K.)



**Citation:** Marchal, C.; Mary, C.; Hammoud, L.; Xi, Q.; Toufaily, J.; Hamieh, T.; Suhadolnik, L.; Fornasiero, P.; Colbeau-Justin, C.; Caps, V.; et al. A Parametric Study of the Crystal Phases on Au/TiO<sub>2</sub> Photocatalysts for CO<sub>2</sub> Gas-Phase Reduction in the Presence of Water. *Catalysts* **2022**, *12*, 1623. <https://doi.org/10.3390/catal12121623>

Academic Editors: Paola Calza and Sixto Malato

Received: 29 September 2022

Accepted: 8 December 2022

Published: 10 December 2022

**Publisher's Note:** MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



**Copyright:** © 2022 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

**Abstract:** Au/TiO<sub>2</sub> photocatalysts were studied, characterized, and compared for CO<sub>2</sub> photocatalytic gas-phase reduction. The impact of the nature of the TiO<sub>2</sub> support was studied. It was shown that the surface area/porosity/TiO<sub>2</sub> crystal phase/density of specific exposed facets and oxygen vacancies were the key factors determining CH<sub>4</sub> productivity under solar-light activation. A 0.84 wt.% Au/TiO<sub>2</sub> SG (Sol Gel) calcined at 400 °C exhibited the best performance, leading to a continuous mean CH<sub>4</sub> production rate of 50 μmol.h<sup>-1</sup>.g<sup>-1</sup> over 5 h, associated with an electronic selectivity of 85%. This high activity was mainly attributed to the large surface area and accessible microporous volume, high density of exposed TiO<sub>2</sub> (101) anatase facets, and oxygen vacancies acting as reactive defects sites for CO<sub>2</sub> adsorption/activation/dissociation and charge carrier transport.

**Keywords:** CH<sub>4</sub> and H<sub>2</sub> production; CO<sub>2</sub> photo-reduction; crystalline phases; titanium dioxide

## 1. Introduction

Amongst the huge variety of semiconductors and composite materials investigated for CO<sub>2</sub> photocatalytic reduction in gas-phase, TiO<sub>2</sub> often prevails due to its chemical stability, moderate cost, and resistance toward corrosion [1–4]. However, its relatively fast electron-hole pair recombination rate and hindrance of visible light harvesting are considered the main limitations for solar light-driven gas phase CO<sub>2</sub> photocatalytic reduction in the presence of water. In the recent years, several strategies have been tested in order to overcome these limitations [5,6], including loading with metal nanoparticles, acting as electron sink, co-catalyst, or inducing surface plasmon phenomena [3,7–10]; combining TiO<sub>2</sub> with other semiconductors [11–13] or other elements by means of mono-doping [14–16] or co-doping approaches [17,18]; or modifying the morphology [19–22].

Among the different reaction products that could be obtained from CO<sub>2</sub> reduction, and also knowing that the energy content of oxygenated compounds decreases as the oxygen content increases (due to the relative decrease in C-H bond storage energy), CH<sub>4</sub> is one of the most interesting, together with methanol. Nonetheless, as methanol's photo-reactivity is much higher than that of CO<sub>2</sub>, leading to easy over-oxidation to formaldehyde and formic acid, high selectivity towards methane formation is preferred [3]. It has already

been reported that TiO<sub>2</sub> anatase crystal facets can impact the performances towards CO<sub>2</sub> photoreduction, the {010} and the {001} facets leading to the highest and lowest selectivity toward methane formation, respectively [23]; whereas the exposure of both facets leads to the highest yields [24]. Furthermore, it has been established that, even if amorphous phases can be active, the crystallinity and defects of the semiconductor also play a crucial role, influencing the mobility of electron-hole pairs [15,24]. Theoretical studies have confirmed that the CO<sub>2</sub> adsorption, activation, and dissociation steps were highly influenced by oxygen-deficiency/defects disorders in TiO<sub>2</sub> anatase, rutile, or brookite crystal phases [25–27]. The role of oxygen vacancies as reactive defect sites in TiO<sub>2</sub> photocatalysts, even at low concentrations, is a key parameter in air-free photocatalytic properties, impacting the surface adsorption, and charge carrier transport [28,29]. Thus, the presence/introduction of oxygen vacancies may result in favorable charge transport phenomena, thus improving the charge carrier lifetime [30,31], and their role in photocatalysis has been extensively studied [32,33]. The TiO<sub>2</sub> particle size, crystallinity, presence of vacancies, density of exposed facets, porosity, and surface area, consequently play crucial roles in CO<sub>2</sub> photoreduction [34].

Between the different metal nanoparticles (NPs) used as co-catalysts and exhibiting surface plasmon resonance (SPR) properties in the visible range, Au can be considered one of the most interesting for driving CH<sub>4</sub> production from CO<sub>2</sub> gas-phase photocatalytic reduction in the presence of water vapor as a reducing agent. Due to interest in their use for catalysis, Au/TiO<sub>2</sub> materials have already become a reference as excellent photocatalysts [35,36]. Furthermore, as TiO<sub>2</sub> (P25 Evonik) is a commercially available reference, Au/TiO<sub>2</sub> P25 is often prepared by the so-called “deposition–precipitation” method [37].

In this paper titania (TiO<sub>2</sub> SG) was prepared by a home-made sol-gel method inspired by the literature [38]. Its structure and surface were tuned by varying various synthesis parameters, including the temperature of the calcination step. Au NPs were subsequently loaded using sodium borohydride reduction of chloroauric acid in the presence of titania. The structural, surface, porosity, and optical properties, as well as the presence of oxygen vacancies, are discussed and compared to those of synthesized TiO<sub>2</sub> brookite, commercially available (TiO<sub>2</sub> P25, TiO<sub>2</sub> UV-100)-based materials, and correlated to photocatalytic activity.

## 2. Results

### 2.1. Structural Characterization (XRD)

The XRD pattern of the TiO<sub>2</sub> SG-X (X stands for the post-synthesis temperature) are presented in Figure 1a and compared to those of bare TiO<sub>2</sub> P25, TiO<sub>2</sub> brookite, TiO<sub>2</sub> UV100, and TiO<sub>2</sub> UV100-X (X stands for the calcination temperature, Figure 1b). The corresponding mean crystallite sizes, calculated from the Debye-Scherrer equation, are summarized in Table 1. One can observe that the uncalcined TiO<sub>2</sub> SG is relatively well crystallized and exhibits a major peak at 25.36°, assigned to (101) planes in anatase phase, in agreement with JCPDS file 00-021-1272 [39,40]. Traces of brookite and rutile could be observed but are difficult to analyze and quantify. Increasing the calcination temperature to 400 °C did not significantly improve the degree of crystallinity of anatase, but rather increased the relative concentration of the rutile phase (from 500 °C) at 27.42° (JCPDS file 00-004-0551, [39]). Calcining further at 500 °C resulted in further crystallization of the anatase and rutile phases, increase in the rutile phase content, with no significant change to brookite (JCPDS file 00-029-1360, [40]). A complete transformation into rutile, accompanied by better crystallinity (29 nm) of the resulting phase occurred after calcination at 600 °C. We can also mention that calcination of TiO<sub>2</sub> UV-100 at 350 °C led to an increased anatase mean crystallite size, which reached a value close to the one determined for TiO<sub>2</sub> P25, without formation of rutile.

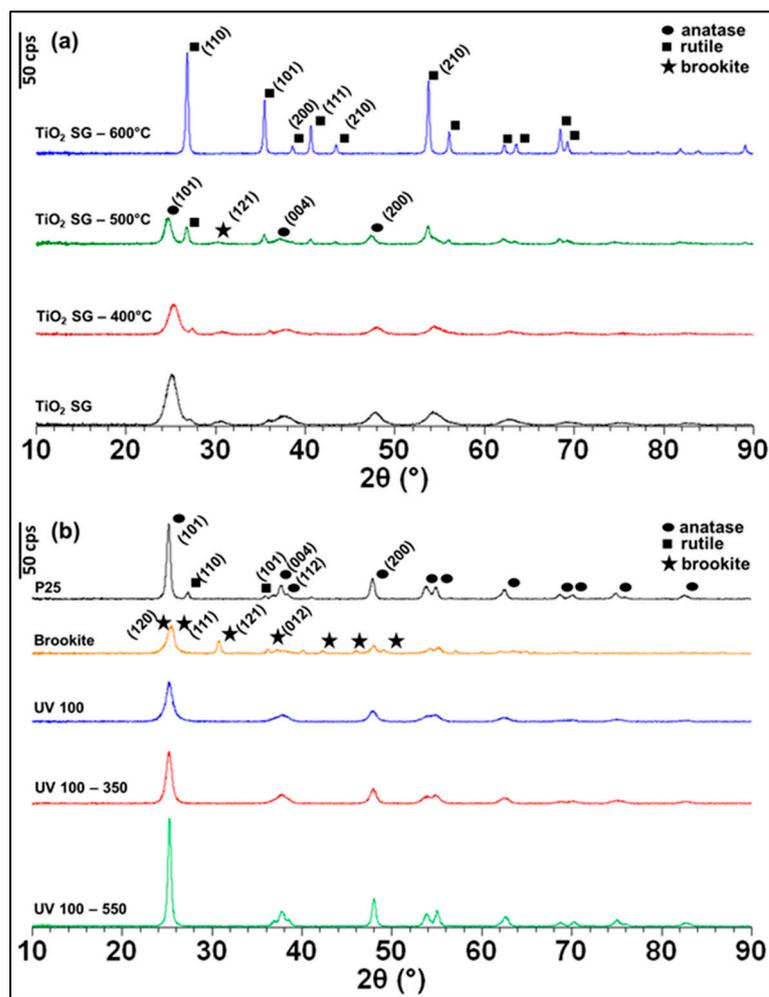


Figure 1. XRD pattern of (a) TiO<sub>2</sub> SG-X and (b) TiO<sub>2</sub> brookite and TiO<sub>2</sub> P25, and TiO<sub>2</sub> UV100-X commercial-based samples.

Table 1. TiO<sub>2</sub> mean crystallite size, surface area, porosity measurements, band-gap value. Experimental error of <sup>a</sup> 10%, <sup>b</sup> 8%, and <sup>c</sup> 5%.

	Mean Crystallite Size (nm) <sup>a</sup>			SBET (m <sup>2</sup> /g) <sup>b</sup>	V <sub>pore</sub> (cm <sup>3</sup> /g) <sup>b</sup>	Mean Pore Diameter (nm) <sup>b</sup>	E <sub>g</sub> (eV) <sup>c</sup>
	Anatase	Brookite	Rutile				
TiO <sub>2</sub> P25	17	/	23	55	0.20	≈30	3.20
TiO <sub>2</sub> brookite	/	19	/	150	0.18	3–5	3.20
TiO <sub>2</sub> UV100	11	/	/	315	0.33	<3	3.25
TiO <sub>2</sub> UV100-350	17	/	/	135	0.24	4.5	3.25
TiO <sub>2</sub> UV100-550	19	/	/	77	0.28	8.0	3.25
TiO <sub>2</sub> SG	6	7	n.d	295	0.19	<4	2.85
TiO <sub>2</sub> SG-400	6	10	n.d	200	0.22	<4	2.96
TiO <sub>2</sub> SG-500	10	11	19	75	0.11	<4	2.95
TiO <sub>2</sub> SG-600	/	/	29	n.d	n.d	n.d.	2.90

## 2.2. Surface Characterizations

### 2.2.1. BET Surface Area and Porosity Measurements

From the Brunauer, Emmett, and Teller (BET) measurements (Table 1, Figure 2), it can be seen that the TiO<sub>2</sub> P25 sample exhibited type-IV adsorption-desorption isotherm profiles with H<sub>2</sub> hysteresis, which are characteristic of mesoporous/macroporous solids with a mean pore diameter of ca. 30 nm. TiO<sub>2</sub> UV100 approximated type I behavior, which is characteristic of microporous solids with H3 hysteresis, attributed to rather uniform slot-type pores in accordance with its lower pore diameter (Table 1) and distribution (Figure 2d, pore size essentially below 3 nm). Increasing its calcination temperature to 350 and 550 °C yielded a mesoporous type-IV-like behavior, in line with the shift of the mean pore size from <3 nm to 4.5 and 8 nm. As for TiO<sub>2</sub> UV-100, brookite revealed a microporous type-I isotherm (Figure 2c) associated with type-H4 hysteresis, related to a non-uniform slot-type porosity, as confirmed by the corresponding broad pore size distribution (Figure 2d). From Figure 2a, one can observe that the TiO<sub>2</sub> SG-based materials (except for TiO<sub>2</sub> SG-600, whose porosity collapsed) showed a type-I microporous behavior, evidencing micropores with H<sub>2</sub>-hysteresis and revealing rather cylindrical channeled porosity. Figure 2b underlines that the TiO<sub>2</sub> SG-X samples exhibited the sharpest pore size distribution, centered at ca. 2.5–3.0 nm, with exclusive contribution of micropores. The corresponding pore volume increased with calcination at 400 °C, then diminished, to reach a very low value and surface area.


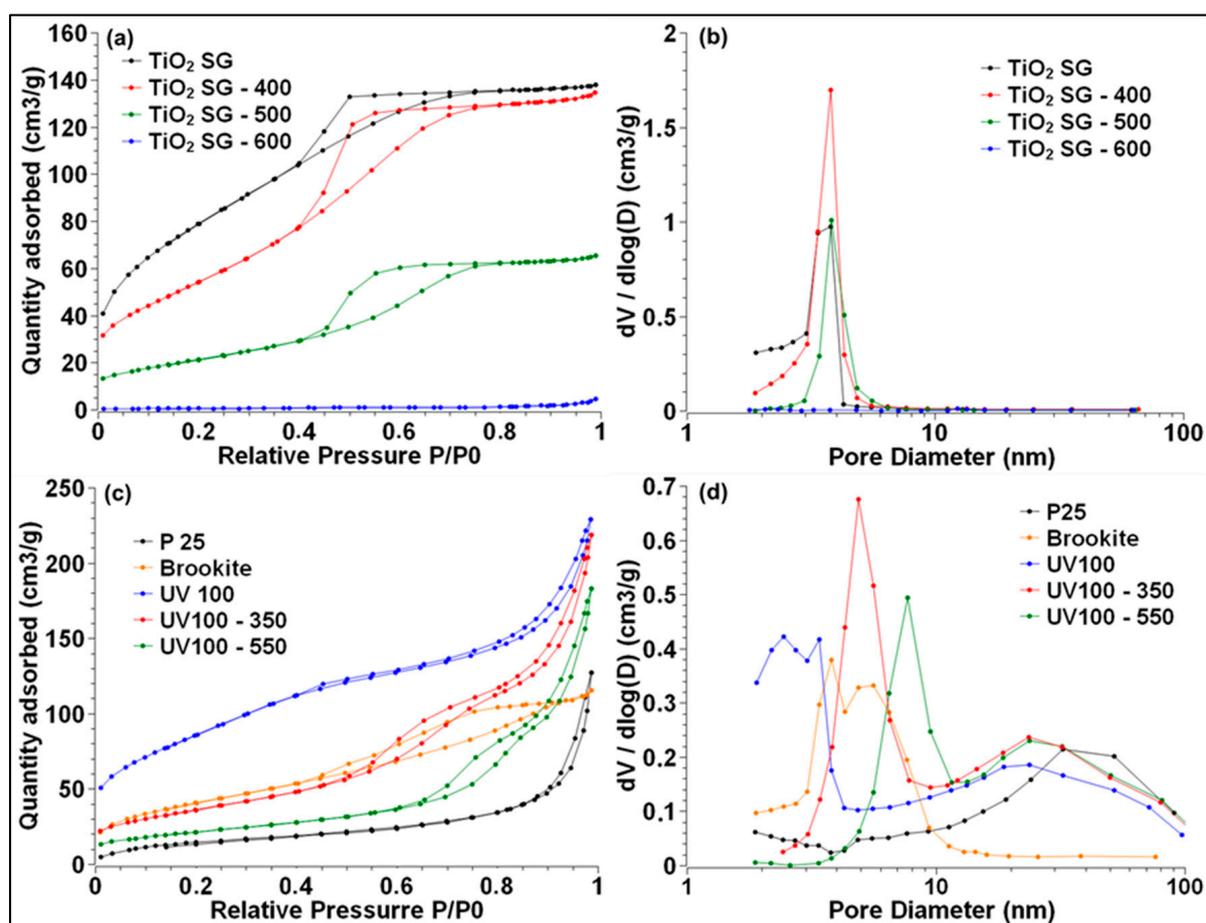


Figure 2. N<sub>2</sub> adsorption/desorption isotherms (a,c) and pore size distribution (b,d) of TiO<sub>2</sub> SG-X, and TiO<sub>2</sub> P25, TiO<sub>2</sub> Brookite, and TiO<sub>2</sub> UV100-X commercial-based samples, respectively.

### 2.2.2. Au NPs Deposition and UV-Vis Absorption Properties

Kubelka–Munk function determination from the different TiO<sub>2</sub> supports (Figure 3) showed the expected behavior for the commercial TiO<sub>2</sub> P25 and UV-100 samples (Figure 3b).

Calcination of TiO<sub>2</sub> UV100 seemed not to affect these properties. The synthesized TiO<sub>2</sub> brookite revealed the same absorption trend and edge, in accordance with band gap values of 3.20–3.25 eV. The as-synthesized TiO<sub>2</sub> SG (Figure 3a) exhibited, in addition to the standard anatase contribution, a visible light absorption contribution, whose origin could be attributed either to precursor residues and/or to oxygen vacancies. These hypotheses were confirmed by the large attenuation of the corresponding contribution tail by calcining at 400 °C. It must, however, be mentioned that calcining TiO<sub>2</sub> SG further induced a shift of the absorption edge towards higher wavelengths (as confirmed by the band-gap determination via a Tauc plot, using Kubelka–Munk formula, insert Figure 3a, correlated with the increase in rutile phase proportion (Table 1)).

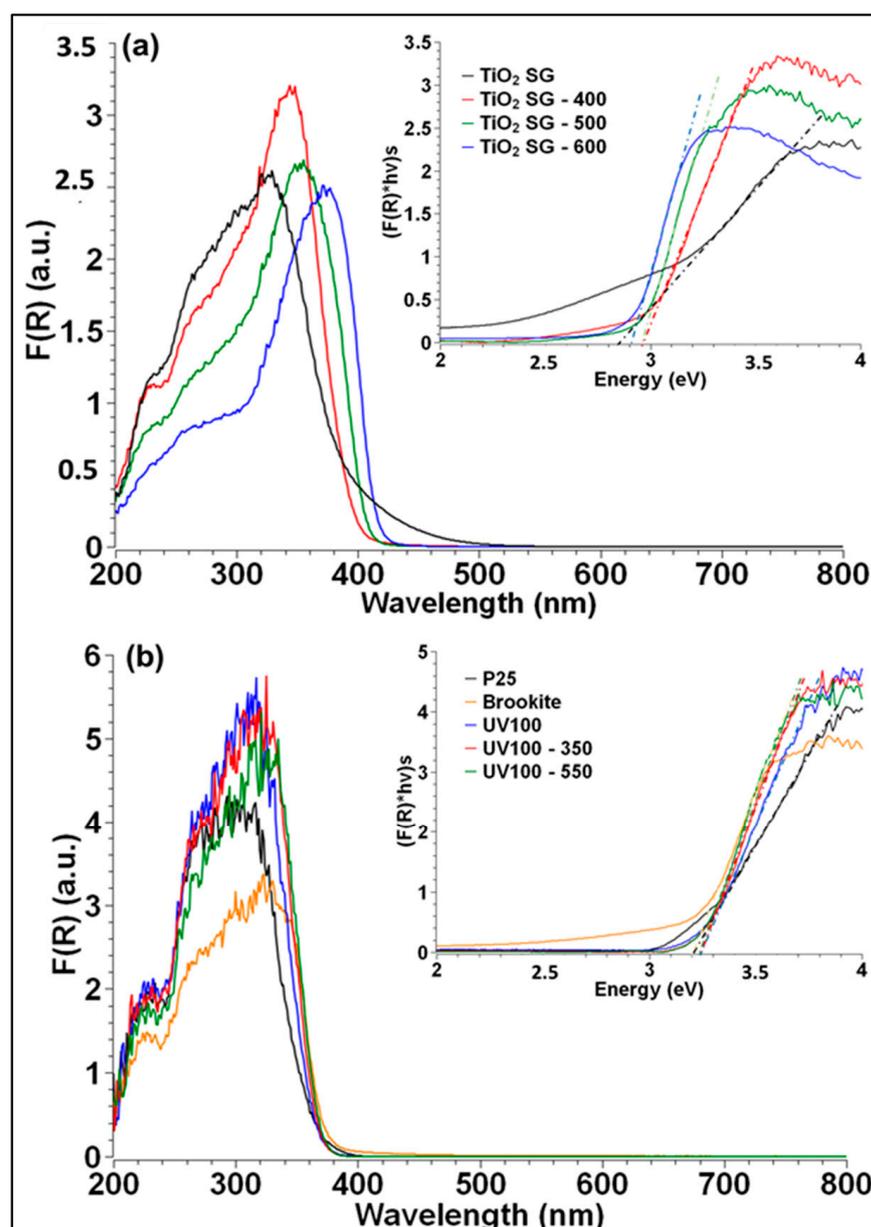

**Figure 3.** Kubelka–Munk function  $F(R)$  of (a) TiO<sub>2</sub> SG - X and (b) TiO<sub>2</sub> P25, TiO<sub>2</sub> Brookite, and TiO<sub>2</sub> UV-100 - X commercial-based samples, (Insert) Tauc plots.


The targeted Au content was 0.86 wt.% for all Au/TiO<sub>2</sub> photocatalysts. ICP-AES analyses showed that the Au deposition yield on some TiO<sub>2</sub> supports was high, varying from 92% to 98%, leading to Au/TiO<sub>2</sub> materials that all contained  $0.82 \pm 0.03$  wt.% gold (Table 2). From the Au/TiO<sub>2</sub> absorbance spectra (Figure 4), two contributions could be

distinguished, assigned respectively to TiO<sub>2</sub>, as discussed previously, and to Au NPs. The second contribution was indeed characteristic of the localized surface plasmon resonance (LSPR) of Au NPs. It was positioned between 541 and 562 nm, in line with Au NPs in interaction with a titania matrix [41]. The variations in terms of position, broadness, and intensity could be linked to variations in Au content, particles size, and morphology, and Au-TiO<sub>2</sub> interactions. The same shape of SPR as observed on Au/TiO<sub>2</sub> P25 and Au/TiO<sub>2</sub> UV100-350 (Figure 4b) confirmed the same Au content as found by ICP-AES and also suggested that both samples exhibited the same gold particle size and interaction with the support. Even if those samples showed almost the same Au content as Au/TiO<sub>2</sub> brookite, one could observe a more intense LSPR signal on the last one, which may have been due to the larger Au NP size, thus suggesting that the dominant brookite phase may have provided less nucleation sites for Au NPs, hence the extended growth over the few sites available. Calcining TiO<sub>2</sub> UV-100 at 550 °C resulted in a more intense signal, but also in a slight red-shift in the LSPR position, suggesting the presence of a broader size distribution of Au NPs, i.e., the occurrence of sintering and aggregation, and associated LSPR coupling. The slight shift towards higher wavelengths observed in the TiO<sub>2</sub> UV100 material may have been correlated with the presence of a larger amount of amorphous phase.

**Table 2.** Au content and deposition yield determined from ICP. Experimental error of 6%.

Support	Au <sub>(Th)</sub> (wt.%)	Au <sub>(Real)</sub> (wt.%)	Au Deposition Yield (%)	λ <sub>SPR</sub> (nm)
TiO <sub>2</sub> P25	0.86	0.79	92	548
TiO <sub>2</sub> Brookite	0.86	0.82	95	550
TiO <sub>2</sub> UV100				556
TiO <sub>2</sub> UV100-350	0.86	0.81	94	548
TiO <sub>2</sub> UV100-550				562
TiO <sub>2</sub> SG				561
TiO <sub>2</sub> SG-400	0.86	0.84	98	556
TiO <sub>2</sub> SG-500				559
TiO <sub>2</sub> SG-600				541

Despite the similar Au contents of Au/TiO<sub>2</sub> P25, Au/TiO<sub>2</sub> UV 100-350, and Au/TiO<sub>2</sub> SG-400, the LSPR of Au/TiO<sub>2</sub> SG-400 was more intense and somewhat broader (Figure 4), suggesting the presence of a much broader size distribution of Au NPs. This may have arisen from the particularly low TiO<sub>2</sub> anatase mean crystallite size (6 nm), which was the lowest observed among the different TiO<sub>2</sub> supports and which was also close to the Au NP size generally produced by the method of deposition used, i.e., 3–5 nm [42,43]. The LSPR intensity was further enhanced after calcination at 500 °C (Figure 4a), as the anatase mean crystal size slightly increased, the surface area diminished, and the rutile phase appeared. Finally, after calcination at 600 °C, the LSPR signal was drastically lowered, in correlation with the huge decrease in surface area and the presence of an exclusively rutile phase.

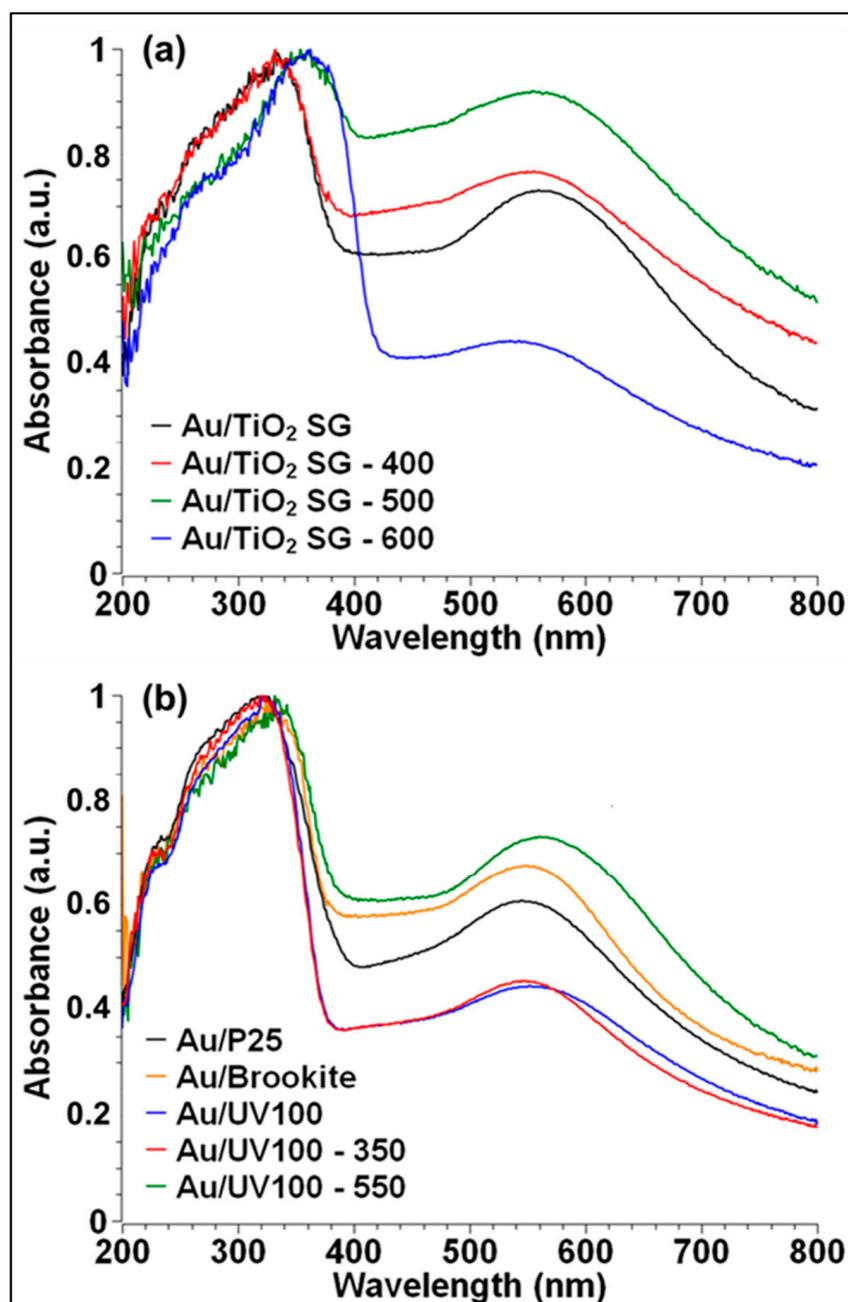


**Figure 4.** UV-Visible spectra of (a) Au/TiO<sub>2</sub> SG – X and (b) Au/TiO<sub>2</sub> P25, Au/TiO<sub>2</sub> Brookite and Au/TiO<sub>2</sub> UV-100 – X commercial-based samples.

### 2.3. Gas-Phase CO<sub>2</sub> Photoreduction Activity


Considering both the CH<sub>4</sub> productivity and electronic selectivity, Au/TiO<sub>2</sub> SG-400 was the best performing photocatalyst, leading to a mean rate of CH<sub>4</sub> production of 50  $\mu\text{mol h}^{-1}\text{g}^{-1}$  over 5 h (Figure 5a). This activity was higher than those reported by the Au/TiO<sub>2</sub> commercial-based reference materials (Figure 5b). Amongst these latter samples, one could observe that the TiO<sub>2</sub> P25 and TiO<sub>2</sub> UV-100 supports led to the same CH<sub>4</sub> productivity. However, the selectivity was much higher for the former. Applying and increasing the thermal treatment on TiO<sub>2</sub> UV-100 resulted in decreasing CH<sub>4</sub> productivity. Au/TiO<sub>2</sub> brookite revealed a moderate CH<sub>4</sub> production and selectivity. From Figure 5a, it can clearly be observed that an optimum calcination temperature of 400 °C was required for TiO<sub>2</sub> SG-based supports. Further increasing the calcination temperature is detrimental for both CH<sub>4</sub> production and selectivity, as is the absence of calcination. Comparing all the

samples from a CH<sub>4</sub> productivity criteria point of view, the following order was obtained: Au/TiO<sub>2</sub> SG-400 > Au/TiO<sub>2</sub> UV100 ≈ Au/TiO<sub>2</sub> P25 > Au/TiO<sub>2</sub> UV100-350 > Au/TiO<sub>2</sub> SG > Au/TiO<sub>2</sub> SG-500 > Au/TiO<sub>2</sub> brookite > Au/TiO<sub>2</sub> UV100-550 > Au/TiO<sub>2</sub> SG-600.

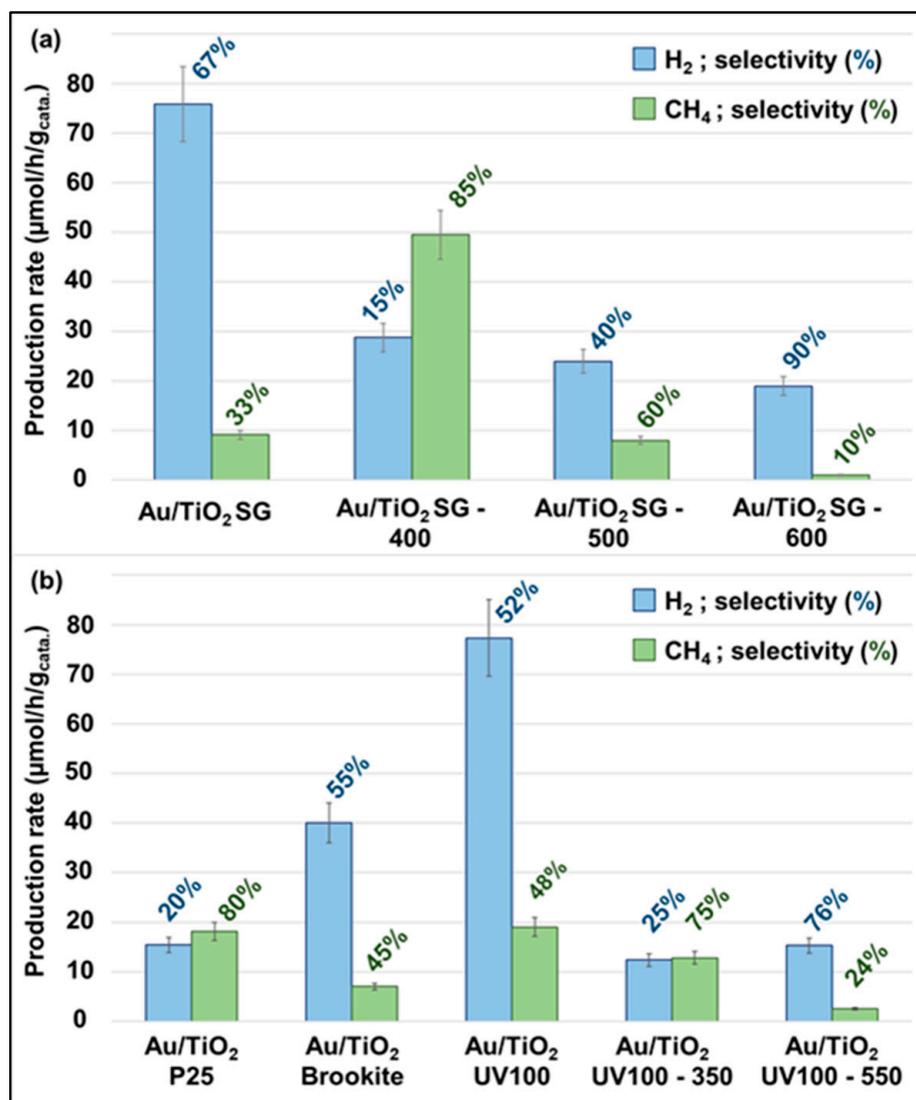

**Figure 5.** Specific H<sub>2</sub> and CH<sub>4</sub> production rate and electronic selectivity (CO<sub>2</sub>/H<sub>2</sub>O = 96/4 mol. ratio), after 5 h at 0.3 mL/min continuous flow under solar light irradiation of (a) Au/TiO<sub>2</sub> SG-X and (b) Au/TiO<sub>2</sub> P25, Au/TiO<sub>2</sub> brookite and Au/TiO<sub>2</sub> UV100-X commercial-based samples.


As all those photocatalysts exhibit large differences in surface area, normalized reaction rates were calculated (Figure 6), allowing comparison of the intrinsic activities. Considering the normalized CH<sub>4</sub> production rates, the following order of activity was observed: Au/TiO<sub>2</sub> P25 > Au/TiO<sub>2</sub> SG-400 > Au/TiO<sub>2</sub> SG-500 > Au/TiO<sub>2</sub> UV100-350 > Au/TiO<sub>2</sub> UV100 > Au/TiO<sub>2</sub> brookite > Au/TiO<sub>2</sub> SG ≈ Au/TiO<sub>2</sub> SG-500 > Au/TiO<sub>2</sub> SG-600, suggesting that the surface area parameter is an impacting parameter but not the only one.

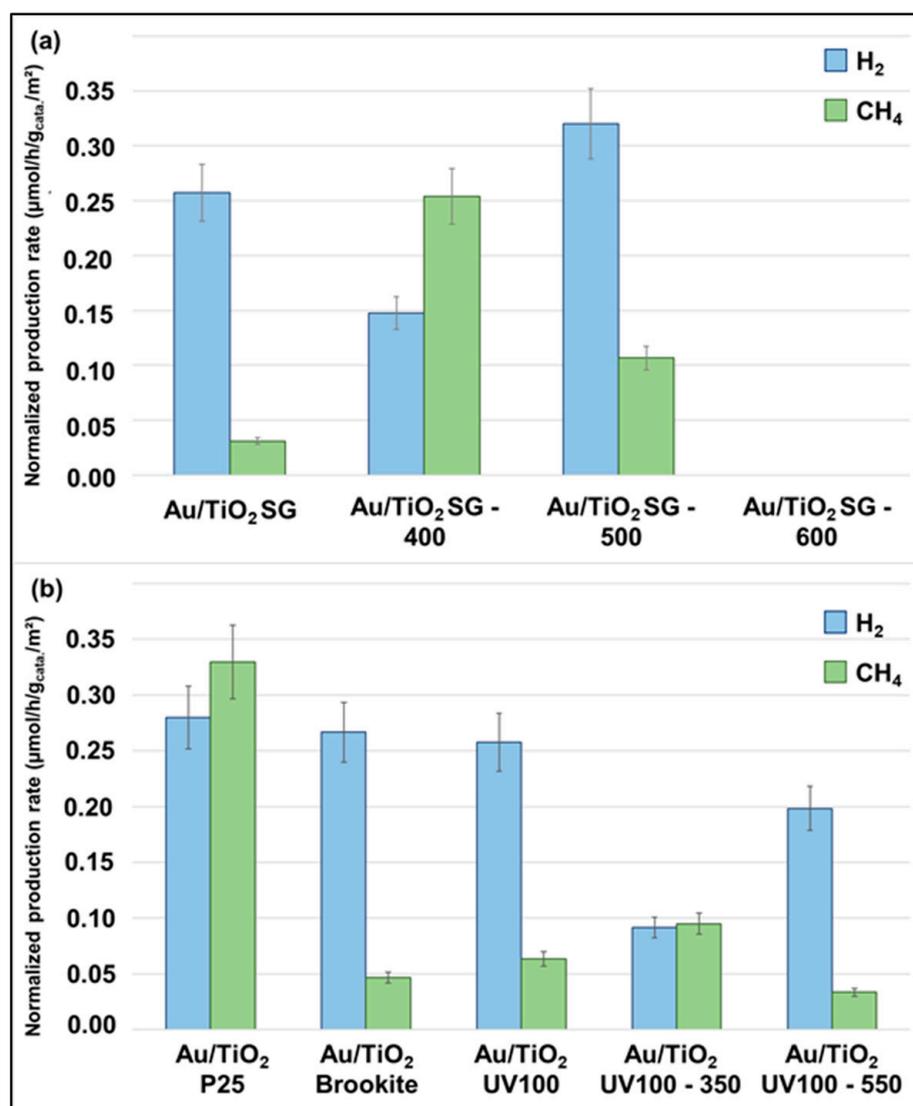


**Figure 6.** Specific normalized H<sub>2</sub> and CH<sub>4</sub> production rates (CO<sub>2</sub>/H<sub>2</sub>O = 96/4 mol. ratio) at 0.3 mL/min continuous flow under solar light irradiation of (a) Au/TiO<sub>2</sub> SG – X and (b) Au/TiO<sub>2</sub> P25, Au/TiO<sub>2</sub> Brookite and Au/TiO<sub>2</sub> UV100 – X commercial-based samples.

#### 2.4. TRMC Measurements

The lifetime of charge-carriers is completely described by the TRMC decay ( $I(t)$ ) [44]. This decay is complex and may be due to different mechanisms that govern free electron mobility (considered as the most mobile charge carriers on TiO<sub>2</sub>-based materials), such as recombination and trapping. At a 360 nm excitation pulse (Figure 7), one could clearly observe that the TiO<sub>2</sub> P25 support showed a higher charge carrier generation and free electron lifetime compared to the TiO<sub>2</sub> SG-X supports. Furthermore, in this latter series, neither an increase in calcination temperature from 400 to 500 °C nor Au NPs deposition seemed to induce any differences in terms of the charge carrier generation and lifetime (Figure 7b). Nevertheless, concerning Au/TiO<sub>2</sub> UV-100-based materials, calcining at 350 °C resulted in limiting both the charge carrier production and free electron lifetime decay, which may be attributed to trapping by Au NPs. Under visible light pulses at 450 nm (Figure 8), only very few charge carriers were generated on the Au/TiO<sub>2</sub> SG-X and Au/TiO<sub>2</sub> UV100-350 samples.

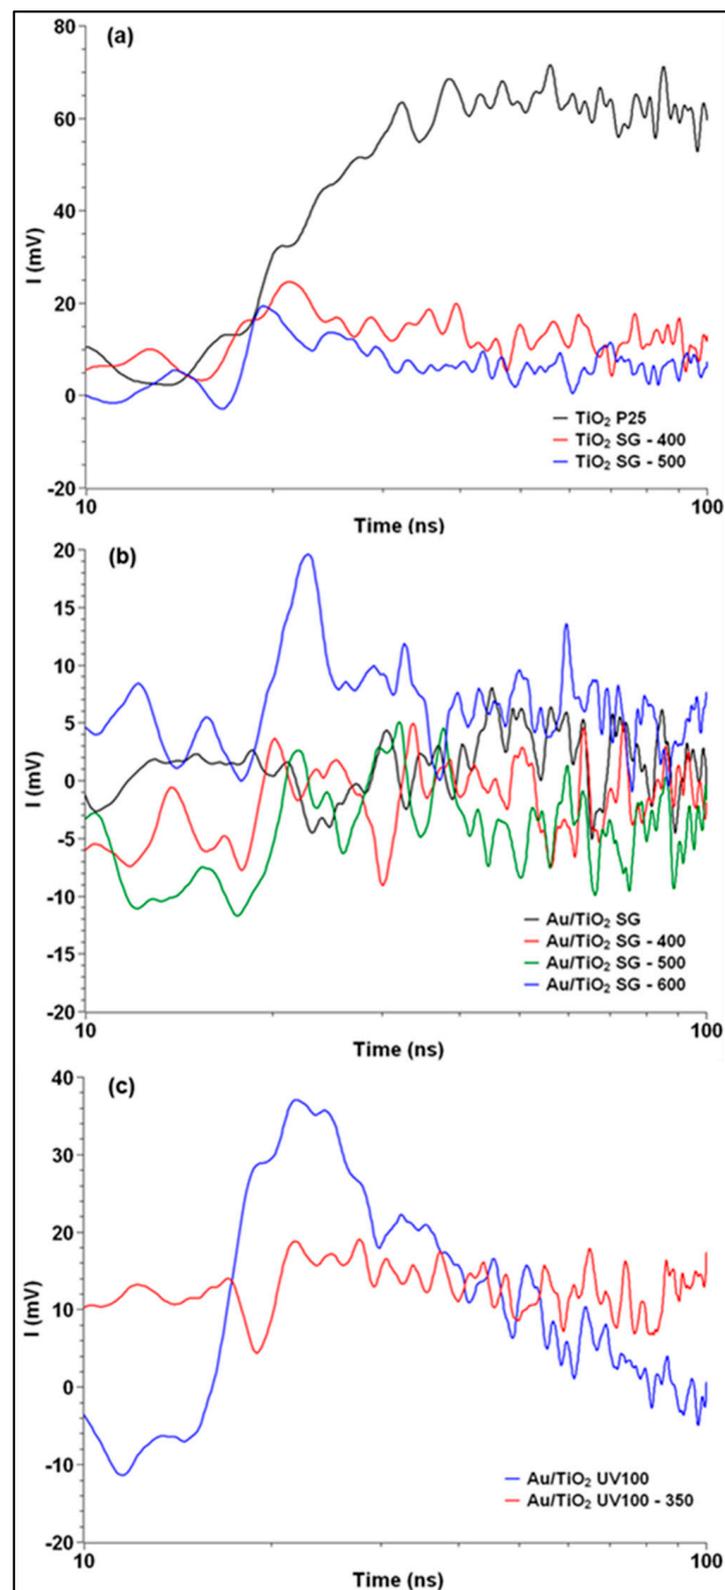


**Figure 7.** TRMC signals at 366 nm obtained on (a)  $\text{TiO}_2$  P25,  $\text{TiO}_2$  SG-400 and  $\text{TiO}_2$  SG-500 supports (b) Au/ $\text{TiO}_2$  SG-X and (c) and Au/ $\text{TiO}_2$  UV100-350 commercial-based samples.

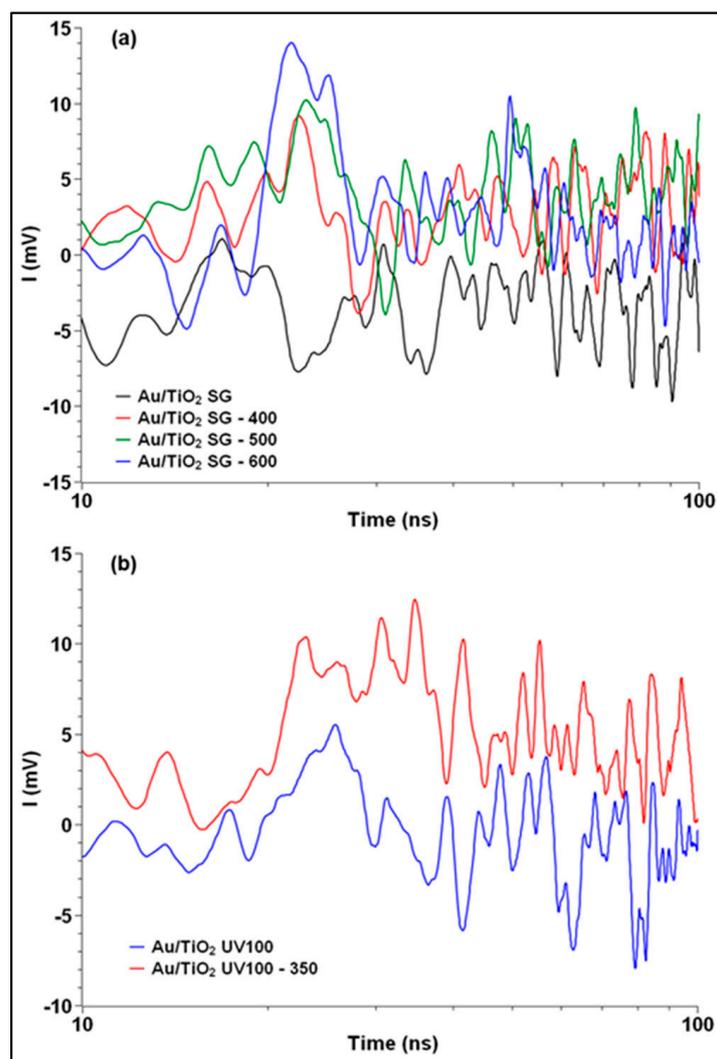

**Figure 8.** TRMC signals at 450 nm obtained on (a) Au/TiO<sub>2</sub> SG-X and (b) Au/TiO<sub>2</sub> UV100-350 commercial-based samples.

### 2.5. EPR Measurements

Electron paramagnetic resonance (EPR) measurements were conducted for the TiO<sub>2</sub> SG-400 support, which outperformed all the other studied samples regarding the total CH<sub>4</sub> productivity criteria, in order to detect potential active sites/defects in TiO<sub>2</sub> (Figure 9). Three types of EPR active centers were identified on TiO<sub>2</sub>: the signals at 336, 332.5, and 330.0 mT (\*) were assigned to the NO species captured at the surface of the porous TiO<sub>2</sub> [45,46]. The other visible signal for TiO<sub>2</sub> was a combination of (1) unpaired electrons trapped on an oxygen vacancy V<sub>o</sub><sup>+</sup>, at g = 2.00 (332 mT; Δ), a common defect created in various metal oxides [47,48]; (2) the substitutional N (the weak signal indicated by I); and (3) the paramagnetic N<sup>2-</sup> nitrogen species in [O-Ti<sup>4+</sup>-N<sup>2-</sup>-Ti<sup>4+</sup>] units (signal marked II) [49]. This last signal might have originated from the nitric acid used for the sol gel synthesis and not eliminated due to the mild annealing temperature used for the TiO<sub>2</sub> SG-400.

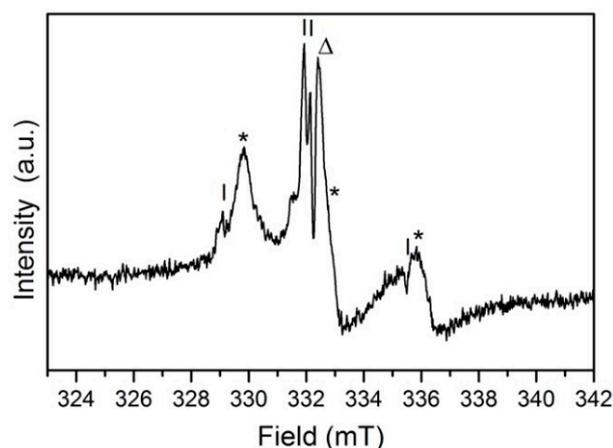

**Figure 9.** EPR signal for TiO<sub>2</sub> SG-400 recorded at 100 K.

### 3. Discussion

In order to obtain more insights into the structure/activity correlation, based on the aforementioned characterizations and solar-light photocatalytic CO<sub>2</sub> reduction activity, one may assume that the main impacting parameters driving CH<sub>4</sub> productivity are linked to the surface area/porosity type and volume/access to porosity, size/density of specific exposed TiO<sub>2</sub> facets, and presence/dispersion/size of Au NPs, as well as the presence/density of surface vacancies. Indeed, Au/TiO<sub>2</sub> SG-400 was the material exhibiting the highest productivity towards CH<sub>4</sub> formation (in terms of production and electronic selectivity). It was observed that its activity was first related to its high surface area and large and exclusive microporosity, presumably leading to larger amounts of adsorbed CO<sub>2</sub> molecules. Regarding charge carrier generation, it was seen from the TRMC measurements that TiO<sub>2</sub> P25 was the semiconductor generating the largest amount of long-life time charge carriers from UV-A activation, although some other TiO<sub>2</sub> supports also exhibited minor charge carrier generation at 450 nm. Among the other influencing factors, anatase crystallite size and orientation may play a determining role. Indeed, TiO<sub>2</sub> SG-400 and TiO<sub>2</sub> SG showed the smallest crystallite size (6 nm) and the largest surface area, even if the latter exhibited lower pore volumes, probably resulting from obstruction of part of the microporosity (hindering CO<sub>2</sub> adsorption) by the residues of precursors, which could be removed by applying a thermal treatment. Consequently, knowing that anatase (101) facets are the most stable [50], it can be assumed that these two TiO<sub>2</sub> SG-materials exposed a high density of anatase (101) facets. In addition, it may be assumed, comparing TiO<sub>2</sub> SG and TiO<sub>2</sub> SG-400, that the former was characterized by a larger contribution of amorphous phase, which was detrimental to the charge carrier mobility and thus the separation. One can also mention that oxygen vacancies, and more precisely the density of oxygen vacancies, confirmed for the TiO<sub>2</sub> SG-400 material, also played a determining role in both the CO<sub>2</sub> adsorption and activation step and in the charge carrier transport, as previously reported in the literature [27–30]. In addition, the deposited Au NPs likely acted as supplementary electron traps, as well as co-catalysts. It seems that the intensity of the corresponding TiO<sub>2</sub> SG-based SPR signal increased with the temperature of the post-treatment, up to 500 °C, leading to a modification of the Au-TiO<sub>2</sub> interaction, which obviously depended of the surface area, crystallinity, and exposed phases of TiO<sub>2</sub>.

### 4. Materials and Methods

Titanium dioxide (TiO<sub>2</sub>) Aeroxide<sup>®</sup> P25 was purchased from Evonik Industries (Essen, Germany) and TiO<sub>2</sub> Hombikat UV-100 was purchased from Sachtleben Chemie GmbH (Duisburg, Germany). Both were used without further purification. TiO<sub>2</sub> Brookite was grown hydrothermally, following a previously reported procedure [51]. Briefly, 3.75 mL of titanium(IV) bis (ammonium lactate) dihydroxide (50 wt.%, Sigma-Aldrich, St. Louis, MO, USA) was mixed with 33.75 mL of 6.0 M urea aqueous solution in a 100 ml-hydrothermal

reactor Teflon cup. Hydrothermal synthesis was carried out at 160 °C for 24 h. After cooling, solid product was washed with bi-distilled water several times and finally dried in a lyophilizer overnight. Titanium(IV) butoxide (Ti(OBu)<sub>4</sub> [Bu = CH<sub>2</sub>CH<sub>2</sub>CH<sub>2</sub>CH<sub>3</sub>], purum, ≥97%, Sigma Aldrich), nitric acid (HNO<sub>3</sub>, ACS reagent 70%, Sigma Aldrich), ethanol (EtOH, CH<sub>3</sub>CH<sub>2</sub>OH, ≥98%, Sigma Aldrich), chloroauric acid (HAu<sup>III</sup>Cl<sub>4</sub>·3H<sub>2</sub>O, ≥99.9% trace metal basic, Alfa Aesar, Haverhill, MA, USA), and sodium borohydride (≥98%, Sigma Aldrich) were used without any further purification.

#### 4.1. TiO<sub>2</sub> Sol Gel (SG) Synthesis and Hombikat UV-100 Treatment

TiO<sub>2</sub> SG was obtained via a sol-gel process, following the protocol below. In a first beaker, 5 mL of Ti(OBu)<sub>4</sub> was mixed with 20 mL EtOH and heated at 40 °C in an oil bath. In a second beaker, 5 mL of H<sub>2</sub>O and 5 mL of EtOH were mixed with 0.9 mL of HNO<sub>3</sub>. After 1 h under magnetic stirring, the solution containing HNO<sub>3</sub> was added drop by drop into the solution containing the Ti precursor. The whole solution was kept at 40 °C (oil bath) under magnetic stirring for 2 h. Then, the gel was dried in an oven under static air at 80 °C for 48 h. After that, the sample was crushed into a fine powder and calcined in a tubular furnace at 400 °C for 2 h, with a heating ramp of 5 °C/min under air flow (100 cm<sup>3</sup>/min). A parametric study was carried out regarding the temperature of calcination (400, 500, and 600 °C).

The TiO<sub>2</sub> UV-100 was used as purchased but also thermally treated at 350 °C or 550 °C in static air for 4 h, with a heating rate of 10 °C/min, in order to remove the amorphous phase.

The resulting samples were labelled TiO<sub>2</sub> SG-X and TiO<sub>2</sub> UV100-X (X stands for the calcination temperature).

#### 4.2. Au Nanoparticles (NPs) Deposition

Gold metal nanoparticles (Au NPs) (Au: 0.86 wt.% theoretical value) were loaded onto TiO<sub>2</sub> via an impregnation–reduction method [52] using HAu<sup>III</sup>Cl<sub>4</sub> as the precursor of gold and NaBH<sub>4</sub> as the reducing agent. In a 100 mL flask, 400 mg of TiO<sub>2</sub> was mixed with 40 mL of H<sub>2</sub>O for 5 min. Then, 80 µL of an aqueous solution of HAu<sup>III</sup>Cl<sub>4</sub>·3H<sub>2</sub>O (2.2 × 10<sup>−1</sup> M) was added and the mixture was left under magnetic stirring (1000 rpm) for 45 min while the precursor is impregnated. Then, 1 mL of a fresh solution of NaBH<sub>4</sub> was added to the mixture. The NaBH<sub>4</sub> concentration solution was adjusted, in order to have a ratio NaBH<sub>4</sub>/M<sub>pr.</sub> = 5. After the reduction, the mixture was stirred for 15 min (1000 rpm) and then the obtained material was filtered and washed with 1 L of distilled water. To finish, the resulting Au/TiO<sub>2</sub> was dried in an oven at 100 °C overnight (air). The same deposition method was applied to all the different TiO<sub>2</sub> supports.

#### 4.3. Characterization Methods

The X-ray diffraction apparatus used was a Bruker D8 Advance (Billerica, MA, USA) diffractometer equipped with a Lynxeye XE detector operating at 40 kV and 40 mA in  $\theta/\theta$  mode. The source of the X-Rays was a copper anticathode using the K $\alpha$  line at 1.5418 Å. In order to obtain normalized diffractograms, a fixed amount of 50 mg of the sample was placed on a plastic holder. The acquisition of diffractograms was performed in scanning mode in steps of  $2\theta = 10^\circ$  to  $2\theta = 90^\circ$  with a step of 0.05 and a counting time of 5 s per step. The mean crystal thickness was calculated using the Debye–Scherrer equation based on the width at half maximum and the position of the most intense peak.

The nitrogen adsorption–desorption isotherms were obtained using a Micromeritics Asap 2420 porosimeter (Norcross, GA, USA). The analysis was carried out at the nitrogen liquefaction temperature (77 K). The materials were degassed at 150 °C under primary vacuum for 5 h with a temperature rise of 10 °C/min, in order to desorb water and adsorbed molecules from their surfaces. The specific surfaces of the materials were calculated from the adsorption isotherm using the BET method. The pore size distribution could be calculated from the desorption data, using the BJH method specifically for mesoporous solids.

UV-vis absorption spectra were recorded on a Perkin Elmer 950 spectrophotometer (Waltham, MA, USA) fitted with a Labsphere 100 nm integrating sphere. The spectra

were acquired in reflection mode (diffuse reflectance). The diffuse reflectance spectra were converted to Kubelka–Munk units via the equation:  $F(R) = \frac{(1-R)^2}{2R}$ . To obtain the band gap ( $E_g$ ) of the semiconductor (SC), the Tauc equation  $(F(R) \cdot h\nu)^S = (h\nu - E_g)$  was used, where  $h$  is the Planck constant,  $\nu$  is the frequency, and  $S$  is a coefficient, which is  $\frac{1}{2}$  in the case of an indirect gap SC and 2 in the case of a direct band gap SC ( $\frac{1}{2}$  for  $\text{TiO}_2$ ).

The charge-carrier lifetimes under illumination were determined through microwave absorption experiments using the time resolved microwave conductivity method (TRMC) [42]. The incident microwaves were generated by a Gunn diode of the  $K_\alpha$  band at 30 GHz. The pulsed light source was an OPO laser (EKSPLA, NT342B, Vilnius, Lithuania) tunable from 225 to 2000 nm. It delivered 8 ns fwhm pulses with a frequency of 10 Hz.

Elemental analyzes of the samples were performed using inductively coupled plasma atomic emission spectrometry (ICP-AES, Varian 720 ES, Palo Alto, CA, USA) with a detection sensitivity for gold of 0.1 mg/mL.

EPR measurements were performed on a Bruker ESP300 (Billerica, MA, USA) apparatus using the X band (10 GHz) at 100 K, and 40 mg of sample was inserted in a quartz tube of 4 mm diameter.

#### 4.4. Photocatalytic Tests

Photocatalytic setup has previously been described elsewhere [37]. During the test, a continuous flowing reaction mixture ( $\text{CO}_2 + \text{H}_2\text{O}$ ) flow ( $0.3 \text{ mL} \cdot \text{min}^{-1}$ ) passes through a light-transparent photoreactor (6 mL) equipped with a Hg lamp, simulating artificial solar light (150 W Ceramic-Metal-Halide Lamp, total photon flux for the whole lamp spectrum:  $0.028 \text{ mol} \cdot \text{s}^{-1} \cdot \text{m}^{-2}$ ). The irradiated surface was  $19.6 \text{ cm}^2$ . For the photocatalytic tests, 50 mg of the materials are mixed in ethanol and deposited on a 50 mm diameter glass disk by evaporation at  $100^\circ\text{C}$ . The surface concentration of photocatalyst on the glass disc was  $\approx 25 \text{ g} \cdot \text{m}^{-2}$ . The glass disk was then put in the reactor and the pilot was purged for 5 min with  $\text{CO}_2$  flow ( $>100 \text{ mL} \cdot \text{min}^{-1}$ ), to remove air and other gas impurities. Before starting the test, the pilot was run with a  $\text{CO}_2$  gas flow ( $0.3 \text{ mL} \cdot \text{min}^{-1}$ ) without illumination, to control the absence of products and the quantity of  $\text{CO}_2$ . Finally, products from the reactor were analyzed using an online micro-GC (Agilent 3000A SRA instrument, Santa Clara, CA, USA). Finally, the lamp is switched on and the duration of the test was 5 h. Production rates were calculated according to the following equation:

$$r_X \left( \text{mol} \cdot \text{h}^{-1} \cdot \text{g}^{-1} \right) = \frac{[X] \times 10^{-6} \times (\text{flow rate}) \times 60}{V_m \times m_{\text{photocat}}}$$

where  $[X]$ : Concentration in ppm,  $m_{\text{photocat}}$ : mass of photocatalyst (g), the flow rate was  $0.0003 \text{ L} \cdot \text{min}^{-1}$ , and  $V_m = 24.79 \text{ L} \cdot \text{mol}^{-1}$  (STP conditions).

Electronic selectivity was calculated using the following equations:

$$\text{CH}_4 \text{ Selectivity} = \frac{8[\text{CH}_4]}{8[\text{CH}_4] + 2[\text{H}_2]}$$

$$\text{H}_2 \text{ Selectivity} = 1 - \text{CH}_4 \text{ Selectivity}$$

## 5. Conclusions

To conclude, in the present paper, Au/ $\text{TiO}_2$  photocatalysts were studied, characterized, and compared for  $\text{CO}_2$  photocatalytic gas-phase reduction, with regards to the nature of the  $\text{TiO}_2$  semi-conductor support. It was shown that the surface area, porosity  $\text{TiO}_2$  crystallographic phase, density of specific exposed facets, and oxygen vacancies were the key factors driving  $\text{CH}_4$  productivity under solar-light activation. Understanding the main impacting factors made it possible to design, via simple sol-gel synthesis, an optimal  $\text{TiO}_2$ -based photocatalyst, exhibiting the best compromise between these impacting factors. In this work, 0.84 wt.% Au/ $\text{TiO}_2$  SG calcined at  $400^\circ\text{C}$  exhibited the best performance, leading to a continuous mean  $\text{CH}_4$  production rate of  $50 \mu\text{mol} \cdot \text{h}^{-1} \cdot \text{g}^{-1}$  over 5 h and an

electronic selectivity of 85%, mainly due to UV-driven activity. This highest activity was attributed to the high surface area and accessible microporous volume, high density of exposed TiO<sub>2</sub> (101) facets, and oxygen vacancies acting as reactive defects sites for CO<sub>2</sub> adsorption/activation/dissociation and charge carrier transport.

**Author Contributions:** Conceptualization, V.K., T.C., C.M. (Clément Marchal); methodology, T.C., Q.X., L.H., C.M. (Caroline Mary), C.M. (Clément Marchal), P.F., C.C.-J.; formal analysis, C.M. (Clément Marchal), C.M. (Caroline Mary), L.H., Q.X., L.S., C.C.-J., V.C., T.C., L.S.; investigation, T.C., V.K., C.M. (Clément Marchal); supervision, V.K., V.C., T.C., J.T., T.H., P.F.; data curation, T.C., C.M. (Clément Marchal), C.M. (Caroline Mary), L.H., V.K., L.S., P.F.; writing-original draft preparation, V.K., C.M. (Clément Marchal); writing-review and editing, V.K., T.C., V.C., C.M. (Clément Marchal). All authors have read and agreed to the published version of the manuscript.

**Funding:** This research was funded by the European Community, (projects H2020-LC-SC3-2019-NZE-RES-CC), grant agreement number 884444. Leila Hammoud wants to thank the « Centre Islamique d’Orientation et de l’Enseignement supérieur » (CIOES) for her PhD. fellowship. Qingyang Xi wants to thank the “China Scholarship Council” (CSC) for his PhD. fellowship (File N°: 201908410202).

**Data Availability Statement:** Data can be available on request from the corresponding authors.

**Acknowledgments:** The authors are very grateful to Nolwenn Le Breton and Bertrand Vileno from the “Institut de Chimie” of Strasbourg for the EPR measurements.

**Conflicts of Interest:** The authors declare no conflict of interest.

## References

1. Inoue, T.; Fujishima, A.; Konishi, S.; Honda, K. Photoelectrocatalytic Reduction of Carbon Dioxide in aqueous Suspensions of Semiconductor Powders. *Nature* **1979**, *277*, 637. [[CrossRef](#)]
2. Kubacka, A.; Fernandez-Garcia, M.; Colon, G. Advanced Nanoarchitectures for Solar Photocatalytic Applications. *Chem. Rev.* **2012**, *112*, 1555–1614.
3. Neatu, S.; Macia-Agullo, J.A.; Garcia, H. Solar Light Photocatalytic CO<sub>2</sub> Reduction: General Considerations and Selected Bench-Mark Photocatalysts. *Int. J. Mol. Sci.* **2014**, *15*, 5246–5262. [[CrossRef](#)]
4. LianJun, L.; Ying, L. Understanding the Reaction Mechanism of Photocatalytic Reduction of CO<sub>2</sub> with H<sub>2</sub>O on TiO<sub>2</sub>-Based Photocatalysts: A Review. *Aerosol Air Qual. Res.* **2014**, *14*, 453–469.
5. Nguyen, T.P.; Nguyen, D.L.T.; Nguyen, V.-H.; Le, T.-H.; Vo, D.N.; Trinh, Q.T.; Bae, S.-R.; Chae, S.Y.; Kim, S.Y.; Le, Q.V. Recent Advances in TiO<sub>2</sub>-Based Photocatalysts for Reduction of CO<sub>2</sub> to Fuels. *Nanomaterials* **2020**, *10*, 337. [[CrossRef](#)] [[PubMed](#)]
6. Shehzad, N.; Tahir, M.; Johari, K.; Murugesan, T.; Hussain, M. A critical review on TiO<sub>2</sub> based photocatalytic CO<sub>2</sub> reduction system: Strategies to improve efficiency. *J. CO<sub>2</sub> Util.* **2018**, *26*, 98–122. [[CrossRef](#)]
7. Li, X.; Zhuang, Z.; Li, W.; Pan, H. Photocatalytic reduction of CO<sub>2</sub> over noble metal-loaded and nitrogen-doped mesoporous TiO<sub>2</sub>. *Appl. Catal. A.* **2012**, *429–430*, 31–38. [[CrossRef](#)]
8. Linic, S.; Aslam, U.; Boerigter, C.; Morabito, M. Photochemical transformations on plasmonic metal nanoparticles. *Nat. Mater.* **2015**, *14*, 567–576.
9. Jia, J.; Wang, H.; Lu, Z.; O’Brien, P.G.; Ghossoub, M.; Duchesne, P.; Zheng, Z.; Li, P.; Qiao, Q.; Wang, L.; et al. Photothermal Catalyst Engineering: Hydrogenation of Gaseous CO<sub>2</sub> with High Activity and Tailored Selectivity. *Adv. Sci.* **2017**, *4*, 1700252. [[CrossRef](#)]
10. Lee, D.-E.; Kim, D.J.; Devthade, V.; Jo, W.-K.; Tonda, S. Size-dependent selectivity and activity of highly dispersed sub-nanometer Pt clusters integrated with P25 for CO<sub>2</sub> photoreduction into methane fuel. *Appl. Surf. Sci.* **2022**, *584*, 152532. [[CrossRef](#)]
11. Barrocas, B.T.; Ambrozova, N.; Koci, K. Photocatalytic Reduction of Carbon Dioxide on TiO<sub>2</sub> Heterojunction Photocatalysts—A review. *Materials* **2022**, *15*, 967. [[CrossRef](#)] [[PubMed](#)]
12. Low, J.; Yu, J.; Jaroniec, M.; Wageh, S.; Al-Ghamdi, A.A. Heterojunction Photocatalysts. *Adv. Mater.* **2017**, *29*, 1601694.
13. Wang, L.; Zhang, Z.; Han, Q.; Liu, Y.; Zhong, J.; Chen, J.; Huang, J.; She, H.; Wang, Q. Preparation of CdS-P25/ZIF-67 composite material and its photocatalytic CO<sub>2</sub> reduction performance. *Appl. Surf. Sci.* **2022**, *584*, 152645. [[CrossRef](#)]
14. Indrakanti, V.P.; Kubicki, J.D.; Schobert, H.H. Photoinduced activation of CO<sub>2</sub> on Ti-based heterogeneous catalysts: Current state, chemical physics-based insights and outlook. *Energy Environ. Sci.* **2009**, *2*, 745–758. [[CrossRef](#)]
15. Ghuman, K.K.; Singh, C.C. Effect of doping on electronic structure and photocatalytic behavior of amorphous TiO<sub>2</sub>. *J. Phys. Condens. Matter* **2013**, *25*, 475501. [[CrossRef](#)]
16. Naik, B.; Kim, S.M.; Jung, C.H.; Moon, S.Y.; Kim, S.H.; Park, J.Y. Enhanced H<sub>2</sub> Generation of Au-Loaded, Nitrogen-Doped TiO<sub>2</sub> Hierarchical Nanostructures under Visible Light. *Adv. Mater. Interfaces* **2014**, *1*, 1300018. [[CrossRef](#)]

17. Cottineau, T.; Béalu, N.; Gross, P.-A.; Pronkin, S.N.; Keller, N.; Savinova, E.R.; Keller, V. One step synthesis of niobium doped titania nanotube arrays to form (N,Nb) co-doped TiO<sub>2</sub> with high visible light photoelectrochemical activity. *J. Mater. Chem.* **2013**, *1*, 2151. [[CrossRef](#)]
18. Ma, X.; Wu, Y.; Lu, Y.; Xu, J.; Wang, Y.; Zhu, Y. Effect of Compensated Codoping on the Photoelectrochemical Properties of Anatase TiO<sub>2</sub> Photocatalyst. *J. Phys. Chem. C* **2011**, *115*, 16963–16969. [[CrossRef](#)]
19. Almaev, A.V.; Yakovlev, N.N.; Kushnarev, B.O.; Kopyev, V.V.; Novikov, V.A.; Zinoviev, M.M.; Yudin, N.N.; Podzivalov, S.N.; Erzakova, N.N.; Chikiryaka, A.V.; et al. Gas Sensitivity of IBSD Deposited TiO<sub>2</sub> Thin Films. *Coatings* **2022**, *12*, 1565. [[CrossRef](#)]
20. Serga, V.; Burve, R.; Krumina, A.; Romanova, M.; Kotomin, E.A.; Popov, A.I. Extraction-Pyrolytic Method for TiO<sub>2</sub> polymorphs Production. *Crystals* **2021**, *11*, 431. [[CrossRef](#)]
21. Devi, A.D.; Pushpavanam, S.; Singh, N.; Verma, J.; Kaur, M.P.; Roy, S.C. Enhanced methane yield by photoreduction of CO<sub>2</sub> at moderate temperature and pressure using Pt coated, graphene oxide wrapped TiO<sub>2</sub> nanotubes. *Results Eng.* **2022**, *14*, 100441. [[CrossRef](#)]
22. Goto, H.; Masegi, H.; Sadale, S.B.; Noda, K. Intricate behaviors of gas phase CO<sub>2</sub> photoreduction in high vacuum using Cu<sub>2</sub>O loaded TiO<sub>2</sub> nanotube arrays. *J. CO<sub>2</sub> Util.* **2022**, *59*, 101964. [[CrossRef](#)]
23. Butburee, T.; Kotchasarn, P.; Hirunsit, P.; Sun, Z.; Tang, Q.; Khemthong, P.; Sangkhun, W.; Thongsuwan, W.; Kumnorkaew, P.; Wang, H.; et al. New understanding of crystal control and facet selectivity of titanium dioxide ruling photocatalytic performance. *J. Mater. Chem. A* **2019**, *7*, 8156–8166. [[CrossRef](#)]
24. Liu, L.; Jiang, Y.; Zhao, H.; Chen, J.; Cheng, J.; Yang, K.; Li, Y. Engineering Coexposed {001} and {101} Facets in Oxygen-Deficient TiO<sub>2</sub> Nanocrystals for Enhanced CO<sub>2</sub> Photoreduction under Visible Light. *ACS Catal.* **2016**, *6*, 1097–1108. [[CrossRef](#)]
25. Scholes, D.T.; Yee, P.Y.; Lindemuth, J.R.; Kang, H.; Onorato, J.; Ghosh, R.; Luscombe, C.K.; Spano, F.C.; Tolbert, S.H.; Schwartz, B.J. The Effects of Crystallinity on Charge Transport and the Structure of Sequentially Processed F<sub>4</sub>TCNQ-Doped Conjugated Polymer Films. *Adv. Funct. Mater.* **2017**, *27*, 1702654. [[CrossRef](#)]
26. Rodriguez, M.M.; Peng, X.H.; Liu, L.J.; Li, Y.; Andino, J.M. A Density Functional Theory and Experimental Study of CO<sub>2</sub> Interaction with Brookite TiO<sub>2</sub>. *J. Phys. Chem. C* **2012**, *116*, 19755–19764. [[CrossRef](#)]
27. Liu, L.J.; Zhao, H.L.; Andino, J.M.; Li, Y. Photocatalytic CO<sub>2</sub> Reduction with H<sub>2</sub>O on TiO<sub>2</sub> Nanocrystals: Comparison of Anatase, Rutile, and Brookite Polymorphs and Exploration of Surface Chemistry. *ACS Catal.* **2012**, *2*, 1817–1828. [[CrossRef](#)]
28. Pan, H.; Gu, B.H.; Zhang, Z.Y. Phase-Dependent Photocatalytic Ability of TiO<sub>2</sub>: A First-Principles Study. *J. Chem. Theory Comput.* **2009**, *5*, 3074–3078. [[CrossRef](#)]
29. Pan, X.; Yang, M.-Q.; Fu, X.; Zhang, N.; Xu, Y.-J. Defective TiO<sub>2</sub> with Oxygen Vacancies: Synthesis, Properties and Photocatalytic Applications. *Nanoscale* **2013**, *5*, 3601. [[CrossRef](#)]
30. Zhou, Z.; Li, J.; You, Z. A facile TiO<sub>2</sub> containing oxygen vacancies and hydroxyl as a Ru-loaded underlay for CO<sub>2</sub> hydrogenation to CH<sub>4</sub>. *Appl. Surf. Sci.* **2022**, *587*, 152856. [[CrossRef](#)]
31. Elbana, O.; Fujitsuka, M.; Kim, S.; Majima, T. Charge Carrier Dynamics in TiO<sub>2</sub> Mesocrystals with Oxygen Vacancies for Photocatalytic Hydrogen Generation under Solar Light Irradiation. *J. Phys. Chem. C* **2018**, *122*, 15163–15170. [[CrossRef](#)]
32. Chen, R.; Fan, F.; Dittrich, T.; Li, C. Imaging photogenerated charge carriers on surfaces and interfaces of photocatalysts with surface photovoltage microscopy. *Chem. Soc. Rev.* **2018**, *47*, 8238–8262. [[CrossRef](#)] [[PubMed](#)]
33. Glass, D.; Quesada-Cabrera, R.; Bardey, S.; Promdet, P.; Sapienza, R.; Keller, V.; Meier, S.A.; Caps, V.; Parkin, I.P.; Cortés, E. Probing the Role of Atomic Defects in Photocatalytic Systems through Photoinduced Enhanced Raman Scattering. *ACS Energy Lett.* **2021**, *6*, 4273–4281. [[CrossRef](#)]
34. Schweke, D.; Mordehovitz, Y.; Halabi, M.; Shelly, L.; Hayrun, S. Defect Chemistry of Oxides for Energy Applications. *Adv. Mater.* **2018**, *30*, 1706300.
35. Kovacic, Z.; Likožar, B.; Hus, M. Photocatalytic CO<sub>2</sub> Reduction: A Review of Ab Initio Mechanism, Kinetics, and Multiscale Modeling Simulations. *ACS Catal.* **2020**, *10*, 14984–15007. [[CrossRef](#)]
36. Marchal, C.; Piquet, A.; Behr, M.; Cottineau, T.; Papaefthimiou, V.; Keller, V.; Caps, V. Activation of solid grinding-derived Au/TiO<sub>2</sub> photocatalysts for solar H<sub>2</sub> production from water-methanol mixtures with low alcohol content. *J. Catal.* **2017**, *352*, 22–34. [[CrossRef](#)]
37. Bardey, S.; Bonduelle-Skrzypczak, A.; Fécant, A.; Zhznpznq, C.; Colbeau-Justin, C.; Caps, V.; Keller, V. Plasmonic photocatalysis applied to solar fuels. *Faraday Discuss.* **2019**, *214*, 417–439. [[CrossRef](#)]
38. Haruta, M.; Bobayashi, T.; Sano, H.; Yamada, N. Novel Gold Catalysts for the Oxidation of Carbon Monoxide at a Temperature far Below 0°C. *Chem. Lett.* **1987**, *16*, 405–408.
39. Mohamed, I.M.A.; Dao, V.-D.; Yasin, A.S.; Barakat, N.A.M.; Choi, H.-S. Design of ultrafine nickel oxide nanostructured material for enhanced electrocatalytic oxidation of urea: Physicochemical and electrochemical analyses. *Appl. Surf. Sci.* **2017**, *400*, 355–364. [[CrossRef](#)]
40. Zhao, H.; Liu, L.; Andino, J.M.; Li, Y. Bicrystalline TiO<sub>2</sub> with controllable anatase-brookite phase content for enhanced CO<sub>2</sub> photoreduction to fuels. *J. Mater. Chem. A* **2013**, *1*, 8209–8216. [[CrossRef](#)]
41. Cheng, X.; Yu, X.; Li, B.; Yan, L.; Xing, Z.; Li, J. Enhanced visible light activity and mechanism of TiO<sub>2</sub> codoped with molybdenum and nitrogen. *Mater. Sci. Eng. B* **2013**, *178*, 425–430. [[CrossRef](#)]
42. Lignier, P.; Comotti, M.; Schüth, F.; Rousset, J.-L.; Caps, V. Effect of the titania morphology on the Au/TiO<sub>2</sub> catalyzed aerobic epoxidation of stilbene. *Catal. Today* **2009**, *141*, 355–360. [[CrossRef](#)]

43. Hammoud, L.; Streibel, C.; Toufaily, J.; Hamieh, T.; Keller, V.; Caps, V. The role of the gold-platinum interface in AuPt/TiO<sub>2</sub>-catalyzed plasmon-induced reduction of CO<sub>2</sub> with water. *Faraday Discuss.* **2022**. [[CrossRef](#)]
44. Colbeau-Justin, C.; Kunst, M.; Huguenin, D. Structural influence on charge-carrier lifetimes in TiO<sub>2</sub> powders studied by microwave absorption. *J. Mater. Sci.* **2003**, *38*, 24.
45. Livraghi, S.; Chierotti, M.R.; Giamello, E.; Magnacca, G.; Paganini, M.C.; Cappelletti, G.; Bianchi, C.L. Nitrogen-Doped Titanium Dioxide Active in Photocatalytic Reactions with Visible Light: A Multi-Technique Characterization on Differently Prepared Materials. *J. Phys. Chem. C* **2008**, *112*, 17244–17252. [[CrossRef](#)]
46. Hensling, F.V.E.; Xu, C.; Gunkel, F.; Dittmann, R. UV radiation enhanced oxygen vacancy formation caused by the PLD plasma plume. *Sci. Rep.* **2017**, *7*, 39953.
47. Deml, A.M.; Holder, A.M.; O'Hayre, R.P.; Musgrave, C.B.; Stevanović, V. Intrinsic Material Properties Dictating Oxygen Vacancy Formation Energetics in Metal Oxides. *J. Phys. Chem. Lett.* **2015**, *6*, 1948–1953. [[CrossRef](#)]
48. Zhang, Z.; Long, J.; Xie, X.; Lin, H.; Zhou, Y.; Yuan, R.; Dai, W.; Ding, Z.; Wang, X.; Fu, X. *ChemPhysChem*, 2012; *13*, 1542–1550.
49. Martsinovich, N.; Troisi, A. How TiO<sub>2</sub> crystallographic surfaces influence charge injection rates from a chemisorbed dye sensitiser. *Phys. Chem. Chem. Phys.* **2012**, *38*, 13392–13401. [[CrossRef](#)]
50. Guillois, K.; Burel, L.; Tuel, A.; Caps, V. Gold-catalyzed aerobic epoxidation of trans-stilbene in methylcyclohexane. Part I: Design of a reference catalyst. *Appl. Catal. A* **2012**, *415–416*, 1–9.
51. Beltram, A.; Romero-Ocana, I.; Delgado-Jaen, J.J.; Montini, T.; Fornasiero, P. Photocatalytic valorization of ethanol and glycerol over TiO<sub>2</sub> polymorphs for sustainable hydrogen production. *Appl. Catal. Gen.* **2016**, *518*, 167–175. [[CrossRef](#)]
52. Vigneron, F.; Piquet, A.; Baaziz, W.; Ronot, P.; Boos, A.; Janowska, I.; Pham-Huu, C.; Petit, C.; Caps, V. Hydrophobic gold catalysts: From synthesis on passivated silica to synthesis on few-layer graphene. *Catal. Today* **2014**, *235*, 90–97. [[CrossRef](#)]