



**HAL**  
open science

## Periodic Arrays of Dopants in Silicon by Ultralow Energy Implantation of Phosphorus Ions through a Block Copolymer Thin Film

Stefano Kuschlan, Riccardo Chiarcos, Michele Laus, Francesc Pérez-Murano, Jordi Llobet, Marta Fernandez-Regulez, Caroline Bonafos, Michele Perego, Gabriele Seguini, Marco de Michielis, et al.

### ► To cite this version:

Stefano Kuschlan, Riccardo Chiarcos, Michele Laus, Francesc Pérez-Murano, Jordi Llobet, et al.. Periodic Arrays of Dopants in Silicon by Ultralow Energy Implantation of Phosphorus Ions through a Block Copolymer Thin Film. ACS Applied Materials and Interfaces, 2023, 10.1021/acsami.3c03782 . hal-04258424

**HAL Id: hal-04258424**

**<https://hal.science/hal-04258424>**

Submitted on 26 Oct 2023

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

This document is confidential and is proprietary to the American Chemical Society and its authors. Do not copy or disclose without written permission. If you have received this item in error, notify the sender and delete all copies.

**Periodic arrays of dopants in silicon by ultra-low energy  
implantation of phosphorus ions through a block copolymer  
thin film**

Journal:	<i>ACS Applied Materials &amp; Interfaces</i>
Manuscript ID	Draft
Manuscript Type:	Article
Date Submitted by the Author:	n/a
Complete List of Authors:	Kuschlan, Stefano; CNR Institute of Microelectronics and Microsystems Chiarcos, Riccardo; University of Eastern Piedmont Amedeo Avogadro - Alessandria Campus, DISIT Laus, Michele; Univ Piemonte Orientale, DISIT Perez-Murano, Francesc; Institut de Microelectrònica de Barcelona Llobet, Jordi; IMB CNM Fernandez-Regulez, Marta; Instituto de Microelectronica de Barcelona, Nanofabrication Bonafos, Caroline; CEMES Perego, Michele; CNR, Institute of Microelectronics and Microsystems Seguini, Gabriele; CNR, IMM, Unit of Agate Brianza De Michielis, Marco; CNR Institute of Microelectronics and Microsystems Tallarida, Graziella; Istituto per la Microelettronica e Microsistemi Consiglio Nazionale delle Ricerche, Unit of Agrate Brianza

SCHOLARONE™  
Manuscripts

# Periodic arrays of dopants in silicon by ultra-low energy implantation of phosphorus ions through a block copolymer thin film

Stefano Kuschlan,<sup>(1)(2)</sup> Riccardo Chiarcos,<sup>(2)</sup> Michele Laus,<sup>(2)</sup> Francesc Pérez-Murano,<sup>(3)</sup> Jordi Llobet,<sup>(3)</sup> Marta Fernandez-Regulez,<sup>(3)</sup> Caroline Bonafos,<sup>(4)</sup> Michele Perego,<sup>(1)\*</sup> Gabriele Seguini,<sup>(1)</sup> Marco De Michielis,<sup>(1)</sup> Graziella Tallarida.<sup>(1)</sup>

(1) CNR-IMM, Unit of Agrate Brianza, Via C. Olivetti 2, I-20864 Agrate Brianza, Italy.

(2) Università del Piemonte Orientale "A. Avogadro", Viale T. Michel 11, I-15121 Alessandria, Italy

(3) Institute of Microelectronics of Barcelona (IMB-CNM, CSIC), Bellaterra 08193, Spain

(4) CEMES-CNRS, Université de Toulouse, CNRS, 31055 Toulouse, France

\* corresponding author

## Abstract

In this work, block copolymer lithography and ultra-low energy ion implantation are combined to obtain nano-volumes with high concentrations of phosphorus atoms periodically disposed over a macroscopic area in a p-type silicon substrate. The high dose of implanted dopants grants a local amorphization of the silicon substrate. In this condition, phosphorus is activated by Solid Phase Epitaxial Regrowth (SPER) of the implanted region with a relatively low temperature thermal treatment preventing diffusion of phosphorous atoms and preserving their spatial localization. Surface morphology of the sample (AFM, SEM), crystallinity of the silicon substrate (UV Raman) and position of the phosphorus atoms (STEM- EDX, ToF-SIMS) are monitored during the process. Electrostatic potential (KPFM) and the conductivity (C-AFM) maps of the sample surface upon dopant activation are compatible with simulated I-V characteristics suggesting the presence of an array of not ideal but working p-n nanojunctions. The proposed approach paves the way to further investigations on the possibility to modulate the dopant distribution within the silicon substrate at the nanoscale by changing the characteristic dimension of the self-assembled BCP film.

**Keywords:** block copolymer, ion implantation, doping, silicon, PS-b-PMMA

## Introduction

Linear block-copolymers (BCPs) formed by two different macromolecular chains linked to each other at one end by a covalent bond have been the subject of an intense research activity for a long time, since they provide an attractive and powerful tool for nanoscale fabrication.<sup>1</sup> Despite their relatively simple structure, when annealed above the glass transition temperature, they spontaneously microphase separate generating a variety of periodic nanostructures, such as spheres, gyroids, lamellae and cylinders. The morphology and characteristic dimensions of the resulting nanostructures can be efficiently tuned by changing the volume fraction ( $f$ ) of the two blocks, the degree of polymerization ( $N$ ) and the Flory-Huggins interaction parameter ( $\chi$ ). The periodicity ( $L_0$ ) of the microdomains can be varied in the 10 – 100 nm range by properly adjusting the molecular weight and the interaction parameter of the two blocks.<sup>2,3</sup> This wide range of possibilities suggested BCPs as fundamental materials for several interesting technological applications. In fact, whenever periodic patterning at the nanoscale over a large surface is required they represent an extremely attractive alternative for lithography<sup>4–7</sup> and nano-templating.<sup>8,9</sup> Possible applications include memories,<sup>10</sup> sensors,<sup>11,12</sup> optically active structures,<sup>13,14</sup> nano-porous membranes,<sup>15,16</sup> nano-catalysts<sup>17,18</sup> and polymer-based photovoltaic cells.<sup>19,20</sup>

The integration of BCP thin films in conventional lithographic processes has been widely explored in the literature,<sup>21</sup> because of the low cost of the self-assembly process, if compared to conventional photolithography,<sup>22,23</sup> and the high throughput, if compared to serial lithographic processes, such as electron beam lithography (EBL).<sup>24</sup> After the deposition of the BCP thin film by spin-coating onto the substrate, the self-assembly of the microdomains is usually promoted either via a simple thermal treatment or via a less standard solvent annealing process.<sup>21,25</sup> The morphology of the nanostructures and their orientation with respect to the underlying substrate are crucial for lithographic applications. In this respect, the most investigated morphologies are the out-of-plane lamellae and cylinders. Accordingly, lamellae or cylinder forming poly(styrene-*b*-methyl methacrylate) (PS-*b*-PMMA) BCPs are considered an excellent and promising candidate for lithographic application since the orientation of the nanodomains with respect to the substrate can

1  
2  
3 be achieved by the robust and simple technique consisting in the formation of a brush layer by means  
4 of a random copolymer (RCP) with tailored composition tethered to the sample surface.<sup>26–28</sup> The  
5 BCP film is then spin-coated and self-assembled on top of this neutral brush layer compensating any  
6 preferential wetting of the substrate by one of the two blocks forming the BCP. In addition, the  
7 registration of the microdomains can be controlled by the so called “directed self-assembly” (DSA)  
8 approach. This process consists in driving the self-assembly of the BCP applying external fields such  
9 as electric fields,<sup>29,30</sup> magnetic fields,<sup>31</sup> shear forces<sup>32,33</sup> or pre-patterning the substrate either  
10 chemically or topologically.<sup>34,35</sup> In particular, the pre-patterning of the substrate has been widely  
11 investigated in BCP lithography: the two approaches are usually referred as chemoepitaxy<sup>36</sup> when  
12 chemical modifications of the surface are used to direct the self-assembly of the BCP, or  
13 graphoepitaxy<sup>37</sup> when topological modification of the substrate is exploited.

14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27 In order to exploit the self-assembled BCP thin films in a lithographic process, one of the two  
28 components of the BCP must be selectively removed from the BCP thin film, generating a nano-  
29 structured soft mask on top of the semiconductor substrate. PS-b-PMMA BCPs are extremely  
30 appealing from this point of view, since the PMMA phase can be selectively removed by means of  
31 deep UV exposure and subsequent rinsing in acetic acid, leaving the PS unaffected.<sup>38,39</sup>  
32 Alternatively, the slight difference in etching rates between PS and PMMA components can be  
33 exploited to remove the PMMA phase with a dry etching process. Unfortunately, due to low etch  
34 resistance of polymeric materials, also the PS film is severely modified during the process, limiting  
35 the applicability of this approach.<sup>40</sup> Similarly, PMMA phase can also be selectively and locally  
36 removed using an electron beam to degrade the PMMA and standard development techniques used  
37 for EBL resist.<sup>41</sup> It is worth noting that depending on the specific application, after the selective  
38 removal of PMMA, a brief dry etching process may be necessary to remove the RCP neutral layer  
39 and to completely expose the underlying substrate. The nanostructured polymer thin film that is  
40 obtained upon removal of the PMMA phase can be transferred to the substrate using either  
41 subtractive or additive processes. More in detail, the nanostructured polymeric mask can be used  
42 for lift-off processes to deposit metals,<sup>42</sup> oxides, or other materials.<sup>43</sup> Otherwise, the nanostructured  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 polymer film can be used as a sacrificial layer to pattern the underlying substrate using reactive ion  
4  
5 etching.<sup>44</sup>  
6  
7

8 Surprisingly, to the best of our knowledge, the possibility to use those nanostructured  
9  
10 polymeric films as soft mask to promote local modification of the substrate by conventional ion  
11  
12 implantation has not been investigated in detail. In this respect, the poor resistance of polymers to  
13  
14 ion bombardment and the limited thickness of these polymer films represent severe limitations and  
15  
16 usually relegates those polymer templates to the role of patterning tool for the preparation of hard  
17  
18 masks<sup>45–48</sup> that are subsequently used during the ion implantation process. Alternatively, ultra-low  
19  
20 energy ( $E < 5$  keV) ion implantation represents a viable solution to overcome those limitations. Ultra-  
21  
22 low energy implantation (1 keV) of  $\text{Si}^+$  ions into a  $\text{SiO}_2$  film through a BCP lithographic mask has  
23  
24 already been reported in literature<sup>49,50</sup> showing that the polymeric film survived the ion implantation  
25  
26 process, successfully shielding the substrate. As a result, regular arrays of silicon-rich nano-volumes  
27  
28 were formed over the substrate with the same periodicity as the mask and with lateral dimension  
29  
30 below 20 nm in the  $\text{SiO}_2$  matrix.  
31  
32  
33

34 In this work, the combination of ultra-low energy implantation of phosphorous ions at high  
35  
36 fluences and BCP thin films is investigated to promote a periodic modulation of the concentration of  
37  
38 dopant impurities over the near-surface layer of a silicon substrate. The low energy of the implanted  
39  
40 ions is expected to preserve the polymer template. Additionally, high implantation doses are  
41  
42 considered to induce local amorphization of the silicon substrate. In this way Solid Phase Epitaxial  
43  
44 Regrowth (SPER) can be exploited to recover the crystallinity of the silicon matrix by thermal  
45  
46 treatments at relatively low temperatures. During the SPER process the phosphorus atoms are  
47  
48 substitutionally incorporated into the silicon lattice. This process takes advantage of a low thermal  
49  
50 budget to activate the phosphorus atoms preserving their spatial confinement<sup>51</sup> in a periodic  
51  
52 distribution with the nanometric periodicity introduced during the implantation process.  
53  
54  
55  
56  
57  
58  
59  
60


## Experimental Section

**Materials.** A -OH terminated poly(styrene-*r*-methyl methacrylate) P(S-*r*-MMA) statistical copolymer was prepared by ARGET-ATRP copolymerization (molecular weight  $M_n = 3.64$  kg/mol, PS fraction  $f_{PS} = 0.61$  and polydispersity  $\mathcal{D} = 1.15$ ). An asymmetric poly(styrene-*b*-methyl methacrylate) (PS-*b*-PMMA) was bought from "Polymer Source Inc.". The polymer has  $M_n = 67.1$  kg/mol,  $f_{PS} = 0.69$  and  $\mathcal{D} = 1.09$ , resulting in a cylindrical morphology with periodicity  $L_0$  of  $\sim 35$  nm.

**Surface cleaning and neutralization.** A (100) Si wafer doped with boron and nominal resistivity  $\rho = 0.01$ - $0.05$   $\Omega$  cm was cleaved in  $1 \times 1$  cm<sup>2</sup> samples. They were cleaned for 40 min in 80°C piranha solution (H<sub>2</sub>O<sub>2</sub> 30% v/v: H<sub>2</sub>SO<sub>4</sub> 99% v/v, ratio 1:3), rinsed in deionized water (DIW) and dried in N<sub>2</sub> flux. A 1%wt solution of the RCP in toluene was spun on the substrates at 3000 rpm for 30 s. The "graft to" reaction was promoted by Rapid Thermal Process (RTP) at 290 °C for 60 s in N<sub>2</sub> atmosphere (Jipelec, JetFirst Series rapid thermal processing system). Ungrafted chains were removed using ultrasonic in toluene for 5 min, samples were dried in N<sub>2</sub> flux, and the thickness of the resulting brush layer was measured  $3.88 \pm 0.14$  nm with a spectroscopic ellipsometer (J. A. Wollam Co., Inc. M-2000U, xenon lamp, 70° angle of incidence).

**Preparation of the BCP lithographic mask.** A 1%wt solution of PS-*b*-PMMA in toluene was spun on top of the neutralized substrates at 2500 rpm for 30 s, resulting in a  $\sim 36$  nm thick film of BCP. Self-assembly was promoted with an RTP at 230 °C for 300 s in N<sub>2</sub> atmosphere. The film consist of hexagonally packed out-of-plane PMMA cylinders embedded in a matrix of PS (**Figure 1A**). The PMMA cylinders exhibit an average diameter  $D_0 \sim 22$  nm and a center-to-center distance  $L_0 \sim 35$  nm. Selective removal of the PMMA phase (**Figure 1B**) was made by exposing the BCP film at UV light (253.7 nm, 5 mW cm<sup>-2</sup>) for 15 min and removing the degraded chains in an acetic acid bath for 8 min. The samples are then rinsed in DIW and dried in N<sub>2</sub> flux. A mild oxygen plasma treatment (40 W for 96 s) is used to clean the bottom of the pores from the random copolymer RCP brush layer.

**Ion implantation and activation of dopants.** Ion implantation was performed at 3 keV normal to the samples at different doses of  $P^+$ , ranging from  $1.55 \times 10^{14} \text{ cm}^{-2}$  to  $5.02 \times 10^{14} \text{ cm}^{-2}$  (**Figure 1C**). Those values were chosen close to the amorphization threshold for  $P^+$  implantation in silicon, in order to create an amorphous layer at the surface of the samples.<sup>52</sup> Thanks to the PS mask,  $P^+$  can reach the Si surface only in correspondence of the nano-pores, while the rest of the ions are trapped in the polymeric film (**Figure 1D**). The layer of PS was removed in a piranha solution bath at 80 °C for 40 min, the samples were then rinsed in deionized water (DIW) and dried in  $N_2$  flux (**Figure 1E**). The native oxide was removed using a 1% v/v solution of HF for 1 min. Samples were then rinsed in DIW and dried with  $N_2$ . SPER was promoted with a RTP at 650 °C for 10 s in  $N_2$  atmosphere (**Figure 1F**).

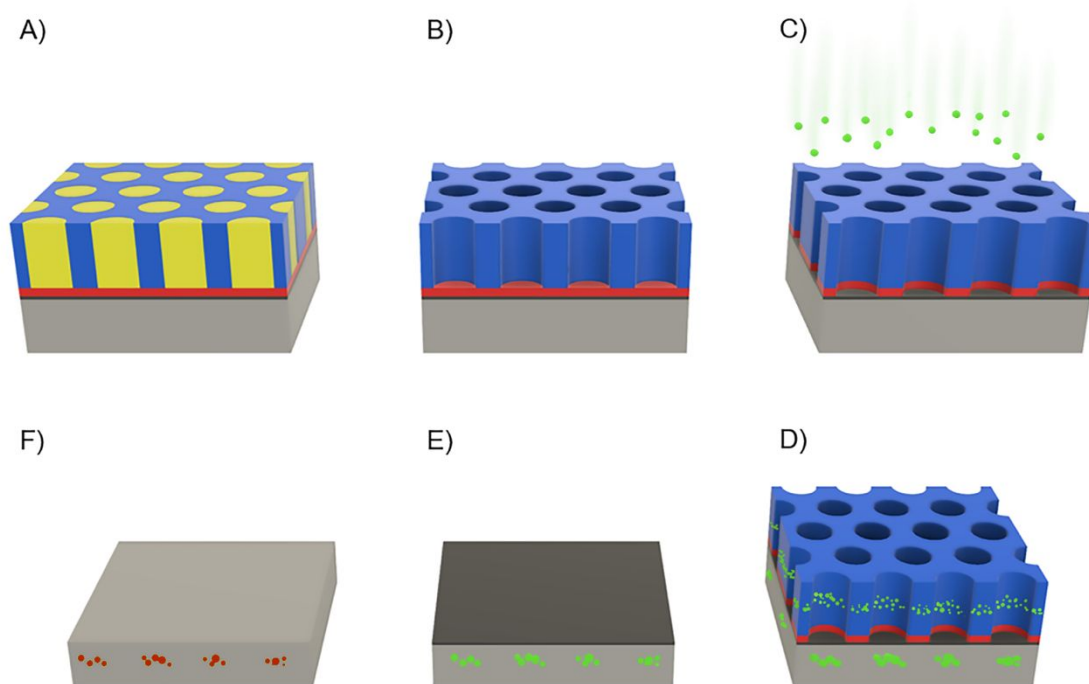

**Figure 1.** Schematic representation of the process: A) Self-assembled BCP thin film composed by hexagonally packed PMMA cylinders (yellow) embedded in a PS matrix (blue) and perpendicularly oriented with respect to the substrate. Prior to BCP deposition the not deglazed silicon substrate was neutralized by a random copolymer brush layer (red). B) Mesoporous polymer film upon selective removal of PMMA phase. C) Removal of RCP brush layer using a mild oxygen plasma treatment, to expose the underlying substrate, and implantation of  $P^+$  ions (green) at 3 keV. D) Accumulation of  $P$  ions in the PS mask and, in correspondence of the nano-pores, in the Si substrate. E) Removal of the polymeric mask. F) Removal of the native oxide film by HF treatment and subsequent annealing at low temperature (650 °C) to activate the dopants.



1  
2  
3       **Scanning electron microscopy.** SEM plan view images were acquired using a ZEISS Supra  
4  
5 40 SEM operating at 15 kV. The analysis of the high-resolution plan view images was performed  
6  
7 using the software ImageJ. To ensure a statistically relevant analysis, the average diameters of the  
8  
9 pores in the mesoporous templates were measured using a set of three images per sample, at high  
10  
11 magnification (100'000x) and the built-in tool of the software for particles measurement. Similarly,  
12  
13 the FFT algorithm of the software was used to measure the periodicity of the nano-pores.  
14  
15

16       **Secondary ion mass spectrometry.** Time of flight secondary ion mass spectrometry (ToF-  
17  
18 SIMS) depth profiling was performed using a dual beam ION-TOF IV system operating in negative  
19  
20 polarity. Cs<sup>+</sup> ions at 1 keV and 110 nA were used to sputter a 300 μm wide square area, while  
21  
22 analysis was performed using Ga<sup>+</sup> ions at 25 keV and 1 pA. Depth scale calibration of phosphorus  
23  
24 profiles in the PS matrix was performed using a 50 nm thick PS film spin coated on top of a silicon  
25  
26 substrate as a reference to measure the sputtering velocity. Similarly, depth scale calibration in  
27  
28 silicon was performed using a 70 nm thick silicon-on-insulator (SOI) sample that was adopted as a  
29  
30 reference. Effective concentration of phosphorus in the silicon substrate was performed by  
31  
32 calibration of the <sup>31</sup>P<sup>-</sup> secondary ion signal using a protocol that is reported in previous publications  
33  
34  
35 53,54 .  
36  
37

38       **Raman spectroscopy.** UV micro-Raman spectroscopy was used to study the crystallinity of  
39  
40 the samples during the process. The set up comprises a Renishaw InVia spectrometer equipped  
41  
42 with a frequency tripled Nd:YAG laser (λ = 355 nm), operating with a confocal optical microscope  
43  
44 using a 40x objective (NA = 0.47) resulting in a laser spot of ~1 μm. The power at the sample was  
45  
46 measured 4 mW, sufficiently low to avoid the recrystallization of the samples during the  
47  
48 measurements. The spectral region between 400 cm<sup>-1</sup> and 600 cm<sup>-1</sup> Raman shift was considered,  
49  
50 because of the characteristic peaks of crystalline silicon (c-Si) at 520 cm<sup>-1</sup> and the one at 480 cm<sup>-1</sup>  
51  
52 typical of the amorphous silicon (a-Si)<sup>55</sup>. The penetration depth of the laser source is less than 10  
53  
54 nm both in c-Si and a-Si, allowing to detect even a very thin amorphous layer at the surface.  
55  
56


57       **Transmission Electron Microscopy.** High Resolution Electron Microscopy observations and  
58  
59 Energy Dispersive X-Ray Spectroscopy (STEM-EDS) analyses were performed on a JEOL ARM  
60

1  
2  
3 cold FEG microscope equipped with a probe spherical aberration corrector at 200 kV and a STEM  
4 resolution of 78 pm. A CENTURIO-X detector with an elevation angle of 24.3 degrees and a  
5 collection angle of 0.98 steradians was used for the EDX measurements. Thin lamellas were  
6 prepared for TEM and STEM-EDX analysis using a FEI Helios Nanolab 600i dual beam microscope  
7 and focused ion beam (FIB). The cross-sectional lamellas were formed by lowering the voltage from  
8 16 kV-50 pA to 5 kV-15 pA. On the region of interest, a thin (1-2  $\mu\text{m}$ ) platinum (Pt) protective layer  
9 was deposited. To prevent Pt diffusion, a thin (100 nm) carbon layer was deposited between the  
10 sample surface and the platinum protective layer.  
11  
12  
13  
14  
15  
16  
17  
18  
19

20  
21 **Scanning Probe Microscopy.** Several Scanning Probe Microscopy (SPM) setups were used  
22 to investigate the surface morphology and the associated electrical properties at the nanoscale. All  
23 measurements were carried out in ambient air and at room temperature using the commercial  
24 system Bruker Dimension Edge. Atomic force microscopy (AFM) was employed to investigate the  
25 surface morphology; measurements were carried out in tapping mode using sharp silicon probes  
26 with nominal tip radius of 7nm and resonance frequency of 300 kHz. Surface electrostatic properties  
27 were explored after dopant activation by amplitude-modulate Kelvin Probe Force Microscopy  
28 (KPFM); measurements were carried out in lift-mode using PtSi silicon probes by Nanosensors™.  
29 At each scan line the surface morphology profile is detected first, then the probe is lifted above the  
30 surface by tens of nanometers while an AC voltage is applied directly to the probe making it  
31 responsive to the local electrostatic forces. A dedicated KPFM feedback loop generates at each  
32 point the potential that must be applied to the probe in order to minimize these forces; this potential,  
33 usually named contact potential difference (CPD), provides information on the electrostatic  
34 landscape of the sample surface in relation to its morphology.<sup>56</sup> Finally, local conduction properties  
35 were investigated by Conductive-AFM (C-AFM); measurements were taken in contact mode using  
36 doped diamond probes (Nanosensors™), while a DC voltage bias was applied to the sample.  
37 Current is collected either concurrently with surface morphology, thus providing current maps at fixed  
38 voltage, or in spectroscopic mode at fixed surface positions while sweeping the applied voltage. Data  
39 analysis of SPM measurements was carried out by Gwyddion software.<sup>57</sup>  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60




1  
2  
3 pores. This analysis was performed on all the implanted samples (**Figure S1**) and the average  
4 diameters are reported as a function of the dose of implanted phosphorus ions in **Figure 2C**. Data  
5 indicate that, within the experimental error, ion implantation did not remarkably change the  
6 distribution of the pore diameters. However, after implantation the average values of the pore  
7 diameter are systematically lower of almost 1 nm than in the pristine mesoporous template. This  
8 slight reduction of the diameter may be due to the swelling of the mesoporous polymer template,  
9 because of phosphorus ion incorporation into the PS matrix. The distribution of the pore diameter,  
10 expressed by the standard deviation of the gaussian fit of the experimental data, remains almost  
11 constant at each dose, compared to the pristine mask. The only exception is made by the sample  
12 implanted at  $2.83 \times 10^{14} \text{ cm}^{-2}$  that shows a different behavior. This deviation can be related to the  
13 presence of more defects in the PS mask, or a more inhomogeneous swelling caused by the ions in  
14 the polymeric film.  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28

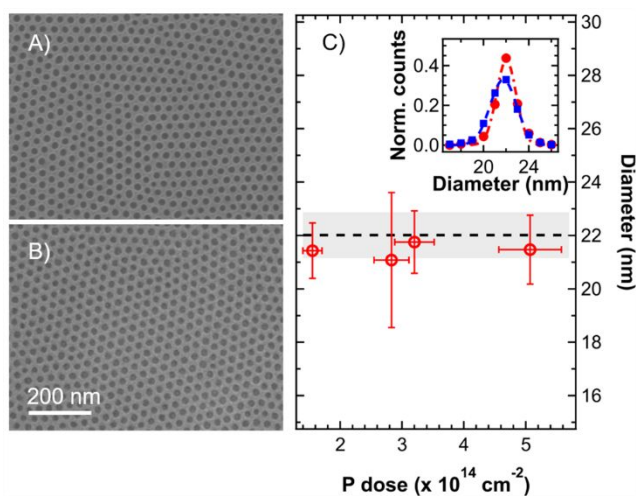

29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46 **Figure 2.** SEM images of the PS mask (A) before and (B) after the implantation, P fluence of  $3.20 \times 10^{14}$   
47  $\text{cm}^{-2}$ . C) Diameter of the pores as a function of the P dose implanted. The diameter of the PS mask before  
48 implantation is reported for comparison (black dashed line). The standard deviation of the average diameter  
49 of the pores in pristine PS template is also reported (grey area). In the inset, the distribution of diameters  
50 before (red bullets) and after (blue squares) the implantation is reported for the fluence  $3.20 \times 10^{14} \text{ cm}^{-2}$ .  
51 Dashed curves correspond to the Gaussian fit of the experimental data.  
52  
53  
54  
55  
56

57 The distribution of phosphorus atoms in the samples after ion implantation was investigated  
58 by ToF-SIMS depth profiles. **Figure 3A** shows the ToF-SIMS depth profile of the samples implanted  
59  
60


with P ions at 3 keV and dose  $3.20 \times 10^{14} \text{ cm}^{-2}$ . The  $\text{C}_5^-$ ,  $\text{SiO}_3^-$  and  $^{30}\text{Si}^-$  secondary ion signals are reported as markers of the mesoporous PS film, the thin native oxide layer of and the silicon bulk, respectively. It is worth noting that, due to the porosity of the polymer film and the large area investigated by ToF-SIMS, the secondary ion signals of the topmost layer of PS are partially overlapped with those of the underlying  $\text{SiO}_2$  and Si layers. This is particularly evident looking at the  $\text{SiO}_3^-$  and  $^{30}\text{Si}^-$  secondary ion signals, exhibiting a long tail in the PS mask. Consequently, it is very hard to isolate the P<sup>-</sup> secondary ion signal originated from the P ions trapped in the mask, preventing the possibility to provide a precise calibration of the P<sup>-</sup> secondary ion signal in the PS matrix. Nonetheless, the presence of an intense P<sup>-</sup> secondary ion signal in the PS matrix, with a maximum located  $\sim 15 \text{ nm}$  below the surface of the polymer film, suggests that effective P ion accumulation occurred in the mesoporous PS template providing clear indication that the mask was able to retain a certain amount of P ions during the implantation process at low energy. Integrating the phosphorus secondary ion signal in the PS mask region (**Figure S2**) it is possible to obtain a qualitative estimation of the ions blocked by the polymer as a function of the total dose of phosphorus implanted as shown in **Figure 3B**. Even if a quantitative analysis of the ToF-SIMS data is prevented in this system, experimental data provide clear evidence of a linear increase of the amount of P ions trapped into the PS matrix when increasing the dose of implanted P ions. This result indicates that, in this range of doses, the mask is effectively shielding the underlying Si substrate.

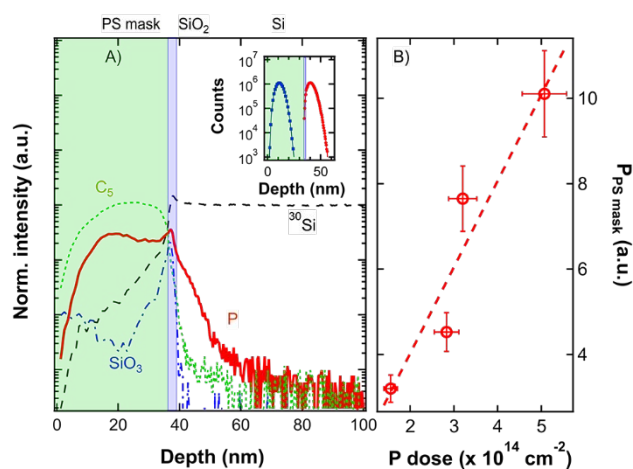


**Figure 3.** A) Normalized ToF-SIMS depth profile of a sample after the implantation at a dose of  $3.20 \times 10^{14} \text{ cm}^{-2}$ . The graph reports the P,  $\text{C}_5$ ,  $^{30}\text{Si}$  and  $\text{SiO}_3$  signals. It is possible to discern between the PS mask, the

1  
2  
3 *thin layer of native oxide and the crystalline bulk of silicon (respectively the light green, light blue and white*  
4 *areas). Due to the porosity of the mask, signals in the light green area have both the contribution of the PS*  
5 *and a small contribution from the layers below. A simulation of the implantation profile in non-deglazed Si*  
6 *(red bullets) and in PS (blue squares) is reported in the inset. To better compare the results, the two curves*  
7 *were shifted along the x-axis to match the different layers of the ToF-SIMS profile. The simulation was made*  
8 *using the software SRIM13. B) P dose inside the PS mask as a function of the implanted dose of P.*  
9  
10  
11  
12  
13

14 After the removal of the polymeric mask, the surface morphology of the silicon substrate was  
15 investigated by AFM. **Figure 4A** shows topographic AFM images of the implanted samples. A  
16 topographic image of a pristine Si substrate is shown in **Figure S3** as a reference. Before  
17 implantation the sample exhibits a flat surface with negligible roughness. Conversely, AFM images  
18 in **Figure 4A-D** clearly show that surface morphology of the samples is significantly modified upon  
19 implantation, with the appearance of hexagonally packed circular swollen areas, whose organization  
20 and periodicity perfectly match the pattern of the mesoporous PS template. This change of the  
21 surface morphology further confirms the efficacy of the mesoporous PS template as soft mask to  
22 shadow the underlying substrate. Analyzing the images and taking into account the roughness of  
23 the sample, it was possible to measure the average heights of the swollen areas that are reported  
24 as a function of the implanted dose in **Figure 4E**. According to the collected data, an increase in the  
25 height of the implanted areas is observed increasing the amount of implanted phosphorus ions.  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39

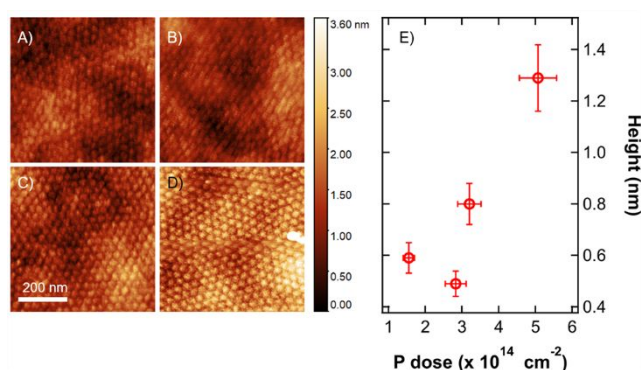


40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53 **Figure 4.** AFM image of the Si surface after the implantation and removal of the mask. Each image  
54 corresponds to a different phosphorous dose: A)  $1.55 \times 10^{14} \text{ cm}^{-2}$ , B)  $2.83 \times 10^{14} \text{ cm}^{-2}$ , C)  $3.20 \times 10^{14} \text{ cm}^{-2}$ ,  
55 D)  $5.07 \times 10^{14} \text{ cm}^{-2}$ . E) Average height of the local swelling induced by the ion implantation as a function of  
56 the P dose, estimated after the removal of the long-range corrugation of the Si surface.  
57  
58  
59  
60

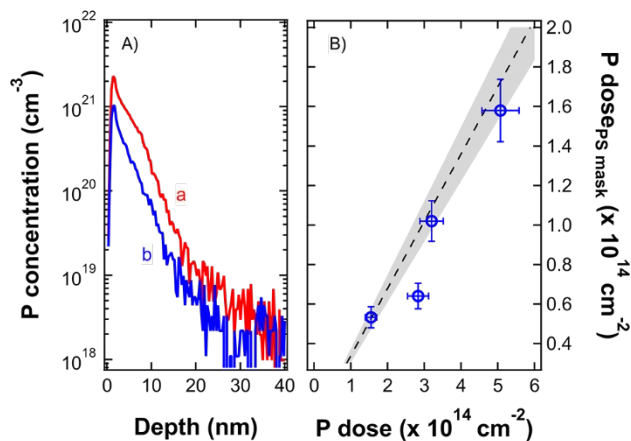

**Figure 5.** A) Calibrated ToF-SIMS depth profiles of phosphorus implanted in Si at  $3.20 \times 10^{14} \text{ cm}^{-2}$  dose. Red curve (a) refers to a sample implanted without the PS mask and blue curve (b) with the mask. In the graph is reported the P fluence of the implantation. B) P dose implanted in Si through the PS mask as a function of the implantation fluence. Black dashed line shows the expected dose with error (grey area) inferred from the analysis of SEM images of the PS mask.

Upon removal of the mesoporous PS template, calibrated depth profiles of the phosphorus atoms implanted into the silicon substrate were acquired by ToF-SIMS analysis for each sample. **Figure 5A** reports the calibrated phosphorus depth profiles for two samples implanted directly into the silicon substrate (red curve) and without (blue curve) the polymeric mask-with the same dose of P ions corresponding to  $3.20 \times 10^{14} \text{ cm}^{-2}$ . The different concentration of phosphorus in the two samples is attributed to the shielding of the substrate by the mesoporous PS template. Integrating the calibrated phosphorus depth profiles, the doses of implanted phosphorus ions are determined in the two samples. The ratio between the calculated doses is  $\sim 0.3$ . This result is perfectly consistent, within the experimental error, with the ratio between the effective surfaces that were exposed during ion implantation in the two samples. **Figure 5B** reports the phosphorus doses implanted in the samples through the mesoporous PS mask as a function of the doses implanted in samples without the mask. The dashed line indicates the expected dose of phosphorus atoms calculated considering that the exposed area in the masked sample is  $\sim 0.34$ . The measured doses are in good agreement with the expected ones. This result further confirms that the mesoporous PS template effectively shielded the substrate from the impinging ions, leading to localized implantation of the phosphorous ion in correspondence of the pores in the PS film.

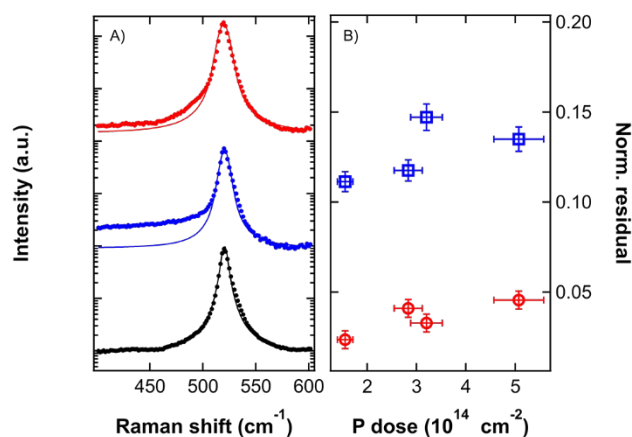


**Figure 6.** A) Raman spectra of the sample implanted with a dose of  $3.20 \times 10^{14} \text{ cm}^{-2}$  without the PS mask before implantation (black bullets), after implantation (blue bullets) and upon annealing at  $650 \text{ }^\circ\text{C}$  for  $10 \text{ s}$  (red bullets). Experimental data are fitted with a Voigt function (solid lines). B) Normalized residuals in the  $400\text{-}500 \text{ cm}^{-1}$  interval as a function of the implantation fluence before (blue squares) and after (red circles) the annealing.

The activation of the dopants upon implantation is commonly achieved by thermal treatments performed in an inert atmosphere at high temperatures. The phosphorus depth profiles for the sample implanted with a phosphorus dose  $1.55 \times 10^{14} \text{ cm}^{-2}$  before and after different high temperature annealing processes are reported in **Figure S5**. Significant in-depth diffusion of the dopants is observed. Accordingly, the process is expected to promote in-plane diffusion of the dopants in the samples implanted throughout the mesoporous PS template, losing control on the spatial localization of the phosphorus atoms. It is worth noting that in our system the very high phosphorus doses are expected to induce a local amorphization of the silicon substrate. The amorphization of the implanted region was investigated by Raman spectroscopy. **Figure 6A** shows the Raman spectra before (black symbols) and after (blue symbols) the implantation process for the sample implanted without any polymeric mask with a P dose of  $3.20 \times 10^{14} \text{ cm}^{-2}$ . Before implantation, the crystal of silicon exhibits a sharp peak centered at  $520 \text{ cm}^{-1}$  that can be fitted with a single Voigt curve. This peak is typically associated to the  $O(\Gamma)$  phonons of the crystalline silicon<sup>55</sup>. After implantation the Raman spectrum of the sample is characterized by a long tail in the region  $400 - 500 \text{ cm}^{-1}$ . The presence of amorphous silicon is usually associated to the presence of a broad peak at  $\sim 480 \text{ cm}^{-1}$  in the Raman spectrum<sup>58</sup>. Due to the limited penetration of the P ions in the silicon




1  
2  
3 substrate when operating at 3 keV, the thickness of the amorphized region is anticipated to be lower  
4 than 10 nm. The signal generated by this very thin layer is expected to be very broad making difficult  
5 to clearly resolve the two peaks at 520  $\text{cm}^{-1}$  and 480  $\text{cm}^{-1}$ . The increased intensity of the signal in  
6 the 400 - 500  $\text{cm}^{-1}$  range is associated to the presence of an a-Si layer at the surface. Accordingly,  
7 P activation in the implanted region can be achieved by a thermal treatment at relatively low  
8 temperature, taking advantage of SPER to recover the crystallinity of the silicon matrix and to  
9 concomitantly incorporate the phosphorus atoms in substitutional sites of the silicon crystal  
10 promoting their activation. **Figure S4** shows representative Raman spectra of an implanted sample  
11 after removal of the native oxide layer by and annealing at temperatures ranging from 550°C to  
12 1100°C. No shift of the position and no broadening of the signal associated to crystalline silicon is  
13 observed irrespective of the annealing temperatures. The tail in 400 - 500  $\text{cm}^{-1}$  region is  
14 progressively reduced as the annealing temperature increases. This reduction is assumed to be  
15 indicative of the recrystallization of the amorphous regions. According to these data the threshold  
16 temperature to achieve an almost complete recrystallization of the silicon substrate without  
17 significant P diffusion is identified to be  $\sim 650^\circ\text{C}$ . **Figure 6A** shows the Raman spectrum upon  
18 annealing at 650°C (red symbols) of the sample implanted without any polymeric mask with a P dose  
19 of  $3.20 \times 10^{14} \text{ cm}^{-2}$ . The symmetry of the peak is almost completely recovered. Fitting the Raman  
20 spectra with a Voight function centered at 520  $\text{cm}^{-1}$  and with FWHM equivalent to the one obtained  
21 in the case of the pristine silicon substrate it is possible to define a parameter that provide a direct  
22 indication of the presence of an amorphized region in the silicon substrate by integrating the  
23 residuals of the fitting procedure in the 400 - 500  $\text{cm}^{-1}$  region. These values, normalized on the  
24 intensity of the Voight function centered at 520  $\text{cm}^{-1}$ , are reported in **Figure 6B** for all the implanted  
25 samples before (blue symbols) and after (red symbols) annealing at 650°C. The two sets are  
26 characterized by a significant reduction of the calculated values upon annealing, suggesting an  
27 almost complete recrystallization of the samples.  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

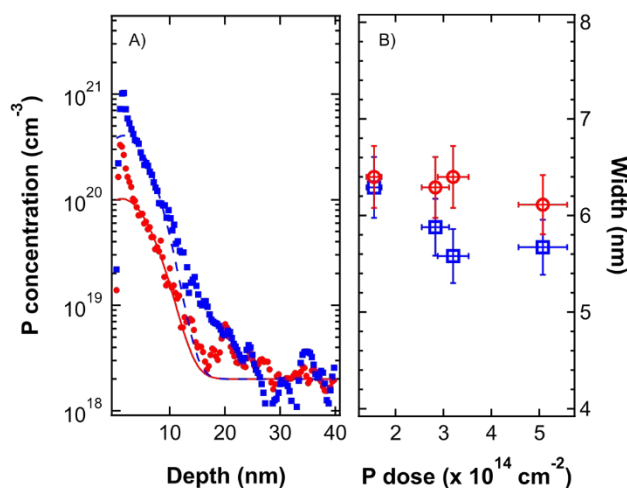

**Figure 7.** A) Calibrated ToF-SIMS depth profiles of phosphorus implanted in Si with the PS mask, dose  $3.20 \times 10^{14} \text{ cm}^{-2}$ . In the graph is reported the P fluence of the implantation. Blue dots refer to the sample before the annealing, while red squares refer to the sample after the implantation. Experimental data were fitted with a gaussian curve (blue dashed line before annealing, red solid line after the annealing). B) Standard deviation of the gaussian fits as a function of the phosphorus dose before the annealing (blue squares) and after (red circles).

To confirm the limited diffusion of phosphorus during the low temperature thermal treatment, calibrated phosphorus depth profiles of each sample upon annealing at  $650^\circ\text{C}$  were acquired by ToF-SIMS analysis and compared with the corresponding calibrated phosphorus depth profiles obtained before the annealing. **Figure 7A** shows two representative calibrated phosphorus depth profiles before (blue symbols) and after (red symbols) annealing for the sample implanted through the mesoporous PS template with a phosphorus dose of  $3.20 \times 10^{14} \text{ cm}^{-2}$ . Due to the removal of the native oxide before the annealing and the subsequent oxidation of the surface, the calibrated phosphorus depth profiles upon annealing is shifted toward the surface along the x-axis. The profiles were fitted with a Gaussian curve. The standard deviations of the fitting curves for all the implanted samples before (blue symbols) and after (red symbols) annealing are reported as function of phosphorous dose in **Figure 7B**. The standard deviation is almost constant for all the implant doses. Moreover the slightly large values obtained upon annealing indicate that the  $650^\circ\text{C}$  thermal treatment introduces no significant variation in the phosphorus depth profile.

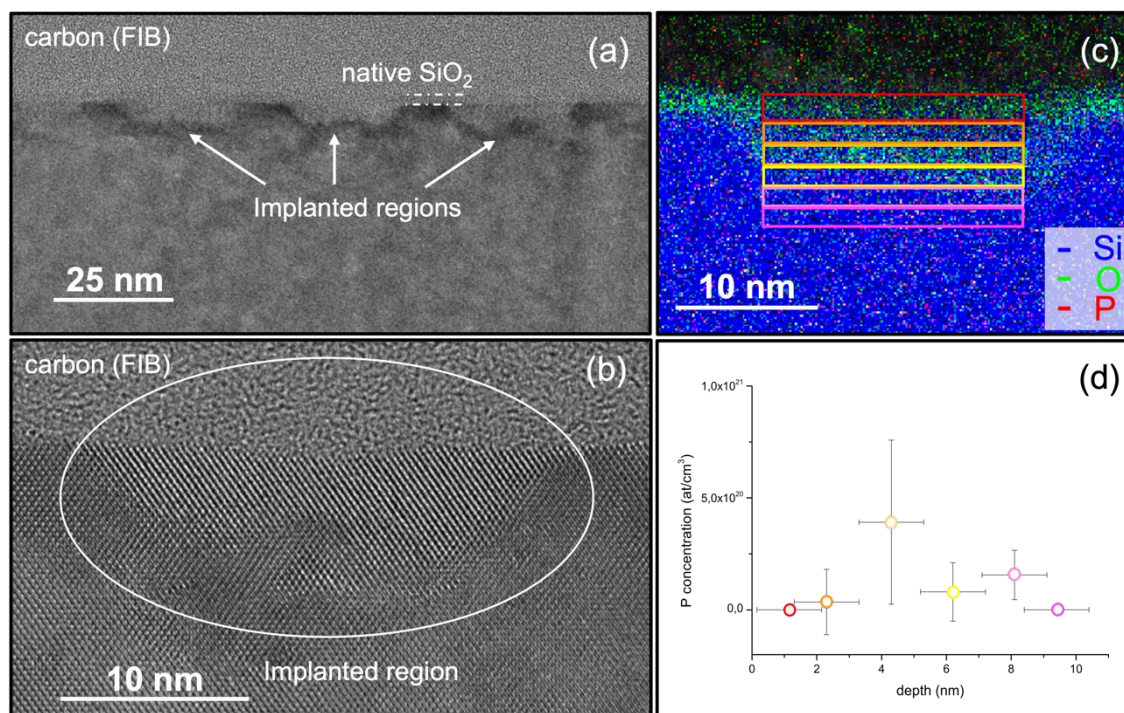


**Figure 8.** (a) High Resolution Electron Microscopy image of the implanted regions. (b) Zoom at high magnification of one of the implanted regions. (c) STEM-EDX elemental mapping in one of the implanted regions. (d) Average P concentration measured in the rectangles of figure (c). Data are reported as a function of depth.

A representative HREM cross-sectional image of the implanted regions is shown in **Figure 8a**.

The implanted regions are conical in shape with lateral dimension of 22–25 nm and center-to-center distance of 36 nm. These values closely match the diameter and periodicity of the pores in the original mesoporous PS template. A 2 nm thick SiO<sub>2</sub> layer is present at the Si surface. A zoom at high magnification of one of the implanted regions is reported in **Figure 8b**. The high magnification image confirms that the implanted Si is fully recrystallized, with a perfectly monocrystalline region on the first 4 nm and deeper, a 4 nm thick damaged region, with some extended defects, which likely formed beneath the former amorphous/crystalline interface. **Figure 8c** displays the STEM-EDX elemental mapping of an implanted region. Although perfectly crystalline, some O atoms can be found in the first 6 nm of the implanted region beneath the 2 nm thick native SiO<sub>2</sub> layer. Phosphorus concentration is too low for the P to be directly visible in the elemental mapping. Moreover an erroneous interpretation of the P-K intensity levels may be due to the Pt-M line with energy extremely close to the P-K line. However, when integrating over the thin slices that are represented by the

colored rectangles of **Figure 8c**, phosphorus quantification is possible, although it is important to pay attention to the quantification parameters because of the presence of the Pt-M $\alpha$  line. **Figure 8d** plots the average P atomic concentration inside each slice as a function of depth, with the error bar representing the standard deviation obtained by measurement performed on different samples. These values perfectly match the P concentrations in the calibrated phosphorus depth profile obtained by TOF-SIMS analysis and reported in **Figure 5a**.

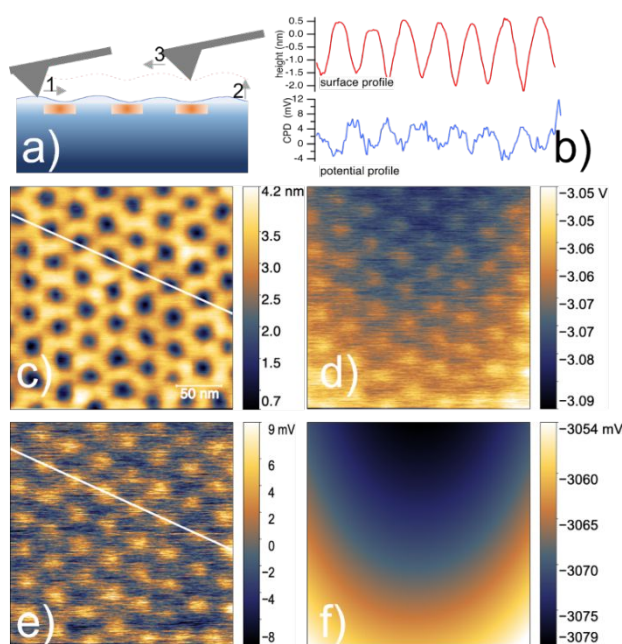


**Figure 9.** KPFM measurement on sample with  $5.07 \times 10^{14} \text{cm}^{-2}$  implanted dose after doping activation. a) schematic of KPFM measurement: surface morphology is traced first, then the CPD signal is collected while retracing the same scan line at a lift height of 200 nm; b) signal profile along the surface morphology image (red curve) reported in c) and along local CPD map reported in e) (blue curve); c) surface morphology image; d) associated as measured CPD map; e) local CPD contrast map obtained by subtracting from d) the long range waviness of surface potential around -3 V; the subtracted signal map is reported in f).

Further information on the distribution and characteristics of implanted regions were obtained by KPFM measurements carried out after the thermal treatment. **Figure 9A** provides a schematic of the KPFM measurement protocol. Representative measurements of the surface morphology and corresponding potential distribution, taken on the sample implanted with a phosphorus dose of  $5.07 \times 10^{14} \text{cm}^{-2}$ , are reported in **Figure 9**. The surface morphology at the end of the fabrication process (**Figure 9B**) has opposite contrast compared to that reported in **Figure 4**, which was

1  
2  
3 measured after ion implantation and polymer mask removal. Implanted regions are now recessed  
4  
5 by ~1.2 nm with respect to the average surface profile. This feature was observed in all samples  
6  
7 after the thermal treatment and confirmed by non-contact AFM measurements using non-conductive  
8  
9 sharp silicon probes (**Figure S6**). The origin of such a change in morphology is not clear.  
10  
11 Nevertheless, it is worth noting that in the annealed sample the native oxide was removed before  
12  
13 the thermal treatment to promote phosphorus activation. This process step and the successive  
14  
15 reoxidation of the silicon surface, which might be inhomogeneous due to the different local doping,<sup>59</sup>  
16  
17 are suggested as the origin of such change in surface morphology.  
18  
19

20  
21 The corresponding contact potential map (**Figure 9D**) shows a long-range waviness plus a  
22  
23 short-range regular, rather weak contrast, around the average value of -3 V. To better evidence the  
24  
25 short-range features, the long-range component was subtracted (**Figure 9F**) and the resulting map  
26  
27 of the relative CPD contrast is reported in **Figure 9E**. Considering the spatial arrangement of the  
28  
29 brighter spots of **Figure 9E**, it is obvious to associate them with phosphorus implanted regions;  
30  
31 moreover, comparison of the line profiles reported in **Figure 9B** evidences that these regions at  
32  
33 higher potential match the hollows in the morphology profile. On the other hand, the contrast between  
34  
35 phosphorus implanted regions and the surrounding p-type silicon is quite weak (~12 mV), while in  
36  
37 an ideal p-n junction array one would naively expect a larger potential difference related to the Fermi  
38  
39 level change between the n-doped regions and the p-type silicon wafer. However, KPFM  
40  
41 measurements on semiconductor surfaces are not straightforward, as the probe-sample system  
42  
43 behaves as a bias-dependent metal-insulator-semiconductor capacitor where probe-sample  
44  
45 interaction and local charge state at the semiconductor surface must be taken into account.<sup>60–62</sup> In  
46  
47 fact, as already pointed out by Polak et al.,<sup>60</sup> the band bending at the semiconductor surface, induced  
48  
49 by the presence of surface and interface charges, greatly affects the measured potential difference  
50  
51 between n- and p-regions, and voltage differences  $\leq 20$  mV were often experimentally observed.<sup>60</sup> In  
52  
53 our system, where no surface passivation step was applied and a defective native oxide likely  
54  
55 developed after the thermal treatment, this effect might be further enhanced by the small geometries  
56  
57 involved (both in-plane and vertical) and by the high doping level expected in the implanted regions.  
58  
59 Incidentally, assuming a work function for the PtSi probe of ~ 5 eV, a rough calculation (see  
60

1  
2  
3 supplementary information) reveals that a density of  $\sim 10^{13}$  q/cm<sup>2</sup> positive fixed charges at the  
4 Si/native oxide interface would account for the measured overall CPD signal of  $\sim -3$  V and,  
5 concurrently, for the  $\sim 12$  mV difference between p- and n-doped regions. Therefore, although partial  
6 activation and/or partial diffusion of implanted phosphorus cannot be definitively excluded, our KPFM  
7 measurements are consistent with the successful activation of phosphorous doping in well localized  
8 and ordered regions, in a system where a large density of positive surface charges dominates the  
9 measured CPD.  
10  
11  
12  
13  
14  
15  
16  
17  
18

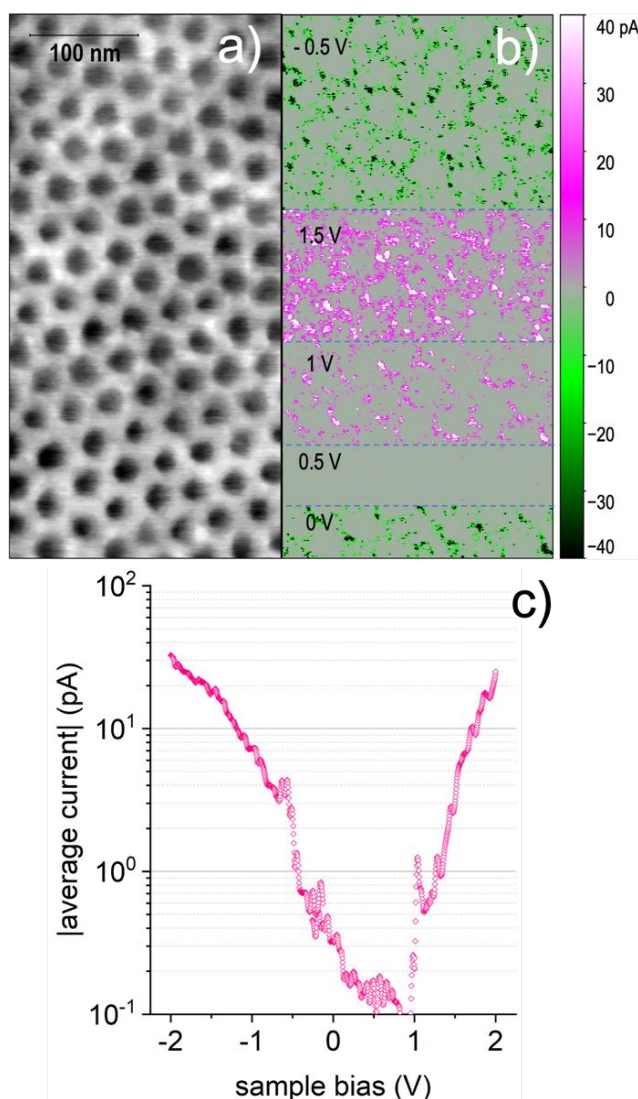


55 **Figure 10** Surface morphology (a) and corresponding current map (b) measured on sample with  $3.20 \times 10^{14}$   
56 cm<sup>-2</sup> dose, while changing the sample voltage bias as reported in the image. The greyscale of the  
57 morphology image corresponds to 3 nm. C) absolute average current vs sample bias voltage in semi-log  
58 scale; the current data are obtained averaging over 60 I-V measurements taken at different surface sites.  
59  
60

1  
2  
3 In the same experimental set-up, the local electrical conductivity was investigated by  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

In the same experimental set-up, the local electrical conductivity was investigated by conductive-AFM. Differently from the KPFM setup, C-AFM measurements are taken in contact mode with the probe acting as local top electrode at virtual ground, while the voltage bias is applied to the sample backside; the current flowing between the probe and the sample is collected through an amplifier, concurrently to the sample surface. **Figure 10a** and **10b** report a representative C-AFM measurement carried out on the sample implanted with  $3.20 \times 10^{14} \text{ cm}^{-2}$  dose. The surface morphology is similar to that already obtained in KPFM measurements. More interestingly, the corresponding current map shows that, at both positive and negative bias, current flows almost solely through the non-implanted regions. Comparing the segments measured at 1V and 1.5V, it is also observed that the current-carrying regions expand with increasing bias. On the other hand, the current collected when the probe passes over the implanted regions is below the detection limit at all applied bias. We also observe that no current is collected at  $V_s = 0.5 \text{ V}$ , whilst some current flows at  $V = 0 \text{ V}$ . Actually, this result is consistent with the assumption that positive charges are present at the semiconductor surface: a positive bias is required at the sample backside to balance the surface negative band bending induced by these positive charges before current starts flowing. Similar trends were observed on the other samples, also using different probes and measurement conditions.

To further explore the characteristics of the collected current, several current-voltage measurements were acquired at various surface sites. However, we realized that it is not possible to discriminate between measurements taken on implanted and non-implanted regions; in fact, the small size of surface features, which is comparable to the probe contact area, combined with the finite precision of tip positioning, does not allow to clearly distinguish the origin of the collected current. Therefore, we chose to automatically acquire many I-V curves at regularly spaced surface sites and then to average the results, thus obtaining a statistical trend of the current-voltage characteristics in the  $\pm 2 \text{ V}$  range, as reported in **Figure 10c**. The obtained IV curve is not symmetric: as already noted for the current map, current minimum lays at positive sample bias voltage, in the interval  $0.5 - 1 \text{ V}$ ; moreover, above  $1 \text{ V}$  the current increases fast, following a nearly exponential trend, whereas below  $0 \text{ V}$  the increase is less steep. The overall impression is that the sample does

not behave as a simple resistor and it is influenced to some extent by the presence of the implanted regions. Unfortunately, the C-AFM analysis does not allow further deductions, due to the limited current range and poor measurement reproducibility related to the modification occurring at the probe-sample system during the flow of high-density current.

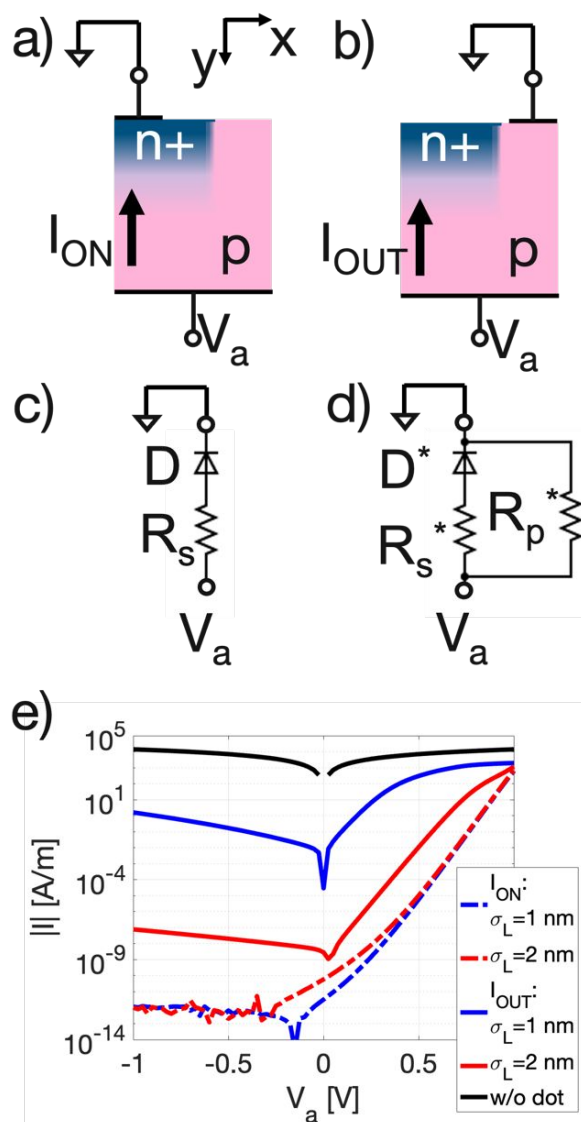

**Figure 11.** Modeling and simulation results. Two cases were schematized: top contact on the dot (a) and top contact located on the region outside the dot (b). In the center panels the equivalent circuits are highlighted for the on-dot case (c) and the outside-dot case (d). On the bottom panel (e) the simulated  $|I|$ - $V$  curves are reported for both cases and for two significant values of the  $\sigma_L = 1\text{ nm}$  and  $2\text{ nm}$ . The curve labeled “w/o dot” shows the  $I_{OUT}$  if there was no dot so when a simple plain p-region slab is simulated. Note that current is not expressed in A but in A/m due to the 2D dimensionality of the model that does not consider the third dimension (z dimension, normal to the plane of the figure).



1  
2  
3  
4 These experimental results can be interpreted by means of numerical simulations stating that  
5  
6 the measured I-V characteristics are compatible with the electrical behavior of a working p-n  
7  
8 nanojunction. To support this statement by simulation results, the sample portion between the n+  
9  
10 well center vertical axis and half the distance between the adjacent n+ well center was modeled as  
11  
12 a 2D rectangular domain with lateral size  $x_D = 17.5$  nm and vertical one  $y_D = 30$  nm. The domain  
13  
14 material was set to be crystalline silicon with a uniform acceptor doping of  $N_A = 8.5 \times 10^{18}$  cm<sup>-3</sup> with  
15  
16 a heavily n+ doped Si well is incorporated in its top-left region. The n+ well featured a Gaussian  
17  
18 doping profile with a maximum of donor doping  $N_D = 3 \times 10^{20}$  cm<sup>-3</sup> located at the domain top border  
19  
20 with a vertical standard deviation  $\sigma_y = 4.2$  nm, as extrapolated from the ToF-SIMS analysis. The  
21  
22 radius of the n+ well was set to  $r = 10$  nm leading to a n+ well of nanoscopic size, namely a quantum  
23  
24 dot. No information on the lateral drop-off doping profile standard deviation of the dot  $\sigma_L$  could be  
25  
26 extracted from the experimental data. Ideal ohmic contacts were applied to the top and to the bottom  
27  
28 of the domain to set the voltage at these boundaries of the system whereas boundary conditions  
29  
30 with zero lateral electric field were applied to the lateral interfaces due to symmetry considerations.  
31  
32 A small top contact, with a lateral size  $r_c = 5$  nm, modeled the radius of the AFM tip. The top contact  
33  
34 was set to a ground potential in all the simulations whereas a DC voltage  $V_a$  was applied to the back-  
35  
36 contact, as specifically done in the experiments. To reduce the number of AFM tip positions to be  
37  
38 modeled, only two main spatial positions of the top contact were considered: in the former the top  
39  
40 contact was positioned on top left region of the dot (see **Figure 11a**) and collects a  $I_{ON}$  current,  
41  
42 whereas in the latter the top contact was set at the top right region (see **Figure 11b**) collecting a  $I_{OUT}$   
43  
44 current.

45  
46 **Figure 10** showed a current flow only when the AFM tip was positioned outside the dot  
47  
48 whereas almost no current was recorded when it was on the dot. This lack of current can be  
49  
50 motivated by guessing that the current levels were below our measurement background noise level.  
51  
52 Actually, simulations reported in **Figure 11e** confirm that  $I_{ON}$  is very low for negative and small positive  
53  
54  $V_a$ , whereas  $I_{OUT}$  is always significantly higher, thus corroborating the experimental findings.  
55  
56 Moreover, the AFM probe whose size is expected to be just smaller than the implanted regions, may  
57  
58 collect current from the surrounding non-implanted regions, especially while measuring local I-V  
59  
60 characteristics; therefore, due to the very small size of the n+ implanted regions and large  $I_{OUT}$ , pure

1  
2  
3  
4  $I_{ON}$  cannot be actually accessed in our C-AFM setup. As already pointed out, the I-V characteristics  
5  
6 shown in **Figure 10c** presents a clear asymmetry. This asymmetry in the shape of the I-V  
7  
8 experimental data is clearly visible also in the simulation results (**Figure 11e**), whereas the voltage  
9  
10 shift of measured I-V is not accounted, because the presence of the thin top oxide, along with its  
11  
12 possible fixed charges, was not included in the model. The asymmetry in the shape can be explained  
13  
14 qualitatively by means of simple circuit models. When top contact is on the dot, the I-V curves can  
15  
16 be mapped to those of an equivalent circuit model of a diode in series with its parasitic resistance as  
17  
18 sketched in **Figure 11c**. When top contact is located outside the dot, the diode is poorly biased and  
19  
20 charge transport effects in the p-region on the right side of the dot can be modeled as an additional  
21  
22 resistor in parallel to the diode (**Figure 11d**). For  $V < 0$  the diode is poorly reversely biased, so the  
23  
24 current is shunted mostly through the resistor in parallel with an equivalent resistance that depends  
25  
26 strongly on  $\sigma_L$ . In Figure 10e we also added the limit case when no dot is formed (see “w/o dot”  
27  
28 curve), showing the foreseen linear I-V behavior in a uniform p-Si slab. When  $V > 0$  the diode is  
29  
30 forward biased so there is a sum of its direct current and of the current flowing through the equivalent  
31  
32 p-region resistor. Here, the current behavior depends on which one of the two components  
33  
34 dominates. The balance between the two depends on  $\sigma_L$ : for  $\sigma_L=1$  nm, i.e. for a narrow dot, the diode  
35  
36 biasing worsens in such a way that the current passing through the resistor in parallel has a higher  
37  
38 impact on the final I-V curve. For a larger  $\sigma_L = 2$  nm, i.e. for a slightly larger dot, there is a better  
39  
40 biasing of the junction, so the I-V characteristic is closer to the common one of a diode. Therefore,  
41  
42 the experimental results can be qualitatively mapped on the simulation ones of a not ideal p-n  
43  
44 nanojunction featuring a very small  $\sigma_L$ .  
45  
46  
47

## 48 **Conclusions**

49  
50 In conclusion, this work demonstrated that mesoporous thin films, obtained by BCP self-  
51  
52 assembly, efficiently shield a substrate during ultra-low energy (3 keV) implantation of phosphorus  
53  
54 ions at high doses. The mesoporous PS soft mask exhibited no modification of the morphology and  
55  
56 no detectable damage after the implantation process. The phosphorus atoms trapped in the mask  
57  
58 linearly increase as the implantation dose increases, confirming the capability of the PS matrix to  
59  
60 properly retain the low energy phosphorus ions in the dose range under investigation. The structural

1  
2  
3 and compositional characterization of the samples upon removal of the mesoporous PS template  
4 demonstrated that the phosphorus ions were implanted into the silicon substrate throughout the  
5 mask, leading to localized implantation in correspondence of the pores of the PS film. Raman spectra  
6 suggested the presence of a thin layer of amorphous Si in the implanted samples. A low temperature  
7 thermal treatment at 650°C was demonstrated to effectively promote silicon recrystallization and  
8 dopant activation without detrimental effects on their spatial confinement. These observations were  
9 further corroborated by specific SPM measurements. In particular, KPFM measurements showed an  
10 ordered modulation of the surface potential signal, compatible with the formation of localized n-doped  
11 regions. C-AFM measurements indicated that these regions hinder the current flow, at least in the  
12 explored voltage range. Conversely asymmetric I-V curves were obtained outside the implanted  
13 regions. According to FEM simulations, measured I-V characteristics are fully compatible with a not  
14 ideal but working p-n nanojunction with a lateral drop-off doping profile in the very few nanometers  
15 range.

16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

The collected results demonstrate the possibility to locally modify the potential landscape and conductivity of the semiconductor substrate by the introduction of a periodic array of dopants. The localization of dopants in very small nano-volumes paves the way to several applications like, for instance, the engineering of the semiconductor band structure, the synthesis of artificial crystals or the formation of quantum dot arrays in a semiconductor host matrix.

### ***Author information***

#### **Corresponding Authors**

\* **Michele Perego** – CNR - IMM, Unit of Agrate Brianza, Via C. Olivetti 2, Agrate Brianza 20864, Italy; <https://orcid.org/0000-0001-7431-1969> Email: [michele.perego@mdm.imm.cnr.it](mailto:michele.perego@mdm.imm.cnr.it)

### ***Acknowledgements***

The authors want to acknowledge the Raimond Castaing platform (T. Hungria) in Toulouse for the TEM and STEM-EDX characterization. The work was partially funded by PNRR MUR project PE0000023-NQSTI.

## References

- (1) Yang, G. G.; Choi, H. J.; Han, K. H.; Kim, J. H.; Lee, C. W.; Jung, E. I.; Jin, H. M.; Kim, S. O. Block Copolymer Nanopatterning for Nonsemiconductor Device Applications. *ACS Appl. Mater. Interfaces* **2022**, *14* (10), 12011–12037. <https://doi.org/10.1021/acsmi.1c22836>.
- (2) Kim, H.-C.; Hinsberg, W. D. Surface Patterns from Block Copolymer Self-Assembly. *J. Vac. Sci. Technol. A Vacuum, Surfaces, Film.* **2008**, *26* (6), 1369–1382. <https://doi.org/10.1116/1.3000056>.
- (3) Seguini, G.; Zanenga, F.; Cannetti, G.; Perego, M. Thermodynamics and Ordering Kinetics in Asymmetric PS-*b*-PMMA Block Copolymer Thin Films. *Soft Matter* **2020**, *16* (23), 5525–5533. <https://doi.org/10.1039/d0sm00441c>.
- (4) Zschech, D.; Kim, D. H.; Milenin, A. P.; Scholz, R.; Hillebrand, R.; Hawker, C. J.; Russell, T. P.; Steinhart, M.; Gösele, U. Ordered Arrays of  $\langle 100 \rangle$ -Oriented Silicon Nanorods by CMOS-Compatible Block Copolymer Lithography. *Nano Lett.* **2007**, *7* (6), 1516–1520. <https://doi.org/10.1021/nl070275d>.
- (5) Ruiz, R.; Kang, H.; Detcheverry, F. A.; Dobisz, E.; Kercher, D. S.; Albrecht, T. R.; De Pablo, J. J.; Nealey, P. F. Density Multiplication and Improved Lithography by Directed Block Copolymer Assembly. *Science* (80-. ). **2008**, *321* (5891), 936–939. <https://doi.org/10.1126/science.1157626>.
- (6) Liu, C.-C.; Franke, E.; Mignot, Y.; Xie, R.; Yeung, C. W.; Zhang, J.; Chi, C.; Zhang, C.; Farrell, R.; Lai, K.; Tsai, H.; Felix, N.; Corliss, D. Directed Self-Assembly of Block Copolymers for 7 Nanometre FinFET Technology and Beyond. *Nat. Electron.* **2018**, *1* (10), 562–569. <https://doi.org/10.1038/s41928-018-0147-4>.
- (7) Feng, H.; Dolejsi, M.; Zhu, N.; Yim, S.; Loo, W.; Ma, P.; Zhou, C.; Craig, G. S. W.; Chen, W.; Wan, L.; Ruiz, R.; de Pablo, J. J.; Rowan, S. J.; Nealey, P. F. Optimized Design of Block Copolymers with Covarying Properties for Nanolithography. *Nat. Mater.* **2022**, *21* (12), 1426–1433. <https://doi.org/10.1038/s41563-022-01392-1>.
- (8) Chai, J.; Buriak, J. M. Using Cylindrical Domains of Block Copolymers to Self-Assemble and Align Metallic Nanowires. *ACS Nano* **2008**, *2* (3), 489–501. <https://doi.org/10.1021/nn700341s>.
- (9) Jung, Y. S.; Jung, W. C.; Tuller, H. L.; Ross, C. A. Nanowire Conductive Polymer Gas Sensor Patterned Using Self-Assembled Block Copolymer Lithography. *Nano Lett.* **2008**, *8* (11), 3777–3780. <https://doi.org/10.1021/nl802099k>.
- (10) Chakrabarti, B.; Chan, H.; Alam, K.; Koneru, A.; Gage, T. E.; Ocola, L. E.; Divan, R.; Rosenmann, D.; Khanna, A.; Grisafe, B.; Sanders, T.; Datta, S.; Arslan, I.; Sankaranarayan, S. K. R. S.; Guha, S. Nanoporous Dielectric Resistive Memories Using Sequential Infiltration Synthesis. *ACS Nano* **2021**, *15* (3), 4155–4164. <https://doi.org/10.1021/acsnano.0c03201>.
- (11) Yun, T.; Jin, H. M.; Kim, D. H.; Han, K. H.; Yang, G. G.; Lee, G. Y.; Lee, G. S.; Choi, J. Y.; Kim, I. D.; Kim, S. O. 2D Metal Chalcogenide Nanopatterns by Block Copolymer Lithography. *Adv. Funct. Mater.* **2018**, *28* (50). <https://doi.org/10.1002/adfm.201804508>.

- 1  
2  
3 (12) Kang, H. S.; Han, S. W.; Park, C.; Lee, S. W.; Eoh, H.; Baek, J.; Shin, D. G.; Park, T. H.; Huh,  
4 J.; Lee, H.; Kim, D. E.; Ryu, D. Y.; Thomas, E. L.; Koh, W. G.; Park, C. 3D Touchless  
5 Multiorder Reflection Structural Color Sensing Display. *Sci. Adv.* **2020**, *6* (30), 1–11.  
6 <https://doi.org/10.1126/sciadv.abb5769>.  
7
- 8 (13) Kim, J. Y.; Kim, H.; Kim, B. H.; Chang, T.; Lim, J.; Jin, H. M.; Mun, J. H.; Choi, Y. J.; Chung,  
9 K.; Shin, J.; Fan, S.; Kim, S. O. Highly Tunable Refractive Index Visible-Light Metasurface  
10 from Block Copolymer Self-Assembly. *Nat. Commun.* **2016**, *7*, 1–9.  
11 <https://doi.org/10.1038/ncomms12911>.  
12
- 13 (14) Dolan, J. A.; Dehmel, R.; Demetriadou, A.; Gu, Y.; Wiesner, U.; Wilkinson, T. D.; Gunkel, I.;  
14 Hess, O.; Baumberg, J. J.; Steiner, U.; Saba, M.; Wilts, B. D. Metasurfaces Atop  
15 Metamaterials: Surface Morphology Induces Linear Dichroism in Gyroid Optical  
16 Metamaterials. *Adv. Mater.* **2019**, *31* (2). <https://doi.org/10.1002/adma.201803478>.  
17
- 18 (15) Yang, S. Y.; Ryu, I.; Kim, H. Y.; Kim, J. K.; Jang, S. K.; Russell, T. P. Nanoporous Membranes  
19 with Ultrahigh Selectivity and Flux for the Filtration of Viruses. *Adv. Mater.* **2006**, *18* (6), 709–  
20 712. <https://doi.org/10.1002/adma.200501500>.  
21
- 22 (16) Bang, J.; Kim, S. H.; Drockenmuller, E.; Misner, M. J.; Russell, T. P.; Hawker, C. J. Defect-  
23 Free Nanoporous Thin Films from ABC Triblock Copolymers. *J. Am. Chem. Soc.* **2006**, *128*  
24 (23), 7622–7629. <https://doi.org/10.1021/ja0608141>.  
25
- 26 (17) Choi, Y.; Cha, S. K.; Ha, H.; Lee, S.; Seo, H. K.; Lee, J. Y.; Kim, H. Y.; Kim, S. O.; Jung, W.  
27 C. Unravelling Inherent Electrocatalysis of Mixed-Conducting Oxide Activated by Metal  
28 Nanoparticle for Fuel Cell Electrodes. *Nat. Nanotechnol.* **2019**, *14* (3), 245–251.  
29 <https://doi.org/10.1038/s41565-019-0367-4>.  
30
- 31 (18) Kim, J. Y.; Lim, J.; Jin, H. M.; Kim, B. H.; Jeong, S. J.; Choi, D. S.; Li, D. J.; Kim, S. O. 3D  
32 Tailored Crumpling of Block-Copolymer Lithography on Chemically Modified Graphene. *Adv.*  
33 *Mater.* **2016**, *28* (8), 1591–1596. <https://doi.org/10.1002/adma.201504590>.  
34
- 35 (19) Tseng, Y. C.; Darling, S. B. Block Copolymer Nanostructures for Technology. *Polymers*  
36 *(Basel)*. **2010**, *2* (4), 470–489. <https://doi.org/10.3390/polym2040470>.  
37
- 38 (20) Topham, P. D.; Parnell, A. J.; Hiorns, R. C. Block Copolymer Strategies for Solar Cell  
39 Technology. *J. Polym. Sci. Part B Polym. Phys.* **2011**, *49* (16), 1131–1156.  
40 <https://doi.org/10.1002/polb.22302>.  
41
- 42 (21) Boyd, D. A. Block Copolymer Lithography. *New Futur. Dev. Catal. Catal. by Nanoparticles*  
43 **2013**, 305–332. <https://doi.org/10.1016/B978-0-444-53874-1.00013-5>.  
44
- 45 (22) Sanders, D. P. Advances in Patterning Materials for 193 Nm Immersion Lithography. *Chem.*  
46 *Rev.* **2010**, *110* (1), 321–360. <https://doi.org/10.1021/cr900244n>.  
47
- 48 (23) Levinson, H. J. High-NA EUV Lithography: Current Status and Outlook for the Future. *Jpn. J.*  
49 *Appl. Phys.* **2022**, *61* (SD). <https://doi.org/10.35848/1347-4065/ac49fa>.  
50
- 51 (24) Yang, X. M.; Wan, L.; Xiao, S.; Xu, Y.; Weller, D. K. Directed Block Copolymer Assembly  
52 versus Electron Beam Lithography for Bit-Patterned Media with Areal Density of 1  
53 Terabit/Inch<sup>2</sup> and Beyond. *ACS Nano* **2009**, *3* (7), 1844–1858.  
54 <https://doi.org/10.1021/nn900073r>.  
55
- 56 (25) Majewski, P. W.; Yager, K. G. Rapid Ordering of Block Copolymer Thin Films. *J. Phys.*  
57 *Condens. Matter* **2016**, *28* (40). <https://doi.org/10.1088/0953-8984/28/40/403002>.  
58
- 59 (26) Ham, S.; Shin, C.; Kim, E.; Ryu, D. Y.; Jeong, U.; Russell, T. P.; Hawker, C. J. Microdomain  
60 Orientation of PS-*b*-PMMA by Controlled Interfacial Interactions. *Macromolecules* **2008**, *41*  
(17), 6431–6437. <https://doi.org/10.1021/ma8007338>.
- (27) Ryu, D. Y.; Ham, S.; Kim, E.; Jeong, U.; Hawker, C. J.; Russell, T. P. Cylindrical Microdomain

- Orientation of PS-b-PMMA on the Balanced Interfacial Interactions: Composition Effect of Block Copolymers. *Macromolecules* **2009**, *42* (13), 4902–4906. <https://doi.org/10.1021/ma900110w>.
- (28) Sparnacci, K.; Antonioli, D.; Gianotti, V.; Laus, M.; Ferrarese Lupi, F.; Giammaria, T. J.; Seguini, G.; Perego, M. Ultrathin Random Copolymer-Grafted Layers for Block Copolymer Self-Assembly. *ACS Appl. Mater. Interfaces* **2015**, *7* (20), 10944–10951. <https://doi.org/10.1021/acsami.5b02201>.
- (29) Olszowka, V.; Tsarkova, L.; Böker, A. 3-Dimensional Control over Lamella Orientation and Order in Thick Block Copolymer Films. *Soft Matter* **2009**, *5* (4), 812–819. <https://doi.org/10.1039/b814365j>.
- (30) Thurn-Albrecht, T.; Schotter, J.; Kastle, G. A.; Emley, N.; Shibauchi, T.; Krusin-Elbaum, L.; Guarini, K.; Black, C. T.; Tuominen, M. T.; Russell, T. P. Ultrahigh-Density Nanowire Arrays Grown in Self-Assembled Diblock Copolymer Templates. *Science (80-. )* **2000**, *290* (5499), 2126–2129. <https://doi.org/10.1126/science.290.5499.2126>.
- (31) Majewski, P. W.; Gopinadhan, M.; Osuji, C. O. Magnetic Field Alignment of Block Copolymers and Polymer Nanocomposites: Scalable Microstructure Control in Functional Soft Materials. *J. Polym. Sci. Part B Polym. Phys.* **2012**, *50* (1), 2–8. <https://doi.org/10.1002/polb.22382>.
- (32) Pujari, S.; Keaton, M. A.; Chaikin, P. M.; Register, R. A. Alignment of Perpendicular Lamellae in Block Copolymer Thin Films by Shearing. *Soft Matter* **2012**, *8* (19), 5358–5363. <https://doi.org/10.1039/c2sm25270h>.
- (33) Marencic, A. P.; Chaikin, P. M.; Register, R. A. Orientational Order in Cylinder-Forming Block Copolymer Thin Films. *Phys. Rev. E - Stat. Nonlinear, Soft Matter Phys.* **2012**, *86* (2), 1–8. <https://doi.org/10.1103/PhysRevE.86.021507>.
- (34) Giammaria, T. J.; Ferrarese Lupi, F.; Seguini, G.; Sparnacci, K.; Antonioli, D.; Gianotti, V.; Laus, M.; Perego, M. Effect of Entrapped Solvent on the Evolution of Lateral Order in Self-Assembled P(S-r-MMA)/PS-b-PMMA Systems with Different Thicknesses. *ACS Appl. Mater. Interfaces* **2017**, *9* (37), 31215–31223. <https://doi.org/10.1021/acsami.6b14332>.
- (35) Gunkel, I. Directing Block Copolymer Self-Assembly on Patterned Substrates. *Small* **2018**, *14*, 1802872. <https://doi.org/10.1002/smll.201802872>
- (36) Luo, M.; Epps, T. H. Directed Block Copolymer Thin Film Self-Assembly: Emerging Trends in Nanopattern Fabrication. *Macromolecules* **2013**, *46* (19), 7567–7579. <https://doi.org/10.1021/ma401112y>.
- (37) Gottlieb, S.; Rösner, B.; Evangelio, L.; Fernández-Regúlez, M.; Nogales, A.; García-Gutiérrez, M. C.; Keller, T. F.; Fraxedas, J.; Ezquerro, T. A.; David, C.; Perez-Murano, F. Self-Assembly Morphology of Block Copolymers in Sub-10 Nm Topographical Guiding Patterns. *Mol. Syst. Des. Eng.* **2019**, *4* (1), 175–185. <https://doi.org/10.1039/c8me00046h>.
- (38) Andreozzi, A.; Poliani, E.; Seguini, G.; Perego, M. The Effect of Random Copolymer on the Characteristic Dimensions of Cylinder-Forming PS-b-PMMA Thin Films. *Nanotechnology* **2011**, *22* (18). <https://doi.org/10.1088/0957-4484/22/18/185304>.
- (39) Ferrarese Lupi, F.; Giammaria, T. J.; Volpe, F. G.; Lotto, F.; Seguini, G.; Pivac, B.; Laus, M.; Perego, M. High Aspect Ratio PS-b-PMMA Block Copolymer Masks for Lithographic Applications. *ACS Appl. Mater. Interfaces* **2014**, *6* (23), 21389–21396. <https://doi.org/10.1021/am506391n>.
- (40) Farrell, R. A.; Petkov, N.; Shaw, M. T.; Djara, V.; Holmes, J. D.; Morris, M. A. Monitoring PMMA Elimination by Reactive Ion Etching from a Lamellar PS-b-PMMA Thin Film by Ex Situ TEM Methods. *Macromolecules* **2010**, *43* (20), 8651–8655. <https://doi.org/10.1021/ma101827u>.


- 1  
2  
3 (41) Gharbi, A.; Tiron, R.; Pimenta Barros, P.; Argoud, M.; Servin, I.; Chevalier, X.; Nicolet, C.;  
4 Navarro, C. PMMA Removal Options by Wet Development in PS- b -PMMA Block Copolymer  
5 for Nanolithographic Mask Fabrication . *J. Vac. Sci. Technol. B, Nanotechnol. Microelectron.*  
6 *Mater. Process. Meas. Phenom.* **2015**, *33* (5), 051602. <https://doi.org/10.1116/1.4929548>.  
7
- 8 (42) Frascaroli, J.; Brivio, S.; Ferrarese Lupi, F.; Seguini, G.; Boarino, L.; Perego, M.; Spiga, S.  
9 Resistive Switching in High-Density Nanodevices Fabricated by Block Copolymer Self-  
10 Assembly. *ACS Nano* **2015**, *9* (3), 2518–2529. <https://doi.org/10.1021/nn505131b>.  
11
- 12 (43) Barrera, G.; Celegato, F.; Coïsson, M.; Manzin, A.; Ferrarese Lupi, F.; Seguini, G.; Boarino,  
13 L.; Aprile, G.; Perego, M.; Tiberto, P. Magnetization Switching in High-Density Magnetic  
14 Nanodots by a Fine-Tune Sputtering Process on a Large-Area Diblock Copolymer Mask.  
15 *Nanoscale* **2017**, *9* (43), 16981–16992. <https://doi.org/10.1039/c7nr04295g>.  
16
- 17 (44) Andreozzi, A.; Lamagna, L.; Seguini, G.; Fanciulli, M.; Schamm-Chardon, S.; Castro, C.;  
18 Perego, M. The Fabrication of Tunable Nanoporous Oxide Surfaces by Block Copolymer  
19 Lithography and Atomic Layer Deposition. *Nanotechnology* **2011**, *22* (33).  
20 <https://doi.org/10.1088/0957-4484/22/33/335303>.  
21
- 22 (45) Segal-Peretz, T.; Ren, J.; Xiong, S.; Khaira, G.; Bowen, A.; Ocola, L. E.; Divan, R.; Doxastakis,  
23 M.; Ferrier, N. J.; De Pablo, J.; Nealey, P. F. Quantitative Three-Dimensional Characterization  
24 of Block Copolymer Directed Self-Assembly on Combined Chemical and Topographical  
25 Prepatterned Templates. *ACS Nano* **2017**, *11* (2), 1307–1319.  
26 <https://doi.org/10.1021/acsnano.6b05657>.  
27
- 28 (46) Kamcev, J.; Germack, D. S.; Nykypanchuk, D.; Grubbs, R. B.; Nam, C. Y.; Black, C. T.  
29 Chemically Enhancing Block Copolymers for Block-Selective Synthesis of Self-Assembled  
30 Metal Oxide Nanostructures. *ACS Nano* **2013**, *7* (1), 339–346.  
31 <https://doi.org/10.1021/nn304122b>.  
32
- 33 (47) Tseng, Y. C.; Peng, Q.; Ocola, L. E.; Elam, J. W.; Darling, S. B. Enhanced Block Copolymer  
34 Lithography Using Sequential Infiltration Synthesis. *J. Phys. Chem. C* **2011**, *115* (36), 17725–  
35 17729. <https://doi.org/10.1021/jp205532e>.  
36
- 37 (48) Seguini, G.; Motta, A.; Bigatti, M.; Caligiore, F. E.; Rademaker, G.; Gharbi, A.; Tiron, R.;  
38 Tallarida, G.; Perego, M.; Cianci, E. Al<sub>2</sub>O<sub>3</sub>Dot and Antidot Array Synthesis in Hexagonally  
39 Packed Poly(Styrene- Block-Methyl Methacrylate) Nanometer-Thick Films for Nanostructure  
40 Fabrication. *ACS Appl. Nano Mater.* **2022**, *5* (7), 9818–9828.  
41 <https://doi.org/10.1021/acsanm.2c02013>.  
42
- 43 (49) Castro, C.; Schamm-Chardon, S.; Pecassou, B.; Andreozzi, A.; Seguini, G.; Perego, M.;  
44 Benassayag, G. In-Plane Organization of Silicon Nanocrystals Embedded in SiO<sub>2</sub> Thin Films.  
45 *Nanotechnology* **2013**, *24* (7). <https://doi.org/10.1088/0957-4484/24/7/075302>.  
46
- 47 (50) Castro, C.; BenAssayag, G.; Pecassou, B.; Andreozzi, A.; Seguini, G.; Perego, M.; Schamm-  
48 Chardon, S. Nanoscale Control of Si Nanoparticles within a 2D Hexagonal Array Embedded  
49 in SiO<sub>2</sub> Thin Films. *Nanotechnology* **2017**, *28* (1). <https://doi.org/10.1088/0957-4484/28/1/014001>.  
50
- 51 (51) Luce, F. P.; Pasini, L.; Sklénard, B.; Mathieu, B.; Licitra, C.; Batude, P.; Mazen, F.  
52 Methodology for Thermal Budget Reduction of SPER down to 450 °c for 3D Sequential  
53 Integration. *Nucl. Instruments Methods Phys. Res. Sect. B Beam Interact. with Mater. Atoms*  
54 **2016**, *370*, 14–18. <https://doi.org/10.1016/j.nimb.2015.12.021>.  
55
- 56 (52) Pelaz, L.; Marqués, L. A.; Barbolla, J. Ion-Beam-Induced Amorphization and Recrystallization  
57 in Silicon. *J. Appl. Phys.* **2004**, *96* (11), 5947–5976. <https://doi.org/10.1063/1.1808484>.  
58
- 59 (53) Mastromatteo, M.; Arduca, E.; Napolitani, E.; Nicotra, G.; De Salvador, D.; Bacci, L.;  
60 Frascaroli, J.; Seguini, G.; Scuderi, M.; Impellizzeri, G.; Spinella, C.; Perego, M.; Carnera, A.  
Quantification of Phosphorus Diffusion and Incorporation in Silicon Nanocrystals Embedded

1  
2  
3 in Silicon Oxide. *Surf. Interface Anal.* **2014**, *46* (S1), 393–396.  
4 <https://doi.org/10.1002/sia.5578>.

- 5  
6 (54) Perego, M.; Seguíni, G.; Arduca, E.; Frascaroli, J.; De Salvador, D.; Mastromatteo, M.;  
7 Carnera, A.; Nicotra, G.; Scuderi, M.; Spinella, C.; Impellizzeri, G.; Lenardi, C.; Napolitani, E.  
8 Thermodynamic Stability of High Phosphorus Concentration in Silicon Nanostructures. *Nanoscale* **2015**, *7* (34), 14469–14475. <https://doi.org/10.1039/c5nr02584b>.  
9  
10 (55) Nazari, M.; Holtz, M. W. Near-Ultraviolet Raman and Micro-Raman Analysis of Electronic  
11 Materials. *Appl. Phys. Rev.* **2018**, *5* (4). <https://doi.org/10.1063/1.5054660>.  
12  
13 (56) Glatzel, T.; Gysin, U.; Meyer, E. Kelvin Probe Force Microscopy for Material Characterization.  
14 *Microscopy* **2022**, *71* (September 2021), 1165–1173. <https://doi.org/10.1093/jmicro/dfab040>.  
15  
16 (57) Nečas, D.; Klapetek, P. Gwyddion: An Open-Source Software for SPM Data Analysis. *Cent.*  
17 *Eur. J. Phys.* **2012**, *10* (1), 181–188. <https://doi.org/10.2478/s11534-011-0096-2>.  
18  
19 (58) Harriman, T. A.; Lucca, D. A.; Lee, J. K.; Klopstein, M. J.; Herrmann, K.; Nastasi, M. Ion  
20 Implantation Effects in Single Crystal Si Investigated by Raman Spectroscopy. *Nucl.*  
21 *Instruments Methods Phys. Res. Sect. B Beam Interact. with Mater. Atoms* **2009**, *267* (8–9),  
22 1232–1234. <https://doi.org/10.1016/j.nimb.2009.01.021>.  
23  
24 (59) Sze, S.; Lee, M.-K. *Semiconductor Devices - Physics and Technology*, third.; Wiley, 1985.  
25  
26 (60) Polak, L.; Wijngaarden, R. J. Two Competing Interpretations of Kelvin Probe Force  
27 Microscopy on Semiconductors Put to Test. *Phys. Rev. B* **2016**, *93* (19), 1–10.  
28 <https://doi.org/10.1103/PhysRevB.93.195320>.  
29  
30 (61) Xu, J.; Chen, D. Interpreting Kelvin Probe Force Microscopy on Semiconductors by Fourier  
31 Analysis. *J. Appl. Phys.* **2021**, *129* (3). <https://doi.org/10.1063/5.0024073>.  
32  
33 (62) Bonilla, R. S. Modelling of Kelvin Probe Surface Voltage and Photovoltage in Dielectric-  
34 Semiconductor Interfaces. *Mater. Res. Express* **2022**, *9* (8). [https://doi.org/10.1088/2053-](https://doi.org/10.1088/2053-1591/ac84c8)  
35 [1591/ac84c8](https://doi.org/10.1088/2053-1591/ac84c8).  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60



## Graphical Abstract

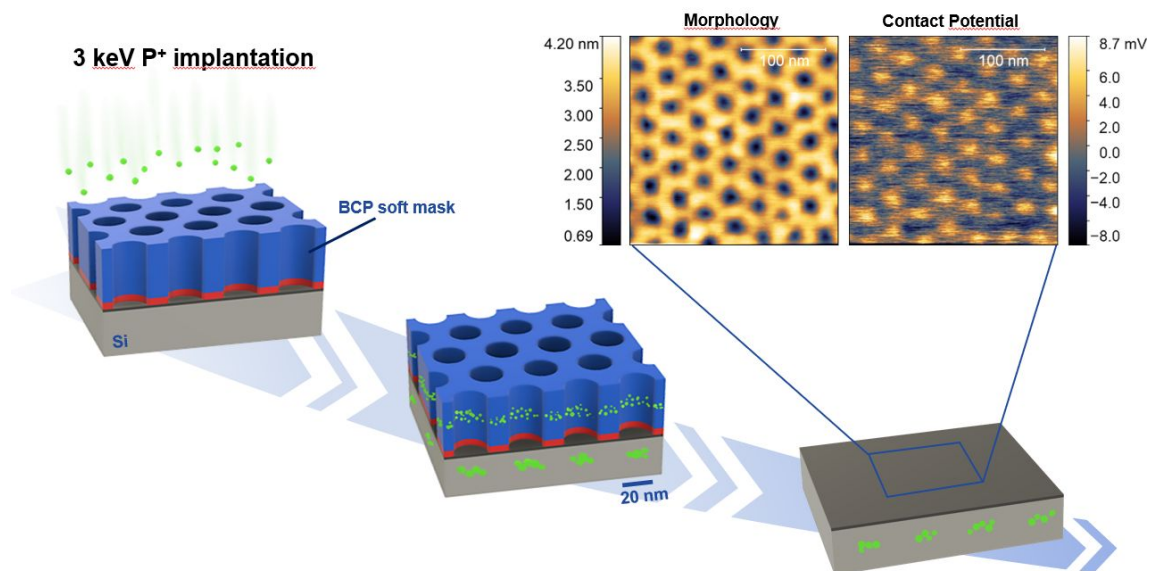

## Supplementary information

# Periodic arrays of dopants in silicon by ultra-low energy implantation of phosphorus ions through a block copolymer thin film

Stefano Kuschlan,<sup>(1)(2)</sup> Riccardo Chiarcos,<sup>(2)</sup> Michele Laus,<sup>(2)</sup> Francesc Pérez-Murano,<sup>(3)</sup> Jordi Llobet,<sup>(3)</sup> Marta Fernandez-Regulez,<sup>(3)</sup> Caroline Bonafos,<sup>(4)</sup> Michele Perego,<sup>(1)\*</sup> Gabriele Seguíni,<sup>(1)</sup>  
Marco De Michielis,<sup>(1)</sup> Graziella Tallarida.<sup>(1)</sup>


(1) *CNR-IMM, Unit of Agrate Brianza, Via C. Olivetti 2, I-20864 Agrate Brianza, Italy.*

(2) *Università del Piemonte Orientale “A. Avogadro”, Viale T. Michel 11, I-15121 Alessandria, Italy*


(3) *Institute of Microelectronics of Barcelona (IMB-CNM, CSIC), Bellaterra 08193, Spain*

(4) *CEMES-CNRS, Université de Toulouse, CNRS, 31055 Toulouse, France*


\* corresponding author: [michele.perego@mdm.imm.cnr.it](mailto:michele.perego@mdm.imm.cnr.it)

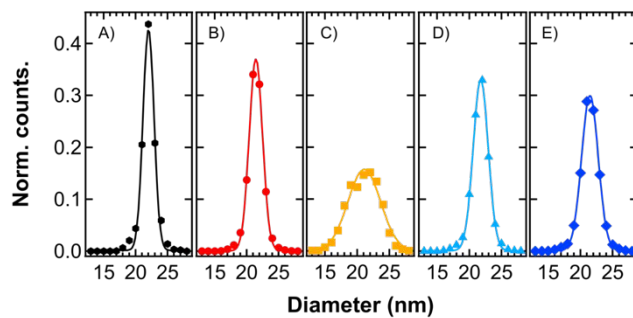


**Figure S1.** Distribution of diameters, solid lines are the gaussian fit of the experimental data. A) Pristine PS mask, B)  $1.55 \times 10^{14} \text{ cm}^{-2}$  dose, C)  $2.83 \times 10^{14} \text{ cm}^{-2}$  dose, D)  $3.20 \times 10^{14} \text{ cm}^{-2}$  dose, E)  $5.07 \times 10^{14} \text{ cm}^{-2}$  dose.

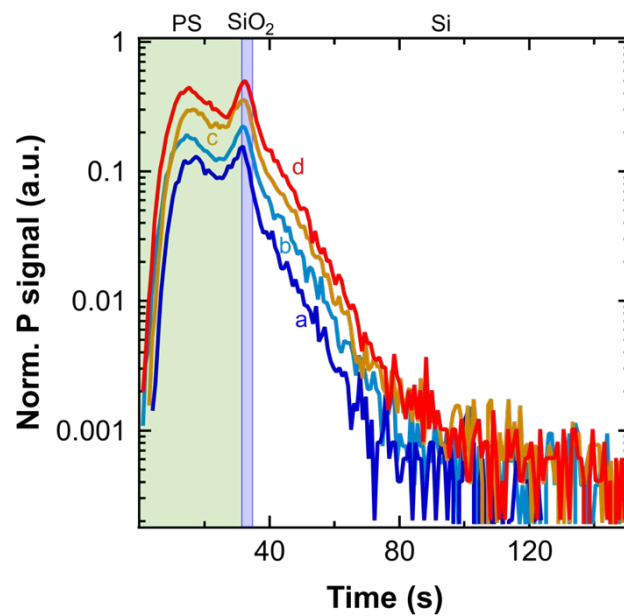


**Figure S2.** Depth profile of P after implantation and before removal of PS mask. a)  $1.55 \times 10^{14} \text{ cm}^{-2}$  dose, b)  $2.83 \times 10^{14} \text{ cm}^{-2}$  dose, c)  $3.20 \times 10^{14} \text{ cm}^{-2}$  dose, d)  $5.07 \times 10^{14} \text{ cm}^{-2}$  dose.

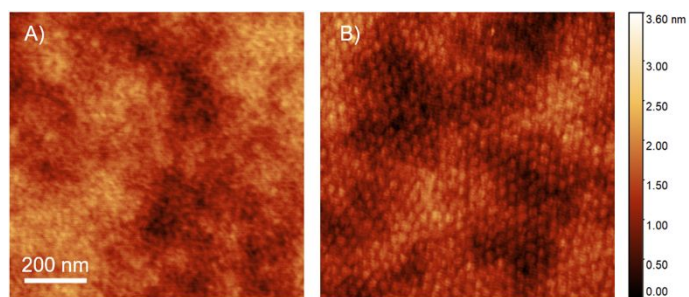


**Figure S3.** AFM image of the silicon surface of (A) a pristine substrate, (B) a sample implanted through BCP mask with a dose of  $1.55 \times 10^{14} \text{ cm}^{-2}$ .

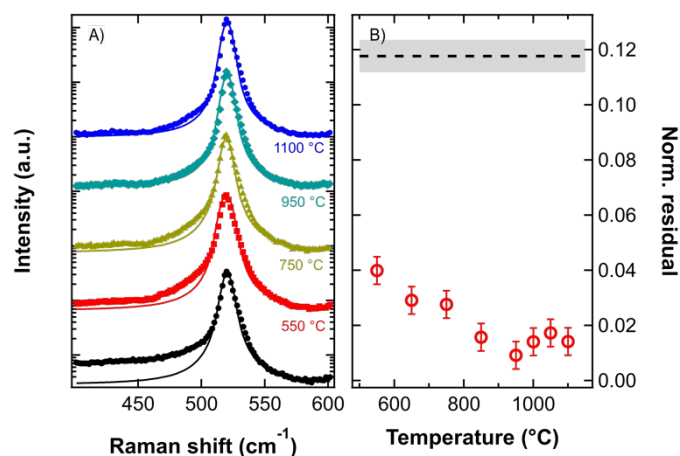

**Figure S4.** A) Raman spectra of the sample implanted with dose of  $1.55 \times 10^{14} \text{ cm}^{-2}$ . In the graph spectra are reported before the annealing and after a 5 s annealing at different temperatures. Solid lines represent the fit with a Voigt function. B) Normalized residuals of the  $[400, 500] \text{ cm}^{-1}$  interval as a function of the annealing temperature. The black dashed line reports the value with error (grey area) of the sample before the annealing.

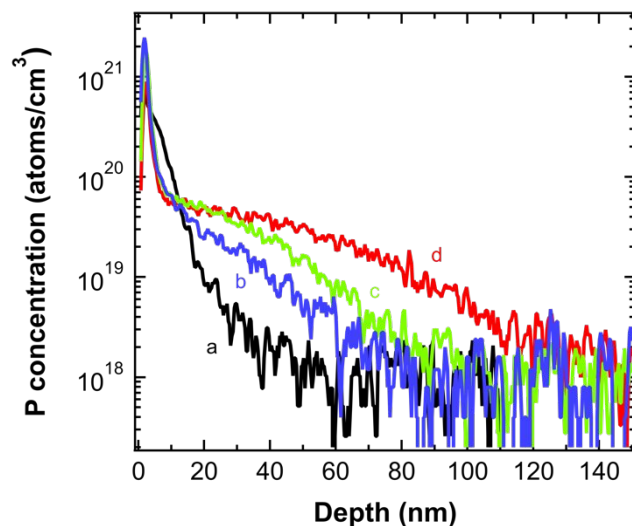

**Figure S5.** Calibrated profile of P for the sample implanted with dose  $1.55 \times 10^{14} \text{ cm}^{-2}$ . Curves represent the sample (a) before the annealing, after 5 s annealing at (b) 1000 °C, (c) 1050 °C, (d) 1100 °C.

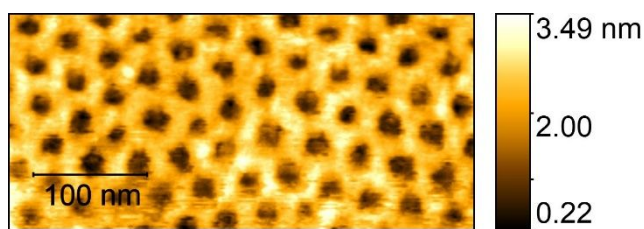

**Figure S6.** Surface morphology after the annealing step of the sample implanted with dose  $3.2 \times 10^{14} \text{ cm}^{-2}$ ; the presence of hollows  $\sim 1.2 \text{ nm}$  deep in correspondence of the implanted regions is confirmed by AFM measurements taken in tapping mode, using uncoated sharp silicon probes (nominal tip radius  $\sim 7 \text{ nm}$ )



## Estimation of the Contact Potential Difference

The surface potential of a semiconductor is influenced by several factors: bulk doping, charge stored at the surface and/or the native oxide, interface defect states, formation of a space charge region, surface band bending.

A general expression for the potential difference between the KPFM probe and the semiconductor surface is [1s]:

$$\Delta V = (V_m - \Phi_m) - V_i - (\phi_s - \Phi_s) \quad \text{Eq. 1}$$

Where  $V_m$  is the voltage applied to the probe;

$\Phi_{m/s}$  are the local workfunction for the metal and the semiconductor, respectively.

$V_i$  is the potential drop across the insulator (the native oxide, in our system) generated by the surface charges;

$\phi_s$  is the surface potential due to the space charge region;

The KPFM feedback loop adjusts  $V_m$  to achieve  $\Delta V=0$ , thus providing the contact potential difference as:

$$CPD = -V_m = -\left(\frac{\Phi_{ms}}{q} + \phi_s + V_i\right) \quad \text{Eq. 2}$$

$$\Phi_s = \chi + \frac{E_g}{2} - \pm \phi_F \quad \text{Eq. 2b}$$

$$\phi_F = \pm KT \ln \frac{N_{dop}}{n_i} \quad \text{Eq. 2c}$$

(Eq. 2c is positive for n-type and negative for p-type)

While scanning between n- and p-doped regions, assuming that  $V_i$ ,  $\Phi_m$  and the silicon electron affinity,  $\chi$ , are constant across the surface, the CPD difference can be written as:

$$\Delta CPD^{n,p} = \Delta V_k$$

1  
2  
3 Where  $\Delta V_k$  depends on the doping level and accounts for the band bending at the surface induced  
4 by the presence of surface and interface charges. In other words, in relation to eq 2,  $\Delta V_k$  includes  
5 the variable part of  $\Phi_s$  due the Fermi level adjustment at the surface, and  $\phi_s$  due to the presence of  
6 surface/interface charges.  
7  
8  
9

10  
11  
12  $\Delta V_k$  was estimated by Polak et al [2s] in a wide range of doping levels and surface/interface  
13 charge densities. Considering the doping densities relevant for our samples ( $N_d=5 \times 10^{20} \text{ cm}^{-3}$  and  
14  $N_a=8.5 \times 10^{18} \text{ cm}^{-3}$ ), a  $\Delta V_k \sim 12 \text{ meV}$  (as detected in our measurements) is obtained with a surface  
15 charge density of  $\sim 10^{13} \text{ cm}^{-2}$   
16  
17  
18  
19

20  
21  
22 Going back to Eq 2 and assuming:

23  
24  
25  $\Phi_m/q = 5 \text{ eV}$  [3s]

26  
27  
28  $\chi/q = 4.05 \text{ eV}$

29  
30  
31  $V_i = \frac{x_0 Q_f}{K_i \epsilon_0}$  where  $Q_f$  is an effective fixed charge density centered at a plane distance  
32  $x_0 \sim 1 \text{ nm}$  from the interface,  $K_i = 3.9$  is the dielectric constant of the native oxide and  $\epsilon_0$  is the  
33 vacuum permittivity [1s];  
34  
35  
36

37  
38 We find that, assuming  $Q_f = 5 \times 10^{13} \text{ cm}^{-2}$ ,  $\text{CPD} \sim -3 \text{ V}$ , which is the experimental background  
39 value detected by KPFM (Fig. 8f).  
40  
41

42  
43 Although this computation is quite rough and not fully self-consistent, KPFM results indicate that  
44 our samples can be thought as arrays of p-n nanojunctions with a surface native oxide characterized  
45 by a high density of positive fixed charges that strongly affect the semiconductor surface band  
46 bending.  
47  
48  
49

50  
51  
52 1s. Ruy Sebastian Bonilla 2022 Mater. Res. Express 9 085901

53  
54  
55 2s. Leo Polak and Rinke J. Wijngaarden, 2016 Phys. Rev. B 93, 195320

56  
57  
58 3s. Manish K. Niranjana, Stefan Zollner, Leonard Kleinman, and Alexander A. Demkov, 2006 Phys.  
59 Rev. B 73, 195332  
60