



**HAL**  
open science

# Mechanical and thermal properties of the lightweight mortar made of wood biomass ash and sunflower particles

Désiré Ndahirwa, Hélène Lenormand, Hafida Zmamou, Nathalie Leblanc

► **To cite this version:**

Désiré Ndahirwa, Hélène Lenormand, Hafida Zmamou, Nathalie Leblanc. Mechanical and thermal properties of the lightweight mortar made of wood biomass ash and sunflower particles. XXIVème Journée de l'École Doctorale Normande de Biologie Intégrative, Santé & Environnement JED 2022, Jun 2022, Online, France. hal-04261310

**HAL Id: hal-04261310**

**<https://hal.science/hal-04261310v1>**

Submitted on 26 Oct 2023

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.






# Mechanical and thermal properties of the lightweight mortar made of wood biomass ash and sunflower particles

Désiré NDAHIRWA<sup>1\*</sup>, Hélène LENORMAND<sup>1</sup>, Hafida ZMAMOU<sup>1</sup>, Nathalie LEBLANC<sup>1</sup>

<sup>1</sup>UniLaSalle, Univ. Artois, ULR7519 - Transformations & Agro-ressources, Normandie Université, 3 rue du Tronquet, 76130 Mont-Saint-Aignan, France.

(\*Corresponding author: desire.ndahirwa@unilasalle.fr)

## 1. Introduction

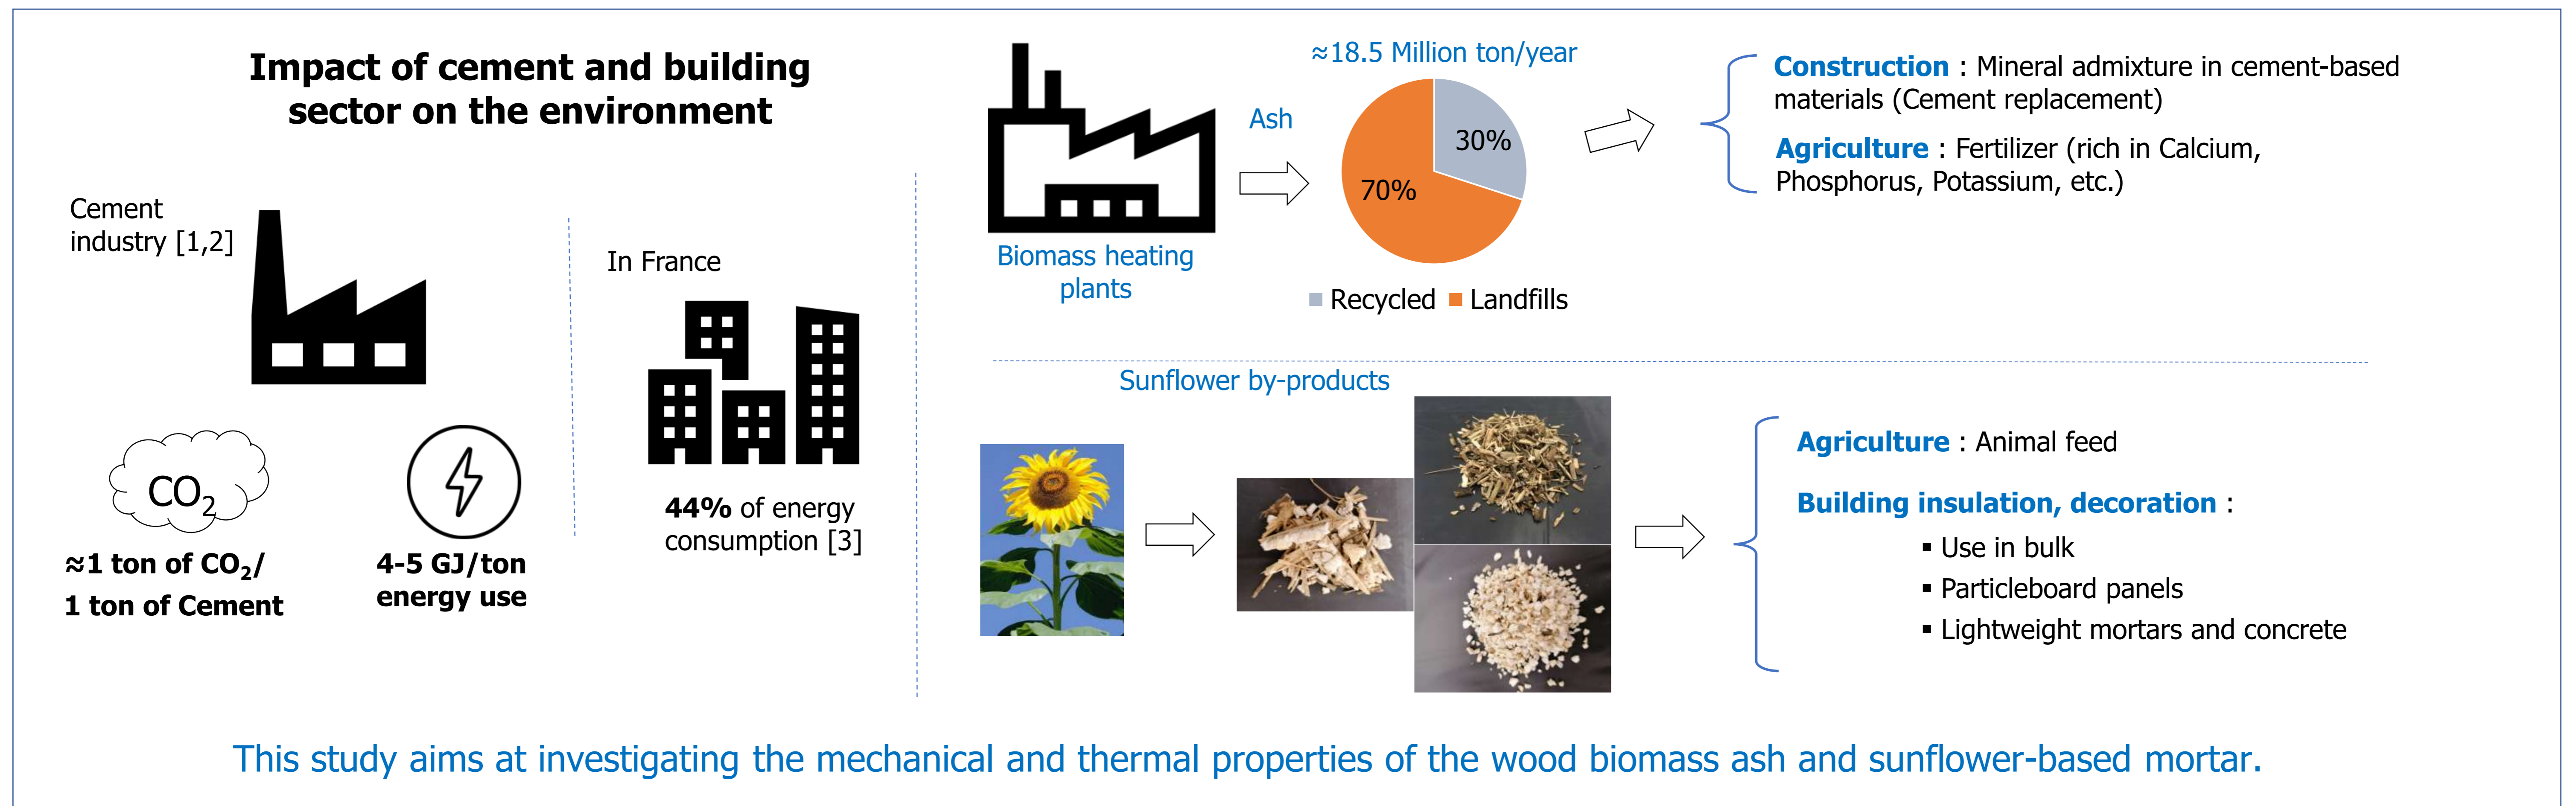

## 2. Materials and methods

### Raw materials

- Ordinary Portland cement C (CEM II) 32.5N
- Wood biomass fly ash : WFA (supplied by Coriance MAEV); The main **oxide compounds**: CaO, SO<sub>3</sub>, K<sub>2</sub>O, MgO, P<sub>2</sub>O<sub>5</sub>, SiO<sub>2</sub>.
- Sunflower bark and pith (from Groupe Dauphinoise)

### Mixture proportion

Mixtures	WBA (%)	C (%)	SP (%)	SB (%)	W/C ratio	W/WBA ratio	W/B ratio
100C	0	100	-	-	0.35	-	-
100WFA	100	0	-	-	-	0.5	-
80WFA-20C	80	20	-	-	-	0.5	-
90WFA-10C	90	10	-	-	-	0.5	-
80WFA-20C-5SP	80	20	5	-	-	-	1.1
80WFA-20C-10SP	80	20	10	-	-	-	1.6
80WFA-20C-15SP	80	20	15	-	-	-	2.2
80WFA-20C-20SB	80	20	-	20	-	-	0.9
80WFA-20C-25SB	80	20	-	25	-	-	0.95
80WFA-20C-30SB	80	20	-	30	-	-	1
90WFA-10C-5SP	90	10	5	-	-	-	1.1
90WFA-10C-10SP	90	10	10	-	-	-	1.6
90WFA-10C-15SP	90	10	15	-	-	-	2.2
90WFA-10C-20SB	90	10	-	20	-	-	0.9
90WFA-10C-25SB	90	10	-	25	-	-	0.95
90WFA-10C-30SB	90	10	-	30	-	-	1

### Main experiments

**Flexural strength** : prismatic specimen, dimensions: 40x40x160 mm<sup>3</sup>

**Compressive strength** : Cubic specimen, dimensions: 40x40x40 mm<sup>3</sup>

**Thermal conductivity (λ)** : dimensions 150x150x50 mm<sup>3</sup>

## 3. Results and discussion

### Compressive strength (Rc) development

- The compressive strength of the reference samples progressively increased as the age was increasing.
- A significant development in Rc was observed between the age of 7 and 28 days.
- After the age of 28 days, slight variations were observed on all the samples containing sunflower particles.

### Thermal conductivity (λ) at the age of 28 days

- The bulk density and thermal conductivity of the mortar declined as a result of the sunflower particles' incorporation.
- The variation of the bulk density and thermal conductivity of the samples containing sunflower pith was relatively higher compared to sunflower bark-contained samples.

## 4. Conclusions

- The addition of sunflower pith and bark significantly reduced the compressive strength of the mortar.
- The compressive strength of the reference samples 100WFA, 80WFA-20C, and 90WFA-10C gradually increased with increasing curing time.
- The overall compressive strength of the sunflower-contained mortar samples ranged between 0.1 and 0.9 MPa while for the reference samples, Rc varied from 0.5 to 7 MPa.
- The incorporation of sunflower particles as aggregates did not only reduce the density but also, improved the thermal properties of the mortar. The thermal conductivity (λ) of the mortar containing sunflower aggregates and reference samples varied from 0.074 to 0.143 W/m.K and 0.304 W/m.K, respectively.

## 5. References

- [1] P.P. Li, H.J.H. Brouwers, W. Chen, Q. Yu, Optimization and characterization of high-volume limestone powder in sustainable ultra-high performance concrete, *Construction and Building Materials*. 242 (2020) 118112. <https://doi.org/10.1016/j.conbuildmat.2020.118112>.
- [2] J. Skibsted, R. Snellings, Reactivity of supplementary cementitious materials (SCMs) in cement blends, *Cement and Concrete Research*. 124 (2019) 105799. <https://doi.org/10.1016/j.cemconres.2019.105799>.
- [3] Énergie dans les bâtiments | Ministère de la Transition écologique, (n.d.). <https://www.ecologie.gouv.fr/energie-dans-batiments> (accessed November 3, 2021).