



**HAL**  
open science

# Ultrafast formation of exciplex species in dicyanoanthracene ZSM-5 revealed by transient emission and fs IR vibrational spectroscopy

Lucie Duploux, Matthieu Hureau, Aurélien Moncombe, Svetlana Mintova, Olivier Gardoll, Alain Moissette, Vincent de Waele

## ► To cite this version:

Lucie Duploux, Matthieu Hureau, Aurélien Moncombe, Svetlana Mintova, Olivier Gardoll, et al.. Ultrafast formation of exciplex species in dicyanoanthracene ZSM-5 revealed by transient emission and fs IR vibrational spectroscopy. *The European Physical Journal. Special Topics*, 2023, 232 (13), pp.2145-2156. 10.1140/epjs/s11734-023-00813-9. hal-04295919

**HAL Id: hal-04295919**

**<https://hal.science/hal-04295919v1>**

Submitted on 20 Nov 2023

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Ultrafast formation of exciplex species in dicyanoanthracene ZSM-5 revealed by transient emission and fs IR vibrational spectroscopy

Lucie Duplouy<sup>1</sup>, Matthieu Hureau<sup>1</sup>, Aurélien Moncomble<sup>1</sup>, Svetlana Mintova<sup>2</sup>, Olivier Gardoll<sup>3</sup>, Alain Moissette<sup>1</sup>, Vincent De Waele<sup>\*1</sup>

\* [vincent.de-waele@univ-lille.fr](mailto:vincent.de-waele@univ-lille.fr)

<sup>1</sup>Univ. Lille, CNRS, UMR 8516, LASIRE-Laboratoire de Spectroscopie pour les Interactions, la Réactivité et l'Environnement, Lille, 59000, France

<sup>2</sup>Normandie Université, Laboratoire Catalyse et Spectrochimie (LCS) ENSICAEN, UNICAEN, CNRS, 6 boulevard Maréchal Juin, Caen, 14050, France

<sup>3</sup>Univ. Lille, CNRS, UMR 8181, UCCS-Unité de Catalyse et Chimie du Solide, Bât. C3, 59650 Villeneuve d'Ascq Cedex, France

**Abstract** The photophysical properties of dicyanoanthracene (DCA) molecules adsorbed on the external surface of ZSM-5 zeolite, forming DCA@ZSM-5 composites, have been investigated by picosecond transient emission, femtosecond transient absorption infrared vibrational spectroscopy, steady state UV-vis and quantum chemistry calculations. Following the photoexcitation at 420 nm of DCA@ZSM-5, the formation of the localized, LE, excited S<sub>1</sub> state of DCA emitting below 500 nm is observed. LE is rapidly and quasi-exclusively converted into two distinct exciplex species, EX1 and EX2, detected by their emission above 520 nm, with a lifetime of 5 ns and 20 ns, respectively. The different transient species can be identified by the frequency of the CN stretching vibration that is a marker of the charge delocalisation and that is peaking respectively at 2162 (LE), 2174 (EX1) and 2187 (EX2) cm<sup>-1</sup>. DFT and TD-DFT calculations further support the assignment. The results show that the external surface of zeolite is an appropriate playground for the development of novel photoactive host-guest materials.

## Introduction

Owing to their remarkable architecture, constituting a regular porous 3D organization of cages and channels whose dimensions are comparable with the size of small chemical entities (molecules, metal complexes or nanoparticles), zeolites constitute a family of microporous materials that are very attractive to design photoactive supramolecular host-guest assemblies [1–6] and promising for applications in the fields of photocatalysis, non-linear optical and luminescent materials, solar cell, sensing, photochemistry and environmental remediation. Not only the spatial organization in the void of the zeolite framework but also the effects of the confinement of guest compounds in the cages and channels result in novel photophysical and photochemical behaviors [7–13] that find their root in the earliest fs-ps processes following the photoexcitation [11,13–18]. Therefore, elucidating the photophysical and photochemical processes governing these applications by ultrafast time-resolved spectroscopy contributes to the optimal and original development of these photoactive host-guest materials.

In most of the studies and applications, the guest chemical species are incorporated into the zeolite by adsorption onto the large internal surface of the porous structure. Beside this common approach, chemical species with dimensions larger than the diameter of the pores can be adsorbed on the external surface of the zeolite crystallites to modulate their photoactivity [19–22]. This alternative strategy for the development of photoactive materials is interesting notably due to the fact that larger molecular compounds can carry several photoactive groups to design multifunctional materials. While micro-sized zeolite crystals exhibit a rather small external surface area (10–50 m<sup>2</sup>/gm) in comparison to the internal surface area (ca 500 m<sup>2</sup>/gm), the emergence of zeolites synthesized in the form of nanosized crystallites and films [23,24] or of 2D-nanosheets [25] has significantly increased the surface-to-volume ratio and the transport efficiency of these materials. This opens novel possibilities for exploiting the high external surface of the zeolitic materials, also in synergy with the encapsulation of active guest compounds whose photochemical behavior can potentially be strongly modified as the dimension of the zeolite is approaching the unit-cell dimension [26,27]. Among other properties, the zeolites are effective in controlling the charge separation between electron donor and acceptor systems [8,28], in certain cases, the zeolite framework participates even directly to the process of charge stabilization [29–32]. The photo-transfer of electrons between the external surface and the internal surface of zeolite can also be achieved by

adsorbing electrons donating and withdrawing compounds [33]. The control of the photo-separation of charge by zeolite is promising in view of photovoltaic, photo-electrochemical and photocatalytic applications.

In this context, we are interested in the spectroscopic characterization of the transient species formed in the fs-ps times scale by charge separation at the surface of the zeolites. In this work, we investigated the functionalization of the external surface of ZSM-5 zeolite micro-crystallites by the adsorption of 9,10-dicyanoanthracene (DCA) molecules (**Scheme 1**). The penetration of DCA in the channel of the MFI structure of ZSM-5 is sterically hindered by the two cyano groups in para position of the central benzyl moiety. Nevertheless, the molecules of DCA can partially enter the channel of ZSM-5, or they can adsorb on different surface sites and with different orientation [22].

The molecules of DCA exhibits an electron acceptor character in the  $S_1$  excited state ( $E = 1.99 V_{\text{NHE}}$ ) making them a strong photo-oxidizing species [34]. So, cyano-substituted arenes molecules are good model compounds to investigate the photoinduced charge separation [35–39] dynamics in solution. So far, the influence of the zeolite of the ultrafast charge separation photodynamics is still poorly documented. We addressed in this work the study of the photophysics of DCA molecules adsorbed on ZSM-5, hereafter **DCA@ZSM-5**. We investigated specifically the nature of the excited states generated upon the photoexcitation of the solid **DCA@ZSM-5** by combining time-resolved emission spectroscopy (TCSPC) measurements and femtosecond transient absorption measurements with an IR probe. The later spectroscopy allowed us to follow the CN stretching vibration that is a good marker of the charge localization in cyano-aromatics molecules [40–45]. To the best of our knowledge, fs IR transient absorption was only applied to zeolite sample to investigate the OH stretching vibration of the framework hydroxyl surface group [46] or of adsorbed water [47] and methanol [48] molecules. With the advances of this spectroscopy, the sensitivity allows us to envision more complex guest compound as it will be illustrated in the following. Quantum chemical calculations are completing the experimental results and interpretation.

## 1. Experimental

### 1.1. Material preparation.

DCA@ZSM-5 samples were prepared according a well-established procedure [31,32]. NaZSM-5 samples (Si/Al ~13.5; average particle size 1  $\mu\text{m}$ ) were obtained from VAW aluminum (Schwandorf, Germany). 9,10-dicyanoanthracene (DCA,  $C_{16}H_{12}N_2$  97% Sigma-Aldrich) was purified by sublimation. Potassium bromide (KBr  $\geq 99\%$  Sigma-Aldrich) was used for pelletization. Pure and dry Ar gas was used to keep our samples under inert atmosphere.

1.2 g of the NaZSM-5 zeolite were weighted and introduced into a long tube-shaped evacuable and heatable silica cell. The tube was then placed in a vertical oven connected to a gas piping network and heated stepwise up to 450  $^{\circ}\text{C}$  under dry argon for at least 12 hours. The sample was then cooled down to room temperature and kept under dry argon flow. The zeolite was transferred into a sealed silica cell connected to dry Ar and vacuum pipes. Weighted amount of DCA at the concentration DCA:ZSM-5 20 mg/g ( $9 \times 10^{-5}$  moles of DCA per gram) were added into the cell without any solvent, the whole set-up being kept under dry Ar. The powders were shaken until the resulting mixture was homogeneous and transferred under dry Ar in a sealed quartz glass Suprasil cell. The sample was placed into an oven kept at 40  $^{\circ}\text{C}$  for the sorption to take place via sublimation. For the subsequent analyses, the sample was kept in the cell or pelletized with KBr.

### 1.2. Thermogravimetric measurements

The moisture content and the organic compound (9,10-dicyanoanthracene,  $C_{16}H_{12}N_2$ ) were investigated using a SETSYS (SETARAM) analyzer (heating rate of 5  $^{\circ}\text{C min}^{-1}$  under 40  $\text{mL.min}^{-1}$  flow of air)

### 1.3. Steady state diffuse reflectance and emission spectroscopy.

A Cary 6000 spectrophotometer was used to record the UV-visible absorption spectra between 200 and 1800 nm. An integrating sphere was connected to the spectrophotometer to measure the diffuse reflectance from the powdered samples stored under dry argon in the Suprasil cells; the corresponding dehydrated bare zeolite was taken as the reference. The Kubelka-Munk function was used to plot the DR UV-vis spectra:

$$F(R) = \frac{(1 - R)^2}{2R}$$

R is the ratio of the diffuse reflectance of the loaded zeolite and bare one. F(R) is a function of wavelength.

A Horiba Fluorolog-3 spectrofluorimeter was used to record the emission spectra between 450 and 800 nm. The apparatus was set in the front face mode to allow the measure of the powdered sample sealed in the quartz cell and in the right-angle mode to measure the emission from the pelletized samples.

#### 1.4. Steady state vibrational spectroscopy

An Avatar 360 spectrometer (Thermo Nicolet) equipped with a DTGS detector ( $400\text{ cm}^{-1} - 4000\text{ cm}^{-1}$ ) was used to record in transmission the infrared spectra with a resolution of  $0.5\text{ cm}^{-1}$ . The Raman spectra were recorded using a FT Raman spectrometer (Bruker RFS 100/S instrument) with a laser excitation at 1064 nm.

#### 1.5. Time-correlated single photon counting measurements.

The fluorescence decays were measured by using the TCSPC spectroscopy using the set-up described here [49]. Briefly, the 420 nm excitation pulses were generated by a femtosecond Ti:sapphire laser (Coherent Chameleon Ultra II, 80 MHz, 200 fs, 3.8 W) coupled with a pulse picker (4 MHz) and a harmonic generator (SHG/THG, APE). The fluorescence lifetime measurements were carried out with the FT200 PicoQuant spectrometer and the emission signal was collected with a polarizer set at the magic-angle and a Czerny-Turner type monochromator connected to a computer for observation wavelength selection. The photons were collected with a cooled microchannel plate photomultiplier tube R3809U (Hamamatsu) and recorded using a PicoHarp 300 TCSPC system (PicoQuant). The instrumental response function (IRF) was measured using Ludox, a colloidal silica and the full width at half maximum (FWHM) was found to be  $\sim 50$  ps. For these experiments, the **DCA@ZSM-5** pellets were mounted on a dedicated home-made support and the emission was collected at ca. 45 degrees. The excitation was cut using a color filter. The software used to plot and process the decays was FluoFit v.4.6.6 (PicoQuant) and a home-made python script.

#### 1.6. IR femtosecond transient absorption measurements.

The pump-probe femtosecond transient absorption set-up is based a Ti:Sa CPA laser (Coherent Libra HE 4 W) delivering at 1kHz, short pulses with a duration of 100 fs and a wavelength centered at 800 nm. 1.4 mW are used to generate the pump beam by SHG, FHG, or SFG in a UV-vis OPA (Coherent OPERA). 2.4 mW are seeded in a second Mid-IR OPA equipped with a NDFG stage to generate the probe beam in the Mid-IR spectral range (3-20  $\mu\text{m}$ ). For these experiments, the pump laser beam was set at 420 nm. After the OPA stage, the pump beam is stirred by using high reflective dielectric mirrors to the entrance of an optical delay line, passing through a Berek waveplate (New Focus) and neutral density filters to adjust the polarization and the intensity of the pump excitation. The optical delay line consists in an aluminum retroreflector mounted on a motorized translation stage (Newport Delay line + controller). After the delay line, the pump beam is propagated and slightly focused several millimeters in front of the surface of the sample by mean of a  $\text{CaF}_2$  lens (typically  $f = +300$  mm). The wavelength of the probe beam was centered at  $4.65\text{ }\mu\text{m}$ , which allow us to record the IR spectra between  $2250\text{-}2050\text{ cm}^{-1}$ . After generation, the probe beam is propagated through a fixed optical delay line made of gold stirring planar mirrors and 2 off-axis ( $15^\circ$ ,  $f = +600\text{mm}$ ) parabolic mirrors that have been aligned to collimate the beam with a ca. 1 magnification. This optical path is compensating the time delay between the output of the pump and probe OPAs. Then the probe beam is focused into the sample by an off-axis parabolic mirror ( $30^\circ$ ,  $f = +450$  mm). The reference (REF) and signal (SIG) beam are generated by inserting a 4 mm-thick  $\text{BaF}_2$  window (Thuete) on the optical path of the IR probe beam, between the focusing parabolic mirror and the sample. The sample is placed at the foci of REF and SIG that are vertically distant by 3-4 mm. After the sample, SIG and REF are imaged on the entrance slit of a spectrograph (Horiba iHr320) and detected by a LN2-cooled MCT  $2 \times 32$  pixels arrays detector (IR-3216, Infrared Systems development). The intensity of each individual SIG and REF pulse is recorded and stored. An optical chopper at 500 Hz synchronous of the laser pulse is placed on the pump beam and its state is recorded by the IR-3216 simultaneously to the SIG and REF signal.

For this study, the transient spectra have been typically recorded by carrying-out 3-4 scans of the pump-probe delays, with an average of 3000-5000 pulses per step. REF and SIG beam were dispersed using a 300 gr/mm

grating ( $\lambda_{\text{blaze}} = 6 \mu\text{m}$ ), resulting in a spectral resolution of  $1\text{-}2 \text{ cm}^{-1}/\text{px}$ . Under these conditions, we reconstructed the transient spectra covering the spectral range  $2240\text{-}2120 \text{ cm}^{-1}$  by the concatenation of three or four independent spectral acquisitions. The transient IR response of the DCA is superposed to a broad and featureless component that was subtracted from each spectrum (see SI).


The femtosecond transient absorption spectra are recorded in transmission by dispersing the sample (**DCA@ZSM-5**) in a 100 mg KBR pellet. The amount of **DCA@ZSM-5** was adjusted to limit the scattering and absorption of the IR probe radiation by the zeolite in the  $2000\text{-}2500 \text{ cm}^{-1}$  spectral window. For the fs IR measurements, the samples are placed in a home-made optical cell composed by a LN<sub>2</sub>-cooled cryostat mounted on a XYZ translation stage and a vacuum chamber coupled to a turbo pump and a gas delivering systems. The pellet is located in the middle of the chamber, about 5 cm away from the two 1 mm thick BaF<sub>2</sub> windows of the cell. Two samples can be hold in the compartment for a better control and reproducibility of the pump-probe measurements under the *in situ* conditions. In this study, all the measurements were performed at room temperature under vacuum. The pellets were dehydrated in the cell at  $10^{-6}$  mbar for several hours before each experiment.

## 1.7. Quantum chemistry calculations

All the computations were carried out using the Gaussian 16 suite of programs. [50] Energies were computed in the framework of Density Functional Theory (DFT). The PBE0 global hybrid functional [51,52] was used throughout with an empirical dispersion correction (GD3). [53] The underlying wave function was developed on the aug-CC-PVTZ basis set [54] on all atoms. Geometries were fully optimized in the vacuum using standard algorithms. The nature of the stationary points was checked by vibrational analysis that also yields the harmonic frequencies that are reported without any scaling in this publication.

## 2. Results and Discussion


### 2.1. Absorption of DCA at the surface of the ZSM-5 crystals

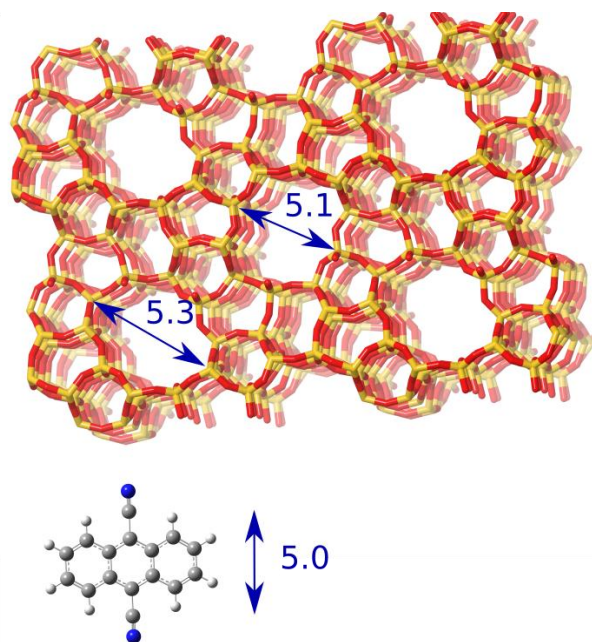

**Scheme 1:** Scheme of the MFI framework of the ZSM-5 zeolite along the (010) channel and molecule structure of the 9,10-dicyanoanthracene for comparison. The lengths are given in Angstroms.

The structure of the ZSM-5 zeolite and of the DCA molecule are illustrated in **scheme 2**. From the characteristic length of the DCA molecule in comparison with the pore diameter of the ZSM-5 zeolite, it is quite obvious that DCA cannot freely enter and diffuse into the zeolitic channel. Therefore, the molecules of DCA are exclusively adsorbed on the external surface of the ZSM-5 crystals and at the mouth of the pores. This does not mean that

there is no specific interaction with the zeolite surface and notably a partial inclusion of the molecule at the entrance of the channel, eventually facilitated by an expected vibrational bending of the CCN angle [22].

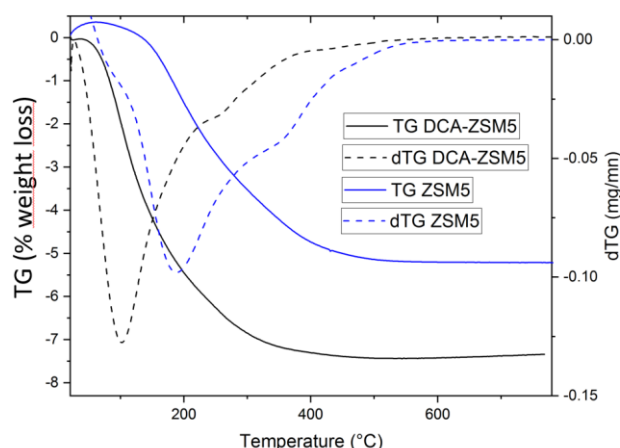

**Fig. 1.** TG (full line) and dTG (dash line) curves of **ZSM-5** (blue) and **DCA@ZSM-5** (black)

**Figure 1** shows the TG and dTG curves obtained for **ZSM-5** and **DCA@ZSM-5** samples. For **ZSM-5**, the total weight lost is 5.1% and corresponds to the loss of the surface and occluded water molecules that occur below 400 °C. For **DCA@ZSM-5**, we notice two clear effects. First, a net increase of the percentage weight loss (+2%) in agreement with the amount of DCA deposited in the zeolite. Second, a net shift of the desorption temperature to a lower value indicating that the distribution of the water molecule is also perturbed in presence of DCA. This point is in good agreement with the fact that the aromatic compounds interact preferentially with the hydrophilic sites of the zeolite surface [22]. Therefore, we can conclude based on the thermogravimetric measurement that the crystals of **ZSM-5** are in interaction with the DCA molecules predominantly on their external surface but also at the mouth of the pores. For a better understanding of DCA at the surface of **ZSM-5**, **Table 1** provides an estimation of the relevant parameters characterizing the **DCA@ZSM-5** composites. The pores at the entrance of the channels of the zeolite crystals constitute a favorable site of adsorption of DCA. From our assessment of the number of pore entrances at the surface of the crystallites, we estimated that ca. 25% of the DCA molecules can be accommodated, for example, in a configuration with one of the terminal benzene ring pointing inside the channel that represents a significant amount of the total of the DCA molecules. The rest of the DCA molecules will be spatially arranged on the external surface according to the specific interaction with zeolite surface and with the DCA molecules that are partially adsorbed in the pores. Advanced structural and textural analysis would be necessary to understand precisely the microscopic interaction of DCA with the MFI porous structure. Nevertheless, the characterization of the adsorption of DCA by using the thermogravimetric analysis has provided the evidence of the interaction of the DCA molecules and the zeolite crystals. In the rest of the manuscript, we will focus on the photophysical properties of **DCA@ZSM-5**, without any assumption regarding the hypothetical microscopic organization of the molecules at the surface of the zeolite.


**Table 1:** main properties of the **DCA@ZSM-5** composite

<b>ZSM-5</b>	
Dimensions of the crystals ( $\mu\text{m}$ )	$2.2 \times 0.6 \times 0.5$
External surface, $S_{\text{ext}}$ ( $\text{m}^2/\text{g}$ ) <sup>a)</sup>	10
Pores density, $N_{\text{pores}}$ (/g) <sup>b)</sup>	$15 \times 10^{18}$
Pores surface, $S_{\text{pores}}$ ( $\text{m}^2/\text{g}$ ) <sup>c)</sup>	3.75
<b>DCA</b>	
Concentration (molecules/g)	$54 \times 10^{18}$
Surface equivalent $S_{\text{DCA}}$ ( $\text{m}^2/\text{g}$ ) <sup>d)</sup>	54

<sup>a)</sup> assuming the **ZSM-5** density of 720 g/L, <sup>b)</sup> with 5 pores per  $330 \text{ \AA}^2$ , <sup>c)</sup> with a pore section of ca.  $25 \text{ \AA}^2$ , <sup>d)</sup> molecular surface of ca.  $100 \text{ \AA}^2$



## 2.2. UV-vis absorption and emission spectroscopy

The absorption and emission spectra ( $\lambda_{\text{exc}} = 420 \text{ nm}$ ) of **DCA@ZSM-5** are depicted in **Figure 2**. The absorption spectrum of **DCA@ZSM-5** exhibits the typical vibronic progression of anthracene-like molecules which is composed of 3 peaks (marked 0-n, n=1-3, on the graph) at  $22083 \text{ cm}^{-1}$ ,  $23535 \text{ cm}^{-1}$ , and  $25308 \text{ cm}^{-1}$ ). Compared with the free molecule of **DCA** in solution [55], the 0-1 band is found at a lower energy. A similar effect, assigned to dipolar interactions in molecular crystal, was also reported for anthracene crystals and nanoaggregates [56]. The emission is also structured and exhibits three maxima observed at  $20033 \text{ cm}^{-1}$ , peak a (499 nm),  $18333 \text{ cm}^{-1}$ , peak b (546 nm) and  $17567 \text{ cm}^{-1}$ , peak c (570 nm). In comparison with the free **DCA** molecules in solution [57,58], we can notice in **Figure 2** that the emission spectrum is not the mirror of the absorption spectrum. Thus, the absorption and emission in **Figure 2** show that the **DCA** molecules in **DCA@ZSM-5** are in interaction with their neighbors in the solid state [56].

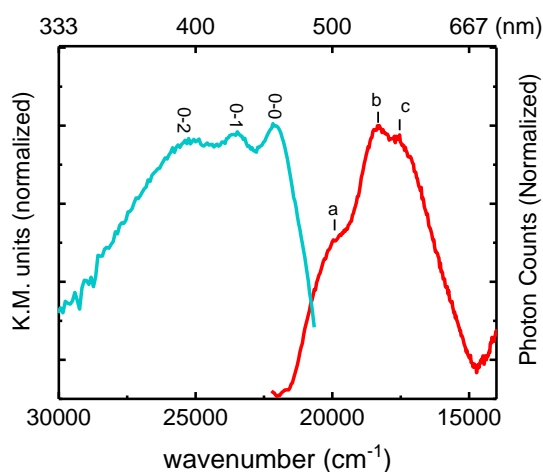

**Fig. 2:** Absorption in Kubelka-Monk unit, and emission spectra ( $\lambda_{\text{exc}} = 420 \text{ nm}$ ) and **DCA@ZSM-5**

The luminescence of **DCA@ZSM-5** was characterized by time-resolved emission spectroscopy. The transient emission spectra reconstructed from the TCSPC emission decays are reported in **Figure 3**. The temporal evolution of the emission of **DCA@ZSM-5** consists in two main contributions. First, a broad emission band, with a maximum located at 480-500 nm and a second maximum around 540 nm, is formed within the IRF of the set-up. During the first hundreds of picosecond, the blue part of the emission is decreasing while a new broad contribution is growing above 550 nm. We notice the presence of a quasi-isobestic point at 540 nm. After 500 ps, the emission spectrum is dominated by that second broad contribution which decays from 500 ps to 50 ns. For anthracene-like molecule, the emission in the blue part ( $< 500 \text{ nm}$ ) is associated with a localized  $S_1$  state (**LE**), while the red-shifted contribution usually correspond to the emission from excimer species (**EX**). So, the temporal evolution of the emission spectra of **DCA@ZSM-5** can be described as (i) below 500 ps, the conversion between the locally excited state (**LE**) of the **DCA** molecules ( $\lambda_{\text{em}} = 500 \text{ nm}$ ) into an excimer species (**EX**) responsible for the long-lived emission above 540 nm, respectively, and (ii) the decay of the **EX** band in the ns time, whose maximum is shifting from ca 550 nm to 570 nm, suggesting the formation of different **EX** species, with different degrees of charge delocalization [55,59,60].

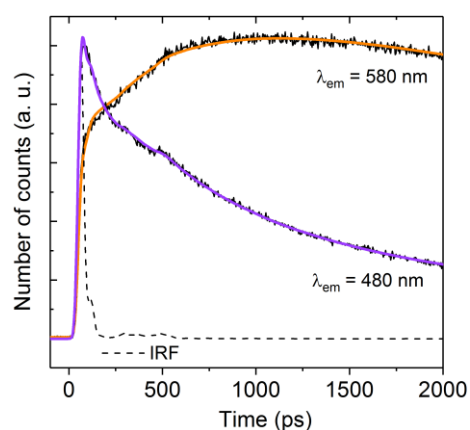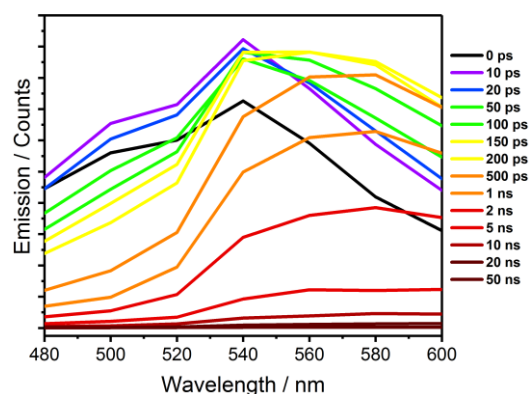

**Fig. 3:** (top) Transient emission spectra of **DCA@ZSM-5** reconstructed from the emission decays recorded by TCSPC upon photoexcitation at 420 nm, and (bottom) emission decay traces and their corresponding fit at 480 nm (violet) and 580 nm (orange). (--) is the IRF trace.

The decay of fluorescence recorded at 480 nm and 580 nm for **DCA@ZSM-5** are depicted in **Figure 3** (between 0 and 2 ns), and as supplementary information (full decay between 0 and 50 ns). The traces were fitted by using a sum of four exponential decays functions (**Table 2**). At 480 nm the signal appears within the IRF and the kinetic trace is well reproduced by a sum of two decays in the sub-ns regime (50 ps and 618 ps) totalizing 72% of the contribution and two decays in the ns timescale: 2.5 ns contributing to 22-24% of the decay, and a less important contribution (5-6%) equal to 13 ns. At 580 nm, about 65% of the signal appears within the IRF and this initial step is followed by rising component ( $t_2 = 567$  ps) that accounts for 33% of the total of the decay components. The time constants  $t_1 = 14$  ps and  $t_2 = 567$  ps for  $\lambda_{em} = 580$  nm in **Table 2** are in a reasonable agreement with their corresponding decays times at  $\lambda_{em} = 480$  nm ( $t_1 = 50$  ps and  $t_2 = 618$  ps), and notably  $t_2$  and  $t_2'$  which are associated with a decreasing and increasing contribution, at  $\lambda_{em} = 480$  nm and  $\lambda_{em} = 580$  nm, respectively. We can also notice that the amplitude of the growth of the emission at 580 nm, associated with the time  $t_2'$ , only accounts for 33% of the total emission decay at this wavelength. Therefore, a fraction of the emitting state at  $\lambda_{em} = 580$  nm is generated within the duration of the IRF. It corresponds therefore either to the excited state emitting at 480 nm or to a second **EX** species with a maximum around 540-550 nm. This second hypothesis is more convincing as it is also suggested by the shape of the spectra in **Figure 3**. After the growing stage, the emission detected at 580 nm exhibits a main contribution with a lifetime of  $t_3 = 5.7$ -5.9 ns and an additional longer decay time ( $t_4 = 21$ -23 ns) accounting for 17-20 % of the emission decay amplitude. These values are quite different from those measured at 480 nm so we ruled out the contribution of the **LE** state above 540 nm, and assume instead the formation of two distinct **EX** species.



**Table 2:** Fit parameters of the emission decays of **DCA@ZSM-5** recording upon photo-excitation at 420 nm

$\lambda_{em}$	$t_1^a)(a1)^b)$	$t_2 (a2)$	$t_3 (a3)$	$t_4 (a4)$
480 nm	50 (34%)	618 (38%)	2.50 (22%)	13.1 (6%)
580 nm	14 (14%)	567 (-33%)	5.75 (66 %)	21.4 (20%)

<sup>a)</sup>  $t_1, t_2, t_3, t_4$  decay time obtained by using a 4-exp model convolved by the IRF signal <sup>b)</sup> amplitude of the component of the fit given in percentage relatively to the total of the decaying components (i.e positive amplitude). With this convention, the growth contributions appear with a negative percentage.


In the following, the decay times ( $t_1, t_2, t_3, t_4$ ) and ( $t'_1, t'_2, t'_3, t'_4$ ), refer to the fit values at  $\lambda_{em} = 480$  nm and  $\lambda_{em} = 580$  nm, respectively. As the decay time  $t_4 = 13$  ns is close to the emission lifetime of the molecule of DCA in solution [38,57], it is therefore assigned to decay of the **S**<sub>1</sub> (**LE**) state of DCA molecules in weak interaction with their surroundings, either spatially isolated or in a geometrical configuration unfavorable to the interaction with the surrounding molecules. This contribution has a small weight (6%) but it counts for more than 50% of the steady state emission at this wavelength. The decays time  $t_2 \approx t'_2 \approx 600$  ps is observed at both wavelength with an inverted amplitude sign and it corresponds to a conversion of the **LE** state of DCA into an excimer (**EX**) species. If we further assume that for these molecules of DCA in **DCA@ZSM-5**, the **LE** → **EX** conversion is in competition with the internal conversion by emission that is characterized by  $t = 13$  ns for the non-interacting DCA, it comes out that 95% of the **LE** state is quenched to form the **EX** species. Therefore, we deduce from the amplitude of the different emission components that the number of photoexcited DCA that is converted into **EX** species is ca. 4 times more important than the ones decaying mainly by emission. Concerning the slow decaying processes at 580 nm,  $t'_3$  and  $t'_4$  are in good agreement with the reported lifetime for DCA or anthracene exciplexes, and the difference between the two values is assigned to different degrees of charge transfer [61]. The remaining short decays  $t_1, t'_1$  and  $t_2$  are similar to those reported for anthracene nanoaggregates [56] and they are assigned to the dynamics of the **LE** state whose lifetime is shortened by trapping at the surface and defect of the crystals. In **DCA@ZSM-5**, the adsorption of DCA molecules at the surface of zeolite favors the formation of defect and so, it supports this interpretation. Alternatively, the shortest  $t_1$  and  $t'_1$  components might also correspond to an ultrafast internal relaxation of **LE**.

### 2.3. Steady state and transient vibrational properties of **DCA@ZSM-5**

In order to get a better insight of the nature of the **LE** and **EX** molecular configurations in **DCA@ZSM-5** we carried out femtosecond pump-probe MidIR spectroscopy and we focused on the CN stretching modes which is a good probe of the charge distribution in the cyano-molecular compounds. Complementary, quantum chemistry modelling of DCA ground state ( $S_0$ ), lowest excited states ( $S_1, T_1$ ) and DCA anion ( $DCA^-$ ) have been performed to support the vibrational assignment.

#### 2.3.1. Quantum chemical calculations

The electronic and vibrational properties of the molecule of DCA in the ground state ( $S_0$ ), lowest excited singlet ( $S_1$ ) and Triplet ( $T_1$ ) state, and in the anionic form ( $DCA^-$ ) have been calculated by using the DFT and TD-DFT method, for the ground and excited state respectively. The corresponding HOMO and LUMO orbitals for the DCA in its ground state are reported in the **Table 3**. The lowest  $S_1 \leftarrow S_0$  electronic transition is described at 98% by the HOMO and LUMO orbitals. From the representation of the orbitals in **Table 3**, we can clearly deduce the  $\pi\pi^*$  nature of this electronic transition without a significant perturbation of CN bonds. So, in DCA, the electronic density on the CN bonds is only perturbed indirectly via the quinoidal distorsion of the central aromatic ring and the subsequent polarization of the carbon atoms in position 9 and 10.

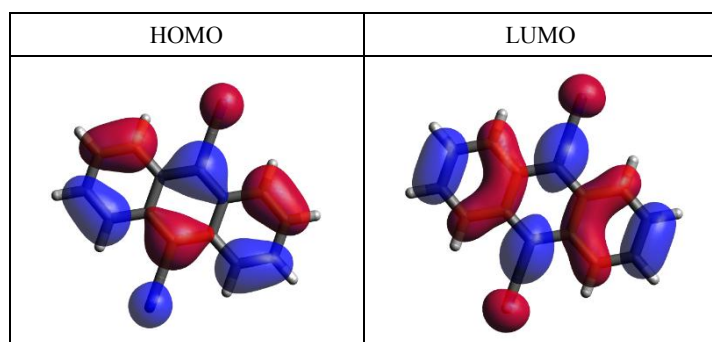**Table 3:** HOMO-LUMO DCA molecular orbitals

The vibrational normal modes and the corresponding wavenumbers and IR intensities were computed at the optimized geometry for the different species of DCA. The values for the symmetric and anti-symmetric CN elongation mode are reported in **Table 4**. From the theoretical modeling, for all the DCA species, only two normal modes are calculated with a frequency in the range 2000 -2400  $\text{cm}^{-1}$  and they correspond to the symmetric and anti-symmetric combination of the CN stretching elongation, hereafter  $\nu(\text{CN})$ . As expected, only the antisymmetric mode is IR active but the calculation also revealed the strong variation of the IR dipole moment, *i.e.* of the intensity of the IR band, between these different chemical species, in good agreement with experimental investigations of nitriles anions [43]. The calculated value for  $\nu(\text{CN})$  also varies significantly with the nature of the DCA species and it is decreasing on going from the ground to the excited and then anionic states. The calculated variation of  $\nu(\text{CN})$  relative to the value in the ground  $S_0$  are  $-46 \text{ cm}^{-1}$  ( $S_1$ ),  $-90 \text{ cm}^{-1}$  ( $T_1$ ) and  $-99 \text{ cm}^{-1}$  ( $\text{DCA}^-$ ), respectively. As expected, the uncorrected harmonic DFT calculation overestimates the experimental frequencies but for a better agreement not only a scaling factor but also the anharmonicity must be included in the model [62]. This is out of the scope of the work. However, we can notice that the experimental shift of the CN frequency on going from the ground to the  $S_1$  and to the anion species of DCA are well reproduced by the calculations (**Table 4**).


**Table 4:** Computed and observed values of the CN stretching vibration of DCA species

	$S_0$		$S_1$		$T_1$	Anion	
	Calca <sup>a)</sup>	Obs.	Calc.	Obs.	Calc.	Calc.	Obs.
$\nu(\text{CN})_{\text{asym}}$	2347	2213 / 2222 <sup>b)</sup>	2301	2160 <sup>d)</sup>	2257	2262	2216 <sup>e)</sup>
$\Delta\nu$ <sup>c)</sup>			-46	-57	-90	-85	-99
Calc. $\mu_{\text{IR}}$	79.2		146.0		30.0	721.9	
$\nu(\text{CN})_{\text{sym}}$	2348	2217 <sup>b)</sup>	2301	-	2258		

<sup>a)</sup> The calculated frequencies are unscaled. <sup>b)</sup> IR and Raman spectra (**Figure 4**) <sup>c)</sup> observed and calculated shift relative to the value in  $S_0$  <sup>d)</sup> this work <sup>e)</sup> Frequency for 9-cyanoanthracene from ref [43]

The IR and Raman vibrational spectra of **DCA@ZSM-5** in the spectra range of the CN stretch mode are depicted in **Figure 4**. The frequencies are close to that measured for the molecule of DCA (see SI) showing that the structure of the DCA molecules is preserved in **DCA@ZSM-5**. The Raman spectrum exhibits a single vibrational band peaking at  $2217 \text{ cm}^{-1}$ , corresponding to the symmetric CN stretching mode that is Raman active by symmetry. The IR spectrum shows a doublet of vibrational bands instead of the single IR allowed transition of the anti-symmetric CN stretching modes. This feature is explained by a Fermi resonance the CN stretching mode with a combination of lower frequency vibration of DCA [63].

### 2.3.2. Time-resolved MidIR absorption spectroscopy

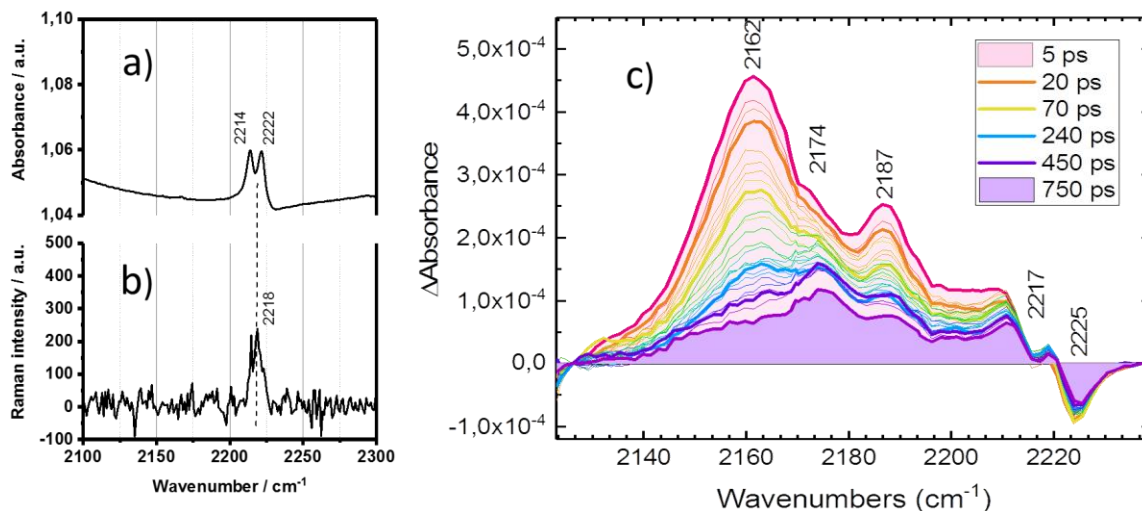


**Figure 4:** a) FTIR b) Raman and c) time-resolved IR spectra ( $\lambda_{\text{pump}} = 420 \text{ nm}$ ) of **DCA@ZSM-5** recorded in the region of the CN stretching mode.

A set of transient spectra recorded for pump-probe delays up to 750 ps is depicted in **Figure 4**. The transient IR spectrum recorded at 5 ps exhibits between 2120 and 2240  $\text{cm}^{-1}$  two negative contributions (peaking at 2217 and 2225  $\text{cm}^{-1}$ ) and corresponding to the expected bleach signal of the ground state  $S_0$  of DCA. A large and structured positive contribution extending from 2220  $\text{cm}^{-1}$  to roughly 2120  $\text{cm}^{-1}$  dominates the transient spectrum on which we can clearly identify two vibrational bands peaking at 2162  $\text{cm}^{-1}$  and 2187  $\text{cm}^{-1}$ , respectively, and a shoulder at 2174  $\text{cm}^{-1}$ . The broad and intense band at 2162  $\text{cm}^{-1}$  is assigned to the antisymmetric stretching mode of the CN elongations of the  $S_1$  state of DCA, hereafter  $\nu_1(\text{CN})$ . This assignment is based on the CN stretching mode reported for the  $S_1$  state of cyanoanthracene (CNA) [42] and it is also supported by the DFT and TDDFT calculations in **Table 1** predicting a decrease of the wavenumber of  $\nu_{\text{as}}(\text{CN})$  of  $\Delta\nu = 47 \text{ cm}^{-1}$ , in good agreement with the experimental data ( $\Delta\nu = -57 \text{ cm}^{-1}$ ) on going from the ground ( $S_0$ ) and to lowest ( $S_1$ ) excited state of DCA. We also point out that the calculations reveal the increase of the IR intensity of  $\nu_{\text{as}}(\text{CN})$  that is in good agreement with the experimental observation that the amplitude of the absorption band peaking at 2162  $\text{cm}^{-1}$  is much higher than the negative contribution (bleach of the  $S_0$  IR bands) in the transient spectra (**Figure 4**). In addition to the band  $\nu_1(\text{CN})$  at 2162  $\text{cm}^{-1}$  of the  $S_1$  state of DCA, two additional vibrational bands are observed at 2174  $\text{cm}^{-1}$  ( $\nu_2(\text{CN})$ ) and at 2188  $\text{cm}^{-1}$  ( $\nu_3(\text{CN})$ ) suggesting the formation of two additional species exhibiting different electron distributions on the CN bonds. According to the calculations (**Table 4**) these bands cannot be associated with the  $T_1$  state or with the anion of DCA. The frequency of these two bands is moreover not compatible with the hypothesis of hot vibrational states of the ground state of DCA [64]. Therefore, we assigned these two contributions to the formation of bounded ion pair (**IP**) or exciplexes (**EX**) species of DCA molecules. Formally the difference between **IP** and **EX** resides only in the degree of charge delocalization. For CNA, and tetracyanoethylene in solution, **EX/IP** states have been identified by their vibrational spectral signature in the 2150-220  $\text{cm}^{-1}$  range [41,42], that is between the  $S_0$  and  $S_1$  CN stretching frequency. In solution, the **EX** contribution is usually broad and featureless due to the delocalization of the electronic cloud over the two partner molecules and to the loose dynamical configuration in solution. **IP** pair gives rise to more defined bands.

For **DCA@ZSM-5**, between 5 ps and 500 ps the relative intensity of the three IR bands is evolving significantly (**Figure 4**). The band  $\nu_1(\text{CN}) = 2162 \text{ cm}^{-1}$  is the most intense at short time but has nearly completely vanished after 250 ps. The intensity of  $\nu_3(\text{CN}) = 2187 \text{ cm}^{-1}$  is also decreasing but in much less proportion in comparison with  $\nu_1(\text{CN})$ . In opposite, from 5 ps to 750 ps, the third band  $\nu_2(\text{CN}) = 2174 \text{ cm}^{-1}$  is becoming the most intense of the spectra, without significantly diminishing its amplitude. These different evolutions confirm the formation of three different transient chemical species. **Figure 5** shows kinetic traces recording around  $\Delta t = 0$ . At negative delay we can recognize the perturbed free induction decay contribution that was first described by P. Hamm [65] predicting the oscillatory component and the signal growth at the

bleach wavenumber ( $2224\text{ cm}^{-1}$ ). Besides, we can notice that the species associated with  $\nu_3(\text{CN}) = 2187\text{ cm}^{-1}$  is formed within the pump-probe cross-correlation, while for  $\nu_1(\text{CN}) = 2162\text{ cm}^{-1}$  the rise time is followed by a second step of growth up to 3 ps. The ground state bleach contribution ( $2224\text{ cm}^{-1}$ ) does not evolve significantly, nor at short time or at long time (**Figure 4**) showing that the internal conversion to the ground  $S_0$  state is a minor process in the sub-ns time scale. Transient spectra recorded before 5 ps are given in **Figure 5**. At this time scale, the slow growth of  $\nu_1(\text{CN})$  and the quasi-instantaneous formation of  $\nu_2(\text{CN})$  and  $\nu_3(\text{CN})$  are well resolved. The kinetic of the three CN vibration bands was fitted by using 3 exponential decay times (SI and **Table 5**). The decay time  $t_1 = 1.5\text{--}1.8\text{ ps}$  is associated with the increase of the intensity of the band  $\nu_1(\text{CN})$ . The same time constant  $t_1$  and  $t_2$  (40 ps) are obtained for  $\nu_1(\text{CN})$  and  $\nu_2(\text{CN})$ , but it is because of the strong contribution of  $\nu_1(\text{CN})$  that dominates the fit. The longer decay time  $t_3$  is equal to 282 ps and 393 ps, for  $\nu_1(\text{CN})$  and  $\nu_2(\text{CN})$ , respectively, and it allows us to distinguish the two kinetics and to assign these two bands to two different species. For  $\nu_3(\text{CN})$  the fit parameters reflect the formation of the band within the duration of our pulse-probe cross-correlation followed by a decay with the kinetic that mimics the decay of  $\nu_1(\text{CN})$  suggesting a correlation between these two bands. As at 750 ps the intensity of  $\nu_1(\text{CN})$  is less than that of  $\nu_3(\text{CN})$ . We assume therefore that a partial conversion of the species associated with  $\nu_1(\text{CN})$ , **LE**, into the species **EX** species associated with  $\nu_3(\text{CN})$  takes place. We notice also that the values of  $t_2$  and  $t_3$  are in good agreement with the emission lifetime measured by TCSPC (**Table 1**).

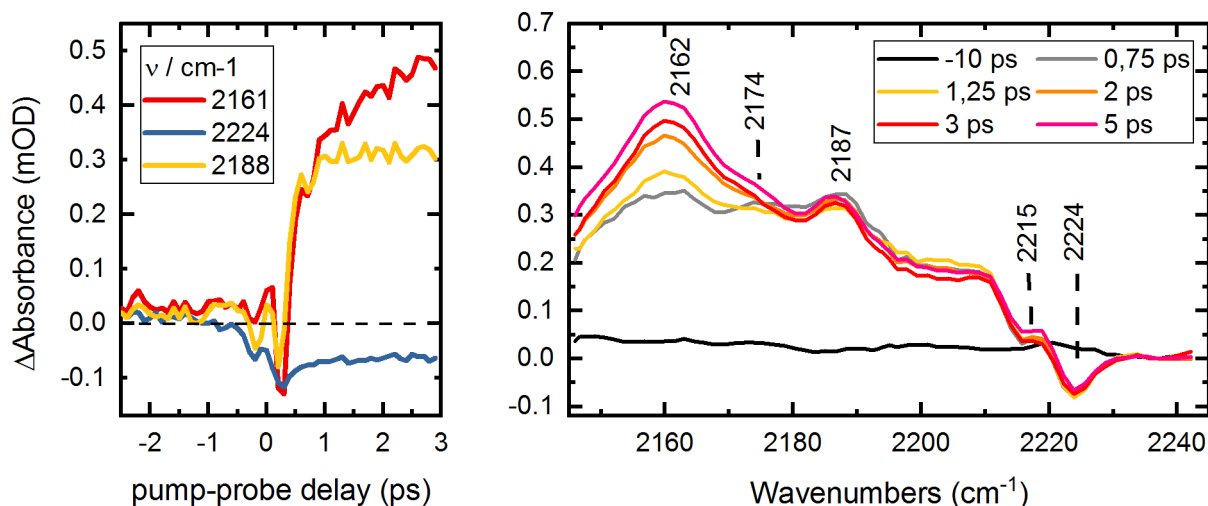

**Figure 5:** Kinetic traces reconstructed from the transient spectra of **DCA@ZSM-5** and selected transient spectra for  $\Delta t < 5\text{ ps}$  ( $\lambda_{\text{pump}} = 420\text{ nm}$ ).

**Table 5:** Fit parameters of the three main vibrational absorption bands

	$\nu_1(\text{CN}), 2162\text{ cm}^{-1}$	$\nu_2(\text{CN}), 2174\text{ cm}^{-1}$	$\nu_3(\text{CN}), 2187\text{ cm}^{-1}$
$t_1$ ( $a_1$ )	$1.5 \pm 0.2\text{ ps}$ (-2.9) <sup>a)</sup>	$1.8 \pm 1.2\text{ ps}$ (-0.45)	$0.2 \pm 0.5\text{ ps}$ (0.36)
$t_2$ ( $a_2$ )	$40 \pm 10\text{ ps}$ (1.9)	$43 \pm 30\text{ ps}$ (0.48)	$36 \pm 11\text{ ps}$ (0.76)
$t_3$ ( $a_3$ )	$282 \pm 86\text{ ps}$ (2.17)	$393 \pm 97\text{ ps}$ (0.93)	$309 \pm 64\text{ ps}$ (0.94)


<sup>a)</sup> the amplitudes have been multiplied by  $10^4$

From the analysis of the transient emission and vibrational spectroscopy data, the following mechanism (**scheme 2**) can therefore be proposed for the photophysical behavior of **DCA@ZSM-5**:

- The first transient species that is formed upon photoexcitation is the localized excited  $S_1$  state (**LE**) of the DCA molecules. **LE** can be clearly identified by its emission band below 500 nm, and the vibrational CN stretching mode  $\nu_1(\text{CN})$  peaking at  $2162\text{ cm}^{-1}$ . Our data show that the **LE** state in

**DCA@ZSM-5** is similar to the  $S_1$  state of DCA molecules in solution. The lifetime of **LE** is however strongly reduced in **DCA@ZSM-5** and it decays following a bimodal distribution ( $t_1 = \text{ca. } 40 \text{ ps}$ ,  $t_2 = \text{ca. } 300 \text{ ps}$ ) resulting from the heterogeneity of the molecular arrangement and of structural defaults. We proved that **LE** is however not decaying by internal conversion to the ground state ( $S_0 \leftarrow S_1$ ) but it is converted efficiently into exciplex **EX** (or bounded ion-pair **IP**) species by the charge delocalization over one or several DCA entities.

- The formation of **EX (IP)** species is demonstrated by the emission spectra and the transient IR data. The highest time resolution of the latest spectroscopy allowed us to show that **EX** species are not only formed by conversion from the **LE**, but also directly (less than 100 fs) by charge transfer excitation. We clearly identified two **EX** species emitting above 520 nm and that can be differentiated by the frequency of the CN stretching vibration, respectively peaking at 2174 and 2188  $\text{cm}^{-1}$ . These charge delocalized states have a lifetime of several nanoseconds that is also probably modulated by the microheterogeneity of the supramolecular organization.

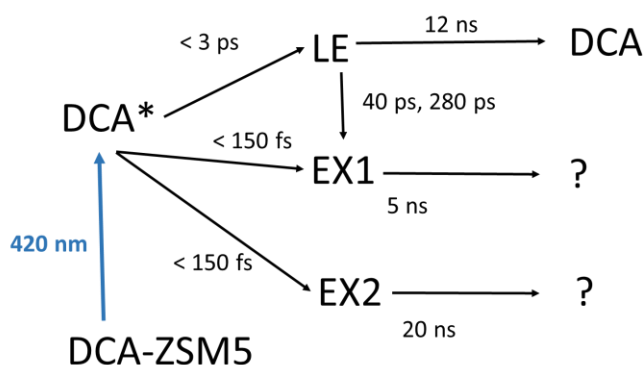

**Scheme 2:** Photophysical processes involved following the photoexcitation of **DCA@ZSM-5** at 420 nm.

## Conclusion

We have characterized by time-resolved spectroscopy (ps TCSCP emission and fs IR transient absorption) the transient chemical species that are generated upon the photoexcitation of DCA molecules adsorbed as dense layers at the surface of microcrystals of zeolite ZSM-5. Following the photoexcitation, the main mechanism is the ultrafast formation of charge delocalized species directly by resonance with a charge transfer transition, or within a few hundreds of picoseconds, through the formation of the localized (LE)  $S_1$  state of DCA. Our results show the potential of **DCA@ZSM-5** for stabilizing efficiently and with a high yield of formation of charge separated states. Further investigations are necessary by carrying out similar photophysical measurements at different degrees of dispersion of the DCA molecules at the surface, by modulating the molecular concentration but also the zeolite type and composition, for a more precise identification of the transient species and the role of the zeolites on their equilibrium and lifetime. Quantum chemistry could also provide a microscopic insight of the **EX** species.

From the spectroscopic point-of-view, this work has extended to the case of zeolites the application of the MidIR transient absorption spectroscopy to characterize photoinduced charge separation processes. We reported IR transient spectra of good quality and, more important, obtained at a reasonable guest concentration of 0.5 molecule/ u.c. So, under these spectroscopic conditions, it is fully possible to consider the investigation of molecules adsorbed at lower concentration, notably by using zeolitic material exhibiting high external surface area like nanozeolite or nanosheets.

Financial support from the Chevreul institute (FR 2638), the Ministère de l'Enseignement Supérieur et de la Recherche, the Région Haut de France, and FEDER is acknowledged. FTIR and FT Raman measurements were carried out using the facilities of the clusters of vibrational spectroscopy of the advanced characterization platform of the Institute E. Chevreul. This work was granted access to the HPC resources of CINES (Centre Informatique National de l'Enseignement Supérieur) and IDRIS (Institut du Développement et des Ressources en Informatique Scientifique) under the allocations A0090806933 and A0110806933 made by GENCI (Grand Équipement National de Calcul Intensif).

The datasets generated during and/or analysed during the current study are available from the corresponding author on reasonable request

## References

- [1] J. C. Scaiano and H. García, *Intrazeolite Photochemistry: Toward Supramolecular Control of Molecular Photochemistry*, *Acc. Chem. Res.* **32**, 783 (1999).
- [2] N. J. Turro, *From Boiling Stones to Smart Crystals: Supramolecular and Magnetic Isotope Control of Radical-Radical Reactions in Zeolites*, *Acc. Chem. Res.* **33**, 637 (2000).
- [3] G. Calzaferri and K. Lutkouskaya, *Mimicking the Antenna System of Green Plants*, *Photochem. Photobiol. Sci.* **7**, 879 (2008).
- [4] H. S. Kim and K. B. Yoon, *Preparation and Characterization of CdS and PbS Quantum Dots in Zeolite Y and Their Applications for Nonlinear Optical Materials and Solar Cell*, *Coord. Chem. Rev.* **263–264**, 239 (2014).
- [5] V. Ramamurthy and J. Sivaguru, *Supramolecular Photochemistry as a Potential Synthetic Tool: Photocycloaddition*, *Chem. Rev.* **116**, 9914 (2016).
- [6] O. Fenwick et al., *Tuning the Energetics and Tailoring the Optical Properties of Silver Clusters Confined in Zeolites*, *Nat. Mater.* **15**, 1017 (2016).
- [7] V. Ramamurthy and N. J. Turro, *Photochemistry of Organic Molecules within Zeolites: Role of Cations*, *J. Incl. Phenom. Mol. Recognit. Chem.* **21**, 239 (1995).
- [8] S. Hashimoto, *Zeolite Photochemistry: Impact of Zeolites on Photochemistry and Feedback from Photochemistry to Zeolite Science*, *J. Photochem. Photobiol. C Photochem. Rev.* **4**, 19 (2003).
- [9] P. K. Dutta and Y. Kim, *Photochemical Processes in Zeolites: New Developments*, *Curr. Opin. Solid State Mater. Sci.* **7**, 483 (2003).
- [10] M. Busby, C. Blum, M. Tibben, S. Fibikar, G. Calzaferri, V. Subramaniam, and L. De Cola, *Time, Space, and Spectrally Resolved Studies on J-Aggregate Interactions in Zeolite L Nanochannels*, *J. Am. Chem. Soc.* **130**, 10970 (2008).
- [11] S. Mintova, V. De Waele, M. Hözl, U. Schmidhammer, B. Mihailova, E. Riedle, and T. Bein, *Photochemistry of 2-(2'-Hydroxyphenyl)Benzothiazole Encapsulated in Nanosized Zeolites*, *J. Phys. Chem. A* **108**, 10640 (2004).
- [12] R. Q. Albuquerque, J. Kühni, P. Belser, and L. de Cola, *On the Reversible Photoisomerization of Spiropyran-Modified Zeolite I Single Crystals*, *ChemPhysChem* **11**, 575 (2010).
- [13] N. Alarcos, B. Cohen, M. Ziótek, and A. Douhal, *Photochemistry and Photophysics in Silica-Based Materials: Ultrafast and Single Molecule Spectroscopy Observation*, *Chem. Rev.* **117**, 13639 (2017).
- [14] G. Flachenecker and A. Materny, *The Elementary Steps of the Photodissociation and Recombination Reactions of Iodine Molecules Enclosed in Cages and Channels of Zeolite Crystals: A Femtosecond Time-Resolved Study of the Geometry Effect*, *J. Chem. Phys.* **120**, 5674 (2004).
- [15] M. Gil, M. Ziótek, J. A. Organero, and A. Douhal, *Confined Fast and Ultrafast Dynamics of a Photochromic Proton-Transfer Dye within a Zeolite Nanocage*, *J. Phys. Chem. C* **114**, 9554 (2010).
- [16] T. Bein, *Host-Guest Interactions in Zeolites and Periodic Mesoporous Materials*, in *Studies in Surface Science and Catalysis*, Vol. 168 (2007), pp. 611–657.
- [17] M. Bryckaert, A. Kharchenko, O. Lebedev, B. Dong, I. De Waele, G. Buntinx, O. Poizat, S. Mintova, and V. De Waele, *Hot-Electron Photodynamics of Silver-Containing Nanosized Zeolite Films Revealed by Transient Absorption Spectroscopy*, *J. Phys. Chem. C* **121**, 26958 (2017).
- [18] F. Kawtharani, S. Mintova, R. Retoux, M. Mostafavi, G. Buntinx, and V. De Waele, *Hot-Electron Photodynamics in Silver-Containing BEA-Type Nanozeolite Studied by Femtosecond Transient Absorption Spectroscopy*, *ChemPhysChem* **21**, 2634 (2020).
- [19] J. K. Thomas, *Physical Aspects of Photochemistry and Radiation Chemistry of Molecules Adsorbed on SiO<sub>2</sub>,  $\gamma$ -Al<sub>2</sub>O<sub>3</sub>, Zeolites, and Clays*, *Chem. Rev.* **93**, 301 (1993).
- [20] J. K. Thomas, *Physical Aspects of Radiation-Induced Processes on SiO<sub>2</sub>,  $\gamma$ -Al<sub>2</sub>O<sub>3</sub>, Zeolites, and Clays*, *Chem. Rev.* **105**, 1683 (2005).
- [21] N. J. Turro, X.-G. Lei, W. Li, Z. Liu, A. McDermott, M. F. Ottaviani, and L. Abrams, *Photochemical and Magnetic Resonance Investigations of the Supramolecular Structure and Dynamics of Molecules and Reactive Radicals on the External and Internal Surface of MFI Zeolites*, *J. Am. Chem. Soc.* **122**, 11649 (2000).
- [22] A. Moscatelli, Z. Liu, X. Lei, J. Dyer, L. Abrams, M. F. Ottaviani, and N. J. Turro, *Photolysis of Dibenzyl Ketones Sorbed on MFI Zeolites in the Presence of Spectator Molecules: Cage Effects, Kinetics, and External Surface Sites Characterization*, *J. Am. Chem. Soc.* **130**, 11344 (2008).
- [23] V. Valtchev and L. Tosheva, *Porous Nanosized Particles: Preparation, Properties, and Applications*, *Chem. Rev.* **113**, 6734 (2013).

- [24] S. Mintova, M. Jaber, and V. Valtchev, *Nanosized Microporous Crystals: Emerging Applications*, Chem. Soc. Rev. **44**, 7207 (2015).
- [25] P. Kumar et al., *One-Dimensional Intergrowths in Two-Dimensional Zeolite Nanosheets and Their Effect on Ultra-Selective Transport*, Nat. Mater. **19**, 443 (2020).
- [26] M. Hureau, A. Moissette, L. Tzanis, and T. J. Daou, *Effects of the Zeolite Particle Size on the Charge Separated States*, Microporous Mesoporous Mater. **254**, 121 (2017).
- [27] L. Duploux, A. Moissette, M. Hureau, V. De Waele, T. J. Daou, and I. Batonneau-Gener, *Effect of Zeolite Morphology on Charge Separated States: ZSM-5-Type Nanocrystals, Nanosheets and Nanosponges*, Phys. Chem. Chem. Phys. **22**, 12015 (2020).
- [28] Y. Kim, A. Das, H. Zhang, and P. K. Dutta, *Zeolite Membrane-Based Artificial Photosynthetic Assembly for Long-Lived Charge Separation*, J. Phys. Chem. B **109**, 6929 (2005).
- [29] X. Liu and J. K. Thomas, *Photophysical Properties of Pyrene in Zeolites: Adsorption and Distribution of Pyrene Molecules on the Surfaces of Zeolite L and Mordenite*, Chem. Mater. **6**, 2303 (1994).
- [30] X. Liu, G. Zhang, and J. K. Thomas, *Spectroscopic Studies of Electron and Hole Trapping in Zeolites: Formation of Hydrated Electrons and Hydroxyl Radicals*, J. Phys. Chem. B **101**, 2182 (1997).
- [31] A. Moissette, H. Vezin, I. Gener, J. Patarin, and C. Brémard, *Electron-Hole Pairs Stabilized in Al-ZSM-5 Zeolites*, Angew. Chem. - Int. Ed. **41**, 1241 (2002).
- [32] A. Moissette, S. Marquis, D. Cornu, H. Vezin, and C. Brémard, *Long-Lived Spin-Correlated Pairs Generated by Photolysis of Naphthalene Occluded in Non-Brønsted Acidic ZSM-5 Zeolites*, J. Am. Chem. Soc. **127**, 15417 (2005).
- [33] P. K. Dutta and M. Severance, *Photoelectron Transfer in Zeolite Cages and Its Relevance to Solar Energy Conversion*, J. Phys. Chem. Lett. **2**, 467 (2011).
- [34] C. Yang, J.-D. Yang, Y.-H. Li, X. Li, and J.-P. Cheng, *9,10-Dicyanoanthracene Catalyzed Decarboxylative Alkynylation of Carboxylic Acids under Visible-Light Irradiation*, J. Org. Chem. **81**, 12357 (2016).
- [35] E. Vauthey, *Investigation of the Photoinduced Electron Transfer Reaction between 9,10-Dicyanoanthracene and 1-Methylnaphthalene in Acetonitrile Using Picosecond Transient Grating Spectroscopy*, J. Phys. Chem. A **101**, 1635 (1997).
- [36] E. Vauthey, C. Högemann, and X. Allonas, *Direct Investigation of the Dynamics of Charge Recombination Following the Fluorescence Quenching of 9,10-Dicyanoanthracene by Various Electron Donors in Acetonitrile*, J. Phys. Chem. A **102**, 7362 (1998).
- [37] S. Iwai, S. Murata, R. Katoh, M. Tachiya, K. Kikuchi, and Y. Takahashi, *Ultrafast Charge Separation and Exciplex Formation Induced by Strong Interaction between Electron Donor and Acceptor at Short Distances*, J. Chem. Phys. **112**, 7111 (2000).
- [38] Y. Wang, O. Haze, J. P. Dinnocenzo, S. Farid, R. S. Farid, and I. R. Gould, *Bonded Exciplexes. A New Concept in Photochemical Reactions*, J. Org. Chem. **72**, 6970 (2007).
- [39] E. Vauthey, *Elucidating the Mechanism of Bimolecular Photoinduced Electron Transfer Reactions*, J. Phys. Chem. B **126**, 778 (2022).
- [40] B. Dereka, M. Koch, and E. Vauthey, *Looking at Photoinduced Charge Transfer Processes in the IR: Answers to Several Long-Standing Questions*, Acc. Chem. Res. **50**, 426 (2017).
- [41] M. Koch, G. Licari, and E. Vauthey, *Bimodal Exciplex Formation in Bimolecular Photoinduced Electron Transfer Revealed by Ultrafast Time-Resolved Infrared Absorption*, J. Phys. Chem. B **119**, 11846 (2015).
- [42] M. Koch, R. Letrun, and E. Vauthey, *Exciplex Formation in Bimolecular Photoinduced Electron-Transfer Investigated by Ultrafast Time-Resolved Infrared Spectroscopy*, J. Am. Chem. Soc. **136**, 4066 (2014).
- [43] T. Mani, D. C. Grills, M. D. Newton, and J. R. Miller, *Electron Localization of Anions Probed by Nitrile Vibrations*, J. Am. Chem. Soc. **137**, 10979 (2015).
- [44] G. Lee, D. Kossowska, J. Lim, S. Kim, H. Han, K. Kwak, and M. Cho, *Cyanamide as an Infrared Reporter: Comparison of Vibrational Properties between Nitriles Bonded to N and C Atoms*, J. Phys. Chem. B **122**, 4035 (2018).
- [45] S. Choi, J. Park, K. Kwak, and M. Cho, *Substituent Effects on the Vibrational Properties of the CN Stretch Mode of Aromatic Nitriles: IR Probes Useful for Time-Resolved IR Spectroscopy*, Chem. - Asian J. **16**, 2626 (2021).
- [46] J. Kubota, M. Furuiki, Y. Goto, J. Kondo, A. Wada, K. Domen, and C. Hirose, *Vibrational Lifetimes of Surface Hydroxyl Groups of Zeolites by Picosecond IR Pulses*, Chem. Phys. Lett. **204**, 273 (1993).
- [47] M. Kashitani et al., *Transient Absorption Spectra of vibrationally excited OH/OD groups in Mordenite zeolites: Effect of Xe adsorption*, J. Chem. Phys. **105**, 6665 (1996).
- [48] M. Bonn, H. J. Bakker, A. W. Kleyn, and R. A. Van Santen, *Dynamics of Infrared Photodissociation of Methanol Clusters in Zeolites and in Solution*, J. Phys. Chem. **100**, 15301 (1996).



- [49] A. Ghose et al., *Emission Properties of Oxyluciferin and Its Derivatives in Water: Revealing the Nature of the Emissive Species in Firefly Bioluminescence*, *J. Phys. Chem. B* **119**, 2638 (2015).
- [50] M. J. Frisch et al., *Gaussian 16 Revision C.01*, (2016).
- [51] J. P. Perdew, K. Burke, and M. Ernzerhof, *Generalized Gradient Approximation Made Simple*, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [52] C. Adamo and V. Barone, *Toward Reliable Density Functional Methods without Adjustable Parameters: The PBE0 Model*, *J. Chem. Phys.* **110**, 6158 (1999).
- [53] S. Grimme, J. Antony, S. Ehrlich, and H. Krieg, *A Consistent and Accurate Ab Initio Parametrization of Density Functional Dispersion Correction (DFT-D) for the 94 Elements H-Pu*, *J. Chem. Phys.* **132**, 154104 (2010).
- [54] R. A. Kendall, T. H. Dunning, and R. J. Harrison, *Electron Affinities of the First-row Atoms Revisited. Systematic Basis Sets and Wave Functions*, *J. Chem. Phys.* **96**, 6796 (1992).
- [55] J. Eriksen and C. S. Foote, *Electron-Transfer Fluorescence Quenching and Exciplexes of Cyano-Substituted Anthracenes*, *J. Phys. Chem.* **82**, 2659 (1978).
- [56] B. Manna, R. Ghosh, and D. K. Palit, *Exciton Dynamics in Anthracene Nanoaggregates*, *J. Phys. Chem. C* **119**, 10641 (2015).
- [57] A. F. Olea, D. R. Worrall, F. Wilkinson, S. L. Williams, and A. A. Abdel-Shafi, *Solvent Effects on the Photophysical Properties of 9,10-Dicyanoanthracene*, *Phys. Chem. Chem. Phys.* **4**, 161 (2002).
- [58] J. S. Beckwith, A. Aster, and E. Vauthey, *The Excited-State Dynamics of the Radical Anions of Cyanoanthracenes*, *Phys. Chem. Chem. Phys.* **24**, 568 (2022).
- [59] I. R. Gould, R. H. Young, L. J. Mueller, S. Farid, and A. C. Albrecht, *Electronic Structures of Exciplexes and Excited Charge-Transfer Complexes*, *J. Am. Chem. Soc.* **116**, 8188 (1994).
- [60] R. H. Young, A. M. Feinberg, J. P. Dinnocenzo, and S. Farid, *Transition from Charge-Transfer to Largely Locally Excited Exciplexes, from Structureless to Vibrationally Structured Emissions*, *Photochem. Photobiol.* **91**, 624 (2015).
- [61] E. Dolotova, D. Dogadkin, I. Soboleva, M. Kuzmin, O. Nicolet, and E. Vauthey, *Lifetimes of Partial Charge Transfer Exciplexes of 9-Cyanophenanthrene and 9-Cyanoanthracene*, *Chem. Phys. Lett.* **380**, 729 (2003).
- [62] F. Vazart, C. Latouche, P. Cimino, and V. Barone, *Accurate Infrared (IR) Spectra for Molecules Containing the C≡N Moiety by Anharmonic Computations with the Double Hybrid B2PLYP Density Functional*, *J. Chem. Theory Comput.* **11**, 4364 (2015).
- [63] J. M. Rodgers, R. M. Abaskharon, B. Ding, J. Chen, W. Zhang, and F. Gai, *Fermi Resonance as a Means to Determine the Hydrogen-Bonding Status of Two Infrared Probes*, *Phys. Chem. Chem. Phys.* **19**, 16144 (2017).
- [64] P. Coulter, M. P. Grubb, D. Koyama, I. V. Sazanovich, G. M. Greetham, and A. J. Orr-Ewing, *Recombination, Solvation and Reaction of CN Radicals Following Ultraviolet Photolysis of ICN in Organic Solvents*, *J. Phys. Chem. A* **119**, 12911 (2015).
- [65] P. Hamm, *Coherent Effects in Femtosecond Infrared Spectroscopy*, *Chem. Phys.* **200**, 415 (1995).