

Observation of Brillouin backscattering in a 50cm-long high-index doped silica chip waveguide

M. Zerbib¹, V.T. Hoang², J. C. Beugnot¹, K. P. Huy¹, B. Little³, S. T. Chu⁴,
D. J. Moss⁵, R. Morandotti⁶, B. Wetzels², and T. Sylvestre^{1,*}

1. Institut FEMTO-ST, CNRS-Université de Franche-Comté, 25030 Besançon, France

2. Université de Limoges, XLIM, UMR CNRS 7252, 123 Avenue A. Thomas, 87060 Limoges, France

3. QXP Technologies Inc., Xi'an, China

4. Department of Physics, City University of Hong Kong, Tat Chee Avenue, Hong Kong, SAR, China

5. Optical Sciences Centre, Swinburne University of Technology, Hawthorn, VIC 3122, Victoria, Australia

6. INRS-EMT, 1650 Boulevard Lionel-Boulet, Varennes, J3X 1S2, Québec, Canada

*Email: thibaut.sylvestre@univ-fcomte.fr

Brillouin scattering (BS), whereby light interacts coherently with hypersonic acoustic waves, is a powerful and flexible optical effect for processing light and microwave, making optical sensors, frequency combs, and lasers. While BS has been early exploited in optical fibers, it is only recently that it has been demonstrated in CMOS-compatible integrated waveguides based on chalcogenide (ChG), silicon (Si), or silicon nitride (SiN) in its stoichiometric composition (Si₃N₄) [1-4].

Here we demonstrate on-chip Brillouin backscattering in a 50-cm long spiral high-index doped silica glass integrated waveguide [5]. The waveguide cross section structure is shown in Fig. 1(a), including a high index (n=1.7) doped silica core embedded in SiO₂ on a thermal oxide and a silicon wafer. The core has a cross-section of 1.5μm by 1.52μm and the total insertion loss of the long spiral waveguide has been measured as 8.9 dB at λ=1550 nm using a high-resolution optical time domain reflectometer (OBR Luna Tech.). The Brillouin spectrum has been measured using a simple heterodyne technique [6], whereby the backscattered Brillouin signal coherently interferes with a local oscillator and is further detected using an electrical spectrum analyser (ESA). The experimental Brillouin spectrum is shown in Fig. 1 (b) for an input c.w. power of 18 dBm at 1550 nm. The measured Brillouin shift and its full-width at half-maximum (FWHM) linewidth were ν_B=16 GHz and Δν_B~200 MHz, respectively. This gives an acoustic velocity of $V_L = \nu_B \lambda / (2n_{\text{eff}}) = 7700 \text{ m.s}^{-1}$, with $n_{\text{eff}}=1.61$ the effective index of the fundamental optical mode. This is in good agreement with theoretical prediction and numerical simulation shown in Fig. 1(c), where we plotted the numerically computed Brillouin spectrum from the elastodynamic equation including electrostriction [6] (kinetic energy density versus the acoustic frequency). The insets in Fig. 1(c) show the computed optical (top) and acoustic (bottom) transverse intensity profiles, respectively.

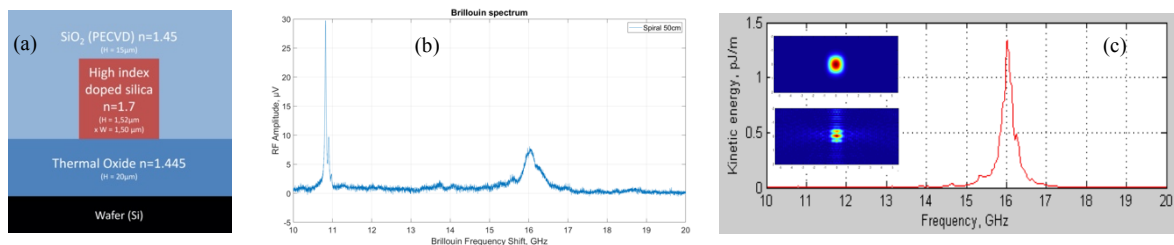


Fig. 1 (a) High-index doped silica chip waveguide cross section structure used for Brillouin observation. (b) Experimental Brillouin spectrum, measured for an input power of 18 dBm at 1550 nm, showing the Brillouin peaks at 16 GHz of the high-index chip, and at 11 GHz due to silica fibers in the setup. (c) Numerical simulation of the Brillouin spectrum (kinetic energy density versus acoustic frequency). The insets show the optical (top) and acoustic (bottom) modes.

References

- [1] B. J. Eggleton, C. G. Poulton, P. T. Rakich, M. Steel, G. Bahl, "Brillouin integrated photonics," *Nat. Phot.* **13** (10), 664-677 (2019).
- [2] R. Pant, C. G. Poulton, D.-Y. Choi, H. McFarlane, S. Hile, E. Li, L. Thevenaz, B. Luther-Davies, S. J. Madden, and B. J. Eggleton, "On-chip stimulated Brillouin scattering," *Opt. Express* **19**, 8285-8290 (2011).
- [3] Kittlaus, E., Shin, H. & Rakich, P. Large Brillouin amplification in silicon. *Nature Photon* **10**, 463-467 (2016).
- [4] Flavien Gyger, Junqiu Liu, Fan Yang, Jijun He, Arslan S. Raja, Rui Ning Wang, Sunil A. Bhave, Tobias J. Kippenberg, and Luc Thévenaz, "Observation of Stimulated Brillouin Scattering in Silicon Nitride Integrated Waveguides," *Phys. Rev. Lett.* **124**, 013902 (2020).
- [5] M. Ferrera, L. Razzari, D. Duchesne, R. Morandotti, Z. Yang, M. Liscidini, J.E. Sipe, S. Chu, B.E. Little, D. J. Moss, "Low-power continuous-wave nonlinear optics in doped silica glass integrated waveguide structures. *Nature Photon* **2**, 737-740 (2008).
- [6] A. Godet, A. Ndao, T. Sylvestre, V. Pecheur, S. Lebrun, G. Pauliat, J.-C. Beugnot, and K. P. Huy, "Brillouin spectroscopy of optical microfibers and nanofibers," *Optica* **4**, 1232-1238 (2017).