



**HAL**  
open science

## Perspective: Machine Learning in Design for 3D/4D Printing

Xiaohao Sun, Kun Zhou, Frédéric Demoly, Ruike Renee Zhao, H. Jerry Qi

► **To cite this version:**

Xiaohao Sun, Kun Zhou, Frédéric Demoly, Ruike Renee Zhao, H. Jerry Qi. Perspective: Machine Learning in Design for 3D/4D Printing. *Journal of Applied Mechanics*, 2024, 91 (3), 10.1115/1.4063684 . hal-04320453

**HAL Id: hal-04320453**

**<https://hal.science/hal-04320453>**

Submitted on 9 Feb 2024

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution 4.0 International License

## **Machine learning in 3D/4D printing design**

Xiaohao Sun<sup>1</sup>, Kun Zhou<sup>2</sup>, Frédéric Demoly<sup>3,4</sup>, Ruike Renee Zhao<sup>5</sup>, H. Jerry Qi<sup>1\*</sup>

<sup>1</sup>The George W. Woodruff School of Mechanical Engineering, Georgia Institute of Technology, Atlanta, GA 30332, USA

<sup>2</sup>Singapore Centre for 3D Printing, School of Mechanical and Aerospace Engineering, Nanyang Technological University, 50 Nanyang Avenue, Singapore 639798, Singapore

<sup>3</sup>ICB UMR 6303 CNRS, Belfort-Montbéliard University of Technology, UTBM, 90010 Belfort, France

<sup>4</sup>Institut universitaire de France (IUF)

<sup>5</sup>Department of Mechanical Engineering, Stanford University, Stanford, CA 94305, USA

\*Corresponding author: [qih@me.gatech.edu](mailto:qih@me.gatech.edu)


## **Abstract**

3D/4D printing offers significant flexibility in manufacturing complex structures with diverse range of mechanical responses, while also posing critical needs in tackling challenging inverse design problems. The rapidly developing machine learning (ML) approach offers new opportunities and has attracted significant interests in the field. In this perspective paper, we highlight recent advancements of utilizing ML for designing printed structures with desired mechanical responses. First, we provide an overview of common forward and inverse problems, relevant types of structures, and design space and responses in 3D/4D printing. Next, we review recent works that employ a variety of ML approaches for the inverse design of different mechanical responses, ranging from structural properties to active shape changes. Finally, we briefly discuss the main challenges, summarize existing and potential ML approaches, and extend the discussion to broader design problems in the field of 3D/4D printing. This paper is hoped to provide foundational guides and insights into the application of ML for the 3D/4D printing design.

Keywords: 3D printing; 4D printing; machine learning; inverse design; mechanical responses.

## 1. Introduction

3D printing, or additive manufacturing, enables the creation of complex physical objects from digital models. Multimaterial printing allows for the fabrication of composite structures with materials of different properties and different active responses [1-3]. Owing to the development of multimaterial printing and active materials, the emerging 4D printing technology takes a step further by introducing time as a dimension, allowing printed objects to change their shape, properties, or functionality when exposed to specific energy stimuli (e.g., light, heat, moisture, pH, solvent, electric/magnetic field, etc.) [4-8]. There exist many 3D printing techniques. Depending on how the raw material is deposited, these techniques can be classified into the following categories: extrusion-based methods such as direct ink writing (DIW) and fused filament fabrication (FFF), inkjet printing, vat-photopolymerization methods such as digital light processing (DLP), stereolithography (SLA), and two-photon polymerization (TPP), powder bed fusion-based methods such as selective laser sintering (SLS), etc. We refer the readers to recent reviews [8, 9] for detailed descriptions of these techniques.

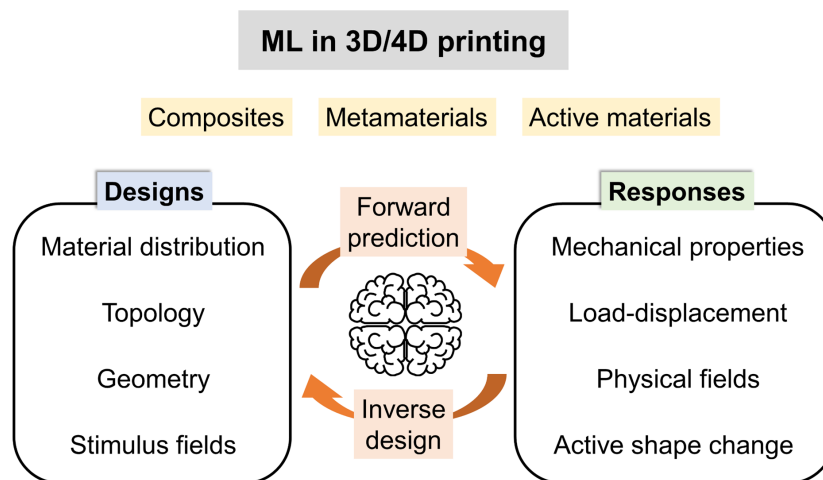

**Figure 1.** Overview of forward and inverse problems in 3D/4D printing utilizing ML. The design space typically involves material distribution, topology, geometry, and stimulus fields. The output generally includes mechanical properties, load-displacement, physical

fields, and shape change.

3D/4D printing offers significant manufacturing flexibility, especially in creating complex shapes and structures that exhibit functions and responses beyond those of printed materials. Here, we refer printed materials as those directly coming out of a printer without specially designed geometry or features. Their properties are only determined by the printing techniques and printer operating parameters. In 3D/4D printing, mechanical design plays an important role in harnessing its advantage to enable intelligent printing and advancing various engineering applications [10-20]. This entails defining the functional description of transformable or deployable systems according for various usage scenarios, on which computational reasoning is needed to embody knowledge and decisions related to 4D printing. To achieve the appropriate geometry and structure of shape-changing objects, decisions can be made on qualitative recommendation with the support of domain ontology (which is a component of symbolic artificial intelligence to formalize knowledge of an expertise domain with machine-interpretable description), as successfully demonstrated in the design of multimaterial 4D-printed objects [X,X]. However, addressing design for 3D/4D printing via symbolic reasoning alone is insufficient and demands both forward prediction of the properties, physical fields, load-displacement, and shape change of printed structures, and the inverse design of material distributions, topology, geometry, and stimulus fields (in terms of amplitude, location, and duration), as illustrated in **Figure 1**. The printed objects can range from digital composites at the pixel (2D) or voxel (3D) level, to metamaterials or architected materials, and other active or intelligent material systems. Microstructures can also be encoded in pixels or voxels to create a hierarchical or multiscale material system [21, 22]. The forward problem takes the inputs from the embodiment and detail design stages, such as material properties, material distributions, geometry, topology, hierarchies, and stimulus fields, and predicts mechanical-response


outputs such as structural properties (e.g., modulus, strength, and toughness, stiffness tensor for anisotropic systems), physical fields (e.g., strain and stress fields), nonlinear load-displacement response and, particularly, the shape or function changes of active material systems (which can be seen as deformation field) (**Figure 1**). The inverse design problem seeks to find appropriate design inputs for tasks such as extremizing property values and obtaining designated properties or responses (**Figure 1**).

Motivated by the needs to fully utilize the manufacturing flexibility, significant advancements have been made in developing design strategies. Topology optimization (TO) [23] represents a large class of methods that optimize the geometric features within a design domain to achieve certain objectives. While initiated for maximizing structural performance and minimizing weight, TO has found significant applications to a wide range of design problems in 3D/4D printing [24, 25]. Examples include multiscale TO for enhanced structural performance [26-29] and programmed shape changes [30], anisotropic composite TO for enhanced performance [31, 32] and target actuated motions [33], and TO for programming force-displacement response [34], shape changes of various 4D-printed systems including active composites [35, 36], inflatable structures [37], rod-based structures [38, 39], and magnetoactive materials [40], and continuous shape morphing paths or motions of soft composites [41, 42]. In addition, TO has been used in the design of supports and infills for improved part printability [24]. Despite its great success, TO generally requires complicated mathematical derivations and can be time-consuming due to the computationally expensive physical simulations, mostly finite element (FE) based, especially when geometric and material nonlinearities are involved.

Machine learning (ML), particularly deep learning [43], offers an alternative approach that can handle complex mapping efficiently, making them attractive tools in the design for

3D/4D printing. ML can be broadly categorized into three types: supervised learning (SL), unsupervised learning (USL), and reinforcement learning (RL). SL learns the mapping in labeled data, which is often used for classification and regression tasks, such as property prediction. USL identifies inherent structures in unlabeled data, which may be used for clustering, dimensionality reduction, and discovering new structures. RL involves an agent that takes actions in an environment to maximize a reward, which is often used for decision-making and optimization tasks. The landscape of ML techniques is vast and consistently evolving. Here we list some popular methods used in design: support vector machine (SVM), decision trees (DT), neural networks (NN), convolutional neural networks (CNN), recurrent neural networks (RNN), graph neural network (GNN), generative adversarial networks (GAN), principal component analysis (PCA), variational autoencoders (VAE), gaussian process (GP), Bayesian learning (BL), active learning (AL), evolutionary algorithms (EA), among many others [44]. The readers are referred to textbooks (e.g., [44]) for working principles of these ML methods and to some recent reviews [45-47] for ML applications to the area of mechanics of materials.

In this perspective article, we will review some recent works that apply ML methods to the design for 3D/4D printing. We primarily focus on the design for the mechanical properties or active responses of printed structures. While ML has many other applications in the entire field of 3D printing [48-52], such as processing parameter refinements [53, 54], in-situ anomaly monitoring for quality controls [55], and printing material design and discovery [56-59], these are not the focus here. The paper is organized as follows. In Section 2, we will summarize existing works on ML in 3D/4D printing designs, which will be discussed in several categories of material systems and target properties/responses, corresponding to subsections 2.1 to 2.4. Section 3 is the last section for providing discussions and perspectives.

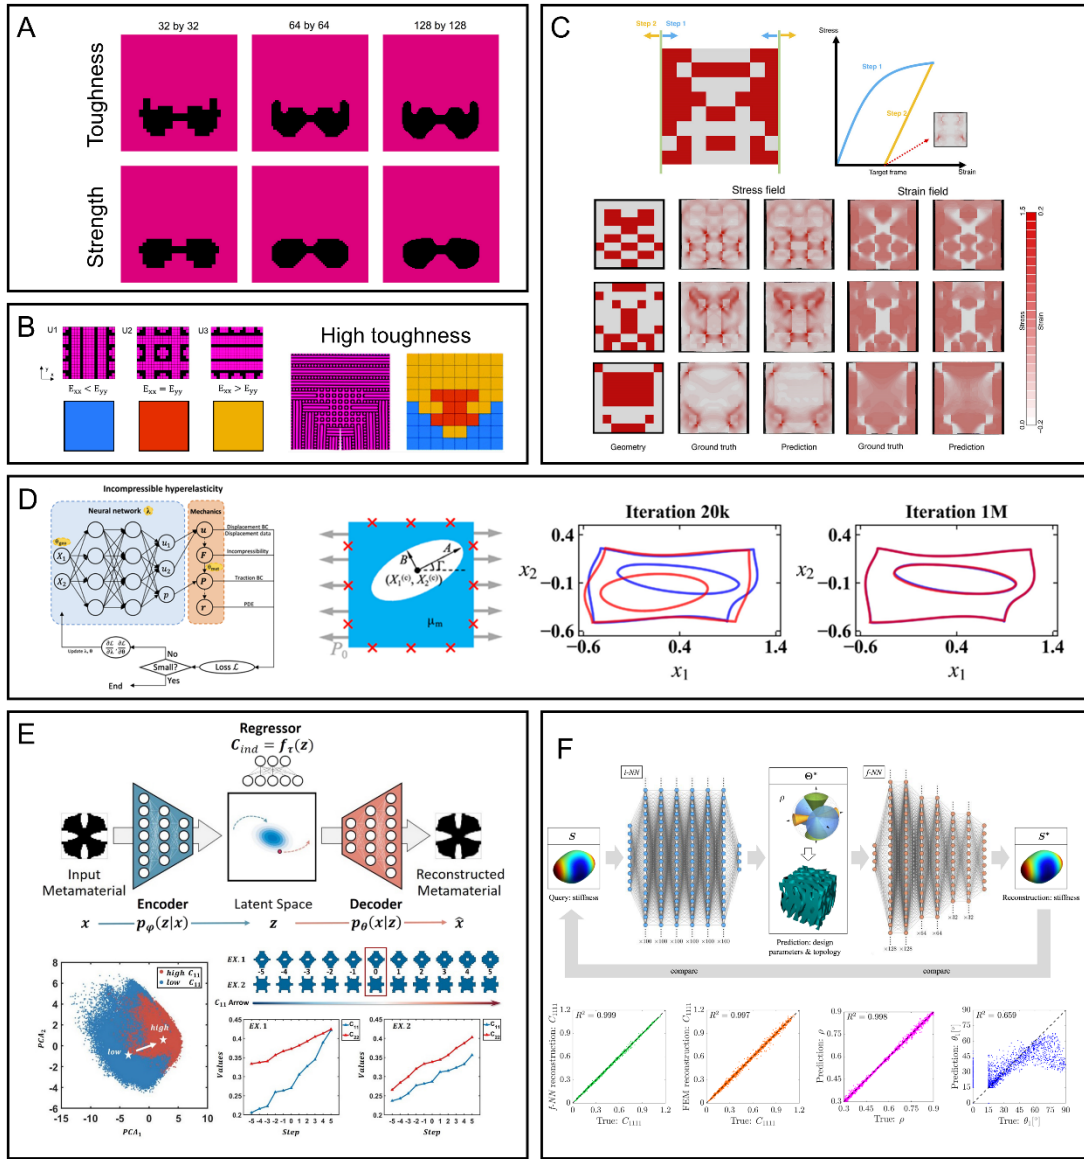

**Figure 2.** Applications of ML in various material systems with different design parameters and mechanical responses. (A) Optimized material distributions of composites for high toughness (top row) and strength (bottom row). (B) Hierarchical design units (left) and optimized designs for high toughness (right). Reproduced from Ref. [13] with permission from the Royal Society of Chemistry. (C) Predictions of stress and strain fields of composites with pixel-level material distributions using conditional GAN. (D) Inverse identification of material distributions based on boundary displacements using physics-



informed ML. (E) VAE enabled low-dimensional, highly structured latent space of microstructures, which allows for generation of diverse architecture families with gradually varying geometries and stiffness. (F) Forward and inverse ML enabled two-way structure-property mapping, where the training of inverse NN is supervised by the pretrained forward NN.

## **2. 3D/4D printing designs**

### **2.1 Mechanical properties of composites**

Composites that possess pixel- or voxel-level material distributions can be naturally encoded as number arrays, which are suitable to serve as input data for ML models. Extensive studies have been done on utilizing ML to predict or optimize various mechanical properties of composite (or heterogeneous) materials, such as effective modulus, strength, toughness, among others. Cecen et al. [60] employed 3D CNN to predict the effective modulus of 3D heterogeneous materials. Li et al. [61] utilized CNN to predict the effective modulus of 2D heterogeneous materials. Regarding strength and toughness, Buehler and coworkers [21, 62, 63] have made significant efforts in exploring the ML capability in composite optimizations. They developed an ML classification model [62] to evaluate 2D composite designs in terms of their strength or toughness, and distinguish them as either “good” or “bad”. The model, once trained with FE-generated data, can be used to assess the ranking of unseen designs, thus empowering the optimization to achieve high strength or toughness. The optimized designs based on this approach are shown in **Figure 2A**. An ML regression model [63] was later developed and combined with EA for optimizing the composite strength and toughness under shear loadings. In composite designs based on pixels, the design space is often tremendous. To mitigate this issue, Buehler and coworkers [21] innovatively incorporated ML with the hierarchical design concept. This strategy uses specific microstructures containing numerous pixels as basic

design units and then performs the prediction or design in a coarse-grain manner. As shown in **Figure 2B**, they proposed three elementary design units with different anisotropies. The ML model was then employed to predict the mechanical properties of the composite system, which, in turn, enabled fast optimizations. In addition to NN and CNN, the application of other ML methods such as active learning [64] and reinforcement learning [65, 66] for the bioinspired composite designs have been explored. Furthermore, minimizing the overall compliance of irregular structural topologies (a form of heterogeneous materials) is a typical inverse problem in TO. A variety of ML models such as generative adversarial network (GAN) [67] and convolutional neural network (CNN) [68] have been developed for TO tasks. We will not elaborate on these works but refer the readers to a recent review [69].

## **2.2 Stress and strain fields**

### ***2.2.1 Forward prediction and material distribution design***

Apart from macroscopic mechanical properties, the physical fields (e.g., stress and strain fields) in materials or composites are often of interest. One associated forward problem is the prediction of stress or strain fields given a structure. Nie et al. [70] proposed a CNN model that can accurately predict the stress fields of cantilever structures with moderately arbitrary topologies and loads. Buehler and coworkers [71] developed a conditional GAN-based ML approach, which can accurately predict the stress and strain fields of composites with pixel-level material distribution, as shown in **Figure 2C**. The model also demonstrated the applicability to different component shapes, boundary conditions, and geometric hierarchies. Later on, they further extended this approach for the complete strain and stress tensor predictions, and demonstrated enhanced model generalization by enriching the training datasets with different hierarchies and component ratios [72].

The inverse problem, which manifests as various specific tasks and applications in different fields, has attracted significant interest. In the context of 3D printing, the goal is to design the material property distribution to achieve the target physical field under external loads. Montgomery et al. [22] managed to realize locally tunable anisotropy by using grayscale digital light processing (DLP) printed microstructural patterned units, where the CNN model was employed for the macroscale design of property field given target strain fields.

### ***2.2.2 Material characterization in experimental mechanics***

In experimental mechanics [46, 47], the inverse problem holds particular significance for the material characterization or elastography, i.e., to identify the mechanical property field based on measured deformation field. Various ML methods have been developed for this problem. Although it differs from the design problem in 3D/4D printing, the underlying objective for both problems is to establish a mapping from deformation to property, suggesting that ML methodologies developed for one might be adapted for the other. Therefore, we briefly discuss the ML strategies used in the material characterization here. Physics-informed neural networks (PINN), pioneered by Karniadakis and coworkers [73], have made significant advancements. PINN has been applied to various systems governed by partial differential equations (PDEs), both for forward and inverse problems. Specifically, Zhang et al. [74] implemented a PINN to determine the modulus field of nonhomogeneous hyperelastic materials subjected to external loads, based on the applied boundary displacement data. Later on, they expanded the approach to materials with heterogeneous inclusions or defects [75]. Using PINN, they were able to identify both the geometry (or topology) and elastic properties of the inclusions (**Figure 2D**), which was demonstrated for materials with various constitutive behaviors, possibly with large deformations or plasticity. Moreover, a similar PINN approach was recently proposed by Mowlavi et al. [76], who demonstrated the identification of inclusions with unknown

numbers, various properties and irregular shapes. In addition to the works above, other PINN methods have been proposed to identify nonhomogeneous mechanical properties using full-field experimental data [77-81]. One of major advantages of PINN is that it can integrate physical laws and data in the loss function, and thus require no or a small amount of data in many cases. Additionally, while PINN does not outperform conventional methods such as FE simulations for forward problems [82], it demonstrates superior performance for many inverse problems [47].

In essence, PINN represents an optimization method leveraging the strong expressivity of deep neural networks. Despite its strength, this optimization nature implies that a fresh optimization run is required for each unique deformation field, making individual tasks time-consuming. Supervised learning (SL), although requiring a large amount of labeled data, can function much faster once the training is complete and thus has also been employed for inverse material characterization tasks. For example, Liu et al. [83] developed an ML model that combines discrete cosine transform (DCT) and CNN for accurate modulus field identification. The DCT was used to transform data into the frequency domain, thereby achieving dimensionality reduction and noise filtering. The CNN was then utilized to learn the inverse mapping of frequency data from the strain to the modulus field. This demonstrates the importance of dimensionality reduction in SL tasks when the design or property space is huge.

### **2.3 Mechanical metamaterials**

Mechanical metamaterials, or architected materials, represent a broad class of engineered structures whose properties are determined more by their geometric configurations than by the constituent materials. They often involve intricate microstructural units (or architectures), making them highly amenable to fabrication via 3D printing. Such

microstructures can yield exotic properties, such as tailorable anisotropy, unusual stress-strain curves, negative Poisson's ratio, and tunable acoustic properties. Therefore, the inverse microstructural design for desired properties is a significant facet in the 3D/4D printing design.

### ***2.3.1 Anisotropic elasticity by generative models***

In the design of mechanical metamaterials, an important objective is to achieve the desired, often anisotropic, stiffness tensor. Here, the associated forward problem, i.e., predicting the homogenized elastic stiffness tensor of an architecture (often referred to as homogenization), is typically more tractable using supervised ML models. However, the inverse problem presents a significant challenge as it is ill-posed due to the infinite-dimensional geometric design space and the one-to-many mapping nature from properties to structures. To tackle the inverse problem, deep generative models have been employed to spawn new complex architected designs. For example, Zhao and coworkers [84] developed a GAN model that learns microstructural features from the enormous database they built. This model was then used to generate a myriad of isotropic-elastic architectures that approach the Hashin-Shtrikman (HS) upper bounds under a wide range of porosity (from 0.05 to 0.75). Additionally, Li and coworkers [85] used a GAN to generate new 3D lattice structures whose compression strength were evaluated using a forward GP regressor [86], thus discovering novel lattice architectures with high compression strength. Moreover, they utilized a GP regressor for finding novel 2D lattices with high recovery stress [87].

Note that the design objective of these GAN-aided tasks is relatively limited, e.g., to extremizing a specific property. When we desire the target property to vary within a range, e.g., designing functionally graded metamaterials with spatially varying properties and microstructures, the problem becomes considerably more challenging. To tackle this

challenge, Chen and coworkers [88] utilized the VAE to aid the design process (**Figure 2E**). After building a large database, the encoder within the VAE can compress the microstructure information into a low-dimensional, highly structured latent space, from which the initial structure can be restored by the decoder. A forward predictor (i.e., regressor) was further employed to learn the relationship between the latent variables and the stiffness. As shown in **Figure 2E**, by continuously sampling points in the latent space, they generated diverse architecture families with gradually varying geometries and stiffness. This, in conjunction with conventional macroscale TO, enabled the multiscale design of functionally graded metamaterials that achieve target shape changes. Later on, Chen and coworkers [89] further utilized the same approach for the design of metamaterial-based mechanical cloaks. In addition to VAE, they also employed latent variable GP to obtain a latent space for the designs of 2D and 3D lattice metamaterials [90].

### ***2.3.2 Anisotropic elasticity by forward ML-supervised inverse ML model***

Alternatively, Kochmann et al. proposed a general inverse design framework that ingeniously exploits a forward ML model to supervise an inverse ML model, and applied it to the spinodoid metamaterials [91]. **Figure 2F** illustrates the concept of this approach. The forward ML model, which takes the design parameters as input to predict the stiffness (property), is pre-trained using labeled data and then leveraged to train the inverse model through the following procedure. The inverse model takes the target property as input and yields a trial design, which is fed into the forward model to predict the trial property. The inverse ML model is trained by minimizing the discrepancy between the predicted and target properties. Once trained, the inverse model can instantaneously generate the optimized designs on-demand, while the forward and inverse models together also provide a computationally efficient two-way structure-property mapping. Moreover, their approach enables the design of spatially varying architectures for functional grading. Later on, they

extended this design framework to truss (or lattice) metamaterials by incorporating an appropriate design parameterization [92], as well as to the pore growth-based cellular metamaterials [93]. More recently, they incorporated the forward ML model into gradient-based multiscale TO, where the ML allows for rapid forward homogenization given microstructure and efficient computation of gradients via automatic differentiation (AD), enabling the accelerated multiscale TO of functional graded spinodoid metamaterials [94].

### ***2.3.3 Stress-strain response***

Owing to their unique microstructures, mechanical metamaterials often exhibit unusual stress-strain curves under external loads. The rational design of these structures, aimed at achieving diverse target load-deformation responses, holds significant engineering values. Given the vast geometric design space, ML has been exploited for accelerating the inverse design process. For instance, Wang et al. [95] combined an NN forward model and an EA to design novel central-symmetry, shell-based metamaterials with various target compressive stress-strain curves, such as strain hardening and softening. Note that a large amount of datapoints is needed to well represent a stress-strain curve, which implies high data dimensionality and can impair network performance. Employing multiple NNs can improve performance while also increasing computational cost [95]. This issue is addressed in an alternative study with a different metamaterial system, where Deng et al. [96] utilized PCA to condense the stress-strain data, obtaining their principal components. They then trained a NN to directly learn the relationship between the geometric design parameters and the resulting principal components, which achieves high prediction accuracy. Combining NN with an evolution strategy (a class of EA), they achieved an effective inverse design. Notably, they also attempted to use an inverse NN to learn the mapping from response to design, demonstrating that an inverse NN does not perform well due to the ill-posed nature of the inverse problem. Moreover, Bayesian ML has also been

used to design super-compressible metamaterial blocks [97].

In addition to the mechanical response mentioned above, other physical properties of metamaterials, including acoustic and optical properties, have also attracted significant interests and inspired studies utilizing ML methods [98-101]. We will not elaborate on these here but refer the readers to a recent review [102].

## **2.4 Active shape-change response by 4D printing**


Integrating 3D printing with active materials (or stimuli-responsive materials) enables the emerging 4D printing technique [8]. The ability to spatially control mechanical properties of multimaterial 3D printing further offers a vast design space. In general, the 4D printing concept is not limited to shape changes, but also property or functionality changing. In this section, we mainly discuss works using ML for designing shape-change response in 4D printing, possibly involving general active material systems. Generally speaking, design for shape change could be more challenging than that for mechanical properties such as stiffness and toughness, as high-dimensional data are needed to fully describe a shape change.

### ***2.4.1 Finite element – evolutionary algorithm approach***

To exploit large design space offered by multimaterial 3D printing, the computational design integrating mechanical simulations and optimizations has become a highly capable tool. For example, the gradient-based TO has made great progress [35-42], yet it may suffer from low design efficiency and high numerical complexity when geometric and material nonlinearities are involved. Alternatively, gradient-free optimization algorithms such as EA have also achieved great success. For example, Hamel et al. [103] employed the FE and EA (FE-EA) for the inverse design of active composite (AC) beams with voxel-level



material distributions. The approach was later extended to magneto-AC beams by Wu et al. [104], who also developed voxel-level encoding approach in direct ink write 3D printing method. Athinarayanarao et al. [105] used FE-EA approach to design AC beams integrated with topological void voxels. The FE-EA approach is time-consuming and cannot deal with very complicated target shapes. This is because the EA typically requires numerous forward FE simulations to explore a large design space, thus suffering from high computational cost. To reduce computational cost, researchers have developed forward reduced order models (ROMs) to speed up evolutionary designs for different material systems, such as 3D voxel ACs [106, 107] and magneto-AC beams [108, 109]. Yet, faster forward models, preferably capable of handling vast amounts of data, are still highly desired to enable more efficient inverse designs. As such, the ML approach is particularly suited to deliver ultrafast, massive predictions and has been extensively exploited to address the inverse design problem.

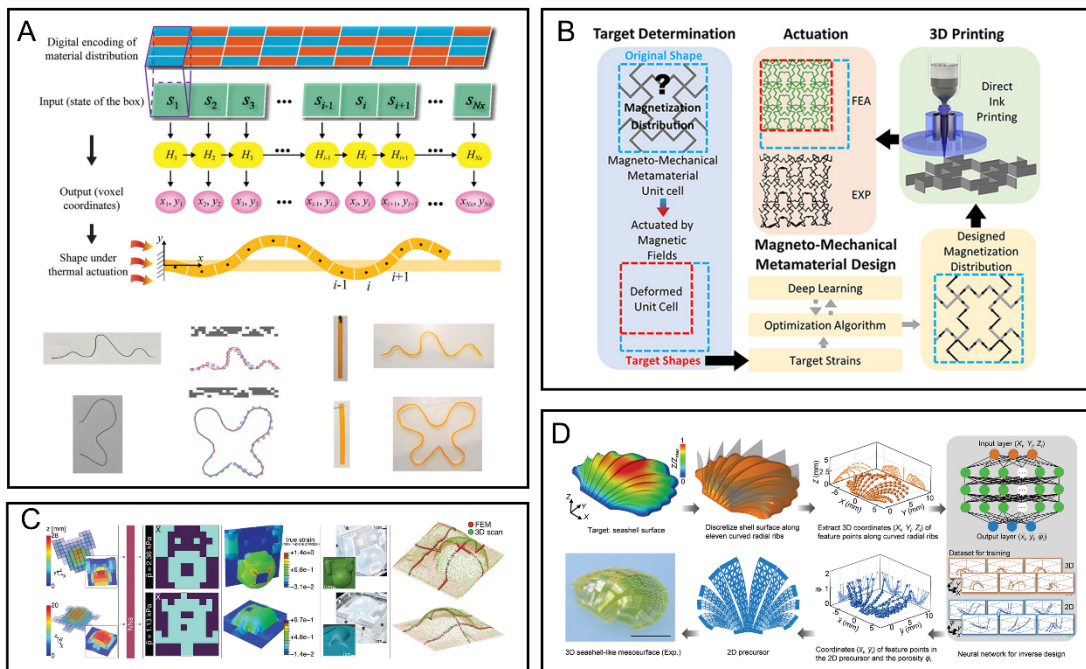

**Figure 3.** Applications of ML in various active material systems for designing active shape-change response. (A) Forward predictions using RNN-based ML and inverse design using

ML-EA for 4D-printed AC structures. (B) Forward predictions using ResNet and inverse design using ResNet-empowered DABC algorithm for 4D-printed magneto-mechanical metamaterials. Reprinted (adapted) with permission from [104]. Copyright 2022 American Chemical Society. (C) Inverse design of inflatable composite membranes using an inverse NN. (D) Inverse design of buckling mesosurfaces using an inverse NN.

#### ***2.4.2 Integrated forward ML and optimization algorithms***

One common approach is to use ML as forward predictive models, which is combined with optimization algorithms for the inverse design. In this case, it is crucial to select the appropriate network architecture based on the specific design problem (active material systems, target response, etc.). For AC beams, Zhang et al. [110] applied multiple ML models to the forward prediction problem and found the CNN performed best. Later on, Sun et al. [111] found the RNN is particularly suited for the beam problem as it inherently preserves a sequential data dependency similar to that arises from the beam deformation (**Figure 3A**). The RNN thus demonstrated remarkably high accuracy in the forward shape prediction based on material distributions, which then empowered EA to achieve highly efficient inverse designs of complicated, even hand-drawn, target shapes. For another AC system, magneto-mechanical metamaterials, Ma et al. [112] ingeniously encoded the magnetization distribution into a 2D array and utilized a deep residual network (ResNet) model to learn the relationship between magnetization distribution and active strain (**Figure 3B**). They further demonstrated the ResNet-empowered discrete artificial bee colony (DABC) algorithm can rapidly achieve inverse designs for various target active strains and Poisson's ratios. In addition, ML has also been used for designing shape changes of auxetic metamaterials with hierarchical pattern distributions [113] and for predicting the bending angle of soft pneumatic robots given geometric parameters [114].


### **2.4.3 Inverse ML approaches**

One alternative approach is to train an inverse ML model that maps from the target response to the optimized design. For example, for inflatable composite membranes, Forte et al. [115] successfully utilized an inverse NN to learn the mapping from 3D target inflated shapes to the optimized 2D pixel-level material distributions (**Figure 3C**). Similarly, for buckling mesosurfaces, Zhang and coworkers [116] trained an inverse NN to directly predict the optimized microlattice precursor configurations needed to realize complex target surfaces upon buckling (**Figure 3D**). More recently, they applied a similar strategy for the inverse design of buckling frame structures that can morph into complex target shapes [117]. Note that these inverse ML models were all trained to learn the inverse mapping directly from the data. Despite their successes, such models may struggle with complex inverse problems where multiple distinct designs can produce very similar responses (thus causing a one-to-many issue that can be harmful to the training), as exemplified in metamaterials design [96]. In this case, the use of forward ML to supervise an inverse ML model [91] can facilitate learning the inverse map, as discussed in Section 2.3.2. Espinosa and coworkers [118] utilized this approach to program the shape changes of kirigami metamaterials upon tension-induced buckling.

## **3. Perspective**

It is typically more tractable to learn the forward mapping from designs to responses given labeled data. However, the inverse problem is challenging as it is ill-posed due to the large, often infinite-dimensional, design space and the one-to-many mapping nature from responses to designs. Moreover, in many design tasks, instead of simply optimizing or extremizing a single property, the target response is desired to vary within a range, such as achieving the various target mechanical properties or attaining different target shape transformations under external/internal stimuli. This scenario makes the inverse design

more challenging, particularly when the target response involves high-dimensional data, such as the shape-change response based on the material distribution in 3D space and stimuli distribution over both time and space. ML holds significant promise in tackling these challenges. In the following, we briefly summarize existing and potential strategies for the effective application of ML in 3D/4D printing designs (**Figure 4**).

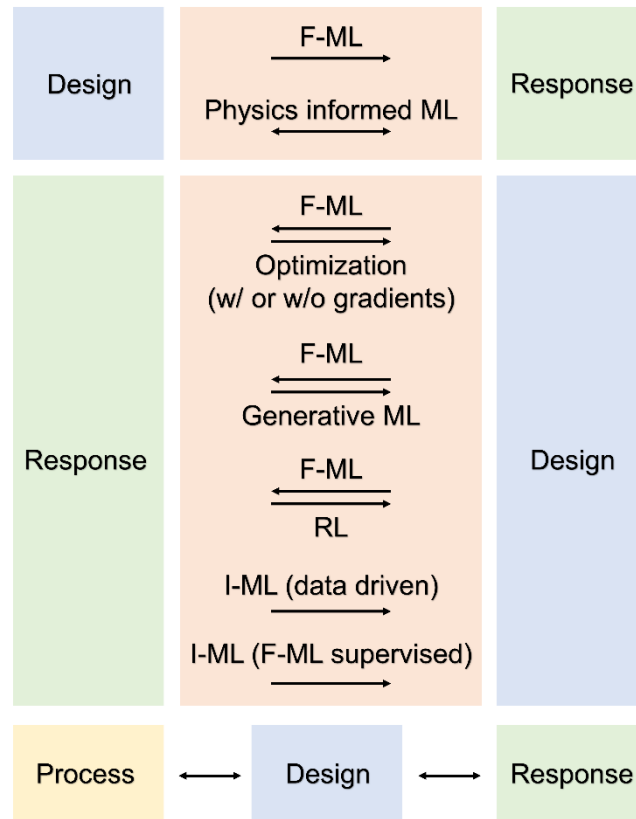

**Figure 4.** Overview of ML strategies for designs in 3D/4D printing.

In inverse design, accurate forward prediction is crucial and, depending on the specific problem, it may require varying amounts of data. As the design space is typically huge, using some data dimensionality reduction methods, such as PCA, DCT and AE, to pre-compress the data often facilitates the learning and improves the performance. Additionally, observing the specific problem to select an appropriate network architecture is important.

With an efficient forward ML (F-ML) model in place, several strategies exist for the optimization.

First, combine an F-ML with an optimization algorithm, either gradient-based or gradient-free. Compared to conventional computational methods, the high speed of ML allows for accelerated design with any optimization algorithms, as they all involve the forward prediction steps. Additionally, the automatic differentiability of F-ML allows for efficient computation of gradients (or sensitivities) and thus can significantly accelerate gradient-based optimizations.

Second, utilize generative models like VAE or GAN to generate new designs and employ an F-ML for screening. Specifically, VAE can be used to create a continuous, structured latent space, and in this case, the F-ML can learn the mapping from the latent variables to the property. Note that EA may also be seen as a form of generative modeling.

- Third, integrated F-ML and RL may be used for the inverse design. Previous studies have employed RL for the toughness maximization of 3D-printed composites [66] and the compliance minimization of structural topologies [119]. In these works, the FE was utilized for the reward evaluation during the RL training, which is computationally expensive. Integrating pretrained F-ML with RL could significantly improve the design efficiency, rendering RL more feasible for large-scale problems.

Furthermore, methods based on inverse ML (I-ML) can be used, which may or may not need F-ML depending on the specific training strategy for the I-ML. One strategy is to directly train the inverse model using labeled data, which can be effective at times [83, 115] but often fails for complex inverse problems [96, 120] due to the ill-definition (i.e., one-to-many mapping). An alternative strategy leverages the F-ML to train the I-ML (i.e., F-

ML supervised I-ML). In this case, the I-ML takes into the target property and yields a trial design, which is fed into the F-ML to predict the trial property. The training of the inverse ML model is done by minimizing the difference between the predicted and target properties. Moreover, the I-ML training may be supervised by other differentiable forward models such as ROMs, not necessarily F-ML. For all strategies above, once the training is complete, the I-ML can promptly generate the optimized designs.

To delve even further into the perspectives and, more specifically, to leverage the benefits of ML while ensuring a complete understanding, there is a strategic need to integrate materials/design informatics and ML for scientists [123-130]. This trend of merging symbolic AI and ML is commonly referred to as neuro-symbolic integration. It entails constructing a comprehensive knowledge/database enhanced with computational procedures to discover innovative materials and structures. Symbolic logic representations can then be used in ML to incorporate background knowledge in learning models and algorithms. This approach ensures transparency to humans, deductive reasoning, the integration of expert knowledge, and structured generalization, particularly in scenarios with limited data where physics is essential [131,132]. This symbolic AI layer proves valuable for working with small datasets and/or providing rationale in quantitative investigations involving extensive data generated from high-throughput computational materials design.

Beyond achieving material or structural designs with optimized responses, the reliable and accurate printing of intended designs is also crucial. This involves issues such as design optimizations considering manufacturability/printability, printing parameters refinement, quality monitoring and controls, and material design and discovery. Additionally, integrated design for the process-structure-property mapping may be important [121].

Using DLP as an example, the desired voxel-level material distributions may deviate significantly from the actual printing, especially for small-sized objects, due to factors such as light penetration, uneven light distribution and species reaction-diffusion [22, 122]. In this case, refining printing parameters (e.g., light field distribution) for appropriate compensations poses a multiphysics inverse problem, which may also be addressed using ML strategies outlined above.

In conclusion, this perspective paper highlights the rapidly growing role of ML in addressing the complex inverse design problems in 3D/4D printing. First, we provide an overview of common forward and inverse problems, relevant types of structures, and design space and responses in 3D/4D printing. Next, by reviewing recent works that employ a variety of ML approaches, we provide an in-depth discussion on how ML can be harnessed to design printed structures with specific mechanical responses, from structural properties to load-displacement responses, physical fields and active shape changes. Finally, after discussing the challenges, we highlight the existing ML approaches and discuss their potential extensions. Broader design problems in the field of 3D/4D printing are further discussed. Despite existing challenges, the integration of ML into 3D/4D printing design has immense potential to revolutionize the field. Our work aims to serve as a foundational guide, offering critical insights for researchers and practitioners looking to leverage ML for efficient and intelligent designs in additive manufacturing.

### **Acknowledgments**

H.J.Q. acknowledges the support of an AFOSR grant (FA9550-20-1-0306; Dr. B.-L. “Les” Lee, Program Manager) and a gift fund from HP, Inc.

## References

1. Kuang, X., et al., *Grayscale digital light processing 3D printing for highly functionally graded materials*. Science Advances, 2019. **5**(5): p. eaav5790.
2. Cheng, J., et al., *Centrifugal multimaterial 3D printing of multifunctional heterogeneous objects*. Nature Communications, 2022. **13**(1): p. 7931.
3. Yue, L., et al., *Single-vat single-cure grayscale digital light processing 3D printing of materials with large property difference and high stretchability*. Nature Communications, 2023. **14**(1): p. 1251.
4. Tibbits, S., *The emergence of "4D printing"*. TED Talks, 2013.
5. Ge, Q., H.J. Qi, and M.L. Dunn, *Active materials by four-dimension printing*. Applied Physics Letters, 2013. **103**(13): p. 131901.
6. Ge, Q., et al., *Multimaterial 4D Printing with Tailorable Shape Memory Polymers*. Scientific Reports, 2016. **6**(1): p. 31110.
7. Yue, L., et al., *Cold-programmed shape-morphing structures based on grayscale digital light processing 4D printing*. Nature Communications, 2023. **14**(1): p. 5519.
8. Kuang, X., et al., *Advances in 4D Printing: Materials and Applications*. Advanced Functional Materials, 2019. **29**(2): p. 1805290.
9. Leanza, S., et al., *Active Materials for Functional Origami*. Advanced Materials. **n/a**(n/a): p. 2302066.
10. Gibson, I., et al., *Design for Additive Manufacturing*, in *Additive Manufacturing Technologies*. 2021, Springer International Publishing: Cham. p. 555-607.
11. Yuan, C., T. Lu, and T.J. Wang, *Mechanics-based design strategies for 4D printing: A review*. Forces in Mechanics, 2022. **7**: p. 100081.
12. Wang, L.-C., et al., *A brief review on mechanical designs for 4D printing*. Soft Science, 2022. **01**(01): p. 2230001.
13. Demoly, F., et al., *The status, barriers, challenges, and future in design for 4D printing*. Materials & Design, 2021. **212**: p. 110193.
14. Ze, Q.J., et al., *Spinning-enabled wireless amphibious origami millirobot*. Nature Communications, 2022. **13**(1).
15. Leanza, S., et al., *Active Materials for Functional Origami*. Advanced Materials, 2023: p. 2302066.
16. Sim, J., et al., *Magneto - Mechanical Bilayer Metamaterial with Global Area - Preserving Density Tunability for Acoustic Wave Regulation*. Advanced Materials, 2023: p. 2303541.
17. Wu, S., et al., *Stretchable origami robotic arm with omnidirectional bending and twisting*. Proceedings of the National Academy of Sciences of the United States of America, 2021. **118**(36).
18. Wu, S., et al., *Ring Origami: Snap-Folding of Rings with Different Geometries*. Advanced Intelligent Systems, 2021. **3**(9): p. 2100107.



19. Sun, X., et al., *Phase diagram and mechanics of snap-folding of ring origami by twisting*. International Journal of Solids and Structures, 2022. **248**: p. 111685.
20. Roach, D.J., et al., *4D Printed Multifunctional Composites with Cooling-Rate Mediated Tunable Shape Morphing*. Advanced Functional Materials, 2022. **32**(36): p. 2203236.
21. Gu, G.X., et al., *Bioinspired hierarchical composite design using machine learning: simulation, additive manufacturing, and experiment*. Materials Horizons, 2018. **5**(5): p. 939-945.
22. Montgomery, S.M., et al., *Locally patterned anisotropy using grayscale vat photopolymerization*. Additive Manufacturing, 2023. **73**: p. 103687.
23. Sigmund, O. and K. Maute, *Topology optimization approaches*. Structural and Multidisciplinary Optimization, 2013. **48**(6): p. 1031-1055.
24. Liu, J., et al., *Current and future trends in topology optimization for additive manufacturing*. Structural and Multidisciplinary Optimization, 2018. **57**(6): p. 2457-2483.
25. Zhu, J., et al., *A review of topology optimization for additive manufacturing: Status and challenges*. Chinese Journal of Aeronautics, 2021. **34**(1): p. 91-110.
26. Wu, J., O. Sigmund, and J.P. Groen, *Topology optimization of multi-scale structures: a review*. Structural and Multidisciplinary Optimization, 2021. **63**(3): p. 1455-1480.
27. Sanders, E.D., A. Pereira, and G.H. Paulino, *Optimal and continuous multilattice embedding*. Science Advances, 2021. **7**(16): p. eabf4838.
28. Senhora, F.V., E.D. Sanders, and G.H. Paulino, *Optimally-Tailored Spinodal Architected Materials for Multiscale Design and Manufacturing*. Advanced Materials, 2022. **34**(26): p. 2109304.
29. Deng, J. and W. Chen, *Concurrent topology optimization of multiscale structures with multiple porous materials under random field loading uncertainty*. Structural and Multidisciplinary Optimization, 2017. **56**(1): p. 1-19.
30. Zhu, B., et al., *Two-Scale Topology Optimization with Microstructures*. ACM Trans. Graph., 2017. **36**(4): p. Article 120b.
31. Boddeti, N., et al., *Simultaneous Digital Design and Additive Manufacture of Structures and Materials*. Scientific Reports, 2018. **8**(1): p. 15560.
32. Boddeti, N., et al., *Optimal design and manufacture of variable stiffness laminated continuous fiber reinforced composites*. Scientific Reports, 2020. **10**(1): p. 16507.
33. Boddeti, N., et al., *Optimal Soft Composites for Under-Actuated Soft Robots*. Advanced Materials Technologies, 2021. **6**(8): p. 2100361.
34. Li, W., et al., *Digital synthesis of free-form multimaterial structures for realization of arbitrary programmed mechanical responses*. PNAS, 2022. **119**(10): p. e2120563119.
35. Maute, K., et al., *Level Set Topology Optimization of Printed Active Composites*.

- Journal of Mechanical Design, 2015. **137**(11).
36. Geiss, M.J., et al., *Combined Level-Set-XFEM-Density Topology Optimization of Four-Dimensional Printed Structures Undergoing Large Deformation*. Journal of Mechanical Design, 2019. **141**(5).
  37. Tanaka, M., et al., *Turing pattern-based design and fabrication of inflatable shape-morphing structures*. Science Advances, 2023. **9**(6): p. eade4381.
  38. Weeger, O., B. Narayanan, and M.L. Dunn, *Isogeometric shape optimization of nonlinear, curved 3D beams and beam structures*. Computer Methods in Applied Mechanics and Engineering, 2019. **345**: p. 26-51.
  39. Weeger, O., *Isogeometric sizing and shape optimization of 3D beams and lattice structures at large deformations*. Structural and Multidisciplinary Optimization, 2022. **65**(2): p. 43.
  40. Zhao, Z. and X.S. Zhang, *Topology optimization of hard-magnetic soft materials*. Journal of the Mechanics and Physics of Solids, 2022. **158**: p. 104628.
  41. Li, W., et al., *Programming and physical realization of extreme three-dimensional responses of metastructures under large deformations*. International Journal of Engineering Science, 2023. **191**: p. 103881.
  42. Yuhn, C., et al., *4D topology optimization: Integrated optimization of the structure and self-actuation of soft bodies for dynamic motions*. Computer Methods in Applied Mechanics and Engineering, 2023. **414**: p. 116187.
  43. LeCun, Y., Y. Bengio, and G. Hinton, *Deep learning*. Nature, 2015. **521**(7553): p. 436-444.
  44. Goodfellow, I., Y. Bengio, and A. Courville, *Deep learning*. 2016: MIT press.
  45. Guo, K., et al., *Artificial intelligence and machine learning in design of mechanical materials*. Materials Horizons, 2021. **8**(4): p. 1153-1172.
  46. Brodnik, N.R., et al., *Perspective: Machine learning in experimental solid mechanics*. Journal of the Mechanics and Physics of Solids, 2023. **173**: p. 105231.
  47. Jin, H., E. Zhang, and H.D. Espinosa, *Recent Advances and Applications of Machine Learning in Experimental Solid Mechanics: A Review*. Applied Mechanics Reviews, 2023. **75**(6).
  48. Jin, Z., et al., *Machine Learning for Advanced Additive Manufacturing*. Matter, 2020. **3**(5): p. 1541-1556.
  49. Meng, L., et al., *Machine Learning in Additive Manufacturing: A Review*. JOM, 2020. **72**(6): p. 2363-2377.
  50. Wang, C., et al., *Machine learning in additive manufacturing: State-of-the-art and perspectives*. Additive Manufacturing, 2020. **36**: p. 101538.
  51. Goh, G.D., S.L. Sing, and W.Y. Yeong, *A review on machine learning in 3D printing: applications, potential, and challenges*. Artificial Intelligence Review, 2021. **54**(1): p. 63-94.

52. Qin, J., et al., *Research and application of machine learning for additive manufacturing*. Additive Manufacturing, 2022. **52**: p. 102691.
53. Roach, D.J., et al., *Utilizing computer vision and artificial intelligence algorithms to predict and design the mechanical compression response of direct ink write 3D printed foam replacement structures*. Additive Manufacturing, 2021. **41**: p. 101950.
54. Killgore, J.P., et al., *A Data-Driven Approach to Complex Voxel Predictions in Grayscale Digital Light Processing Additive Manufacturing Using U-Nets and Generative Adversarial Networks*. Small, 2023. **n/a(n/a)**: p. 2301987.
55. Roach, D.J., et al., *Invertible neural networks for real-time control of extrusion additive manufacturing*. Additive Manufacturing, 2023. **74**: p. 103742.
56. Liu, Y., et al., *Materials discovery and design using machine learning*. Journal of Materiomics, 2017. **3(3)**: p. 159-177.
57. Chen, G., et al., *Machine-Learning-Assisted De Novo Design of Organic Molecules and Polymers: Opportunities and Challenges*. 2020. **12(1)**: p. 163.
58. Batra, R., L. Song, and R. Ramprasad, *Emerging materials intelligence ecosystems propelled by machine learning*. Nature Reviews Materials, 2021. **6(8)**: p. 655-678.
59. Yan, C. and G. Li, *The Rise of Machine Learning in Polymer Discovery*. 2023. **5(4)**: p. 2200243.
60. Cecen, A., et al., *Material structure-property linkages using three-dimensional convolutional neural networks*. Acta Materialia, 2018. **146**: p. 76-84.
61. Li, X., et al., *Predicting the effective mechanical property of heterogeneous materials by image based modeling and deep learning*. Computer Methods in Applied Mechanics and Engineering, 2019. **347**: p. 735-753.
62. Gu, G.X., C.-T. Chen, and M.J. Buehler, *De novo composite design based on machine learning algorithm*. Extreme Mechanics Letters, 2018. **18**: p. 19-28.
63. Yu, C.-H., Z. Qin, and M.J. Buehler, *Artificial intelligence design algorithm for nanocomposites optimized for shear crack resistance*. Nano Futures, 2019. **3(3)**: p. 035001.
64. Chen, C.-T. and G.X. Gu, *Generative Deep Neural Networks for Inverse Materials Design Using Backpropagation and Active Learning*. Advanced Science, 2020. **7(5)**: p. 1902607.
65. Sui, F., et al., *Deep Reinforcement Learning for Digital Materials Design*. ACS Materials Letters, 2021. **3(10)**: p. 1433-1439.
66. Yu, C.-H., et al., *Hierarchical Multiresolution Design of Bioinspired Structural Composites Using Progressive Reinforcement Learning*. Advanced Theory and Simulations, 2022. **5(11)**: p. 2200459.
67. Rawat, S. and M. Shen, *A novel topology design approach using an integrated deep learning network architecture*. arXiv preprint arXiv:1808.02334, 2018.
68. Yan, J., et al., *Deep learning driven real time topology optimisation based on initial*

- stress learning*. Advanced Engineering Informatics, 2022. **51**: p. 101472.
69. Woldseth, R.V., et al., *On the use of artificial neural networks in topology optimisation*. Structural and Multidisciplinary Optimization, 2022. **65**(10): p. 294.
  70. Nie, Z., H. Jiang, and L.B. Kara, *Stress Field Prediction in Cantilevered Structures Using Convolutional Neural Networks*. Journal of Computing and Information Science in Engineering, 2019. **20**(1).
  71. Yang, Z., C.-H. Yu, and M.J. Buehler, *Deep learning model to predict complex stress and strain fields in hierarchical composites*. Science Advances, 2021. **7**(15): p. eabd7416.
  72. Yang, Z., et al., *End-to-end deep learning method to predict complete strain and stress tensors for complex hierarchical composite microstructures*. Journal of the Mechanics and Physics of Solids, 2021. **154**: p. 104506.
  73. Raissi, M., P. Perdikaris, and G.E. Karniadakis, *Physics-informed neural networks: A deep learning framework for solving forward and inverse problems involving nonlinear partial differential equations*. Journal of Computational Physics, 2019. **378**: p. 686-707.
  74. Zhang, E., M. Yin, and G.E. Karniadakis, *Physics-informed neural networks for nonhomogeneous material identification in elasticity imaging*. arXiv preprint arXiv:2009.04525, 2020.
  75. Zhang, E., et al., *Analyses of internal structures and defects in materials using physics-informed neural networks*. Science Advances, 2022. **8**(7): p. eabk0644.
  76. Mowlavi, S. and K. Kamrin, *Topology optimization with physics-informed neural networks: application to noninvasive detection of hidden geometries*. arXiv preprint arXiv:2303.09280, 2023.
  77. Hamel, C.M., K.N. Long, and S.L.B. Kramer, *Calibrating constitutive models with full-field data via physics informed neural networks*. Strain, 2023. **59**(2): p. e12431.
  78. Chen, C.-T. and G.X. Gu, *Learning hidden elasticity with deep neural networks*. 2021. **118**(31): p. e2102721118.
  79. Kamali, A., M. Sarabian, and K. Laksari, *Elasticity imaging using physics-informed neural networks: Spatial discovery of elastic modulus and Poisson's ratio*. Acta Biomaterialia, 2023. **155**: p. 400-409.
  80. Chen, C.-T. and G.X. Gu, *Physics-Informed Deep-Learning For Elasticity: Forward, Inverse, and Mixed Problems*. 2023. **10**(18): p. 2300439.
  81. Liu, C. and H. Wu, *cv-PINN: Efficient learning of variational physics-informed neural network with domain decomposition*. Extreme Mechanics Letters, 2023. **63**: p. 102051.
  82. Grossmann, T.G., et al., *Can physics-informed neural networks beat the finite element method?* arXiv preprint arXiv:2302.04107, 2023.
  83. Liu, Y., Y. Chen, and B. Ding, *Deep learning in frequency domain for inverse*

- identification of nonhomogeneous material properties*. Journal of the Mechanics and Physics of Solids, 2022. **168**: p. 105043.
84. Mao, Y., Q. He, and X. Zhao, *Designing complex architected materials with generative adversarial networks*. Science Advances, 2020. **6**(17): p. eaaz4169.
  85. Challapalli, A., D. Patel, and G. Li, *Inverse machine learning framework for optimizing lightweight metamaterials*. Materials & Design, 2021. **208**: p. 109937.
  86. Challapalli, A. and G. Li, *Machine learning assisted design of new lattice core for sandwich structures with superior load carrying capacity*. Scientific Reports, 2021. **11**(1): p. 18552.
  87. Challapalli, A., J. Konlan, and G. Li, *Inverse machine learning discovered metamaterials with record high recovery stress*. International Journal of Mechanical Sciences, 2023. **244**: p. 108029.
  88. Wang, L., et al., *Deep generative modeling for mechanistic-based learning and design of metamaterial systems*. Computer Methods in Applied Mechanics and Engineering, 2020. **372**: p. 113377.
  89. Wang, L., et al., *Mechanical cloak via data-driven aperiodic metamaterial design*. Proceedings of the National Academy of Sciences, 2022. **119**(13): p. e2122185119.
  90. Wang, L., et al. *Data-Driven Multiscale Topology Optimization Using Multi-Response Latent Variable Gaussian Process*. in *ASME 2020 International Design Engineering Technical Conferences and Computers and Information in Engineering Conference*. 2020.
  91. Kumar, S., et al., *Inverse-designed spinodoid metamaterials*. npj Computational Materials, 2020. **6**(1): p. 73.
  92. Bastek, J.-H., et al., *Inverting the structure-property map of truss metamaterials by deep learning*. Proceedings of the National Academy of Sciences, 2022. **119**(1): p. e2111505119.
  93. Van 't Sant, S., et al., *Inverse-designed growth-based cellular metamaterials*. Mechanics of Materials, 2023. **182**: p. 104668.
  94. Zheng, L., S. Kumar, and D.M. Kochmann, *Data-driven topology optimization of spinodoid metamaterials with seamlessly tunable anisotropy*. Computer Methods in Applied Mechanics and Engineering, 2021. **383**: p. 113894.
  95. Wang, Y., et al., *Inverse design of shell-based mechanical metamaterial with customized loading curves based on machine learning and genetic algorithm*. Computer Methods in Applied Mechanics and Engineering, 2022. **401**: p. 115571.
  96. Deng, B., et al., *Inverse Design of Mechanical Metamaterials with Target Nonlinear Response via a Neural Accelerated Evolution Strategy*. Advanced Materials, 2022. **34**(41): p. 2206238.
  97. Bessa, M.A., P. Glowacki, and M. Houlder, *Bayesian Machine Learning in Metamaterial Design: Fragile Becomes Supercompressible*. 2019. **31**(48): p.

- 1904845.
98. Li, X., et al., *Designing phononic crystal with anticipated band gap through a deep learning based data-driven method*. Computer Methods in Applied Mechanics and Engineering, 2020. **361**: p. 112737.
  99. Wu, L., et al., *A machine learning-based method to design modular metamaterials*. Extreme Mechanics Letters, 2020. **36**: p. 100657.
  100. He, L., et al., *Inverse design of topological metaplates for flexural waves with machine learning*. Materials & Design, 2021. **199**: p. 109390.
  101. Wang, L., et al., *Data-driven multiscale design of cellular composites with multiclass microstructures for natural frequency maximization*. Composite Structures, 2022. **280**: p. 114949.
  102. Muhammad, J. Kennedy, and C.W. Lim, *Machine learning and deep learning in phononic crystals and metamaterials – A review*. Materials Today Communications, 2022. **33**: p. 104606.
  103. Hamel, C.M., et al., *Machine-learning based design of active composite structures for 4D printing*. Smart Materials and Structures, 2019. **28**(6): p. 065005.
  104. Wu, S., et al., *Evolutionary Algorithm-Guided Voxel-Encoding Printing of Functional Hard-Magnetic Soft Active Materials*. Advanced Intelligent Systems, 2020. **2**(8): p. 2000060.
  105. Athinarayanarao, D., et al., *Computational design for 4D printing of topology optimized multi-material active composites*. npj Computational Materials, 2023. **9**(1): p. 1.
  106. Sossou, G., et al., *Design for 4D printing: A voxel-based modeling and simulation of smart materials*. Materials & Design, 2019. **175**: p. 107798.
  107. Sossou, G., et al., *Design for 4D printing: Modeling and computation of smart materials distributions*. Materials & Design, 2019. **181**: p. 108074.
  108. Wang, L., et al., *Hard-magnetic elastica*. Journal of the Mechanics and Physics of Solids, 2020. **142**: p. 104045.
  109. Wang, L., et al., *Evolutionary design of magnetic soft continuum robots*. Proceedings of the National Academy of Sciences, 2021. **118**(21): p. e2021922118.
  110. Zhang, Z. and G.X. Gu, *Finite-Element-Based Deep-Learning Model for Deformation Behavior of Digital Materials*. Advanced Theory and Simulations, 2020. **3**(7): p. 2000031.
  111. Sun, X., et al., *Machine Learning-Evolutionary Algorithm Enabled Design for 4D-Printed Active Composite Structures*. Advanced Functional Materials, 2022. **n/a**(n/a): p. 2109805.
  112. Ma, C., et al., *Deep Learning-Accelerated Designs of Tunable Magneto-Mechanical Metamaterials*. ACS Applied Materials & Interfaces, 2022. **14**(29): p. 33892-33902.

113. Wilt, J.K., C. Yang, and G.X. Gu, *Accelerating Auxetic Metamaterial Design with Deep Learning*. *Advanced Engineering Materials*, 2020. **22**(5): p. 1901266.
114. Zolfagharian, A., et al., *4D printing soft robots guided by machine learning and finite element models*. *Sensors and Actuators A: Physical*, 2021. **328**: p. 112774.
115. Forte, A.E., et al., *Inverse Design of Inflatable Soft Membranes Through Machine Learning*. *Advanced Functional Materials*, 2022. **n/a**(n/a): p. 2111610.
116. Cheng, X., et al., *Programming 3D curved mesosurfaces using microlattice designs*. *Science*, 2023. **379**(6638): p. 1225-1232.
117. Jin, T., et al., *Deep learning aided inverse design of the buckling-guided assembly for 3D frame structures*. *Journal of the Mechanics and Physics of Solids*, 2023. **179**: p. 105398.
118. Alderete, N.A., N. Pathak, and H.D. Espinosa, *Machine learning assisted design of shape-programmable 3D kirigami metamaterials*. *npj Computational Materials*, 2022. **8**(1): p. 191.
119. Brown, N.K., et al., “*Deep reinforcement learning for engineering design through topology optimization of elementally discretized design domains*”. *Materials & Design*, 2022. **218**: p. 110672.
120. Kumar, S. and D.M. Kochmann, *What Machine Learning Can Do for Computational Solid Mechanics*, in *Current Trends and Open Problems in Computational Mechanics*, F. Aldakheel, et al., Editors. 2022, Springer International Publishing: Cham. p. 275-285.
121. Jiang, J., et al., *Machine learning integrated design for additive manufacturing*. *Journal of Intelligent Manufacturing*, 2022. **33**(4): p. 1073-1086.
122. Montgomery, S.M., et al., *Pixel-Level Grayscale Manipulation to Improve Accuracy in Digital Light Processing 3D Printing*. *Advanced Functional Materials*, 2023. **n/a**(n/a): p. 2213252.
123. Baird, S.G., et al., *DiSCoVeR: a materials discovery screening tool for high performance, unique chemical compositions*. *Digital Discovery*, 2022, **1**: p. 226-240.
124. Ward, L., et al., *Strategies for accelerating the adoption of materials informatics*. *MRS Bulletin*, 2018, **43**(9): p. 683-689.
125. Wang, A.Y.-T., et al., *Machine learning for materials scientists: An introductory guide toward best practices*. *Chem. Mater.*, 2020, **32**(12): p. 4954-4965.
126. Jain, A., et al., *New opportunities for materials informatics: Resources and data mining techniques for uncovering hidden relationships*. *Journal of Materials Research*, 2016, **31**(8): p. 977-994.
127. Vasudevan, R.K., *Materials science in the artificial intelligence age: high-throughput library generation, machine learning, and a pathway from correlations to the underpinning physics*. *MRS Communications*, 2019, **9**(3): p. 821-838.

128. Warren, J.A., *The Materials Genome Initiative and artificial intelligence*. MRS Bulletin, 2018, **43**(6), p. 452-456.
129. Agarwal, A., and Choudhary, A., *Deep materials informatics: Applications of deep learning in materials science*. MRS Communications, 2019, **9**(3): p. 779-792.
130. Oweida, T.J., et al., *Merging materials and data science: Opportunities, challenges, and education in materials informatics*. MRS Advances, 2020, **5**(7): p. 329-346.
131. Liu, S., et al., *Physics-informed machine learning for composition-process-property design: Shape memory alloy demonstration*. Applied Materials Today, 2021, **22**: p. 100898.
132. Zhang, Z., and Gu, G.X., *Physics-informed deep learning for digital materials*. Theoretical and Applied Mechanics Letters, 2021, **11**(1), p. 100220.