



**HAL**  
open science

# X-ray crystallographic analysis of the antiferromagnetic low-temperature phase of galvinoxyl: investigating magnetic duality in organic radicals

Rie Suizu, Yoshiaki Shuku, Vincent Robert, Pablo Roseiro, Nadia Ben Amor, Zain Khawar, Neil Robertson, Kunio Awaga

## ► To cite this version:

Rie Suizu, Yoshiaki Shuku, Vincent Robert, Pablo Roseiro, Nadia Ben Amor, et al.. X-ray crystallographic analysis of the antiferromagnetic low-temperature phase of galvinoxyl: investigating magnetic duality in organic radicals. Dalton Transactions, 2024, 53 (3), pp.1961-1965. 10.1039/D3DT03601d . hal-04426580

**HAL Id: hal-04426580**

**<https://hal.science/hal-04426580v1>**

Submitted on 17 Oct 2024

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# X-ray crystallographic analysis of the antiferromagnetic low-temperature phase of galvinoxyl: Investigating magnetic duality in organic radicals

Rie Suizu,<sup>1,2</sup> Yoshiaki Shuku,<sup>1</sup> Vincent Robert,<sup>3</sup> Pablo Roseiro,<sup>3</sup> Nadia Ben Amor,<sup>4</sup> Zain Khawar,<sup>5</sup> Neil Robertson,<sup>5</sup> and Kunio Awaga<sup>\*,1</sup>

1. Department of Chemistry & Integrated Research Consortium on Chemical Sciences (IRCCS), Nagoya University, Furo-cho, Chikusa-ku, Nagoya 464-8602, Japan.
2. Japan Science and Technology Agency (JST), PRESTO, 4-1-8 Honcho, Kawaguchi, Saitama 332-0012, Japan
3. Université de Strasbourg, CNRS, Laboratoire de Chimie Quantique UMR 7177, 67000 Strasbourg, France
4. Laboratoire de Physique et Chimie Quantiques, UMR 5626 Université Paul Sabatier, 118 route de Narbonne, 31062 Toulouse, France.
5. School of Chemistry, The University of Edinburgh, Joseph Black Building, David Brewster Road, Edinburgh EH9 3FJ, The United Kingdom.

Corresponding Author

\* awaga.kunio.h8@f.mail.nagoya-u.ac.jp

**KEYWORDS.** *Crystal structure, Low temperature analysis. Organic stable radical, Phase transition, Magnetic interaction.*

---


**ABSTRACT:** Galvinoxyl, as one of the most extensively studied organic stable free radicals, exhibits a notable phase transition from a ferromagnetic (FM) high-temperature (HT) phase to an antiferromagnetic (AFM) low-temperature (LT) phase at 85 K. Despite significant research efforts, the crystal structure of the AFM LT phase has remained elusive. This study successfully elucidates the crystal structure of the LT phase, which belongs to the  $P\bar{1}$  space group. The crystal structure of the LT phase is found to consist of a distorted dimer, wherein the distortion arises from the formation of short intermolecular distances between anti-node carbons in the singly-occupied molecular orbital (SOMO). Starting from the structure of the LT phase, wave function calculations show that the AFM coupling  $2J/k_B$  varies significantly from  $-1069$  K to  $-54$  K due to a parallel shift of the molecular planes within the dimer.

---

Stable organic radicals have garnered significant attention in a range of research fields, encompassing biology, chemistry, and physics, due to their exceptional reactivity and physical properties arising from their open-shell electronic structures. Among the diverse array of organic radicals,<sup>1</sup> galvinoxyl (4-[[3,5-Bis(1,1-dimethylethyl)-4-oxo-2,5-cyclohexadien-1-ylidene]methyl]-2,6-bis(1,1-dimethylethyl)phenoxy, see Scheme 1), a phenoxyl radical synthesized in 1957,<sup>2,3</sup> stands out as an extraordinarily unique case. While most stable radicals, such as nitroxyl radicals, possess a localized unpaired electron on a specific functional group, galvinoxyl exhibits a captivating characteristic: the unpaired electron is extensively delocalized along an odd alternating  $\pi$  conjugation, and the nodes of the singly-occupied molecular orbital (SOMO) alternately appear on the molecular skeleton (Scheme 1). Galvinoxyl has

a rich research history, initially serving as an excellent sample for magnetic resonance research in solution. Electron paramagnetic resonance (EPR) spectroscopy revealed a substantial spin polarization on the molecular skeleton of galvinoxyl,<sup>4,5</sup> and the first successful electron nuclear double resonance (ENDOR) measurements were conducted on this molecule.<sup>4</sup> Subsequently, galvinoxyl has found utility in various applications, including as a target molecule for radical scavengers in food chemistry,<sup>7,8</sup> an additive material in organic solar cells,<sup>9,10</sup> and a redox-active material in rechargeable batteries.<sup>11</sup> Notably, galvinoxyl's most remarkable features lie in its magnetic intermolecular interactions and pronounced phase transition. At room temperature, galvinoxyl exhibits ferromagnetic (FM) intermolecular interaction,<sup>12-14</sup> distinguishing it from the majority of organic radicals that display antiferromagnetic (AFM) interactions

in their solids. Additionally, galvinoxyl undergoes a first-order structural phase transition below 85 K,<sup>12-14</sup> resulting in a change of the intermolecular magnetic coupling to AFM. Although switchable FM/AFM coupling has been observed in intermolecular systems,<sup>15,16</sup> it is quite unique of galvinoxyl that FM and AFM intermolecular couplings switch across the phase transition. The crystal structure of the high-temperature (HT) phase was determined in 1969.<sup>17</sup> However, the crystal structure of the low-temperature (LT) phase still eludes resolution. Pioneering efforts in single-crystal X-ray analysis faltered due to crystal disintegration during the phase transition.<sup>18</sup> In contrast, EPR measurements indicated the formation of an AFM dimer ( $S=0$ ) in conjunction with a thermally accessible  $S=1$  state in the LT phase.<sup>19</sup> Given its historical significance, it is crucial to uncover the hidden aspects of galvinoxyl's dual nature, particularly its molecular and crystal structures in the LT phase. Understanding these aspects is essential for comprehending the distinct properties and reactivity exhibited by galvinoxyl.

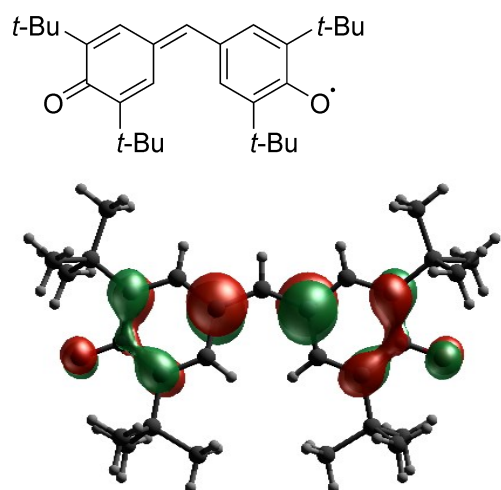

Scheme 1. Molecular structure of galvinoxyl and its SOMO calculated from a doublet CASSCF calculation.

In the present investigation, our aim was to determine the crystal structure of the LT phase of galvinoxyl. Through the diligent resolution of various technical challenges, we ultimately achieved success in the structural analysis. The results obtained settled a long-standing unresolved issue of more than 30 years, unveiling a radical dimer structure that is formed by intermolecular, interatomic contacts among the anti-node carbons.

## Results and discussion

### Crystal structure of HT phase

The galvinoxyl radical was prepared employing the procedure described in the literature,<sup>2,3</sup> and its needle-shaped crystals were obtained via recrystallization from solutions in 4:1 methanol/diethyl ether mixed solvent at  $-20$  °C. Figure S1 illustrates the temperature dependence of the paramagnetic susceptibility  $\chi_p$ , which is in agreement with previously reported data.<sup>12-14</sup> Specifically, in the HT phase,  $\chi_p$

conforms to the Curie-Weiss law with a Curie constant of  $0.374 \text{ emu K mol}^{-1}$  and a Weiss constant of 12.2 K. In contrast, in the LT phase,  $\chi_p$  is substantially diminished.

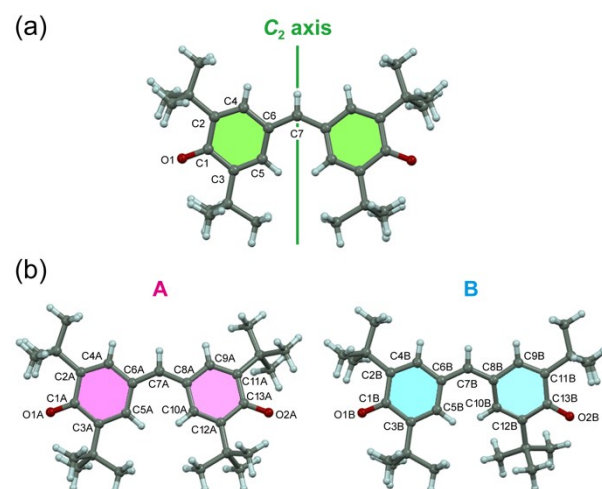


Figure 1. Comparison between the molecular structures of galvinoxyl in the HT (a) and LT (b) phases. While half of the molecule is crystallographically independent in the HT phase, two molecules are crystallographically independent in the LT phase.

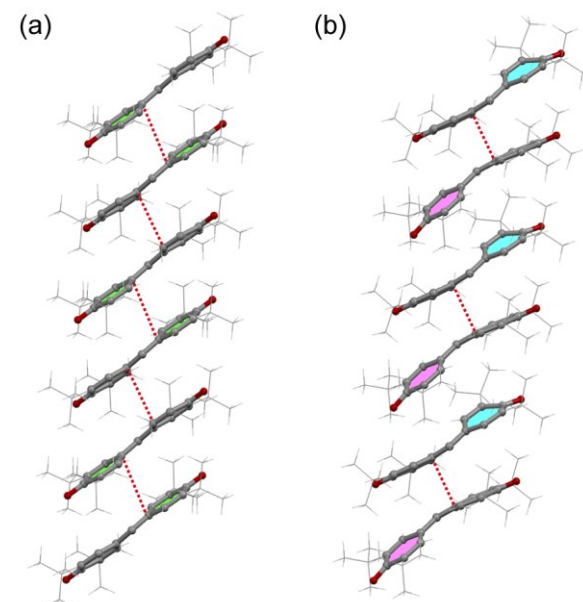


Figure 2. 1D stacking of galvinoxyl in the HT (a) and LT (b) phases.

We conducted a reexamination of the crystal structure in the HT phase at 123 K for the purpose of comparison with the LT phase. The results were consistent with the reported ones.<sup>17,18</sup> The lattice parameters for the HT phase are listed in Table S1. This phase belongs to the monoclinic  $I2/a$  space group. Figure 1a depicts the molecular structure in this phase, where a  $C_2$  axis is present, making half of this unit crystallographically independent. The selected bond distances are listed in Table S2. The  $\pi$  molecular plane displays notable planarity, while the phenoxyl ring manifests bond

alternation akin to that observed in benzoquinone. Notably, within the three methyl groups of the *t*-butyl moiety, two form intramolecular hydrogen bonds with the oxygen atom, while the C-C bond in the remaining methyl group lies coplanar with the phenoxy ring. This characteristic is also evident in the molecular structures of mono-, di-, and tri-substituted *t*-butylbenzenes (refer to Fig. S3), suggesting a probable steric effect arising from the hydrogen atoms in the methyl group and the hydrogen atoms on the phenoxy ring. In Fig. 2a, the presence of a one-dimensional (1D)  $\pi$ -stacking chain in the HT phase is apparent, featuring intermolecular and interatomic distance of 0.3903 nm for C6 and C6 (red dotted line). Fig. 3a depicts the intermolecular arrangement within the 1D chain of the HT phase. The discussion regarding the magneto-structural correlation will be presented subsequently.

Space-filling views of the intermolecular arrangement in the HT phase are provided in Figure 4. It is likely that the intermolecular arrangement in the HT phase is determined to avoid steric hindrance between the bulky *t*-butyl groups. This suggests that the intermolecular arrangement in the HT phase is not caused by the FM interaction in this phase, but rather is obtained accidentally due to the steric hindrance between the *t*-butyl groups. This is supported by the fact that galvinoxyl can form isostructural mixed crystals with its corresponding closed-shell compound, hydrogalvinoxyl.<sup>18</sup>

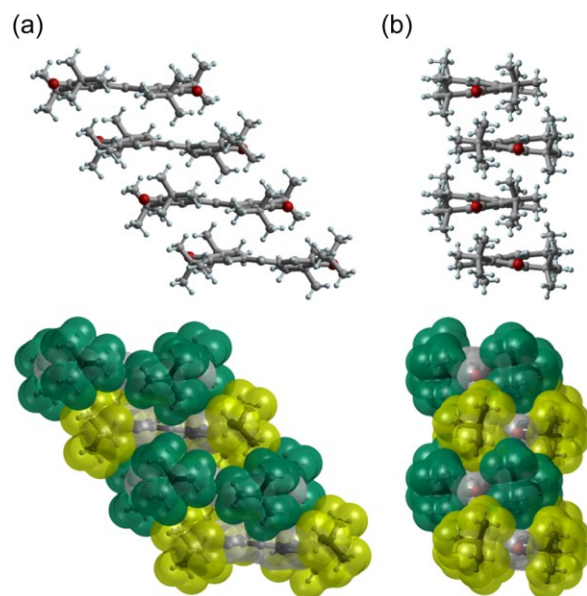


Figure 4. Space-filling views for the intermolecular arrangements in the HT phase.

### Crystal structure of LT phase

We conducted X-ray crystallographic analysis of the LT phase of galvinoxyl at 50 K using an X-ray diffractometer equipped with a He-gas open-flow cryostat. Initially, we opted for large single crystals for the experiments. How-

ever, during the cooling and/or at the phase transition, microcrystals detached from the parent crystal and remained on the crystal surface, compromising the diffraction data. To address this issue, we selected flake-shaped crystals, which resulted in the detachment of split microcrystals from the parent crystal. Consequently, we obtained diffraction data exclusively from the parent crystal. Twinning of the crystals due to the phase transition also posed a challenge. Nonetheless, we successfully tackled this obstacle by employing structural analysis that considered twinning. Through these approaches, we achieved the resolution and refinement of the crystal structure of the LT phase.

The crystal parameters for the LT phase are presented in Table S1. This phase belongs to the triclinic  $P\bar{1}$  space group, featuring two crystallographically independent molecules. The structures of these molecules, designated as A and B, are illustrated in Fig. 1b. Table S2 provides the selected bond distances. In comparison to the molecular structure observed in the HT phase, the  $\pi$  skeletons of molecules A and B in the LT phase exhibit more pronounced bending. However, there are no significant differences in the corresponding bond distances among the molecules A and B in the LT phase compared to those in the HT phase. It is worth noting, however, that one *t*-butyl group in molecule B deviates from the coplanar rule. Figure 2b depicts the distinct alternation observed in the stacking chain of the LT phase.

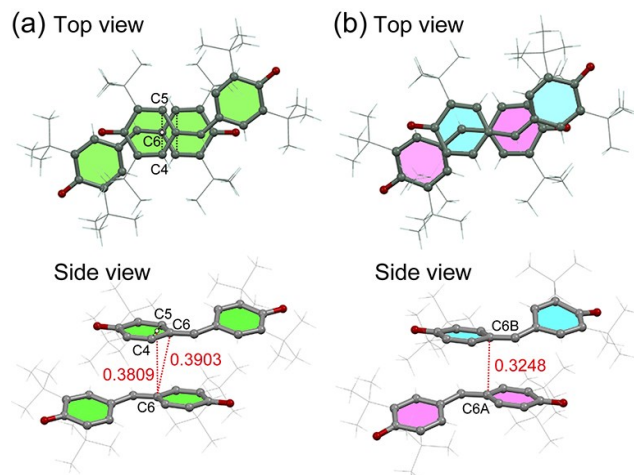


Figure 3. Nearest neighbor intermolecular arrangements in the HT (a) and LT (b) phases.

Figure 3 illustrates a comparison of the nearest neighbor intermolecular arrangements observed in the HT and LT phases. In the HT one, the intermolecular distance between C6 and the midpoint between C4 and C5 (3.809 Å) of the neighboring molecule is shorter than that between C6 position (3.903 Å) (see Fig. 3a). Since galvinoxyl is an odd-alternant  $\pi$  conjugated compound, the SOMO manifests nodes at C1, C4, and C5. Therefore, the short distance between C6 and C4 or C5 indicates an overlap between the node and anti-node carbons (Type-A in Fig. S6).<sup>20</sup> This and absence of short distance between anti-node carbon atoms suggests a nearly orthogonal relationship between the SOMOs and a FM coupling, resulting from the potential exchange interac-



tion. In contrast, the nearest-neighbor intermolecular arrangement in the LT phase reveals a short interatomic distance of 3.248 Å between C6A and C6B (Fig. 3b), implying close contact between anti-node carbons, which is expected to induce an AFM coupling (Fig. S6).

### Magneto-structural correlation

While the existence of FM coupling was confirmed by *ab initio* calculations,<sup>21</sup> we performed CAS[2,2]SCF+DDCI3 wavefunction calculations to estimate the energy differences between the  $S=0$  and  $S=1$  states  $\Delta_{ST}$ , utilizing simplified nearest-neighbor dimer geometries in the two phases (see SI). This value is correlated to the exchange coupling constant  $J$ , as  $\Delta_{ST} = 2J$ . For the HT phase, the calculation concluded an  $S=1$  ground state with  $2J/k_B = 36$  K. This value is in reasonably good agreement with the positive Weiss constant, and is slightly larger than the value obtained by the EPR measurement ( $17 \pm 8$  K).<sup>19</sup> On the other hand, the calculations for the LT structure concluded on an  $S=0$  ground state with  $2J/k_B = -1069$  K, which is nearly the double of the EPR data ( $-580$  K).<sup>19</sup> To comprehend this disparity, we computed  $\Delta_{ST}$  for hypothetical dimer structures, wherein one molecule of the dimer in the LT phase was incrementally shifted in parallel (see the inset in Table S4). The outcomes are presented in Table S4, where the structure at  $\delta = 0$  Å represents the LT phase. Notably, a minor shift of  $\Delta\delta \approx 0.06$  Å leads to a substantial  $2J/k_B$  alteration by a factor of twenty. Taking into account this sensitivity to the structure, experimental errors, and temperature effects,<sup>21,22</sup> the current calculations provide a reasonable approximation of the experimental results. Figure 5 illustrates the isoelectronic density surfaces of the highest occupied molecular orbital (HOMO), representing the bonding orbital between the SOMOs.

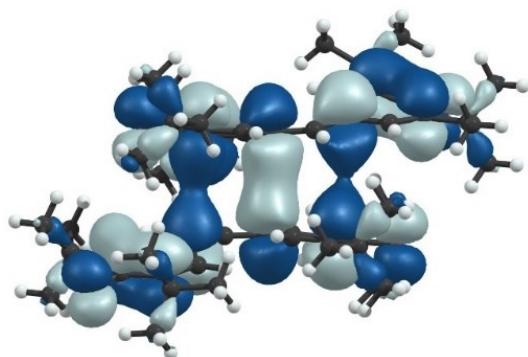


Figure 5. HOMO of the galvinoxyl dimer in the LT phase.

### Conclusions

In conclusion, we have successfully resolved a long-standing problem related to the extensively studied galvinoxyl radical, which had remained unsolved. While it is known that this molecule exhibits FM and AFM interactions in the HT and LT phases, respectively, we were able to elucidate the crystal structure of the AFM LT phase. In contrast to the high symmetry of the HT phase, which belongs to the  $I2/a$  space group, the symmetry of the LT phase dropped to the  $P\bar{1}$  space group. Moreover, the FM 1D chains in the HT phase underwent noticeable dimerization in the LT phase,

leading to a distorted geometry in the LT phase dimer. This distortion was attributed to the formation of short distances between the anti-node carbons in the SOMO. The wavefunction calculations for the LT phase dimer indicated a strong and structural-sensitive AFM coupling  $2J/k_B$  that varies by more than one order of magnitude by a parallel shift of  $\Delta\delta \approx 0.06$  Å. These findings shed light on the unique properties and interactions of the galvinoxyl radical in different phases, providing valuable insights for further research in this field.

### Author Contributions

R. S. carried out single crystal structure analysis. Y. S. and Z. K. performed the synthesis and magnetic measurements. V. R., P. R., and N. B. A. carried out theoretical model calculations. All authors contributed to writing and reviewing the manuscript. N. R. and K. A. directed the project.

### Conflicts of interest

There are no conflicts to declare.

### Acknowledgments

A part of this work was conducted in Institute for Molecular Science, supported by “Advanced Research Infrastructure for Materials and Nanotechnology in Japan (ARIM)” of the Ministry of Education, Culture, Sports, Science and Technology (MEXT). Proposal Number JPMXP1222MS1089. The authors acknowledge Japan Society for the Promotion of Science (JSPS) KAKENHI Grants 19K15520 (to Y.S.), 20H02707 (to R.S.) and 20H05621 (K.A.), and Japan Science and Technology Agency (JST) PRESTO Grant JPMJPR21A9 (to R.S.) for funding this work.

### REFERENCES

- (1) Chen, Z.X.; Li, Y.; Huang, Persistent and stable organic radicals: design, synthesis, and applications, *F. Chem* **2021**, *7*, 288–332.
- (2) Coppinger, G.M. A stable phenoxy radical inert to oxygen, *J. Am. Chem. Soc.*, **1957**, *79*(2), 501-502.
- (3) Kharasch M. S.; Joshi B. S. Reactions of hindered phenols. I. Reactions of 4,4'-dihydroxy-3,5,3',5'-tetra-tert-butyl diphenylmethane, *J. Org. Chem.*, **1957**, *22*(11), 1435-1438.
- (4) Besev, C.; Lund, A.; Vännegård, T.; Håkansson, R. Proton and carbon-13 splittings in the ESR spectra of two phenoxy radicals. *Acta Chem. Scand.*, **1963**, *17*(8), 2281-2284. DOI number: 10.3891/acta.chem.scand.17-228.
- (5) Luckhurst, G.R. The structure of Coppinger's radical and its orientation within a cluster of a liquid crystal, *Mol. Phys.*, **1966**, *11*, 205-211. <https://doi.org/10.1080/00268976600101041>.
- (6) Hyde J.S.; Maki A.H. ENDOR of a free radical in solution. *J. Chem. Phys.*, **1964**, *40*, 3117–3118. doi: <https://doi.org/10.1063/1.1724957>.
- (7) Esatbeyoglu, T.; Wagner, A.E.; Motafakkerzad, R.; Nakajima, Y.; Matsugo, S.; Rimbach, G. Free radical scavenging and antioxidant activity of betanin: Electron spin resonance spectroscopy studies and studies in cultured cells, *Food Chem. Toxicol.*, **2014**, *73*, 119-126. DOI10.1016/j.fct.2014.08.007.

- (8) Dose, J.; Matsugo, S.; Yokokawa, H.; Koshida, Y.; Okazaki, S.; Seidel, U.; Eggersdorfer, M.; Rimbach, G.; Esatbeyoglu, T. Free radical scavenging and cellular antioxidant properties of astaxanthin, *Inter. J. Mol. Sci.*, **2016**, 17(1), 103. DOI10.3390/ijms17010103.
- (9) Zhang, Y.; Basel, T.P.; Gautam, B.R.; Yang, X.M.; Mascaro, D.J.; Liu, F.; Vardeny, Z.V. Spin-enhanced organic bulk heterojunction photovoltaic solar cells, *Nature Commun.*, **2012**, 3, 1043. DOI10.1038/ncomms2057.
- (10) Basel, T.; Huynh, U.; Zheng, T.Y.; Xu, T.; Yu, L.P.; Vardeny, Z.V. Optical, electrical, and magnetic studies of organic solar cells based on low bandgap copolymer with spin 1/2 radical additives, *Adv. Funct. Mater.*, **2015**, 25(12), 1895-1902. DOI10.1002/adfm.201403191
- (11) Suga, T.; Ohshiro, H.; Sugita, S.; Oyaizu, K.; Nishide, H. Emerging n-type redox-active radical polymer for a totally organic polymer-based rechargeable battery, *Adv. Mater.*, **2009**, 21(16), 1627. DOI10.1002/adma.200803073.
- (12) Awaga, K.; Sugano, T.; Kinoshita, M. Ferromagnetic intermolecular interactions in a series of organic mixed crystals of galvinoxyl radical and its precursory closed shell compound, *J. Chem. Phys.* **1986**, 85(4), 2211-2218. DOI10.1063/1.451115.
- (13) Mukai, K.; Nishiguchi, H.; Deguchi, Y. Anomaly in the  $\chi$ -T curve of galvinoxyl radical, *J. Phys. Soc. Japan*, **1967**, 23, 125. <https://doi.org/10.1143/JPSJ.23.125>.
- (14) Mukai, K. Anomalous magnetic properties of stable crystalline phenoxyl radicals, *Bull. Chem. Soc. Japan*, **1969**, 42(1), 40-46. <https://doi.org/10.1246/bcsj.42.40>.
- (15) Izuoka, A.; Murata, S.; Sugawara, T.; Iwamura, H. Molecular design and model experiments of ferromagnetic intermolecular interaction in the assembly of high-spin organic molecules – generation and characterization of the spin states of isomeric bis(phenylmethylene)[2.2]paracyclophanes, *J. Am. Chem. Soc.*, **1987**, 109(9), 2631-2639. DOI10.1021/ja00243a014.
- (16) Rajca, A.; Lu, K.; Rajca, S.; Ross II, C.R. II, Singlet-triplet bistability in a 1,3-phenylene-based bis(aminoxyl) diradical, *Chem. Commun.*, **1999**, 1249-1250. DOI10.1039/a901906e.
- (17) Williams, D.E. Structure of galvinoxyl, a stable phenoxyl radical, *Mol. Phys.*, **1969**, 16(2), 145-151. DOI10.1080/00268976.1969.10310426.
- (18) Chi, K.M.; Calabrese, J.C.; Miller, J.S.; Khan S.I., Single crystal X-ray structure of [galvinoxyl]<sub>x</sub>[hydrogalvinoxyl]<sub>1-x</sub> (x=0.85±0.02) at 20 and 203 K, *Mol. Cryst. Liq. Cryst.*, **1989**, 176, 185-198. <https://doi.org/10.1080/00268948908037479>
- (19) Awaga, K.; Sugano, T.; Kinoshita, M. Electron-spin resonance evidence for the ferromagnetic and antiferromagnetic intermolecular interaction in pure and diluted mixed crystals of galvinoxyl. *Chem. Phys. Lett.*, **1986**, 128(5-6), 587-590. DOI10.1016/0009-2614(86)80679-0.
- (20) Awaga, K.; Sugano, T.; Kinoshita, M. Ferromagnetic intermolecular interaction in the galvinoxyl radical – cooperation of spin polarization and charge-transfer interaction, *Chem. Phys. Lett.*, **1987**, 141(6), 540-544. DOI10.1016/0009-2614(87)85077-7.
- (21) Luo, S.J.; Yao, K.L. Ab initio studies of ferromagnetic properties of galvinoxyl, *J. Mag. Mag. Mater.*, **2003**, 257(1), 11-14. DOI10.1016/S0304-8853(02)00980-0.
- (22) Leitch, A.A.; Yu, X.; Winter, S.M.; Secco, R.A.; Dube P.A.; Oakley, R.T. Structure and Property Correlations in Heavy Atom Radical Conductors, *J. Am. Chem. Soc.* **2009**, 131(20), 7112-7125. <https://doi.org/10.1021/ja900853t>.