



HAL
open science

Rheo-SAXS study of a shear-thinning hydrogel containing clay nanoplatelets

Claire Hotton, Guylaine Ducouret, Juliette Sirieix-Plénet, Thomas Bizien, Clément Guibert, Pierre Levitz, Laurent Michot, Natalie Malikova

► **To cite this version:**

Claire Hotton, Guylaine Ducouret, Juliette Sirieix-Plénet, Thomas Bizien, Clément Guibert, et al.. Rheo-SAXS study of a shear-thinning hydrogel containing clay nanoplatelets. 2024. hal-04440893

HAL Id: hal-04440893

<https://hal.science/hal-04440893>

Preprint submitted on 6 Feb 2024

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution - NonCommercial - NoDerivatives 4.0 International License

Rheo-SAXS study of a shear-thinning hydrogel containing clay nanoplatelets

Claire Hotton^a, Guylaine Ducouret^b, Juliette Sirieix-Plénet^a, Thomas Bizien^c, Clément Guibert^d, Pierre Levitz^a,
Laurent Michot^a, Natalie Malikova^{a,*}

^aLaboratory of Physical Chemistry of Electrolytes and Interfacial Nanosystems (PHENIX), Sorbonne Université, CNRS, 75005 Paris, France

^bLaboratory of Soft Matter Sciences and Engineering (SIMM), ESPCI Paris, PSL Research University, Sorbonne University, CNRS, F-75005 Paris, France

^cSynchrotron SOLEIL, l'Orme des Merisiers, Saint-Aubin - BP 48, 91192 Gif-sur-Yvette CEDEX, France

^dSurface Reactivity Laboratory (LRS), Sorbonne Université, CNRS, 75005 Paris, France

Abstract

Shear-induced orientation of clay nanoplatelets within a physically cross-linked hydrogel based on ionenes, positively charged polyelectrolytes, is studied here. Small angle X-ray scattering measurements (SAXS) are performed under shear within a Couette cell cylinder (rheo-SAXS). As the SAXS signal is dominated by that of the clay component, we follow the evolution of the orientational distribution of the clay nanoplatelets within the hydrogel as a function of shear. We investigate the effect of the clay volume fraction, polyelectrolyte concentration, clay charge location and clay charge density by screening three different types of clay: Wyoming and Arizona montmorillonites and Idaho beidellite. The orientational field of clay nanoplatelets in the gel is shown to strongly depend on the clay charge location and shear rate, whereas it is independent of the clay volume fraction. Approaching the critical gelation concentration of the polyelectrolyte system, these features change drastically.

Keywords: Clay nanoplatelets, Hydrogel, Particle orientation, Polyelectrolyte, Rheo-SAXS

1. Introduction

Clay-containing hydrogels are promising materials as the interaction between polymer and clay leads to enhanced mechanical [1, 2], thermal [3], swelling [4] or barrier properties [5]. This allows them to have numerous applications especially in the biomedical fields where they can be used as scaffolds for tissue regeneration, implants or biosensors [6]. Moreover, the shear-thinning behaviour of clay-based hydrogel as well as the possibility of tuning the orientation of clay nanoplatelets to modify the permeation properties of the hydrogel, allows them to act as an efficient injectable drug-delivery system [7]. For this purpose, it is relevant to establish the parameters that may influence the clay orientation inside the hydrogel. In this study, we investigate the orientation of clay platelets under shear in a physically cross-linked hydrogel. This hydrogel is formed from cationic polyelectrolytes based on ionenes, a class of polyelectrolytes containing quaternary ammonium parts in the main chain [8, 9, 10]. Additionally, the presence in the main chain of aromatic rings and amide moieties allows gelation through a combination of electrostatic repulsions, π - π stacking, hydrogen bonding and anion- π and cation- π interactions that can be tune according to the nature and

the valence of the counterions [11]. In a previous study, we investigated the organisation of clay nanoplatelets in this ionene-based hydrogel [10]. We have brought to light that clay nanoplatelets present a local lamellar order within the gel. First, this ordering is mediated by the polyelectrolyte network and is independent of the clay volume fraction. Then, the degree of ordering of the system, as well as the mechanical properties of the hydrogel, is sensitive to the exact negative clay charge location and clay charge density. In this study, we aim to probe the shear-induced orientation as a function of the clay type, clay volume fraction and polyelectrolyte concentration. Using different types of clay enable to study the effect of different clay charge densities and clay charge locations. We also would like to see if the orientational field of clay platelets can be linked to the shear-thinning behaviour of hydrogel. The shear-induced orientation of clay nanoplatelets in the hydrogel is studied by small angle X-ray scattering (SAXS) measurements within a Couette cell cylinder (rheo-SAXS).

2. Experimental section

2.1. 6-Cl modified ionene and precursor synthesis

The cationic polyelectrolyte used in this study is an ionene referred to 6-Cl modified ionene (6-Cl) ((Supplementary Material S1). The 6-Cl and its precursor were synthesized via a two-step reaction according to a protocol already described in a previous article [10]. All chemi-

*Corresponding author

Email address: natalie.malikova@sorbonne-universite.fr
(Natalie Malikova)

cal reagents were purchased from Sigma-Aldrich and used without further purification. All solvents were purchased from Sigma-Aldrich and VWR.

2.1.1. First step: synthesis of 1,4-bis-[4-(chloromethyl)benzamido]benzene

All vials used were dried in an oven at 80°C the day before. *p*-phenylenediamine (1.08 g, 10 mmol, 1 eq) was dissolved in freshly distilled dichloromethane (100 mL) into a 250 mL round-bottom flask with a magnetic stirrer and placed under an inert argon atmosphere. The solution in the round-bottom flask was then cooled to 0°C by using an ice-water bath and triethylamine (3.5 mL, 25 mmol, 2.5 eq) was added. A solution of 4-(chloromethyl)benzoyl chloride (3.78 g, 20 mmol, 2 eq) dissolved in distilled dichloromethane (70 mL) was added dropwise with an isobar dropping funnel. After the addition, the ice-water bath was removed, and the system was warmed up to room temperature. The system was stirred for 24h to ensure complete conversion. The obtained white precipitate was vacuum filtrated and then washed with distilled water (2 x 80 mL). The product was dried under vacuum at 90°C. The product was obtained in high yield (85%). Structural analysis was carried out by ¹H-NMR in DMSO-d₆.

2.1.2. Second step: synthesis of 6-Cl modified ionene

1,4-bis-[4-(chloromethyl)benzamido]benzene (2.06 g, 5 mmol) was dissolved in dimethylformamide (200 mL) at 80°C in a 500 mL round-bottom flask with a magnetic stirrer. Then, N,N,N',N'-tetramethyl-1,6-hexanediamine (1.07 mL, 5 mmol) was added. The system was stirred at 80°C for 48h. The obtained yellow precipitate was vacuum filtrated and washed subsequently with dimethylformamide (100 mL), acetonitrile (100 mL) and dichloromethane (100 mL). The product was dried under vacuum at 50°C. The 6-Cl modified ionene was obtained in good yield (75%). Structural analysis was carried out by ¹H-NMR in D₂O. The average molecular weight of the 6-Cl modified ionene was previously determined as 7.84 10⁴ Da [9].

2.2. Clay fraction, purification and cations exchange

Three different clay minerals (two Na-montmorillonites, Arizona (SAz-1) and Wyoming (SWy-2), and a Na-beidellite from Idaho (BIId)) were purchased from the Source Clays Minerals Repository of the Clay Mineral Society at Purdue University, Indiana. Clay suspensions were purified and separated in size fractions by successive centrifugation following the previously established procedure [12, 13]. Each fraction has a defined average platelet size with a reduced size polydispersity. Here we used one size fraction denoted T3 for all clays. The characteristic sizes and the cation-exchange capacities related to the charge densities of the clay particles we are interested in are summarized in Table 1 [12]. The BIId is a tetrahedrally substituted clay whereas the SAz-1 and the SWy-2 are octahedrally substituted clays.

Table 1: Main features of different clay particles used in this study: the lateral dimension D, the polydispersity in diameter, the average thickness e and the cation-exchange capacity (CEC). All systems were used with Na as the compensating counterion.

	SAz-1	SWy-2	BIId
D (nm)	95	100	209
Polydispersity (%)	19	25	38
e (nm)	0.7	0.7	1
CEC (mmol/100g)	122.5	96.4	94.3

2.3. Preparation of the 6-Cl/clay hydrogels

The 6-Cl was first added into a clay suspension and dispersed by using a sonicator (Fisher Scientific FB 15051) for 15 minutes. Then the mixture was heated at 70°C for 10 minutes followed by cooling to room temperature to form the hydrogel. The sonication step was seen as essential for producing visually transparent gels. The critical gelation concentration (CGC) was determined to be around 10 g/L via vial inversion method and rheology measurements.

2.4. Viscosity measurements

The rheo-SAXS experiments were performed with an Anton Paar MCR-501 imposed stress rheometer equipped with a Couette cell at 25°C. The Couette geometry consisted of two co-axial cylinders: a static outer cylinder (the stator) and a rotating inner cylinder (the rotor). The external R_{ext} radius of the stator and the internal radius of the rotor R_{in} were 10.25 mm and 9.75 mm respectively. Thus we had a gap of 500 μm and a total immersed volume height of 17 mm. The Couette cell was made of polycarbonate in order to limit the X-ray absorption by the cell. The samples were prepared several days before the experiment. After introduction of the sample into the rheometer, a shear rise from 100 s⁻¹ to 5000 s⁻¹ in 145 seconds and a 2-minute pre-shear at 5000 s⁻¹ was applied. The sample was then left at rest for 3 minutes. This pre-shear was necessary to remove the history of the sample and to have the same initial state for each sample before the measurement. The flow measurements were then carried out from 5000 s⁻¹ to 1 s⁻¹. In preliminary measurements, we found that when a constant shear rate was applied to the sample over time, the viscosity decreased for 1 minute and then stabilised and reached a plateau. The samples were therefore sheared for 5 minutes at each shear rate during the experiment to ensure that this plateau was reached prior to the SAXS measurement. The flow curves presented here correspond to the measurements made during the ramp of decreasing shear rates.

2.5. Small Angle X-ray Scattering (SAXS)

Rheo-SAXS experiments were conducted at the SWING beamline of the SOLEIL synchrotron (Orsay, France) using a fixed incident energy of 12 keV with one sample-to-detector distance of 1.5 m. Thus the q range available, q

being the scattering wavevector, was $0.006 \text{ \AA}^{-1} < q < 0.6 \text{ \AA}^{-1}$. The rheometer described above was implemented on the beamline to measure the scattered intensity under shear. For each sample, the scattered intensity was measured at different shear rates from 5000 s^{-1} to rest.¹⁵⁵ The system was kept at the same shear rate for 5 minutes. After 1 minute of shear, the viscosity plateau was reached. Thereafter an average over 50 acquisitions (over 5 minutes of total duration) was made to achieve good statistics. For each sample and shear rate, the scattered intensity was measured at two different positions within the Couette geometry: in radial and tangential position. These two different positions are shown in Figure 1. In the radial position, the incident beam is perpendicular to the streamlines, also called velocity lines. In the tangential position, the incident beam passes through the Couette cell in the direction of flow, i.e. parallel to the streamlines.¹⁵⁵

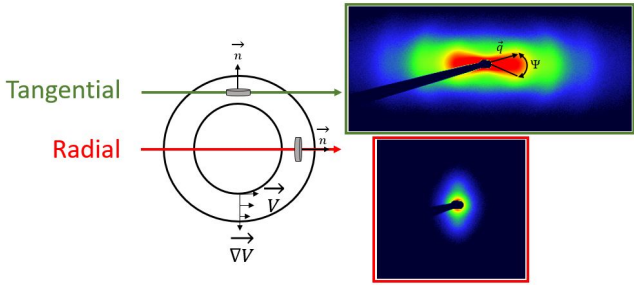


Figure 1: Cross-section of the Couette geometry. 2D SAXS images obtained, under a shear of 3000 s^{-1} , in the tangential position (green) and in the radial position (red) for 30 g/L 6-Cl gel and 0.15% BId-T3-Na. The vectors represent the velocity lines and the velocity gradient. The angle ψ representing the orientation of the scattering vector in the plane of the detector is shown in the scattering image in the tangential position.

Two-dimensional scattering patterns were recorded on an Eiger 4M (Dectris) detector. The size of the symbols of the SAXS curves reflects the errors bars.¹⁶⁵

To analyse the anisotropy of the 2D images and thus determine the orientation field of the clay platelets within the gel, we analyse the scattered intensity as a function of the angle ψ for a fixed scattering wavevector value q . In fact, to study the orientation of the platelets, we study the orientation distribution function (PDF or probability density function) of the vector normal to the surface of a platelet, shown in the shear reference frame [14, 15]. The normal vector is defined in the shear reference frame by a polar angle θ and an azimuthal angle ϕ . The statistical confinement of the normal vector to the platelet under shear describes an ellipsoid [16, 17, 18]. Taking this description into account, we can write the PDF as [16]:¹⁷⁰

$$PDF(\theta, \phi) = \frac{a_x a_y a_z}{4\pi} \frac{1}{((a_x^2 \cos^2 \phi + a_y^2 \sin^2 \phi) \sin^2 \theta + a_z^2 \cos^2 \theta)^{\frac{3}{2}}} \quad (1)$$

With a_x , a_y and a_z the semi-axes of the ellipsoid ($a_x > a_y > a_z$) thus representing the anisotropic parameters of the normal¹⁸⁰

vector. The scattered intensity as a function of the angular variations of the 2D images can therefore be written as [16]:

$$I(q, \psi) = C \int_0^{2\pi} \int_0^\pi F^2(q, \psi) PDF(\theta, \phi) d\theta d\phi \quad (2)$$

With C a constant, $F(q, \psi)$ the platelet form factor, $PDF(\theta, \phi)$ the probability density function of the normal vector, ψ the angle marking the angular variations of the 2D images, θ the polar angle and ϕ the azimuthal angle marking the platelet position. The angular variations of the scattered intensity of the 2D images are fitted with Equation 2 to extract the values of the anisotropic parameters. For this purpose, the scattered intensities are normalized by the average scattered intensity for angles between $\psi = 0$ and $\psi = 2\pi$. In addition, appropriate projections of the normal vector to the platelet from the shear frame of reference to the detector frame of reference are made to redefine the angles θ and ϕ as a function of the angle ψ [19]. An example of the normalized intensity as a function of angle ψ at the radial and tangential positions for a 30 g/L 6-Cl gel with 0.15% in volume fraction of beidellite is given in Figure 2. The solid lines in Figure 2 represent the fit of the experimental data with Equation 2.

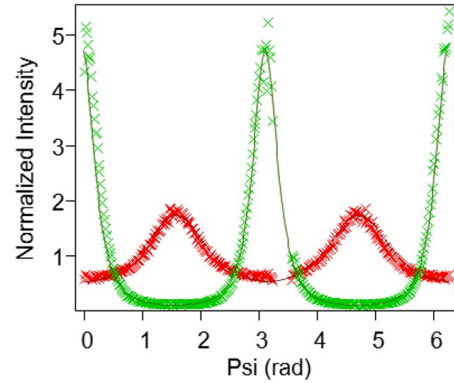


Figure 2: Normalized scattering intensity as a function of angle ψ for a 30 g/L 6-Cl gel and 0.15% BId-T3-Na under a shear of 3000 s^{-1} . In red: scattering intensity obtained in the radial position. In green: scattering intensity obtained in the tangential position. Crosses represent the experimental points and solid lines represent the fit of the experimental data with Equation 2.

The ratios of anisotropic parameters a_y/a_x and a_z/a_y are obtained from the modelling of the curves in Figure 2 in the radial and tangential positions respectively. These anisotropic parameters allow us to then calculate the ratio of parameters a_z/a_x . The ratios a_z/a_x and a_y/a_x provide access to the motions shown in Figure 3 (A) and Figure 3 (B) respectively. Thus, a_z/a_x describes the rotation of the normal vector \vec{n} around the Z axis in the plane $(\vec{\nabla}\vec{V}, \vec{V})$ (Z being the direction perpendicular to the cross-sections depicted in Figure 3). The ratio a_y/a_x describes the rotation of the normal vector \vec{n} around an axis parallel to \vec{V} in the plane $(\vec{\nabla}\vec{V}, Z)$. These two ratios reach values between

0 and 1, where 0 corresponds to platelets being completely oriented in one direction and 1 corresponds to platelets being randomly oriented. The statistical confinement of the normal vector in this latter case describes a sphere.

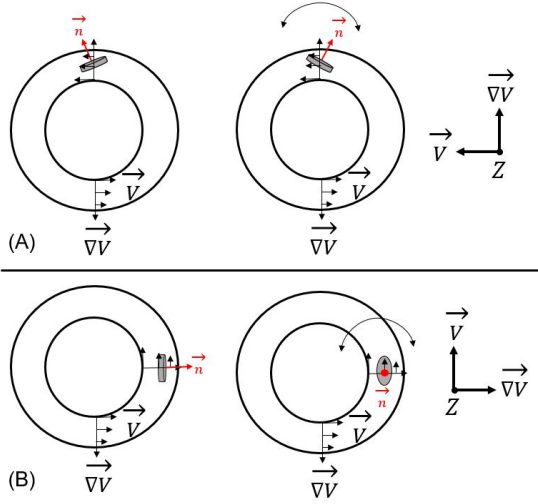


Figure 3: (A) Rotation of the normal vector \vec{n} in the plane $(\vec{\nabla V}, \vec{V})$ around the axis Z as described by the ratio of anisotropic parameters a_z/a_x . (B) Rotation of the normal vector \vec{n} in the plane $(\vec{\nabla V}, Z)$ around the axis represented by \vec{V} as described by the ratio of anisotropic parameters a_y/a_x .

3. Results and discussion

3.1. Macroscopic behaviour under flow

We study the evolution of the viscosity of clay containing gels as a function of shear rate. Figure 4 (A) shows the evolution of viscosity as a function of shear rate for a 6-Cl hydrogel at 30 g/L for different volume fractions of the three clay types studied. A decrease in viscosity is observed with increasing shear rate. The gels thus exhibit a strong shear thinning behaviour. The decrease in viscosity η can therefore be described according to a power law with the shear rate such as [20, 21, 22] :

$$\eta \sim K \dot{\gamma}^{n-1} \quad (3)$$

With K a constant in Pa.s^n corresponding to the consistency index and n a dimensionless number named rheofluidification index. If we take the example of the 30 g/L 6-Cl gel with 0.15% SAz1-T3-Na, we obtain a consistency value $K = 24.5 \text{ Pa.s}^n$ and a rheofluidification index $n = 0.16$ lower than 1, characteristic of a shear-thinning fluid. These values are similar regardless of the clay volume fraction for the 30 g/L ionene gel. Considering a 10% uncertainty in the viscosity values, there are no significant changes in the hydrogel viscosity when platelets are added to the gel. Figure 4 (B) presents the evolution of the viscosity of the gels as a function of the shear rate for a volume fraction fixed at 0.15% in clay and for different

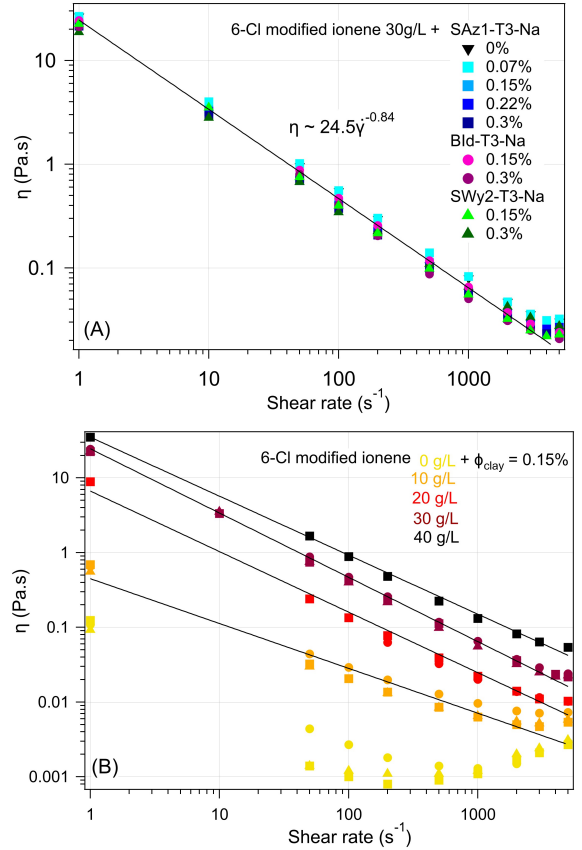


Figure 4: (A) Evolution of viscosity versus shear rate for 30 g/L 6-Cl gels for different clay volume fractions. The black solid line represents the power law fit of the experimental data for the 30 g/L 6-Cl gel and 0.15% SAz1-T3-Na. (B) Evolution of viscosity as a function of shear rate for gels with different concentrations of 6-Cl for a volume fraction of 0.15% clay and for the corresponding 0.15% clay suspensions. Bid-T3-Na is represented by circles, SAz1-T3-Na by squares and SWy2-T3-Na by triangles. The black solid lines represent the power law fits of the experimental data.

6-Cl concentrations. The viscosities of the corresponding clay suspensions at 0.15% are plotted in yellow in Figure 4 (B). We observe that the increase of the viscosity is mainly sensitive to the polyelectrolyte concentration. When we increase the concentration of 6-Cl from 10 g/L to 40 g/L, the viscosity of the gels increases by more than a factor 10. In Table 2 are listed the values of consistency K and rheofluidification index n for the gels at different concentrations of 6-Cl. We notice an increase of K when increasing the concentration of 6-Cl, which is expected since the K constant is directly related to viscosity. The rheofluidification index n decreases by a factor of 2 when increasing the concentration of 6-Cl from 10 g/L to 20 g/L. Then it appears to be almost constant. Thus, the shear-thinning behavior of the gels is more pronounced for more concentrated gel rather than gels at the critical gelation concentration. Furthermore, it is observed at 6-Cl 10 g/L that the viscosity of the gel with Bid-T3-Na at 0.15% is slightly higher than that of the gels with SWy2-T3-Na and SAz1-T3-Na

at 0.15%. This is in agreement with previous studies [10] specifying the fact that the highest G' value for these systems is also the one for the gel containing 0.15% beidellite. In the same way as for G' , the differences in viscosity according to the nature of the clay seem to be visible only when the gel is close to the CGC.

Table 2: Values of K and n parameters and R^2 of the power law 3 for the 6-Cl hydrogels at different concentrations in ionene and 0.15% of clay.

	K (Pa.s ^{n})	n	R^2
6-Cl 10g/L	0.42	0.4	0.9967
6-Cl 20g/L	6.7	0.19	0.9998
6-Cl 30g/L	24.5	0.16	0.9999
6-Cl 40g/L	35	0.21	0.9999

The pure clay suspensions plotted in yellow on Figure 4 (B) present a very weak shear-thinning behavior at the concentrations studied, with a nearly constant viscosity between 50 s^{-1} and 1000 s^{-1} . However, a slight increase of the viscosity is noticed at high shear rates from 2000 s^{-1} . This is characteristic of a Taylor-Couette instability [23]. This instability characterizes the appearance of secondary currents at very high shear rates. In the same way as for a low density gel, we also observe that the BId-T3-Na has a higher viscosity than the 0.15% montmorillonite suspensions. Overall, the shear-thinning behavior of the system as well as its viscosity are essentially governed by the 6-Cl modified ionene.

3.2. Orientation of clay platelets inside the gel

The organisation of clay platelets at rest has been evidenced in our previous article, featuring a local lamellar order, with a repeat distance of roughly 20 nm, characterized by periodic modulations of the scattered intensity in the middle- q region [10]. As the planar platelet surface gives a q^{-2} dependence of $I(q)$ vs q (the platelet form factor), the Kratky representation, $q^2 I(q)$, is the best to highlight the platelet-platelet correlations, i.e. the structure factor. Figure 5 represents the evolution of the structure factor of the 6-Cl gel at 30g/L and 0.15% of SAz1-T3-Na between 5000 s^{-1} and 0 s^{-1} in tangential and radial positions. The same periodic oscillations compared to rest are observed under shear. We notice therefore that the interparticle distance and their periodic face-to-face organisation remains unchanged regardless of the shear rate. These observations are valid for all the other systems studied by rheo-SAXS in this article. We observe the appearance of an additional shoulder between 0.02 \AA^{-1} and 0.03 \AA^{-1} in radial position for shear rates higher than 3000 s^{-1} . The origin of this shoulder remains unknown. Since the scattering curves are different depending on whether one is placed parallel or perpendicular to the velocity lines, we can already state that the clay platelets are oriented under shear. To quantify this orientation, let us study the evolution of the two ratios of the anisotropic parameters as a function of the shear rate. To extract these parameters from the angular

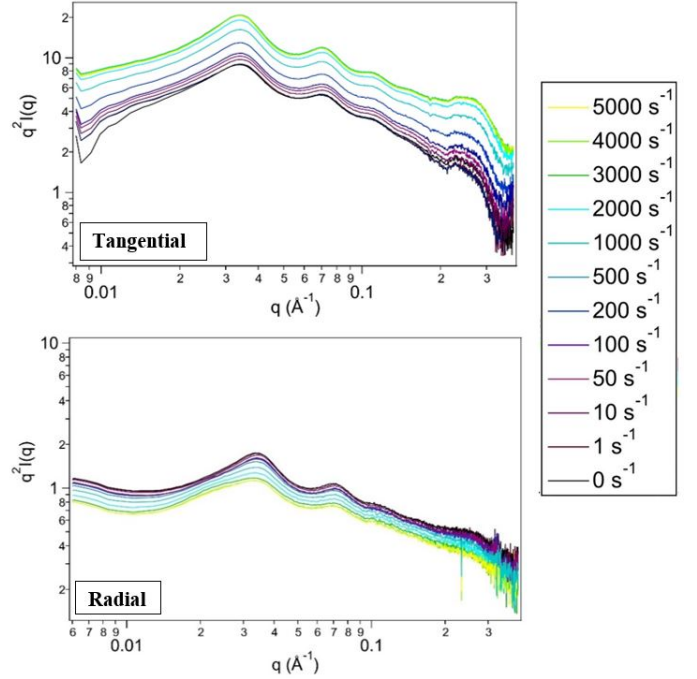


Figure 5: Evolution of the structure factor $q^2 I(q)$ as a function of the scattering vector q for 6-Cl gel at 30 g/L and 0.15% of SAz1-T3-Na at different shear rates in the tangential and radial positions.

variations, we set the value of the scattering wavevector q at the first maximum of the oscillations, at around 0.03 \AA^{-1} . We take this value in order to have the maximum of intensity.

Figure 6 shows the evolution of a_y/a_x and a_z/a_x as a function of the shear rate for 6-Cl gels at 30 g/L and at different volume fractions in clay. We first notice that both ratios are dependent on the shear rate from a critical shear rate of 50 s^{-1} . The ratio a_y/a_x is constant and close to 1 until 50 s^{-1} , and then decreases until 4000 s^{-1} from 1 to 0.85-0.75. Thus, the rotation of \vec{n} in the plane $(\nabla\vec{V}, Z)$ around the \vec{V} axis (Figure 3 (B)) occurs quite freely regardless of the nature of the clay. The parameter a_z/a_x also begins to decrease from 50 s^{-1} until 4000 s^{-1} for values between 0.9 and 0.6 for both montmorillonites, and between 0.6 and 0.2 in the case of beidellite. The rotation of the normal vector to the platelet in the plane $(\nabla\vec{V}, \vec{V})$ around the Z axis (Figure 3 (A)) thus depends on the nature of the clay. For BId-T3-Na, a_z/a_x is close to 0.2 for shear rates above 3000 s^{-1} which means that the normal vector \vec{n} is highly confined along the axis $\nabla\vec{V}$ and that its rotation in the plane $(\nabla\vec{V}, \vec{V})$ around the Z axis is minimal. There is no difference in orientation between SAz1-T3-Na and SWy2-T3-Na, both of them have a less confined normal vector along the $\nabla\vec{V}$ axis than that of BId-T3-Na in the plane $(\nabla\vec{V}, \vec{V})$. These trends are almost identical for different clay volume fraction. Thus, the orientation of the platelets is close to independent of the clay volume fraction at this polyelectrolyte concentration. We note that

for hydrogels with beidellite particles, residual orientation is clearly seen at low shear rates. In other words the system does not relax completely to a non-oriented state, as the shear rate is decreased.

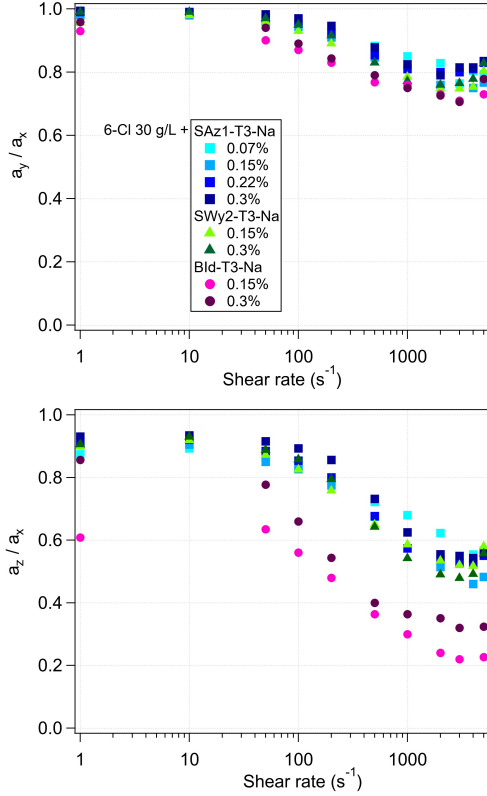


Figure 6: Evolution of the anisotropic parameters ratios a_y/a_x and a_z/a_x as a function of shear rate for 6-Cl gels at 30 g/L for different clay volume fractions. The same legend is used for both figures.

If the SAz1-T3-Na volume fraction is now set at 0.15% and the polyelectrolyte concentration varies from 20 g/L to 40 g/L, the same type of behaviour is observed in Figure 7. Orientation also takes place from a critical shear rate of 50 s^{-1} . The rotation of \vec{n} in the plane $(\nabla\vec{V}, Z)$ around the \vec{V} axis occurs more readily, while the normal vector \vec{n} is confined in the plane $(\nabla\vec{V}, Z)$. Moreover, orientation is independent of the polyelectrolyte concentration in this range. The viscosity of the system, on the other hand, rises sharply with the polyelectrolyte concentration. Thus, platelet orientation is independent of the viscosity of the system. Furthermore, previous studies [24] have shown that the vicinity of particles with their neighbours improves platelet orientation. Thus, we would have expected that a decrease in interparticle distance i.e. an increase of the polyelectrolyte concentration would increase the degree of orientation, which is not the case here.

Figure 8 shows the evolution of anisotropic parameter ratios as a function of shear rate for 10 g/L 6-Cl gels with 0.15% of clay. The 10g/L system stands out from the other 6-Cl concentrations. In fact, when close to the CGC, we

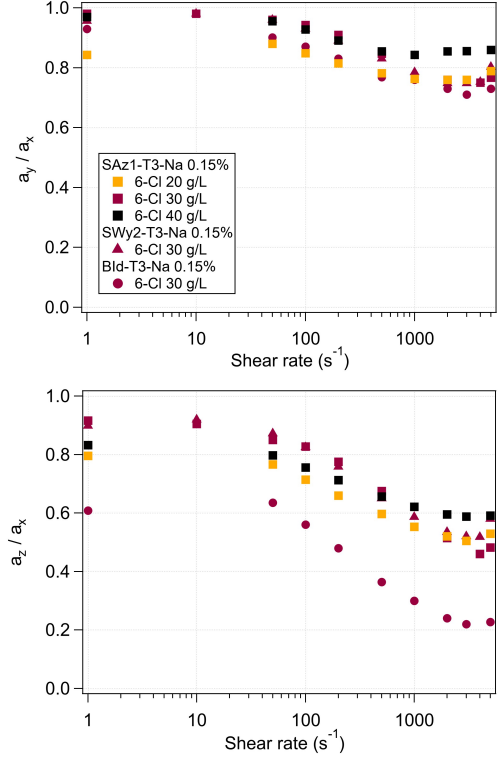


Figure 7: Evolution of the anisotropic parameters ratios a_y/a_x and a_z/a_x as a function of shear rate for 6-Cl gels at different concentration and with a clay volume fraction fixed at 0.15%. The same legend is used for both figures.

no longer observe a critical shear rate at which platelets orient themselves. Their orientation is then independent of the shear rate for both a_z/a_x and a_y/a_x . We demonstrate in the previous section that the 10 g/L gel is less shear-thinning than those between 20 g/L and 40 g/L in 6-Cl. Thus, dependence of shear rate on platelet orientation and shear-thinning behavior of the gel are closely linked. A difference between SAz1-T3-Na and SWy2-T3-Na then emerged. Indeed, SWy2-T3-Na is the least oriented of the three clays with the highest a_y/a_x and a_z/a_x ratios. Bid-T3-Na remains the platelets with the most confined normal vector in the plane $(\nabla\vec{V}, Z)$ with the lowest a_z/a_x ratio. SAz1-T3-Na has an intermediate orientation between SWy2-T3-Na and Bid-T3-Na with intermediate a_z/a_x values. In contrast, rotation of the normal vector around the \vec{V} axis in the plane $(\nabla\vec{V}, Z)$ occurs more freely for Bid-T3-Na than for SAz1-T3-Na, the a_y/a_x ratio of beidellite being higher than that of SAz1. The clay with the most confined normal along $\nabla\vec{V}$ (beidellite) gives a gel with the highest viscosity. A low-density gel therefore emphasizes the differences in orientation depending on the nature of the clay. If we compare the system with 6-Cl 10 g/L and 0.3% of clay, where platelets are known to be aggregated within the gel [10], there is a difference in platelet orientation compared with the 0.15% clay system (Supplementary Material S2). Both anisotropic parameter ratios

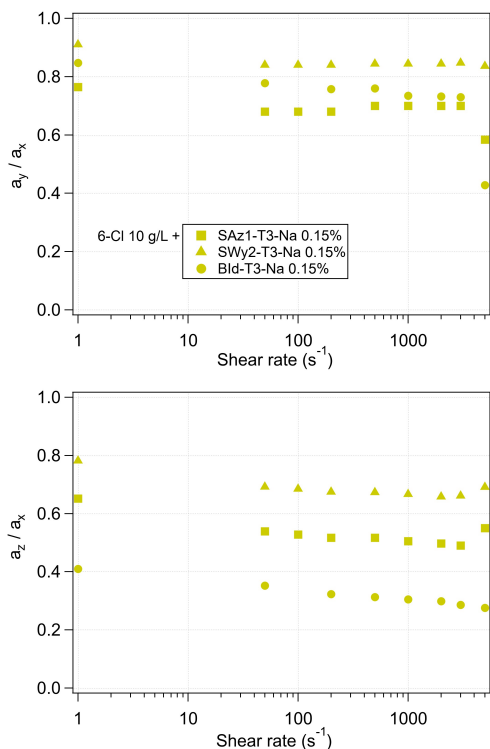


Figure 8: Evolution of the anisotropic parameters ratios a_y/a_x and a_z/a_x as a function of shear rate for 6-Cl gels at 10g/L and for 0.15% of clay volume fraction. The same legend is used for both figures.

are higher, so orientation is much lower. Thus, the presence of tactoids, i.e. the presence of a stack of platelets at short distances is detrimental to orientation. It is interesting to compare these results with previous work by Philipe et al. [19] on the orientation under shear of clay platelets in suspension. In suspension, beidellite is also the system with platelets having the most confined normal vector along the $\vec{\nabla V}$ axis compared to the two types of montmorillonite. SWy2 is also the clay that orientates the least under shear. So, although the system is different due to the presence of a dense meshwork of ionene polyelectrolytes, we find the same trends as in the case of pure clay gels or suspensions. Thus, it seems that platelet orientation is essentially sensitive to charge location. When the charge is located at the surface of the platelet, the degree of orientation is greater. The charge density of clays seems to have no effect, except for low-density gels with 10g/L of 6-Cl. In this case, higher charge density results in better platelet orientation. We have shown in a previous study [10] that the degree of organisation of the clay platelets within the modified ionene gel depends as much of the location of the charge as of the charge density. As a consequence, the differences according to the nature of the clay are not reflected in the same way in their ability to orientate under shear than in the degree of platelet organisation.

4. Conclusion

These studies have shown the possibility to orientate clay platelets within the matrix of ionene-based gels under shear. The vector normal to the platelet is then essentially confined to the plane $(\vec{\nabla V}, Z)$ during shear. Platelet orientation differs depending on whether the concentration of ionene in the gel is greater than or equal to the CGC. For ionene concentrations higher than the CGC, this orientation is independent of the clay volume fraction and independent of the ionene concentration. Thus, interparticle distance has no effect on platelet orientation. The orientation field is dependent on the shear rate and has a critical shear rate at which the platelets are oriented. The shear-thinning properties and viscosities of these systems are governed by the behaviour of the ionene. Thus, viscosity is decorrelated from the preferential orientation of the clay particles within the gel. When the concentration of ionene is equal to the CGC, the clay platelets exhibit an orientation independent of the shear rate. Regardless of the ionene concentration, orientation is essentially dependent on the nature of the platelet and, more specifically, on the location of the charge. On the other hand, the differences in charge density are only visible for ionene concentrations close to the CGC, i.e. for a weak gel network. In this case, the clay with the highest charge density is more oriented than the clay with the lowest charge density for the same charge location.

The organisation of clays nanoplatelets in a local lamellar order paves the way to a promising material for drug delivery system with potentially anisotropic permeability. Indeed, a regular stacking of clay particles could lead to a tortuous diffusion pathway of the drug within the hydrogel. Moreover the shear-induced orientation of clays opens the possibility to tune at will the anisotropy of permeation properties of the hydrogel. The orientation of clay particles within the hydrogel with other methods such as applying a magnetic field could be investigated.

Author contribution

CH was the main contributor to the study. CH, GD, JSP, TB, CG, PL, LM and NM performed experimental work. CH, GD, JSP, LM and NM jointly contributed to the design of the work. GD, JSP, LM and NM supervised the work. CH drafted the manuscript and the remaining authors contributed to its final version.

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgments

The authors acknowledge the SOLEIL synchrotron for awarding the beamtime on beamline SWING. The authors acknowledge Adrian-Marie Philippe for the analysis tool for the SAXS datas treatment.

Appendix A. Supplementary material

The Supplementary data to this article can be found at: Supplementary Material.pdf

References

- [1] H. Takeno, S. Nagai, Mechanical Properties and Structures of Clay-Polyelectrolyte Blend Hydrogels, *Gels* 4 (3) (2018) 71. doi:10.3390/gels4030071.
- [2] C.-W. Chang, A. van Spreeuwel, C. Zhang, S. Varghese, Peg/clay nanocomposite hydrogel: a mechanically robust tissue engineering scaffold, *Soft Matter* 6 (2010) 5157–5164. doi:10.1039/C0SM00067A.
- [3] L. Z. Zhao, C. H. Zhou, J. Wang, D. S. Tong, W. H. Yu, H. Wang, Recent advances in clay mineral-containing nanocomposite hydrogels, *Soft Matter* 11 (48) (2015) 9229–9246. doi:10.1039/C5SM01277E.
- [4] Z. Darvishi, K. Kabiri, M. J. Zohuriaan-Mehr, A. Morsali, Nanocomposite super-swelling hydrogels with nanorod bentonite, *Journal of Applied Polymer Science* 120 (6) (2011) 3453–3459. doi:https://doi.org/10.1002/app.33417.
- [5] C. R. N. Jesus, E. F. Molina, S. H. Pulcinelli, C. V. Santilli, Highly controlled diffusion drug release from ureasil-poly(ethylene oxide)-na+-montmorillonite hybrid hydrogel nanocomposites, *ACS Applied Materials & Interfaces* 10 (22) (2018) 19059–19068. doi:10.1021/acsami.8b04559.
- [6] S. Murugesan, T. Scheibel, Copolymer/clay nanocomposites for biomedical applications, *Advanced Functional Materials* 30 (17) (2020) 1908101. doi:https://doi.org/10.1002/adfm.201908101.
- [7] A. Sheikhi, S. Afewerki, R. Oklu, A. K. Gaharwar, A. Khademhosseini, Effect of ionic strength on shear-thinning nanoclay-polymer composite hydrogels, *Biomater. Sci.* 6 (2018) 2073–2083. doi:10.1039/C8BM00469B.
- [8] R. Noguchi, Reactions of n,n,n',n'-tetramethyl-diaminoalkanes with dihaloalkanes, *Macromolecules* 5 (3) (1972) 253–260.
- [9] Y. Misawa, N. Koumura, H. Matsumoto, N. Tamaoki, M. Yoshida, Hydrogels Based on Surfactant-Free Ionene Polymers with N,N'-(p-Phenylene)dibenzamide Linkages, *Macromolecules* 41 (22) (2008) 8841–8846. doi:10.1021/ma801350k.
- [10] C. Hotton, J. Sirieix-Plénet, G. Ducouret, T. Bizien, A. Chennetière, L. Porcar, L. Michot, N. Malikova, Organisation of clay nanoplatelets in a polyelectrolyte-based hydrogel, *Journal of Colloid and Interface Science* 604 (2021) 358–367. doi:https://doi.org/10.1016/j.jcis.2021.07.010.
- [11] C. Hotton, G. Ducouret, J. Sirieix-Plénet, T. Bizien, L. Porcar, N. Malikova, Tuning structure and rheological properties of polyelectrolyte-based hydrogels through counterion-specific effects, *Macromolecules* 56 (2023) 923–933. doi:https://doi.org/10.1021/acs.macromol.2c01565.
- [12] E. Paineau, I. Bihannic, C. Baravian, A.-M. Philippe, P. Davidson, P. Levitz, S. S. Funari, C. Rochas, L. J. Michot, Aqueous Suspensions of Natural Swelling Clay Minerals. 1. Structure and Electrostatic Interactions, *Langmuir* 27 (9) (2011) 5562–5573. doi:10.1021/la2001255.
- [13] L. J. Michot, I. Bihannic, K. Porsch, S. Maddi, C. Baravian, J. Mougel, P. Levitz, Phase Diagrams of Wyoming Na-Montmorillonite Clay. Influence of Particle Anisotropy, *Langmuir* 20 (25) (2004) 10829–10837. doi:10.1021/la0489108.
- [14] A. M. Philippe, C. Baravian, V. Bezuglyy, J. R. Angilella, F. Meneau, I. Bihannic, L. J. Michot, Rheological Study of Two-Dimensional Very Anisometric Colloidal Particle Suspensions: From Shear-Induced Orientation to Viscous Dissipation, *Langmuir* 29 (17) (2013) 5315–5324. doi:10.1021/la400111w.
- [15] G. B. Jeffery, L. N. G. Filon, The motion of ellipsoidal particles immersed in a viscous fluid, *Proceedings of the Royal Society of London. Series A, Containing Papers of a Mathematical and Physical Character* 102 (715) (1922) 161–179. doi:10.1098/rspa.1922.0078.
- [16] I. Bihannic, C. Baravian, J. F. Duval, E. Paineau, F. Meneau, P. Levitz, J. P. de Silva, P. Davidson, L. J. Michot, Orientational order of colloidal disk shaped particles under shear flow conditions: a rheological-small-angle x-ray scattering study, *The Journal of Physical Chemistry B* 114 (49) (2010) 16347–16355.
- [17] C. Baravian, L. J. Michot, E. Paineau, I. Bihannic, P. Davidson, M. Impéror-Clerc, E. Belamie, P. Levitz, An effective geometrical approach to the structure of colloidal suspensions of very anisometric particles, *EPL (Europhysics Letters)* 90 (3) (2010) 36005. doi:10.1209/0295-5075/90/36005.
- [18] L. J. Michot, C. Baravian, I. Bihannic, S. Maddi, C. Moynes, J. F. L. Duval, P. Levitz, P. Davidson, Sol-Gel and Isotropic/Nematic Transitions in Aqueous Suspensions of Natural Nontronite Clay. Influence of Particle Anisotropy. 2. Gel Structure and Mechanical Properties, *Langmuir* 25 (1) (2009) 127–139. doi:10.1021/la801894a.
- [19] A.-M. Philippe, C. Baravian, M. Imperor-Clerc, J. P. de Silva, I. Bihannic, P. Davidson, F. Meneau, P. Levitz, L. J. Michot, Rheo-saxs investigation of shear-thinning behaviour of very anisometric repulsive disc-like clay suspensions, *J. Phys. Condens. Matter* 23 (19) (2011) 194112. doi:10.1088/0953-8984/23/19/194112.
- [20] M. Á. Vigilato, M. Horn, V. C. A. Martins, A. M. de G. Plepis, Rheological study of gels based on chitosan and carbon nanotubes, *Brazilian Journal of Thermal Analysis* 4 (2015) 35–38.
- [21] M. N. A. Rahman, O. A. J. A. Qader, S. Sukmasari, A. F. Ismail, A. A. Doolaanea, Rheological characterization of different gelling polymers for dental gel formulation, *J Pharm Sci* 9 (2017) 8.
- [22] V. Kumbár, Š. Nedomová, R. Pytel, L. Kilián, J. Buchar, Study of rheology and friction factor of natural food hydrocolloid gels, *Potravinárstvo Slovak Journal of Food Sciences* 11 (1) (2017) 203–209. doi:10.5219/735.
- [23] A. M. Philippe, C. Baravian, M. Jenny, F. Meneau, L. J. Michot, Taylor-couette instability in anisotropic clay suspensions measured using small-angle x-ray scattering, *Phys. Rev. Lett.* 108 (2012) 254501. doi:10.1103/PhysRevLett.108.254501.
- [24] D. H. Berry, W. B. Russel, The rheology of dilute suspensions of slender rods in weak flows, *Journal of Fluid Mechanics* 180 (1987) 475–494. doi:10.1017/S0022112087001915.