



**HAL**  
open science

# Tensile stress effect on magnetic Barkhausen noise of silicon steel single crystal (measurements and simulations)

Benjamin Ducharne, Eric Wasniewski, Laurent Daniel, Mathieu Domenjoud,  
Patrick Fagan

## ► To cite this version:

Benjamin Ducharne, Eric Wasniewski, Laurent Daniel, Mathieu Domenjoud, Patrick Fagan. Tensile stress effect on magnetic Barkhausen noise of silicon steel single crystal (measurements and simulations). 2024 INTERMAG, IEEE International Magnetic Conference, May 5 - 10 2024 Rio de Janeiro, Brazil, May 2024, Rio de Janeiro (BR), Brazil. hal-04613689

**HAL Id: hal-04613689**

**<https://hal.science/hal-04613689v1>**

Submitted on 17 Jun 2024

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Tensile stress effect on magnetic Barkhausen noise of silicon steel single crystal (measurements and simulations)

Benjamin Ducharme<sup>1,2</sup>, Eric Wasniewski<sup>3,4,5</sup>, Laurent Daniel<sup>4,5</sup>, Mathieu Domenjoud<sup>4,5</sup> and Patrick Fagan<sup>4,5</sup>

<sup>1</sup>ELyTMax IRL3757, CNRS, Univ. Lyon, INSA Lyon, Centrale Lyon, Université Claude Bernard Lyon 1, Tohoku University, Sendai, Japan, [benjamin.ducharme@insa-lyon.fr](mailto:benjamin.ducharme@insa-lyon.fr)

<sup>2</sup>Univ. Lyon, INSA-Lyon, LGEF EA682, F69621, France

<sup>3</sup>Cetim, 52 avenue Félix Louat 60300 Senlis, France

<sup>4</sup>Université Paris-Saclay, CentraleSupélec, CNRS, GeePs, 91192 Gif-sur-Yvette, France

<sup>5</sup>Sorbonne Université, CNRS, GeePs, 75252, Paris, France

The Magnetic Barkhausen Noise (MBN) measurement can be used to evaluate non-destructively mechanical internal stress in electrical steel laminations. However such evaluation is complex as various factors can distort the MBN signal similarly. Internal stress is one of them, but an increase in dislocation density or other defects can be just as influential. This work focuses on single crystals with pre-determined crystallographic orientation to isolate basic mechanisms. The reconstructed MBN energy hysteresis cycles are compared to classical hysteresis loops, and to simulation obtained from a multiscale model. These comparisons provide new insights into the impact of tensile stress on the magnetization process and the magnetic domains kinetics and bring perspectives regarding the ideal way to perform MBN non-destructive evaluation of internal mechanical stress.

**Index Terms**—Magnetic Barkhausen Noise, magnetization mechanisms, non-destructive testing, multiscale model, tensile stress effect.

## I. INTRODUCTION

THE MAGNETIC Barkhausen Noise (MBN) characterization technique is a valuable Non-Destructive Testing (NDT) of ferromagnetic steel components due to its sensitivity to microstructural changes, rapid inspection capabilities, subsurface defect detection, quantitative analysis, automation potential, and versatility. Its application ensures the integrity and reliability of ferromagnetic parts in critical sectors such as transportation, public structures, or energy. [1].

MBN is generated by the motion of magnetic domain walls encountering microstructural features like grain boundaries and dislocations under the influence of an external magnetic field. The resulting abrupt movements cause rapid changes in magnetic flux, producing the so-called Barkhausen noise.

Standardizing procedures and controlling experimental parameters are crucial for reproducibility in MBN NDT. The raw signal, containing undesired noise, is classically replaced with reproducible indicators like the amplitude of the MBN activity, frequency distribution, and energy content. For years, our group has privileged the Magnetic Barkhausen Noise energy ( $MBN_{energy}$ ) for its physical meaning and specific link with the magnetic flux density. The computation of the  $MBN_{energy}$  involves the following successive steps [2]:

— Monitor the MBN signal under the form of an electrical voltage:  $e(t)$

— Integrate the product of the sign of the magnetic excitation time-derivative and the square of the MBN signal:

$$MBN_{energy}(t) = \int_0^t \text{sign}\left(\frac{dH_{surf}}{ds}\right) e^2(s) ds \quad (1)$$

In parallel to the concept of the  $MBN_{energy}$  quantity arises the idea of  $MBN_{energy}(H_{surf})$  hysteresis cycles, which depict how  $MBN_{energy}$  changes with respect to the external magnetizing field  $H_{surf}$  measured tangential to the specimen surface.

This graphical chart includes the  $MBN_{energy}$  on the y-axis and  $H_{surf}$  on the x-axis. The resulting cycles provide additional

information about the magnetization process, especially compared to classical magnetization loops ( $B_a(H_{surf})$ , where  $B_a$  is the flux density averaged through the specimen cross-section). More precisely, it helps establishing the respective weights of domain wall motion and rotation contribution during the magnetization process. Previous works, for instance, revealed similarities between  $MBN_{energy}$  and classical hysteresis loops for grain-oriented electrical steel (GOFesi) but significant differences for iron-cobalt (FeCo) laminations, meaning that the rotation contribution is limited for GOFesi and important for FeCo [3].

Still, most of these results are qualitative and based on experimental observations. They lack theoretical confirmation, especially considering that MBN is sensitive to many parameters (dislocation density, grain boundaries). In this work, we want to confirm these results by focusing MBN measurement on single crystals with pre-established crystallographic orientation. Hence, the number of parameters influencing MBN measurements will be limited. By combining experimental results (both  $MBN_{energy}$  and classical hysteresis cycles) and simulation predictions from a multiscale model [3][4], our objective is to define precisely the role of each of the magnetization mechanisms and to establish their order of appearance. The influence of uniaxial tensile stress  $\sigma$  will be studied too, with the objective to establish which magnetization mechanism is most sensitive to stress and what is the ideal solution for its assessment in NDT conditions.

## II. SPECIMENS DESCRIPTION AND SINGLE CRYSTAL MBN CHARACTERIZATION

### A. Tested specimens description

In this work, the tested specimens were GOFesi laminations submitted to specific thermal treatment to induce grains of exceptional size (of the order of centimeters). Fig. 1 depicts one of these specimens.

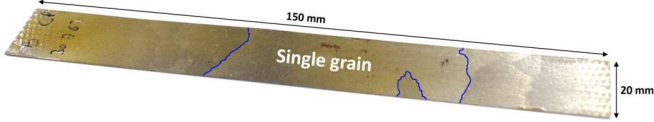


Fig. 1. Picture and dimensions of a tested specimen (thickness is 250  $\mu\text{m}$ ).

Laminations of GOFesi were used to obtain a series of samples cut at  $\theta = 0, 30, 45, 54.7, 60,$  and  $90^\circ$ , where  $\theta = 0^\circ$  and  $90^\circ$  are the rolling and the transverse directions, respectively (see Fig. 2). The cutting areas were chosen so that a large grain stands in the middle of the samples [5]. Two specimens were prepared for each angle.

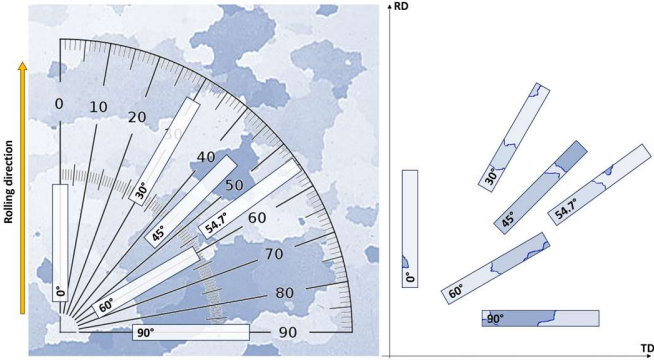


Fig. 2. Tested specimens and their orientations

### B. Experimental setup

A dedicated experimental bench was set up to measure the  $MBN_{energy}(H_{surf})$  and  $B_a(H_{surf})$  under different uniaxial tensile stresses  $\sigma$  (elastic regime). A 2D sketch of this experimental setup is shown in Fig. 3. Two 200-turns wrapped coil sensors plugged in series opposition and positioned in the vicinity of the same grain (Fig. 3.B) are used for the MBN measurement.

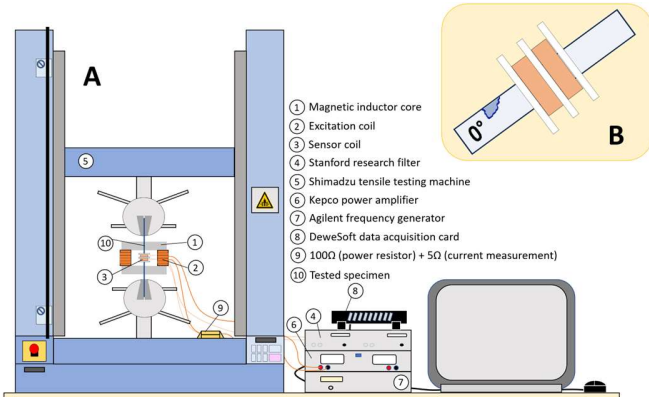


Fig. 3. A 2D sketch of the experimental setup. B Close view of the double coil sensor positioned in the vicinity of the single-grain

### III. MULTISCALE MODEL

The magnetic behavior under the influence of tensile stress is simulated thanks to the multiscale model described in [3] but in a single crystal configuration [6]. The multiscale simulation is used to predict the anhysteretic behavior of both classical and  $MBN_{energy}$  cycles. The latter are obtained by suppressing the magnetization rotation contribution.

### IV. FIRST RESULTS

The first results shown in this abstract correspond to the comparisons between the  $MBN_{energy}(H_{surf})$  and the  $B_a(H_{surf})$  hysteresis cycles for applied tensile force  $F = 0, 250, 500, 750,$  and  $1000$  N (corresponding to  $\sigma = 0, 50, 100, 150,$  and  $200$  MPa, respectively). The maximum stress level was set to keep the material in the elastic regime.

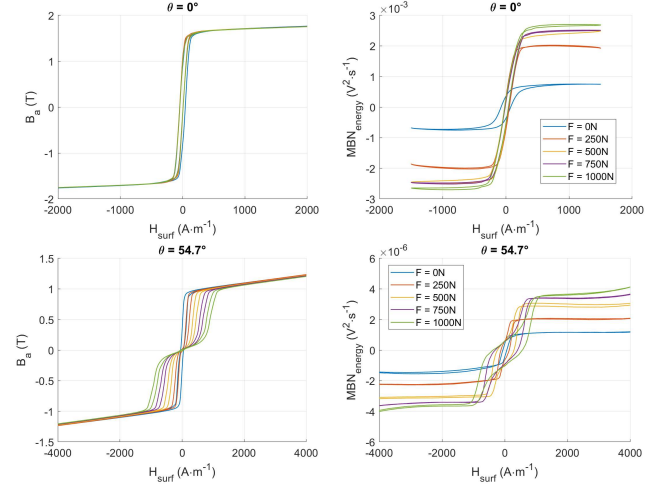


Fig. 4. Comparison  $MBN_{energy}(H_{surf})$  and  $B_a(H_{surf})$  hysteresis loop for different levels of  $\sigma$  and  $\theta = 0$  and  $54.7^\circ$ .

In this abstract, only the results obtained for  $\theta = 0$  and  $54.7^\circ$  are shown. These orientations are expected to be the easiest and the hardest magnetic angles. No rotation is expected at  $\theta = 0^\circ$ ; the  $MBN_{energy}(H_{surf})$  and  $B_a(H_{surf})$  cycles have similar shapes. Oppositely, at  $\theta = 54.7^\circ$ , a significant rotation contribution is expected, which is confirmed by the evident difference between both types of cycles. Concerning the  $\sigma$  influence, almost no effect is visible on the  $\theta = 0^\circ$   $B_a(H_{surf})$  loops, while the amplitude of the  $MBN_{energy}(H_{surf})$  loops is highly affected.

### V. CONCLUSION

$MBN$  NDT is a promising route for the assessment of internal stresses in GOFesi. This preliminary work reduced the influent parameters by working with single crystals of pre-characterized crystallographic orientation.

### REFERENCES

- [1] R. Tomkowiak, The Barkhausen Noise Measurements: Good Practice Guide, 2nd ed. Stockholm : KTH Royal Institute of Technology, 2022.
- [2] P. Fagan, S. Zhang, G. Sebald, T. Uchimoto and B. Ducharme, Barkhausen noise hysteresis cycle: Theoretical and experimental understanding. *J. Magn. Magn. Mater.*, vol. 578, pp.170810, 2023.
- [3] P. Fagan, B. Ducharme, L. Daniel and A. Skarlatos, Multiscale modelling of the magnetic Barkhausen noise energy cycles. *J. Magn. Magn. Mater.*, vol. 517, pp.167395, 2021.
- [4] P. Fagan, B. Ducharme, L. Daniel, A. Skarlatos, M. Domenjoud and C. Reboud, Effect of stress on the magnetic Barkhausen noise energy cycles: A route for stress evaluation in ferromagnetic materials. *Mater. Sc. Eng., B*, vol. 278, p.115650, 2022.
- [5] K.J. Rizzo, O. Hubert and L. Daniel, Magnetic and magnetostrictive behavior of Iron-Silicon single crystals under uniaxial stress. *IEEE Tran. Magn.*, vol. 46, n°2, 2010.
- [6] L. Daniel, O. Hubert, R. Billardon, Homogenisation of magneto-elastic behaviour: from the grain to the macro scale. *Comput. Appl. Math.*, vol. 23, pp. 285-308, 2004.