



HAL
open science

Infrared thermovision of damage in brittle geomaterials

Minh-Phong Luong, Mehrdad Emami Tabrizi, Jean-Christophe Eytard,
Siegfried Maiolino

► **To cite this version:**

Minh-Phong Luong, Mehrdad Emami Tabrizi, Jean-Christophe Eytard, Siegfried Maiolino. Infrared thermovision of damage in brittle geomaterials. NDRM'2009 - 3rd International Conference on New Development in Rock Mechanics and Engineering, 2012, Sanya, China. pp.1-6. hal-04667420

HAL Id: hal-04667420

<https://hal.science/hal-04667420v1>

Submitted on 4 Aug 2024

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

INFRARED THERMOVISION OF DAMAGE IN BRITTLE GEOMATERIALS

MINH-PHONG LUONG, MEHRDAD EMAMI-TABRIZI,
JEAN-CHRISTOPHE EYTARD, SIEGFRIED MAIOLINO

*LMS (Solids Mechanics Laboratory), Civil Engineering, Department of Mechanics
Ecole Polytechnique – CNRS UMR7649, 91128 Palaiseau Cedex, France*

Email: maiolino ; emami ; eytard ; luong@lms.polytechnique.fr

This paper aims to illustrate the use of infrared thermography as a non-destructive and non-contact technique to observe the phenomenological manifestation of damage in brittle geomaterials under unconfined compression. It allows records and observations in real time of heat patterns produced by the dissipation of energy generated by plasticity. The experimental results show that this technique, which couples mechanical and thermal energy, can be used for illustrating the onset of damage mechanism by stress concentration in weakness zones.

1 Introduction

Current technological developments tend towards increased exploitation of material strengths and towards tackling extreme loads and environmental actions. The tendency to extend the service life of materials and structures by increasing maintenance, rather than replacement, increases the need for monitoring structures and supports the need to perform global or local test loading. Diverse damage analysis methodologies for engineering materials have been developed in recent years which isolate the factors affecting crack initiation and growth, and enable the prediction of their cumulative effects on the fatigue performance of structural components¹. In cases where continuum mechanics can be applied, the concept of an effective stress $\sigma_{ef} = \sigma/(1-\delta)$ has been introduced with a continuous variable δ related to the scalar density of defects or faults. This has been the starting point of damage theories developed for fatigue, creep, and creep-fatigue interaction in engineering materials.

Brittle geomaterials are mainly characterized by their salient fracturing nature. A different approach has been proposed using the plasticity formalism with the concept of a fracturing stress (considered hereafter as a threshold of acceptable damage TAD) or a fracturing strain to describe the inelastic behavior of progressively fracturing solids². Failure in brittle geomaterial may be viewed as a micro-structural process through the activation and growth of one pre-existing flaw or site of weakness, or through the coalescence of a system of interacting small flaws and growing micro-cracks³. The formation of micro-cracks are often associated with points of stress concentration that are located on flaws present in the material, or on existing cracks and notches.

Several scientific studies have been carried out in recent years on the infrared radiation in the process of rock deformation leading to fracturing and failure⁴⁻⁵⁻⁶. Within the framework of a consistent theoretical approach, this paper emphasizes the application and use of infrared thermography to detect and evaluate quantitatively the extent of damage in brittle geomaterials owing to the non-linear coupled thermomechanical effects.

2 Background of thermomechanical coupling in solids

The development of the thermo-elastic- plasticity governing equations⁷ leads to the following coupled thermomechanical equation:

$$\rho C_v \theta_{,t} = \rho r + \text{div} (k \text{ grad} \theta) - (\beta : D : E^c_{,t}) \theta + S : E^I_{,t} \quad (1)$$

where ρ ($\text{kg}^{-1} \cdot \text{m}^{-3}$) denotes the mass density, C_v ($\text{J} \cdot \text{kg}^{-1} \cdot \text{K}^{-1}$) the specific heat at constant deformation, $\theta_{,t}$ ($\text{K} \cdot \text{sec}^{-1}$) the time derivative of the absolute temperature, r the heat sources, div the divergence operator, k ($\text{W} \cdot \text{m}^{-1} \cdot \text{K}^{-1}$) the thermal conductivity, grad the gradient operator, β (K^{-1}) the coefficient of the thermal expansion matrix, $:$ the scalar product operator, D the fourth-order elastic stiffness tensor, $E^c_{,t}$ the time derivative of the elastic strain tensor, S the second Piola-Kirchhoff stress tensor and finally E^I the inelastic strain tensor. The volumetric heat capacity $C = \rho C_v$ of the material is the energy required to raise the temperature of a unit volume by 1°C (or 1 Kelvin).

This coupled thermomechanical equation suggests the potential applications of the infrared scanning technique in diverse engineering domains⁸⁻⁹⁻¹⁰: detection of fluid leakage, non-destructive testing using thermal conduction phenomena, elastic stress measurements, and localization of dissipative phenomena. Thus the detected temperature change, resulting from four quite distinctive phenomena (heat sources, thermal conduction, thermo-elasticity and intrinsic dissipation), must be correctly discriminated by particular test conditions and/or specific data reduction. This analysis is the principal difficulty when interpreting the thermal images obtained from experiments under the usual conditions.

3 Infrared thermography

Infrared thermography allows imaging and measuring temperature from radiation in the infrared spectral band. In this paper the infrared imaging system utilizes an infrared focal plane camera operating in MWIR wavelength band (mid-wave infrared window from 3 to 5 μm) and in snap shot mode of image capture. The

infrared detector converts the emitted radiation into electrical signals that are recorded and displayed on a color or black & white computer monitor. Since infrared radiation is emitted by all objects according to the black body radiation law, the amount of radiation emitted by an object increases with temperature, thermography allows the detections of variations in temperature. The quantity of energy emitted as infrared radiation is a function of the temperature and the emissivity of the specimen according to the Stefan-Boltzman equation. The higher the temperature, the more important is the emitted energy. Differences of radiated energy reflect temperature differences.

4 Infrared thermovision of rock failure

In the laboratory, a fully digital servo-hydraulic test machine, MTS 100 KN, was used for uniaxial loading test. The test machine is controlled by a sophisticated closed-loop electronic control system. The sample is scanned in a non-destructive, non-contact manner by means of an infrared thermographic system. The thermal image is shown on the monitor screen (Figure 1). Temperature differences in heat patterns as fine as 0.1°C are discernible instantly and represented by several pseudo color grades.

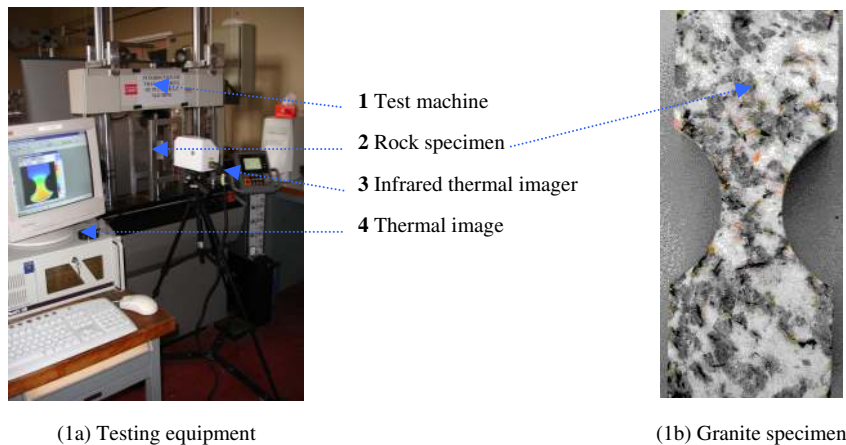


Figure 1. Experimental setup of infrared thermovision on rock specimen

Brittle geomaterials often present a very low thermomechanical conversion under monotonic loading. In addition the thermal image of the specimen is often affected by several other factors such as the induced heat of the loading machine system, the

undesired effects of the specimen ends, etc. This difficulty can be overcome when using thermal image subtraction or *differential thermography*. This procedure of thermal image processing readily evidences the manifestation of damage caused by the loading application between the two thermograms. The resulting image is a subtracted image showing the temperature change between two compared images, obtained under nearly identical test conditions, as shown in Figure 2. This thermal image processing provides quantitative values of dissipation. The damaged areas are precisely located and highlighted by heat patterns in pseudo colors.

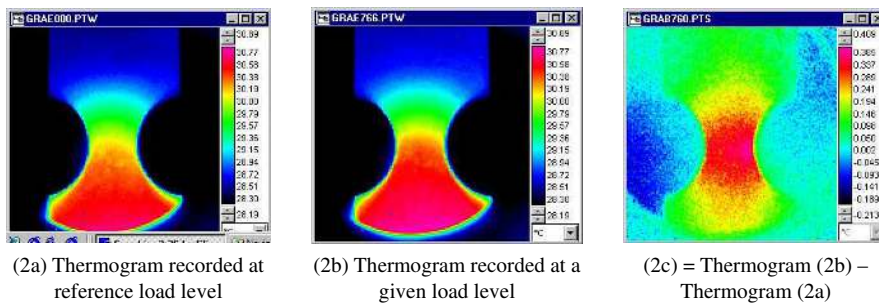


Figure 2. The differential infrared thermography enhances the localization of intrinsic dissipation (temperature changes are given in °C)

5 Experimental results

The proposed technique has been applied in the laboratory on two brittle rock specimens: Massif Central diorite (France) and Viseu granite (Portugal).

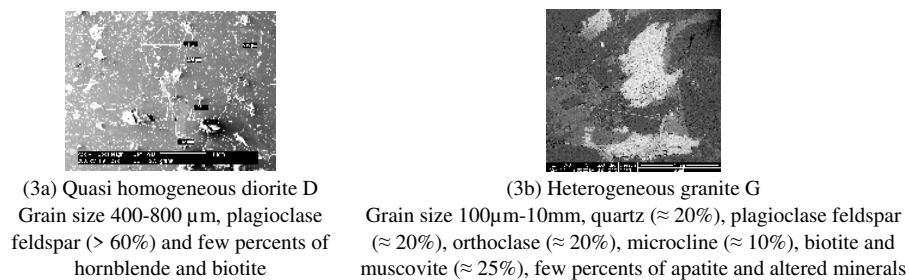


Figure 3. SEM (Scanning Electron Microscopy) images of the two specimens

The parameter investigated in this work is the heat generation due to the dissipative behavior of the material under loading. The thermal images are recorded when the uniaxial compressive loading is applied on the test specimen (Figure 4). The

contribution of the plasticity term is revealed by the rapid evolution of dissipation, evidencing the occurrence of damage caused by stress concentration in the central part of the specimen.

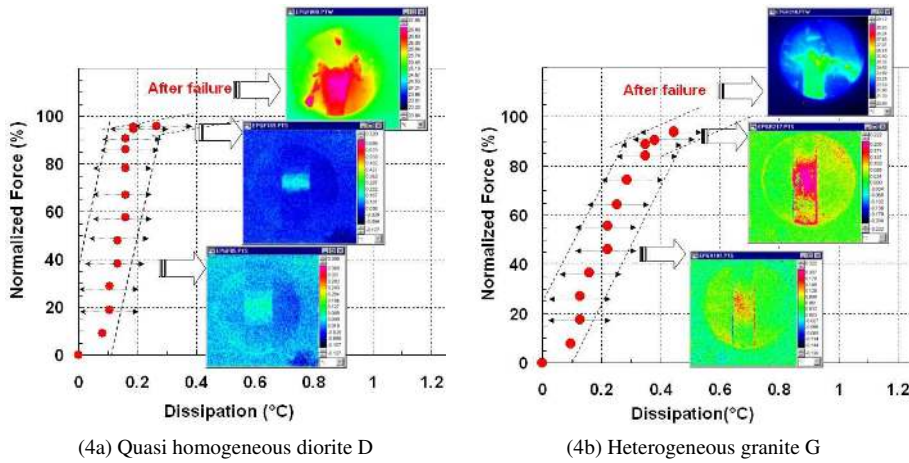


Figure 4. Different stages of heat dissipation describing the process of the damage extent in the specimen. Graphical determination of the threshold of acceptable damage TAD of tested materials subject to unconfined loading up to failure.

When the compressive loading is applied on the specimen up to failure, the results suggest a threshold of acceptable damage TAD, separating low and high regimes of dissipation or damage. This threshold TAD is readily determined graphically on figures (4a) and (4b) for diorite D and granite G owing to the change of slope of the experimental curve. Its value is consistent with characteristic data obtained from other testing techniques based on strain gages, acoustic emission AE or wave propagation phenomena (Figure 5) despite of their quite different nature.

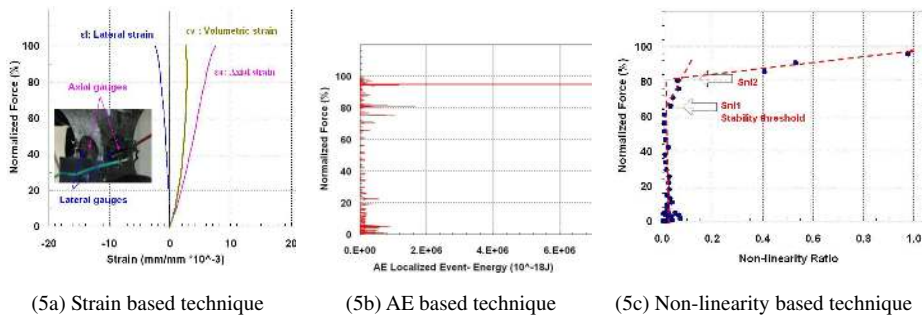


Figure 5. Experimental results obtained when using other testing techniques on brittle rock specimen.

6 Concluding remarks

This work has demonstrated that (1) the evolution of heat change facilitates the detection of damage extent in geomaterials (even for very brittle rocks) subjected to loading up to failure, and (2) the dissipative behavior of geomaterials under solicitations is a highly sensitive and accurate manifestation of damage.

Thanks to the thermomechanical coupling, the proposed differential infrared thermography offers a non-destructive, non-contact and real-time testing technique to observe quantitatively the dissipative mechanism of damage in geomaterials. It thus readily provides a measure of the material damage and allows the definition of a threshold of acceptable damage TAD under load beyond which the material is susceptible to failure.

The main interest of this energy approach is to unify microscopic and macroscopic test data. The parameter intrinsic dissipation under consideration is a scalar quantity, easy to evaluate accurately. Subsequently it may suggest multiaxial design criteria, highly relevant for full-scale testing on engineering rock structures.

In conjunction with others testing techniques based on quite different physical nature, the proposed differential infrared thermography promotes the possibility of investigating more thoroughly the mechanical behavior of brittle geomaterials up to failure from different physical points of view.

References

1. H. D. Bui, *Fracture Mechanics*, Springer, (2006).
2. J.W. Dougill, *Symp. Mech. Geomaterials*, NWU, Evanston USA 17-54 (1983).
3. M.P. Luong, *Comprehensive Rock Engineering*, Pergamon Press, **4**(26): 715-730 (1993).
4. S. Liu et al., *In. J. Rock Mech. & Min. Sci.*, **43**(6): 972-979 (2006).
5. L. Wu et al., *In. J. Rock Mech. & Min. Sci.* **43**(3):473-493 (2006).
6. L. Wu et al., *In. J. Rock Mech. & Min. Sci.* **39**(6): 825-831 (2002).
7. J. Kratochvil & O.W. Dillon, *J. Appl. Phys.*, **40**:3207-3218 (1969).
8. M.P. Luong, *Nuclear Engineering & Design*, **158**: 363-376 (1995).
9. M.P. Luong, *Infrared Physics & Technology*, **49**: 306-311 (2007).
10. M.P. Luong, *Materials in sports equipment*, WP-CRC, **2**(2): 35-59 (2007).