



**HAL**  
open science

# Unmasking The Magic of Magic Blue in Perovskite Doping

Zuzanna Molenda, Guillaume Wantz, Sylvain Chambon, Dario M Bassani,  
Lionel Hirsch

► **To cite this version:**

Zuzanna Molenda, Guillaume Wantz, Sylvain Chambon, Dario M Bassani, Lionel Hirsch. Unmasking The Magic of Magic Blue in Perovskite Doping. *Journal of Materials Chemistry C*, 2024, 10.1039/D4TC02149E . hal-04699928

**HAL Id: hal-04699928**

**<https://hal.science/hal-04699928v1>**

Submitted on 17 Sep 2024

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.




Distributed under a Creative Commons Attribution - NonCommercial 4.0 International License

# Journal of Materials Chemistry C

Materials for optical, magnetic and electronic devices

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: Z. Molenda, G. Wantz, S. Chambon, D. M. Bassani and L. Hirsch, *J. Mater. Chem. C*, 2024, DOI: 10.1039/D4TC02149E.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

## COMMUNICATION

## Unmasking The Magic of Magic Blue in Perovskite Doping

Zuzanna Molenda<sup>a,b</sup>, Guillaume Wantz<sup>a</sup>, Sylvain Chambon<sup>a</sup>, Dario M. Bassani<sup>b</sup>, Lionel Hirsch<sup>a</sup>Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

**The broader utilization of perovskite semiconductors in electronic devices is constrained by the inherent challenge of doping these materials. Magic Blue (tris(4-bromophenyl) ammoniumyl hexachloroantimonate) is a cationic salt which, once introduced in a polycrystalline film of methylammonium lead iodide (CH<sub>3</sub>NH<sub>3</sub>PbI<sub>3</sub> or MAPI) perovskite, increases by a maximum 30-fold conductivity and shifts the Fermi level by about 100 meV towards the valence energy. The latter is confirmed by surface potential measurements using Kelvin probe and ultraviolet photoelectron spectroscopy. The photoluminescence quenching of the doped samples confirms the presence of an excess of free charge carriers, while the optical bandgap remains unchanged. The doping mechanism most likely resembles molecular charge transfer doping, with the electron transfer from MAPI to the ammoniumyl cation residing at grain boundaries of the polycrystalline perovskite film.**

## 1. Introduction

The family of metal halide perovskites (MHPs) is a promising candidate for conceiving semiconductors for the next generation of electronic devices, with solar cells as their prime example<sup>1–6</sup>. Perovskite-based solar cells and LEDs reach efficiencies close to their thermodynamic limits<sup>7,8</sup> using charge selective contacts that allow mimicking the p-i-n or n-i-p device structure by employing contacts of different work functions and charge selective interlayers. The devices that employ classic semiconductors (Si, GaAs etc.) introduce p- and n-type dopants to achieve charge selectivity and induce a built-in potential. Perovskite doping would thereby allow to simplify device fabrication processes and open new application possibilities, such as field effect transistors, in which well-defined n- and p-

type zones are essential. Other advantages of this class of semiconductors include facile synthesis, inexpensive precursors, high defect tolerance<sup>9</sup> and bandgap tunability.

Perovskite doping, however, must overcome more obstacles than those found in classical semiconductors, notably due to the ionic character of the perovskite crystal and the electroneutrality of the precursor solutions. This implies that any heterovalent dopant is accompanied by the requisite number of counter ions that cancels out the potential doping effect. In addition, heterovalent dopants are unlikely to be incorporated in the crystal structure of the perovskite. So far, to the best of our knowledge, only one report of substitutional doping using a heterovalent element has been reported<sup>10</sup>, using Sm<sup>2+</sup> to replace Pb<sup>2+</sup> during the crystallization step, followed by its spontaneous oxidation to Sm<sup>3+</sup>. This results in the release of an electron to the conduction band of the material, leading to n-type doping. This approach requires a careful selection of the dopant, that must be metastable at the oxidation state 2+ to substitute Pb<sup>2+</sup> and stable at 3+ for n-type doping and 1+ for p-type doping. The radius of the doping ion should also be the closest possible to the one of the substituted metal.

Amongst recent reports on perovskite doping, the most common approach is inspired by the field of organic semiconductors and is based on electron transfer from the perovskite to the dopant for p-type and from the dopant to the perovskite for n-type<sup>11–16</sup> doping. Molecular charge transfer doping consists in adding a compound whose LUMO energy level is below that of the HOMO or valence energy ( $E_V$ ) of the host for p-type. This induces electron transfer from the  $E_V$  to the LUMO level, depleting the  $E_V$  of electrons which therefore increases the hole density and shifts the Fermi level ( $E_F$ ) towards  $E_V$ . The opposite is true for n-type doping. The dopant is typically an organic molecule much larger than the perovskite unit cell. Thus, the dopant is not incorporated within the perovskite crystalline domains and is instead located at grain boundaries or at the surface of the film. This type of doping has met with some success<sup>12,14</sup>, notably for the p-type doping of

<sup>a</sup> Univ. Bordeaux, CNRS, Bordeaux INP, IMS, UMR 5218, F-33400 Talence, France<sup>b</sup> Univ. Bordeaux, CNRS, Bordeaux INP, ISM UMR 5255, F-33400 Talence, France

† email: lionel.hirsch@ims-bordeaux.fr

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x



$\text{CH}_3\text{NH}_3\text{Pb}_{0.5}\text{Sn}_{0.5}\text{I}_3$ , using tetrafluorotricyanoquinine (F4TCNQ)<sup>11</sup>. This dopant possesses a LUMO level at  $-5.24$  eV that is well-suited for mixed-metal perovskites possessing high  $E_V$ . Efficient charge transfer is manifested in a conductivity increase of around 5 orders of magnitude upon doping. However, the same approach is inefficient for  $\text{CH}_3\text{NH}_3\text{PbI}_3$  as its  $E_V$  is higher, rendering electron transfer less likely. Considering that to date only lead-based perovskites exhibit reasonable device stability and efficiency, most of the doping study should concentrate on these materials.

A recently published work shows both p- and n-type molecular dopants of the  $\text{FA}_{0.75}\text{CS}_{0.25}\text{Pb}(\text{I}_{0.92}\text{Br}_{0.08})_3$ , introduced by the co-evaporation method<sup>15</sup>. However, as the authors report, it is difficult to achieve for the methylammonium-containing perovskites, as MAI precursor has been proven to be difficult to evaporate reliably due to its high vapor pressure and thermal instabilities<sup>17–19</sup>. Therefore, identifying a trasvelsal p-type dopant, suitable for many perovskite formulations and solution-processable, is still of significant importance.

Tris(4-bromophenyl) ammoniumyl hexachloroantimonate, also called Magic Blue (MB) has recently been living a renaissance as a dopant for organic semiconductors<sup>20–24</sup>. For instance, Feaugas et al.<sup>25</sup> used it as a dopant for the PTQ10:ITIC-4F blend, leading to an increase in conductivity and work function ( $WF$ ) for dopant concentrations  $>10\%$  (molar ratio). The doped layer serves as an efficient hole transporting layer, avoiding the use of hygroscopic PEDOT:PSS. Lee et al.<sup>26</sup> showed that MB can be incorporated between the organic spacers in the butylammonium-methylammonium lead iodide ( $\text{BA}_2\text{MA}_{n-1}\text{Pb}_{n+1}\text{I}_{3n+1}$ ) 2D Ruddelsen-Poppers perovskite. The study, although primarily centred on the 2D structure, opens a gateway to broader explorations within the domain of 3D perovskites. Herein, we report our investigation of the use of MB to dope MAPI, a 3D perovskite. Our findings not only shed light on the unique doping mechanisms in the 3D context, but also hint at potential applications and considerations for the 3D counterparts.

## 2. Methods

**Materials:** Methylammonium iodide ( $\text{CH}_3\text{CN}_3\text{I}$ ,  $> 4\text{N}$ ) was purchased from *GreatCell Solar Materials*. All the following precursors and solvent were purchased from Merck: lead(II) iodide ( $\text{PbI}_2$ , 99.999%, perovskite grade), tris(4-bromophenyl)ammoniumyl hexachloroantimonate ( $[(4\text{-BrC}_6\text{H}_4)_3\text{N}]\text{SbCl}_6$ , technical grade) was conserved in the glove box under inert atmosphere, *N,N*-dimethylformamide, anhydrous (98.8%).

**Substrates:** Glass substrates with patterned gold electrodes were used for the conductivity measurements. Glass substrates covered with a thin layer of ITO ( $10 \Omega \text{sq}^{-1}$ ) were selected for the measurements of the surface potential difference (Kelvin probe) and Ultraviolet photoelectron spectroscopy (UPS).

**Sample fabrication:** The substrates were cleaned in a sonication bath first with Hellmanex™ III solution (*Sigma Aldrich*) and in DI water for 15 minutes each, and then in isopropanol (4N) for 10 min. Subsequently, they were treated with UV-ozone for 15 minutes. Sample fabrication was performed under a controlled

nitrogen atmosphere in a glove box. The perovskite precursor solutions consisted of 1.5 M  $\text{PbI}_2$  and 1.5 M MAI dissolved in DMF by stirring at 60°C for around 20 min. The MB was dissolved in DMF with concentrations of 50 or 200 mg/mL by energetic shaking at RT right before adding the appropriate amount to the perovskite solutions in order to obtain 0.5 mL solutions with the MB/perovskite molar ratios of 0, 0.1%, 0.2%, 0.5%, 1% and 5%. The solutions were filtered through a 0.45  $\mu\text{m}$  PTFE filter and spin coated on appropriate substrates at a spin rate of 3000 rpm for 30 sec. After 5 s, 0.3 mL of diethyl ether was dropped onto the spinning substrate. The samples were then annealed on a hot plate for 10 min at 100 °C. The perovskite film thickness was around 600 nm. A 200 mg/mL MB solution was used to fabricate bare MB films by spin coating at 1000 rpm for 30 s. The films were then dried on a hot plate at 100°C for 10 min. The resulting films were around 20 nm thick. **Characterization:** Conductance was measured between two symmetric Ti/Au electrodes (10 and 50 nm, respectively) with the distance 200  $\mu\text{m}$  between them, deposited on the glass substrates using the electron beam evaporator. The perovskite layer was then spin coated on top of the electrodes. Conductivity was calculated from the  $IV$  curves of the 250 nm thick film spin-coated on the glass substrate with gold electrodes thermally evaporated on the top. The data was collected using a *Keithley 4200* source meter unit (SMU). The samples were scanned from  $-1$  V to 1 V at a rate of 5  $\text{mV s}^{-1}$ . The  $WF$  was measured using a Kelvin probe station from *Besocke Delta Phi*. Absorbance and photoluminescence spectra were recorded using a *Shimadzu UV-3600 Plus UV-Vis-NIR* spectrophotometer or a *Photon Technology International* setup, model: P21LRXS-LNN-NS-17, respectively. A *Bruker Innova NanoScope* instrument was used in a tapping mode to obtain AFM images of the sample's surface. UPS was performed with a *PHOIBOS 100* hemispherical energy analyzer equipped with a *SPECS UVS 10/35* light source. Conductance measurements were performed in a glovebox. Ultraviolet photoelectron spectra were obtained under vacuum with the samples transferred using a nitrogen-filled transfer box which was only opened in the measurement chamber when sufficient vacuum was obtained. AFM and surface potential difference were performed in air. Absorption and PL spectra were performed on encapsulated samples.

## 3. Results and discussion

The MB p-type doping was applied to 3D MAPI perovskite thin films as these have been widely studied. As a first assessment of the changes of the charge carrier density, we compared the conductivity of the undoped polycrystalline MAPI film with those of MB-doped films with concentration of 0.1% - 5%. The conductivity increase is observed already for the lowest concentration used (

Fig. 1) and it reaches the average of nearly 16-fold increase (from  $11.4 \pm 1.8$  nS/cm to  $180.3 \pm 42.7$  nS/cm) and the maximum 30-fold increase for 1% MB (from 8 nS/cm for the undoped to 240 nS/cm for 1% MB). At doping concentrations greater than 1%, the conductivity stabilizes, indicating a probable limit for this system.



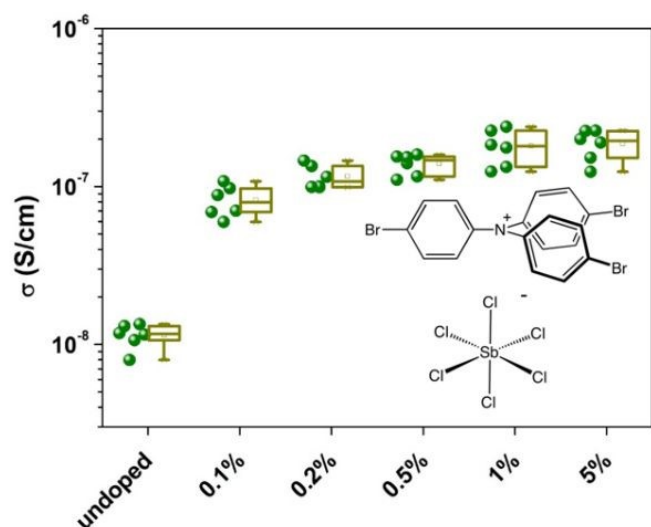


Fig. 1. Conductivity as a function of doping concentration.

To confirm the change in the majority carrier type, the *WF* of the undoped and doped MAPI, as well as that of the MB layer alone, was determined from the secondary cut-off of the UPS. The *WF* of the undoped MAPI film is 4.45 eV and increases to 4.57 eV for the 1% doping. This trend is confirmed by the surface potential measurements using a Kelvin probe, even though the values are higher by 0.5 eV for the perovskite samples and 0.2 eV for the MB film. This discrepancy stems probably from different ambient (air for the Kelvin probe vs. vacuum for the UPS), therefore traces of oxygen or water could adsorb to the sample surface, increasing its *WF*. Additionally, Kelvin probe is known to be sensitive to surface impurities and MB undergoes slow oxidative dimerization in the solid to form products that are also strong oxidants<sup>31</sup>. Nevertheless, both UPS and Kelvin probe confirm the increase of the *WF* of the doped perovskite upon doping. The *WF* of the MB at the level of 5.7 eV is in agreement with a previous study by Feaugas *et al.*<sup>25</sup>.

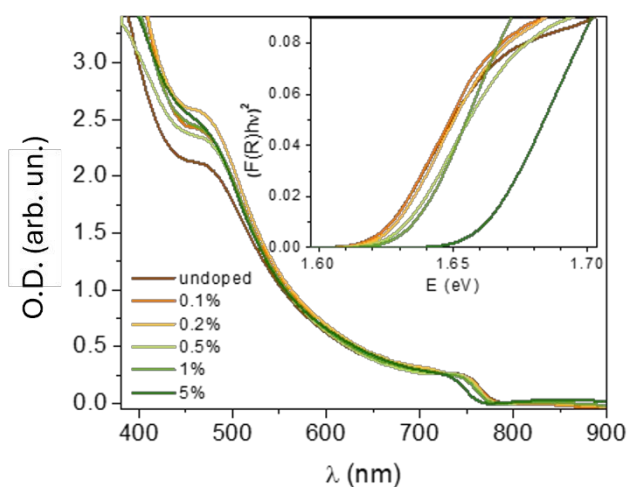


Fig. 2. UV-vis absorption spectra and Tauc plots in the inset.

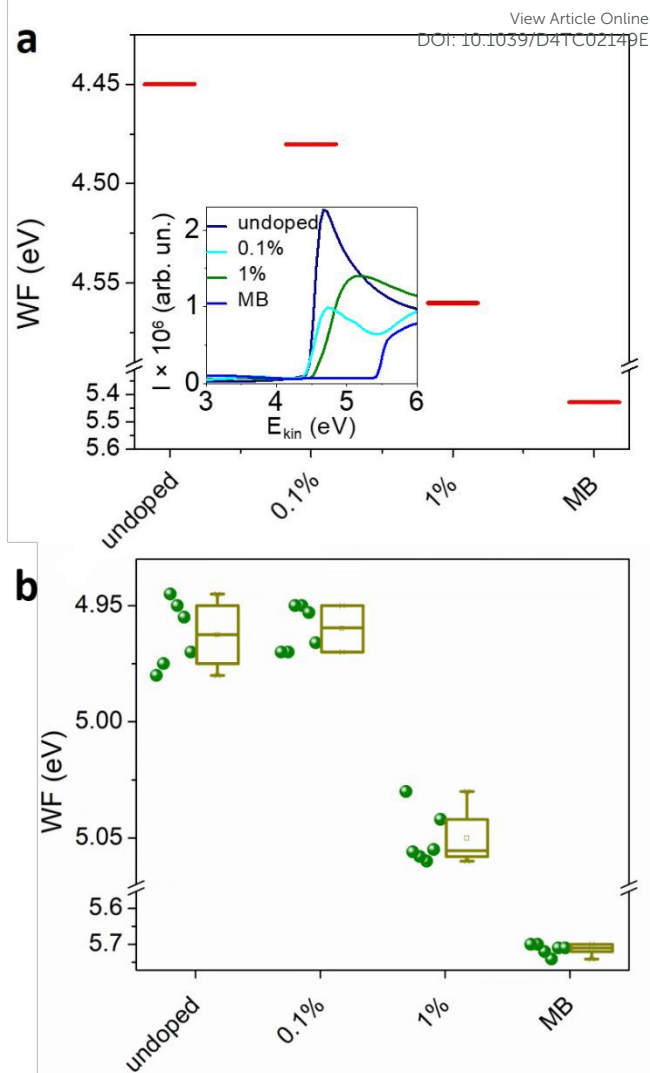


Fig. 3. *WF* determined from (a) UPS secondary cut-off and (b) surface potential difference measurement, using a Kelvin probe.

In order to confirm that the MB doping does not affect the bandgap of the perovskite, the absorbance spectra of the doped and undoped samples were compared. All the spectra are typical for MAPI, with comparable absorbance in the measured region. The bandgap ( $E_g$ ) determined from the Tauc plots are between 1.62 and 1.63 eV. A small bandgap widening ( $\sim 10$  meV) might be a result of the filling the shallow traps, just above the  $E_v$ , by the excess of holes, upon the doping. For 5% of MB the  $E_g$  increases to 1.66 eV. This result shows that the conductivity increase cannot be due to the presence of additional electronic states within the bandgap, nor due to the bandgap narrowing due to defects or lattice distortion.

Doping may be evidenced from the increase of the free charge carrier density, which may be indirectly deduced from photoluminescence (PL) measurements. The PL spectra of the undoped and doped MAPI are shown in Fig. 4. The maximum PL intensity falls at 765 nm for all the samples and this is in agreement with the bandgap value of MAPI. The average PL



signal is almost 3 times less intense upon doping with 0.1% MB and 7 and 6.5 times less intense for the doping concentration 0.5% and 1%, respectively. Our results are consistent with what is usually observed in doped semiconductors. Due to the presence of free charge carriers (here free holes), the lifetime shortening of minority carriers leads to a strong quenching of the luminescence<sup>27–29</sup>. For 5% MB, two weak peaks can be observed, one at 756 nm, belonging to MAPI, and another at 793 nm, that belongs to MB (Supporting Information). This information, together with the “saturation” of conductivity for 5% MB and the shift of the absorption edge, points to a possible phase separation for the highest doping concentrations.

perovskite thin film upon doping with MB can be clearly observed.

DOI: 10.1039/D4TC02149E

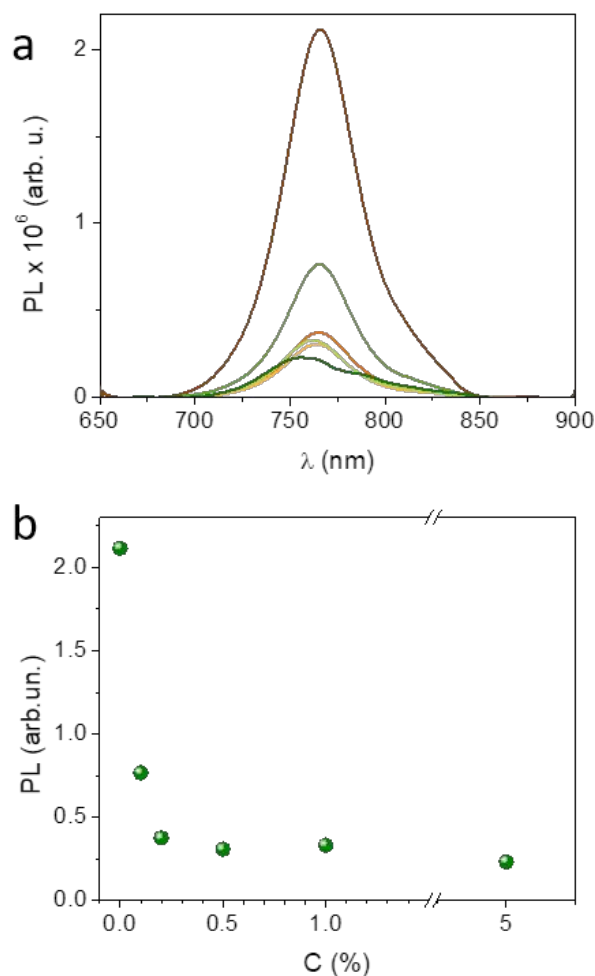


Fig. 4. Photoluminescence as a function of the doping concentration.

Ultraviolet photoelectron spectroscopy (UPS) allows investigation of the electronic properties of a semiconductor at its bandgap edges. Fig. 5a shows the onset of the valence energies for the doped and undoped samples. It can be seen that the energy with respect to the Fermi level ( $E$  w.r.t.  $E_F$ ) decreases by 0.1 eV upon doping with MB at 0.1% and 1%. This result is consistent with the increase of the WF found from the UPS cutoff and surface potential difference measurements (Fig. 2). Both HOMO and LUMO levels, together with the unaltered  $E_g$ , are presented in Fig. 5b, where the shift of the  $E_F$  of the

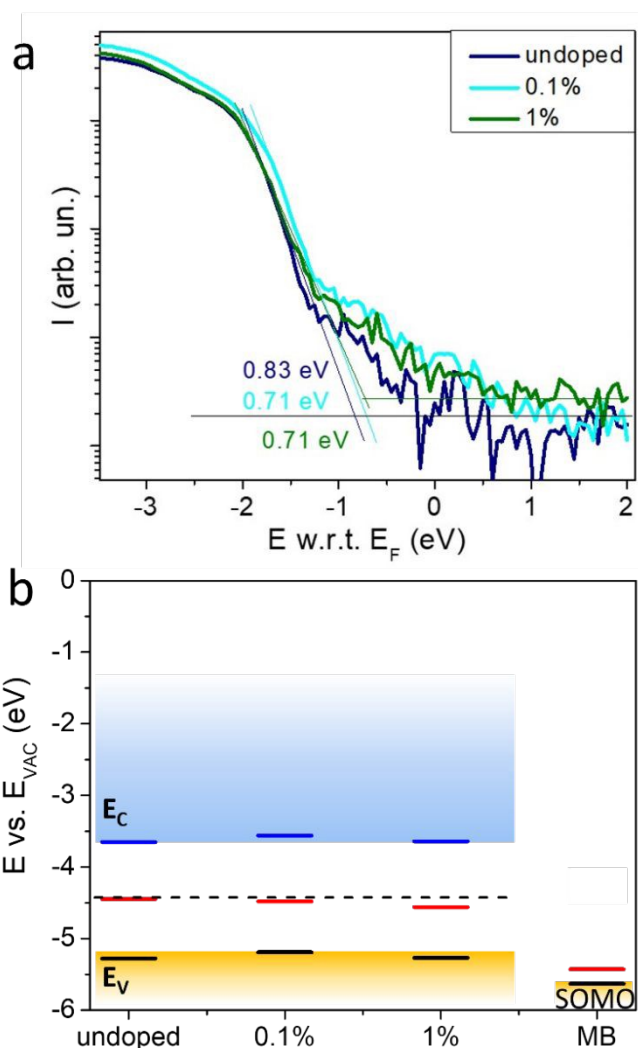


Fig. 5. a) Valence band region of the UPS spectra for undoped and doped MAPI. b)  $E_F$  shift upon doping with MB as well as the SOMO and  $E_F$  of a MB thin film. The SOMO level of MB is estimated from UPS assuming that it is the highest (partly) occupied molecular orbital.  $E_c$  and  $E_v$  represent the energy of the conduction and valence band of MAPI, respectively. Filled states are black, empty blue, and  $E_F$  red.

The UPS analysis was also carried-out for a thin film of pure MB. The latter evidences MB's strong electron-accepting character consistent with a high EA. The energy level of the Singly occupied molecular orbital (SOMO) determined from UPS (ca. 5.45eV, see Fig. 3) is not far from the value of the EA estimated by Zhang *et al.* using cyclic voltammetry (5.5 eV)<sup>30</sup>. This suggests that ionization of MB occurs from the SOMO or that its energy level is close to that of the highest fully-occupied molecular orbital from which ionization occurs (Fig S3).<sup>32</sup> The doping process of MAPI is therefore proposed to occur through electron transfer from the perovskite valence band ( $E_v = -5.3$  eV) to the partially-filled SOMO of the MB, leading to p-type doping of the perovskite. The driving force for electron transfer may be estimated to be ca.  $-0.3$  eV from the difference in ionization potential of MAPI and the EA of MB. In this context,



the doping mechanism exhibits similarities to molecular charge transfer doping previously reported by Euvrard *et al.*<sup>11</sup>. AFM images of the doped vs. undoped MAPI show that doping results in a modest decrease of the grain size (Fig. S2). Taking into account the size of the MB molecule, as well as the ionic character of the perovskite crystal, it is very likely that the dopant is located at the grain boundaries. This would limit electron transfer doping by MB to the interfacial intergrain region. The roll-off of the conductivity observed upon increasing the dopant level may therefore reflect the localized nature of the doping as well as the formation of reduced MB (an electrical insulator) in the intergrain region.

## Conclusions

We demonstrate a simple, spin-coating route for MAPI p-type doping, where tris(4-bromophenyl) ammoniumyl hexachloroantimonate, commonly known as Magic Blue, is blended into a polycrystalline perovskite film. The doping mechanism resembles the molecular charge transfer doping, where electron transfer takes place from the perovskite valence band to the HOMO level of the MB, rendering the perovskite p-type. The quenching of the MAPI's photoluminescence suggests the presence of free charges. The UPS measurement confirmed the shift of the MAPI's  $E_F$  towards the  $E_V$  by around 0.1 eV.

We believe that these results can shed light on how a careful selection of the dopant can influence and optimize the performance and properties of perovskite semiconductors, thereby advancing the development of more efficient and stable electronic devices. This still understudied field is soon expected to be flourishing, considering the possibility of the MHPs development towards energy-effective electronics.

## Author Contributions

GW proposed the dopant. ZM planned and performed the experiments, analysed the data and wrote the first draft of this article. All the authors participated in constructive discussions and the final version of this article.

## Conflicts of interest

There are no conflicts of interest to declare.

## Acknowledgements

The Agence Nationale de la Recherche (HYPER SOL project no. ANR-18-CE05-0021-01) and the Region Nouvelle Aquitaine (STRIPE project no. 2019-1R1M08) are gratefully acknowledged for their financial support. UPS analyses were made with the ELORPrintTec facility with the help of Roland Lefèvre.

## References

- 1 E. H. Anaraki, A. Kermanpur, L. Steier, K. Domanski, T. Matsui, W. Tress, M. Saliba, A. Abate, M. Grätzel, A.

- Hagfeldt and J.-P. Correa-Baena, *Energy Environ. Sci.*, 2016, **9**, 3128–3134. DOI: 10.1039/D4TC02149E
- D. B. Khadka, Y. Shirai, M. Yanagida, J. W. Ryan and K. Miyano, *J. Mater. Chem. C*, 2017, **5**, 8819–8827.
- D. Barrit, P. Cheng, M. C. Tang, K. Wang, H. Dang, D. M. Smilgies, S. Liu, T. D. Anthopoulos, K. Zhao and A. Amassian, *Adv. Funct. Mater.* 2019, **29**, 1807544.
- X. Bao, Y. Wang, Q. Zhu, N. Wang, D. Zhu, J. Wang, A. Yang and R. Yang, *J. Power Sources*, 2015, **297**, 53–58.
- J. V. Patil, S. S. Mali and C. K. Hong, *ACS Sustain. Chem. Eng.*, 2020, **8**, 16364–16371.
- Z. Molenda, S. Chambon, D. M. Bassani and L. Hirsch, *Eur. J. Inorg. Chem.*, 2021, **2021**, 2533–2538.
- J. Park, J. Kim, H. S. Yun, M. J. Paik, E. Noh, H. J. Mun, M. G. Kim, T. J. Shin and S. Il Seok, *Nature*, 2023, **616**, 724–730.
- M. A. Green, E. D. Dunlop, J. Hohl-Ebinger, M. Yoshita, N. Kopidakis, K. Bothe, D. Hinken, M. Rauer and X. Hao, *Prog. Photovoltaics Res. Appl.*, 2022, **30**, 687–701.
- D. H. Fabini, R. Seshadri and M. G. Kanatzidis, *MRS Bull.*, 2020, **45**, 467–477.
- Z. Molenda, B. Politi, R. Clerc, M. Abbas, S. Chambon, D. M. Bassani and L. Hirsch, *Mater. Horizons*, 2023, **10**, 2845–2853.
- J. Euvrard, O. Gunawan, X. Zhong, S. P. Harvey, A. Kahn and D. B. Mitzi, *Mater. Adv.*, 2021, **2**, 2956–2965.
- N. K. Noel, S. N. Habisreutinger, A. Pellaroque, F. Pulvirenti, B. Wenger, F. Zhang, Y. H. Lin, O. G. Reid, J. Leisen, Y. Zhang, S. Barlow, S. R. Marder, A. Kahn, H. J. Snaith, C. B. Arnold and B. P. Rand, *Energy Environ. Sci.*, 2019, **12**, 3063–3073.
- D. Parobek, B. J. Roman, Y. Dong, H. Jin, E. Lee, M. Sheldon and D. H. Son, *Nano Lett.*, 2016, **16**, 7376–7380.
- E. A. Gaulding, J. Hao, H. S. Kang, E. M. Miller, S. N. Habisreutinger, Q. Zhao, A. Hazarika, P. C. Sercel, J. M. Luther and J. L. Blackburn, *Adv. Mater.*, 2019, **31**, 1–9.
- T. Schramm, M. Deconinck, R. Ji, E. Siliavka, Y. J. Hofstetter, M. Löffler, V. V. Shilovskikh, J. Brunner, Y. Li, S. Bitton and others, *Adv. Mater.*, 2024, 2314289.
- Q. Ou, Y. Zhang, Z. Wang, J. A. Yuwono, R. Wang, Z. Dai, W. Li, C. Zheng, Z. Q. Xu, X. Qi, S. Duhm, N. V. Medhekar, H. Zhang and Q. Bao, *Adv. Mater.*, 2018, **30**, 1–10.
- J. Ávila, C. Momblona, P. P. Boix, M. Sessolo and H. J. Bolink, *Joule*, 2017, **1**, 431–442.
- S. Wang, L. K. Ono, M. R. Leyden, Y. Kato, S. R. Raga, M. V. Lee and Y. Qi, *J. Mater. Chem. A*, 2015, **3**, 14631–14641.
- E. J. Juarez-Perez, Z. Hawash, S. R. Raga, L. K. Ono and Y. Qi, *Energy & Environ. Sci.*, 2016, **9**, 3406–3410.
- S. Oh, P. H. Nguyen, T. M. Tran, A. J. DeStefano, K. Tagami, D. Yuan, A. Nikolaev, M. Condarcure, S. Han, J. R. de Alaniz and others, *J. Mater. Chem. C*, 2023, **11**, 15435–15442.
- K. Singh, A. A. Mohapatra, D. Giri, C. Gangadharappa, S. Jhulki, S. Barlow, S. R. Marder, A. Ghosh, S. Patil and N. Chauhan, *ACS Appl. Electron. Mater.*, 2023, **5**, 6765–6777.
- D. W. Burke, R. R. Dasari, V. K. Sangwan, A. K. Oanta, Z. Hirani, C. E. Pelkowski, Y. Tang, R. Li, D. C. Ralph, M. C. Hersam and others, *J. Am. Chem. Soc.*, 2023, **145**, 11969–11977.



## COMMUNICATION

Journal Name

- 23 S.-W. Kim, H. Jung, M. S. Okyay, H.-J. Noh, S. Chung, Y. H. Kim, J.-P. Jeon, B. M. Wong, K. Cho, J.-M. Seo and others, *Angew. Chemie Int. Ed.*, 2023, **62**, e202310560.
- 24 A. I. Hofmann, R. Kroon, S. Zokaei, E. Järsvall, C. Malacrida, S. Ludwigs, T. Biskup and C. Müller, *Adv. Electron. Mater.*, 2020, **6**, 1–8.
- 25 F. Feugas, T. Nicolini, G. H. Roche, L. Hirsch, O. J. Dautel and G. Wantz, *Sol. RRL*, 2023, **7**, 1–8.
- 26 J. Lee, K.-Y. Baek, J. Lee, H. Ahn, Y. Kim, H. Lim, Y. Kim, J. Woo, S. D. Stranks, S. K. Lee and others, *Adv. Funct. Mater.*, 2023, 2302048.
- 27 M. Liu, A. H. Kitai and P. Mascher, *J. Lumin.*, 1992, **54**, 35–42.
- 28 D. Kouyate, J. C. Ronfard-Haret, P. Valat, J. Kossanyi, U. Mammel and D. Oelkrug, *J. Lumin.*, 1990, **46**, 329–337.
- 29 M. Leroux, N. Grandjean, B. Beaumont, G. Nataf, F. Semond, J. Massies and P. Gibart, *Phys. Status Solidi Basic Res.*, 1999, **216**, 605–608.
- 30 S. Zhang, H. M. Hill, K. Moudgil, C. A. Ritcher, A. R. Hight Walker, S. Barlow, S. R. Marder, C. A. Hacker, S. J. Pookpanratana, *Adv. Mater.*, 2018, **30**, 1802991.
- 31 M. R. Talipov, M. M. Hossain, A. Boddeda, K. Thakur and R. Rathore, *Org. & Biomolec. Chem.*, 2016, **14**, 2961-2968.
- 32 S. Kasemthaveechok, L. Abella, J. Crassous, J. Autschbach and L. Favereau, *Chem. Sci.*, 2022, **13**, 9833-9847.

View Article Online  
DOI: 10.1039/D4TC02149E

Open Access Article. Published on 12 September 2024. Downloaded on 9/17/2024 10:43:09 AM.  
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.



Journal of Materials Chemistry C Accepted Manuscript



## Data Availability Statement

View Article Online  
DOI: 10.1039/D4TC02149E

The data supporting this article have been included as part of the Supplementary Information.

