



HAL
open science

Three-dimensional Green tensor of one-dimensional hexagonal quasicrystals

Markus Lazar, Thomas M. Michelitsch, Eleni Agiasofitou

► **To cite this version:**

Markus Lazar, Thomas M. Michelitsch, Eleni Agiasofitou. Three-dimensional Green tensor of one-dimensional hexagonal quasicrystals. *Crystals*, 2024, 14 (12), pp.1034. 10.3390/cryst14121034 . hal-04798496

HAL Id: hal-04798496

<https://hal.science/hal-04798496v1>

Submitted on 22 Nov 2024

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution 4.0 International License

Article

Three-dimensional Green tensor of one-dimensional hexagonal quasicrystals

Markus Lazar ^{1,*} , Thomas Michelitsch ²  and Eleni Agiasofitou ¹ 

¹ Institute for Mechanics, Technical University of Darmstadt, D-64287 Darmstadt, Germany; eleni.agiasofitou@tu-darmstadt.de

² Sorbonne Université, Institut Jean le Rond d'Alembert, CNRS UMR 7190, 4 place Jussieu, 75252 Paris cedex 05, France; michel@lmm.jussieu.fr

* Correspondence: markus.lazar1@tu-darmstadt.de

Abstract: In this work, the elastic 4×4 Green tensor of one-dimensional quasicrystals is given and has phonon, phason and phonon-phason coupling components. Using the residue method, a closed-form expression of the elastic 4×4 Green tensor for one-dimensional hexagonal quasicrystals of Laue class 10, which possess 10 independent material constants, is derived. The 10 independent components of the obtained 4×4 Green tensor are numerically presented in contour plots revealing features of anisotropy as well as the interesting result that the phason component of the Green tensor has the strongest contribution in comparison with all the other components. In the case of vanishing phonon-phason coupling, the phonon part of the derived Green tensor reproduces Kröner's well-known elastic 3×3 Green tensor for hexagonal crystals. The analytical closed-form expression of the derived Green tensor provides an advantage for efficient computational calculations in various applications.

Keywords: quasicrystals; Green tensor; one-dimensional hexagonal quasicrystals; residue method



Citation: Lazar, M.; Michelitsch, T.; Agiasofitou, E. Three-dimensional Green tensor of one-dimensional hexagonal quasicrystals. *Crystals* **2024**, *1*, 0. <https://doi.org/>

Academic Editor: Firstname Lastname

Received: 29 October 2024

Revised:

Accepted:

Published:



Copyright: © 2024 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Quasicrystals belong to aperiodic crystals and possess long-range orientational order but no translational symmetry in the quasiperiodic directions [1]. Their special features provide them with unique properties such as low friction coefficient [2], low adhesion [3] and high wear resistance [4], which are desired in various applications in technology. Nowadays, quasicrystals belong to new or novel materials enjoying the interest for their theoretical and experimental study as well as their potential use in many technological devices [5].

The basis of the continuum theory of solid quasicrystals is set up by two elementary excitations; the phonons and the phasons [6,7]. In the atomistic picture, phonons are related to the translation of atoms and phasons lead to local rearrangements of atoms in a cell. A systematic and comprehensive overview concerning the study of generalized elasticity of quasicrystals and their defects has been given by Fan [8]. There are three types of quasicrystals: one-, two- and three-dimensional quasicrystals. One-dimensional quasicrystals are an important class of quasicrystals (see [8–13]). In one-dimensional quasicrystals, there is a quasiperiodic arrangement of atoms in one direction, usually in z -direction, and a regular periodic arrangement of atoms in the plane perpendicular to this direction, that is in the xy -plane. One-dimensional quasicrystals are quasicrystals with crystallographic symmetries, namely 31 point groups and 10 Laue classes [9]. One-dimensional hexagonal quasicrystals are divided in two Laue classes: Laue class 9 and Laue class 10. As it was pointed out in Agiasofitou and Lazar [14], a distinction has to be made between the two Laue classes concerning the material moduli and the constitutive relations, a fact that is often ignored in the literature of elasticity theory of one-dimensional hexagonal quasicrystals. Specifically, the constitutive relations of one-dimensional hexagonal quasicrystals of Laue class 9 are different than that of one-dimensional hexagonal quasicrystals of Laue class 10, since the former possess 11 material moduli and the latter possess 10 material moduli [14].

From the point of view of generalized elasticity of quasicrystals, Lazar and Agiasofitou [13] using rotational transformations have examined the corresponding isotropy condition and proved that a one-dimensional hexagonal quasicrystal of Laue class 10 is isotropic in the basal xy -plane.

Green functions are the fundamental solutions of linear partial differential equations [15–17] and play an important role in the solution of many problems in various scientific areas like applied mathematics, physics, engineering science and material science. If the differential operator entering the partial differential equation is a scalar one, then we speak of a Green function, whereas if it is a tensorial one, then we speak of a Green tensor. For isotropic materials, the elastic Green tensor was derived by Lord Kelvin [18]. For general anisotropy, Fredholm [19] deduced the form of the elastic Green tensor in terms of the roots of a sextic algebraic equation. An integral expression for the elastic Green tensor has been given by Lifshitz and Rosenzweig [20] and Synge [21] (see also [22,23]) for general anisotropy. As far as elasticity is concerned, a hexagonal medium is equivalent to a transversely isotropic medium. A fact which is important to find closed-form expressions for an elastic Green tensor. The closed-form expression for the elastic Green tensor of a hexagonal medium has been explicitly calculated by Lifshitz and Rosenzweig [20], Kröner [24] and Willis [25] (see also [26,27]). In particular, Kröner [24] used the algebraic method of Fredholm [19]. Willis [25] evaluated the elastic Green tensor from the contour integral representation given by Synge [21] for a transversely isotropic medium and pointed out some important misprints in the results of Kröner [24]. Moreover, Willis [25] gave a proof of the equivalence of the integral expression given by Synge [21] to the result of Fredholm [19] which was utilized by Kröner [24]. Note that only for isotropic and hexagonal crystals, closed-form expressions of the elastic Green tensor exist (see [20,22–24]). As a generalization of the elastic 3×3 Green tensor for hexagonal materials, the 4×4 Green tensor for hexagonal piezoelectric crystals of point group $6mm$, which is a transversely isotropic medium, has been derived by Michelitsch [28] (see also [29]) from the integral expression of the 4×4 Green tensor for general piezoelectric media given by Deeg [30], Chen [31] and Dunn [32]. Only for hexagonal piezoelectric crystals of point group $6mm$, a closed-form expression of the 4×4 piezoelectric Green tensor can be derived. In the present paper, we consider the class of one-dimensional quasicrystals which have in a continuum setting an analogous constitutive behavior as a piezoelectric crystal of transversely isotropic symmetry (see also [14]), that are one-dimensional hexagonal quasicrystals of Laue class 10.

Concerning Green functions in quasicrystals, De and Pelcovits [33] found the two-dimensional Green functions for pentagonal quasicrystals and Ding *et al.* [34] found the explicit expressions of two-dimensional Green tensors for various forms of planar quasicrystals. Bachteler and Trebin [35] gave an approximative solution for the elastic Green tensor of three-dimensional icosahedral quasicrystals, assuming that the coupling between phonons and phasons is small. Lazar and Agiasofitou [36] derived the generalized three-dimensional elastic Green tensor for arbitrary quasicrystals, that is, for one-dimensional, two-dimensional and three-dimensional quasicrystals. The Green function for constrained cubic quasicrystals has been given by Zhang *et al.* [37]. Moreover, the generalized three-dimensional Green tensor for arbitrary piezoelectric quasicrystals has been recently given by Lazar and Agiasofitou [38]. Three-dimensional general solutions for static problems in thermo-elasticity of one-dimensional hexagonal quasicrystals have been given by Li and Li [39].

The aim of this work is to derive an analytical closed-form expression of the elastic 4×4 Green tensor for one-dimensional hexagonal quasicrystals of Laue class 10 using the integral representation of the Green tensor in Synge form given by Lazar and Agiasofitou [36] and applying the residue method. As it has been shown by Willis [25] and Michelitsch [28], the residue method is a useful tool to obtain closed-form expressions of the Green tensors in media with hexagonal symmetry. The residue calculus method can also be used for the numerical evaluation of the Green tensor and its derivatives for generally anisotropic materials as well as for piezoelectric materials (see, e.g., [40–44]).

The paper is organized as follows. In section 2, the basic equations for one-dimensional quasicrystals are given and a suitable hyperspace notation is employed in order to derive

the Green tensor for one-dimensional quasicrystals in section 3. The 10 independent elastic constants of one-dimensional hexagonal quasicrystals of Laue class 10 together with the conditions of positive definiteness are given in section 4. The Green tensor for one-dimensional hexagonal quasicrystals of Laue class 10 is derived in section 5 with the residue method. In section 6, the 10 components of the Green tensor for one-dimensional hexagonal quasicrystals of Laue class 10 are plotted in contour plots. Conclusions are given in section 7. The limit of the obtained Green tensor of one-dimensional hexagonal quasicrystals of Laue class 10 to the Green tensor of hexagonal crystals is given in the Appendix A.

2. Basic equations of one-dimensional quasicrystals

In this section, we provide the basic equations of the generalized elasticity theory of one-dimensional quasicrystals necessary for the forthcoming calculations with focus on the hyperspace notation, which is appropriate for the representation of the phonon and phason fields in the corresponding extended field "living" in the hyperspace.

A one-dimensional quasicrystal can be generated by the projection of a four-dimensional periodic structure to the three-dimensional physical space. The four-dimensional hyperspace E^4 can be decomposed into the direct sum of two orthogonal subspaces

$$E^4 = E_{\parallel}^3 \oplus E_{\perp}^1, \quad (1)$$

where E_{\parallel}^3 is the three-dimensional physical or parallel space of the phonon fields and E_{\perp}^1 is the one-dimensional perpendicular space of the phason fields with quasiperiodicity in z-direction. Throughout the text, phonon fields will be denoted by $(\cdot)^{\parallel}$ and phason fields by $(\cdot)^{\perp}$. Note that all quantities (phonon and phason fields) depend on the so-called material space coordinates $x \in \mathbb{R}^3$. Indices in the parallel space are denoted by small letters i, j, k, l with $i, j, k, l = 1, 2, 3$.

In the theory of generalized elasticity of one-dimensional quasicrystals, the *phonon displacement field* is denoted by $u_k^{\parallel} \in E_{\parallel}^3$, $k = 1, 2, 3$ and the *phason displacement field*, which is in z-direction, is denoted by $u_3^{\perp} \in E_{\perp}^1$. That is, for one-dimensional quasicrystals the phason displacement field is a scalar field. That is the reason that there is a mathematical analogy between one-dimensional quasicrystals and piezoelectric crystals. The *phonon and phason distortion tensors*, β_{kl}^{\parallel} and β_{3l}^{\perp} , are defined as the spatial gradients of u_k^{\parallel} and u_3^{\perp} , respectively

$$\beta_{kl}^{\parallel} = \partial_l u_k^{\parallel}, \quad (2)$$

$$\beta_{3l}^{\perp} = \partial_l u_3^{\perp}, \quad (3)$$

where $\partial_l = \partial/\partial x_l$ indicates the derivative with respect to the spatial coordinates x_l . The equilibrium conditions are of the form (see, e.g., [45,46])

$$\partial_j \sigma_{ij}^{\parallel} + f_i^{\parallel} = 0, \quad (4)$$

$$\partial_j \sigma_{3j}^{\perp} + f_3^{\perp} = 0, \quad (5)$$

where σ_{ij}^{\parallel} denotes the *phonon stress tensor*, σ_{3j}^{\perp} are the *phason stresses*, f_i^{\parallel} is the *phonon body force density* and f_3^{\perp} is the *phason body force density*. The phonon stress tensor is a symmetric tensor of rank two: $\sigma_{ij}^{\parallel} = \sigma_{ji}^{\parallel}$.

The associated linear constitutive relations between the stresses and distortions are

$$\sigma_{ij}^{\parallel} = C_{ijkl} e_{kl}^{\parallel} + D_{ij3l} \beta_{3l}^{\perp}, \quad (6)$$

$$\sigma_{3j}^{\perp} = D_{kl3j} e_{kl}^{\parallel} + E_{3j3l} \beta_{3l}^{\perp}, \quad (7)$$

where C_{ijkl} is the tensor of the elastic moduli of phonons, E_{3j3l} is the tensor of the elastic moduli of phasons and D_{ij3l} is the tensor of the elastic moduli of the phonon-phason coupling for one-dimensional quasicrystals. The constitutive tensors possess the following *major symmetries* (see [45])

$$C_{ijkl} = C_{klij}, \quad E_{3j3l} = E_{3l3j} \quad (8)$$

and *minor symmetries*

$$C_{ijkl} = C_{jikl} = C_{ijlk}, \quad D_{ij3l} = D_{ji3l}. \quad (9)$$

Substituting Eqs. (6), (7), (2) and (3) into Eqs. (4) and (5), we obtain the *coupled inhomogeneous Navier equations for the phonon and phason displacement fields*

$$C_{ijkl} \partial_j \partial_l u_k^{\parallel} + D_{ij3l} \partial_j \partial_l u_3^{\perp} = -f_i^{\parallel}, \quad (10)$$

$$D_{kl3j} \partial_j \partial_l u_k^{\parallel} + E_{3j3l} \partial_j \partial_l u_3^{\perp} = -f_3^{\perp}. \quad (11)$$

A major tool used in deriving the results of later sections in this article is the *hyperspace notation of quasicrystals* introduced by Lazar and Agiasofitou [36], so that the phonon and phason fields can be unified in the corresponding *extended field in the hyperspace*. The components of the extended fields will be denoted by capital letters, e.g., $I, K = 1, 2, 3, 4$. In the hyperspace notation, the following extended fields can be defined:

- The *extended displacement vector* $U_K = (u_k^{\parallel}, u_3^{\perp}) \in E_{\parallel}^3 \oplus E_{\perp}^1$

$$U_K = \begin{cases} u_k^{\parallel}, & K = 1, 2, 3, \\ u_3^{\perp}, & K = 4. \end{cases} \quad (12)$$

- The *extended elastic distortion tensor* $B_{KI} \in (E_{\parallel}^3 \oplus E_{\perp}^1) \otimes E_{\parallel}^3$

$$B_{KI} = \begin{cases} \beta_{kl}^{\parallel}, & K = 1, 2, 3, \\ \beta_{3l}^{\perp}, & K = 4. \end{cases} \quad (13)$$

- The *extended stress tensor* $\Sigma_{Ij} \in (E_{\parallel}^3 \oplus E_{\perp}^1) \otimes E_{\parallel}^3$

$$\Sigma_{Ij} = \begin{cases} \sigma_{ij}^{\parallel}, & I = 1, 2, 3, \\ \sigma_{3j}^{\perp}, & I = 4. \end{cases} \quad (14)$$

- The *extended body force vector* $F_I = (f_i^{\parallel}, f_3^{\perp}) \in E_{\parallel}^3 \oplus E_{\perp}^1$

$$F_I = \begin{cases} f_i^{\parallel}, & I = 1, 2, 3, \\ f_3^{\perp}, & I = 4. \end{cases} \quad (15)$$

- The *tensor of the extended elastic moduli* $C_{IjKI} \in (E_{\parallel}^3 \oplus E_{\perp}^1) \otimes E_{\parallel}^3 \otimes (E_{\parallel}^3 \oplus E_{\perp}^1) \otimes E_{\parallel}^3$

$$C_{IjKI} = \begin{cases} C_{ijkl}, & I = 1, 2, 3; \quad K = 1, 2, 3, \\ D_{ij3l}, & I = 1, 2, 3; \quad K = 4, \\ D_{kl3j}, & I = 4; \quad K = 1, 2, 3, \\ E_{3j3l}, & I = 4; \quad K = 4. \end{cases} \quad (16)$$

The tensor C_{IjKI} retains the *major symmetry*

$$C_{IjKI} = C_{KlIj}. \quad (17)$$

In matrix form, Eq. (16) reads

$$C_{IjKl} = \begin{pmatrix} C_{ijkl} & D_{ij3l} \\ D_{kl3j} & E_{3j3l} \end{pmatrix}. \quad (18)$$

Using the hyperspace notation and the above introduced extended fields, the basic equations of one-dimensional quasicrystals can be rewritten in a "compact" form as follows. Eqs. (2) and (3) can be written as

$$B_{Kl} = \partial_l U_K. \quad (19)$$

The equilibrium conditions (4) and (5) read

$$\partial_j \Sigma_{Ij} + F_I = 0 \quad (20)$$

with the constitutive relations (6) and (7) to be given by

$$\Sigma_{Ij} = C_{IjKl} B_{Kl}. \quad (21)$$

Eqs. (10) and (11) read in terms of the extended displacement vector U_K

$$C_{IjKl} \partial_j \partial_l U_K + F_I = 0. \quad (22)$$

Eq. (22) is a Navier-type partial differential equation for the extended displacement vector U_K .

3. Three-dimensional Green tensor for one-dimensional quasicrystals

In this section, we derive the three-dimensional Green tensor for one-dimensional quasicrystals in an integral form expression.

Introducing the Navier-type differential operator in the hyperspace

$$\mathcal{T}_{IK}(\nabla) = C_{IjKl} \partial_j \partial_l \quad (23)$$

with $\mathcal{T}_{IK}(\nabla) = \mathcal{T}_{KI}(\nabla)$ due to the major symmetry of C_{IjKl} , Eq. (17), the field equation (22) becomes

$$\mathcal{T}_{IK}(\nabla) U_K + F_I = 0, \quad (24)$$

where ∇ indicates the gradient operator. The symmetric 4×4 second-order differential operator $\mathcal{T}_{IK}(\nabla)$ can be written in the form

$$\mathcal{T}_{IK}(\nabla) = \begin{pmatrix} T_{ik}(\nabla) & t_i(\nabla) \\ t_k(\nabla) & \tau(\nabla) \end{pmatrix}, \quad (25)$$

where $T_{ik}(\nabla)$ is a 3×3 tensor operator given by

$$T_{ik}(\nabla) = C_{ijkl} \partial_j \partial_l, \quad (26)$$

which represents the phonon part, $t_i(\nabla)$ is a (3×1) vector operator given by

$$t_i(\nabla) = D_{ij3l} \partial_j \partial_l, \quad (27)$$

which represents the phonon-phason coupling part and τ is the (1×1) scalar operator given by

$$\tau(\nabla) = E_{3j3l} \partial_j \partial_l, \quad (28)$$

which describes the phason part.

The vector field U_K can then be represented by the elastic 4×4 Green tensor G_{KM} of one-dimensional quasicrystals according to

$$U_K(\mathbf{r}) = \int_{\mathbb{R}^3} \mathcal{G}_{KM}(\mathbf{R}) F_M(\mathbf{r}') d\mathbf{r}', \quad (29)$$

where $\mathbf{R} = \mathbf{r} - \mathbf{r}'$. The elastic 4×4 Green tensor \mathcal{G}_{KM} of one-dimensional quasicrystals is defined by

$$\mathcal{T}_{IK}(\nabla) \mathcal{G}_{KM}(\mathbf{r}) + \delta_{IM} \delta(\mathbf{r}) = 0, \quad (30)$$

where $\delta(\mathbf{r})$ is the three-dimensional Dirac delta function and δ_{IM} denotes the 4×4 unit matrix. Note that the Green tensor $G_{KM}(\mathbf{R})$ is a symmetric tensor of rank two in the hyperspace. This property follows from the symmetry of the differential operator $\mathcal{T}_{IK}(\nabla) = \mathcal{T}_{KI}(\nabla)$ in Eq. (23).

The elastic 4×4 Green tensor $\mathcal{G}_{KM}(\mathbf{R})$ ($K, M = 1, 2, 3, 4$) of one-dimensional quasicrystals can be decomposed into its phonon, phason and phonon-phason coupling parts

$$\mathcal{G}_{KM}(\mathbf{R}) = \begin{pmatrix} G_{km}^{\parallel\parallel}(\mathbf{R}) & G_{k4}^{\parallel\perp}(\mathbf{R}) \\ G_{4m}^{\perp\parallel}(\mathbf{R}) & G_{44}^{\perp\perp}(\mathbf{R}) \end{pmatrix} \quad (31)$$

or explicitly

$$\mathcal{G}_{KM} = \begin{pmatrix} G_{11}^{\parallel\parallel} & G_{12}^{\parallel\parallel} & G_{13}^{\parallel\parallel} & G_{14}^{\parallel\perp} \\ G_{12}^{\parallel\parallel} & G_{22}^{\parallel\parallel} & G_{23}^{\parallel\parallel} & G_{24}^{\parallel\perp} \\ G_{13}^{\parallel\parallel} & G_{23}^{\parallel\parallel} & G_{33}^{\parallel\parallel} & G_{34}^{\parallel\perp} \\ G_{14}^{\perp\parallel} & G_{24}^{\perp\parallel} & G_{34}^{\perp\parallel} & G_{44}^{\perp\perp} \end{pmatrix} \quad (32)$$

and it has the following physical interpretation [36]:

$G_{km}^{\parallel\parallel}(\mathbf{R})$ is the phonon displacement at \mathbf{r} in the x_k -direction due to a unit phonon point force at \mathbf{r}' in the x_m -direction, $k, m = 1, 2, 3$;

$G_{k4}^{\parallel\perp}(\mathbf{R})$ is the phonon displacement at \mathbf{r} in the x_k -direction due to a unit phason point force at \mathbf{r}' in the x_3 -direction, $k = 1, 2, 3$;

$G_{4m}^{\perp\parallel}(\mathbf{R})$ is the phason displacement at \mathbf{r} in the x_3 -direction due to a unit phonon point force at \mathbf{r}' in the x_m -direction, $m = 1, 2, 3$;

$G_{44}^{\perp\perp}(\mathbf{R})$ is the phason displacement at \mathbf{r} in the x_3 -direction due to a unit phason point force at \mathbf{r}' in the x_3 -direction.

Using Fourier transform, the *elastic 4×4 Green tensor of arbitrary anisotropic one-dimensional quasicrystals* in integral form reads (at $\mathbf{r}' = 0$) [36]

$$\mathcal{G}_{KM}(\mathbf{r}) = \frac{1}{8\pi^2 r} \int_0^{2\pi} \mathcal{T}_{KM}^{-1}(\boldsymbol{\zeta}(\phi)) d\phi. \quad (33)$$

The integral is taken around the unit circle ($\boldsymbol{\zeta}^2 = 1$) in the plane normal to \mathbf{r} . $\mathcal{T}_{IK}(\boldsymbol{\zeta})$ is obtained from Eq. (25) by replacing ∂_i by ζ_i ($i = 1, 2, 3$) in Eqs. (26), (27) and (28) and it reads

$$\mathcal{T}_{IK}(\boldsymbol{\zeta}) = C_{Ijkl} \zeta_j \zeta_l = \begin{pmatrix} C_{ijkl} \zeta_j \zeta_l & D_{ij3l} \zeta_j \zeta_l \\ D_{kl3j} \zeta_j \zeta_l & E_{3j3l} \zeta_j \zeta_l \end{pmatrix}. \quad (34)$$

The vector $\boldsymbol{\zeta}$ can be represented as [22,28,47]

$$\boldsymbol{\zeta}(\phi) = \mathbf{e}_1 \cos \phi + \mathbf{e}_2 \sin \phi, \quad (35)$$

where the vectors \mathbf{e}_i form a useful orthonormal basis

$$\mathbf{e}_1 = \frac{1}{\rho} \begin{pmatrix} -y \\ x \\ 0 \end{pmatrix}, \quad \mathbf{e}_2 = \frac{1}{\rho r} \begin{pmatrix} -zx \\ -zy \\ \rho^2 \end{pmatrix}, \quad \mathbf{e}_3 = \frac{1}{r} \begin{pmatrix} x \\ y \\ z \end{pmatrix} \quad (36)$$

with $\rho^2 = x^2 + y^2$, $r^2 = \rho^2 + z^2$ and $\mathbf{r} = r\mathbf{e}_3$. The orientation of this coordinate system can be expressed by $\mathbf{e}_i = \frac{1}{2}\epsilon_{ijk}\mathbf{e}_j \times \mathbf{e}_k$, where ϵ_{ijk} denotes the three-dimensional Levi-Civita tensor.

4. Elastic moduli of one-dimensional hexagonal quasicrystals of Laue class 10

In this section, one-dimensional hexagonal quasicrystals of Laue class 10 are considered. Regarding generalized elasticity of quasicrystals, a one-dimensional hexagonal quasicrystal of Laue class 10 is a transversely isotropic medium. Specifically, a one-dimensional hexagonal quasicrystal of Laue class 10 is isotropic in the basal xy -plane (see [13]). Laue class 10 consists of the following point groups [8]: 62_h2_h , $6mm$, $\bar{6}m2_h$, $6/m_hmm$.

The one-dimensional hexagonal quasicrystals of Laue class 10 possess 10 independent elastic constants (see [9]):

- 5 independent elastic moduli of phonons

$$\begin{aligned} C_{1111} = C_{2222} = C_{11}, \quad C_{1122} = C_{2211} = C_{12}, \quad C_{1133} = C_{2233} = C_{3311} = C_{3322} = C_{13}, \\ C_{3333} = C_{33}, \quad C_{2323} = C_{2332} = C_{3223} = C_{3232} = C_{1313} = C_{1331} = C_{3113} = C_{3131} = C_{44}, \\ C_{1212} = C_{1221} = C_{2112} = C_{2121} = C_{66} = (C_{11} - C_{12})/2 \end{aligned} \quad (37)$$

- 3 independent elastic moduli of phonon-phason coupling

$$D_{1133} = D_{2233} = R_1, \quad D_{3333} = R_2, \quad D_{3232} = D_{2332} = D_{3131} = D_{1331} = R_3 \quad (38)$$

- 2 independent elastic moduli of phasons

$$E_{3333} = K_1, \quad E_{3131} = E_{3232} = K_2. \quad (39)$$

The set of necessary and sufficient conditions for the positive definiteness of the elastic energy density of one-dimensional hexagonal quasicrystals of Laue class 10 is given by the following 5 inequalities imposed on the elastic constants [48]

$$C_{11} > |C_{12}|, \quad (C_{11} + C_{12})C_{33} - 2C_{13}^2 > 0, \quad C_{44} > 0, \quad (40)$$

$$C_{44}K_2 - R_3^2 > 0, \quad (41)$$

$$[(C_{11} + C_{12})C_{33} - 2C_{13}^2]K_1 + 2(2C_{13}R_2 - C_{33}R_1)R_1 - (C_{11} + C_{12})R_2^2 > 0. \quad (42)$$

5. Three-dimensional Green tensor for one-dimensional hexagonal quasicrystals of Laue class 10

In this section, the main result of this article is given. The three-dimensional Green tensor for one-dimensional hexagonal quasicrystals of Laue class 10 is explicitly derived from the integral expression (33) in closed-form expression using the residue method.

In order to obtain a convenient representation of the Green tensor (33), we use an appropriate orthonormal basis to represent the 4×4 matrix $\mathcal{T}(\xi)$ and later $\mathcal{T}^{-1}(\xi)$ (see [28])

$$\mathbf{e}_b = \frac{1}{\xi_b} \begin{pmatrix} \xi_1 \\ \xi_2 \\ 0 \\ 0 \end{pmatrix}, \quad \mathbf{e}_{b\perp} = \frac{1}{\xi_b} \begin{pmatrix} -\xi_2 \\ \xi_1 \\ 0 \\ 0 \end{pmatrix}, \quad \mathbf{e}_c = \begin{pmatrix} 0 \\ 0 \\ 1 \\ 0 \end{pmatrix}, \quad \mathbf{e}_4 = \begin{pmatrix} 0 \\ 0 \\ 0 \\ 1 \end{pmatrix} \quad (43)$$

with $\xi_b = \sqrt{\xi_1^2 + \xi_2^2}$ and $\xi_c = \xi_3$. This basis represents the hexagonal symmetry. The vectors \mathbf{e}_b and $\mathbf{e}_{b\perp}$ are parallel to the basal plane and \mathbf{e}_c represents the c -direction perpendicular to the basal plane and they are the suitable basis in the parallel space E_{\parallel}^3 for hexagonal

symmetry. e_4 comes into play because of the phason component and is the basis in the perpendicular space E_{\perp}^1 . Using the basis (43), we obtain the following expression

$$\begin{aligned} \mathcal{T}(\xi) = & T_{b\perp} e_{b\perp} \otimes e_{b\perp} + T_b e_b \otimes e_b + T_{bc}(e_b \otimes e_c + e_c \otimes e_b) + T_c e_c \otimes e_c \\ & + t_{b4}(e_b \otimes e_4 + e_4 \otimes e_b) + t_{c4}(e_c \otimes e_4 + e_4 \otimes e_c) + \tau e_4 \otimes e_4. \end{aligned} \quad (44)$$

The scalar quantities $T_{b\perp}, T_b, T_{bc}, T_c, t_{b4}, t_{c4}$, and τ correspond to the tensors T, t and τ from Eqs. (26), (27) and (28), respectively (\otimes indicates dyadic multiplication). They are obtained as

$$T_{b\perp} = C_{66}\xi_b^2 + C_{44}\xi_c^2, \quad (45)$$

$$T_b = C_{11}\xi_b^2 + C_{44}\xi_c^2, \quad (46)$$

$$T_{bc} = (C_{13} + C_{44})\xi_b\xi_c, \quad (47)$$

$$T_c = C_{44}\xi_b^2 + C_{33}\xi_c^2, \quad (48)$$

$$t_{b4} = (R_1 + R_3)\xi_b\xi_c, \quad (49)$$

$$t_{c4} = R_3\xi_b^2 + R_2\xi_c^2, \quad (50)$$

$$\tau = K_2\xi_b^2 + K_1\xi_c^2. \quad (51)$$

Here and in what follows, the elastic constant $C_{66} = (C_{11} - C_{12})/2$ is used instead of C_{12} , since it provides more elegant expressions. The inverse 4×4 matrix $\mathcal{T}^{-1}(\xi)$ is given by

$$\mathcal{T}^{-1}(\xi) = \frac{\Lambda(\xi)}{f(\xi)}, \quad (52)$$

where $\Lambda(\xi) = \text{adj } \mathcal{T}(\xi)$ is the adjoint of the 4×4 matrix $\mathcal{T}(\xi)$, which are polynomials of degree 6 in ξ , and $f(\xi) = \det \mathcal{T}(\xi)$ is the determinant of the 4×4 matrix $\mathcal{T}(\xi)$, which is a polynomial of degree 8 in ξ . Using Eq. (44), Λ can be written as follows

$$\begin{aligned} \Lambda(\xi) = & \Lambda_{b\perp} e_{b\perp} \otimes e_{b\perp} + \Lambda_b e_b \otimes e_b + \Lambda_{bc}(e_b \otimes e_c + e_c \otimes e_b) + \Lambda_c e_c \otimes e_c \\ & + \Lambda_{b4}(e_b \otimes e_4 + e_4 \otimes e_b) + \Lambda_{c4}(e_c \otimes e_4 + e_4 \otimes e_c) + \Lambda_4 e_4 \otimes e_4, \end{aligned} \quad (53)$$

where

$$\Lambda_{b\perp} = \tau(T_b T_c - T_{bc}^2) - (t_{c4}^2 T_b - 2t_{c4} t_{b4} T_{bc} + t_{b4}^2 T_c), \quad (54)$$

$$\Lambda_b = T_{b\perp}(T_c \tau - t_{c4}^2), \quad (55)$$

$$\Lambda_{bc} = -T_{b\perp}(T_{bc} \tau - t_{b4} t_{c4}), \quad (56)$$

$$\Lambda_c = T_{b\perp}(T_b \tau - t_{b4}^2), \quad (57)$$

$$\Lambda_{b4} = T_{b\perp}(T_{bc} t_{c4} - T_c t_{b4}), \quad (58)$$

$$\Lambda_{c4} = -T_{b\perp}(T_b t_{c4} - T_{bc} t_{b4}), \quad (59)$$

$$\Lambda_4 = T_{b\perp}(T_b T_c - T_{bc}^2). \quad (60)$$

The determinant $f(\xi)$ of \mathcal{T} can be written as

$$f(\xi) = \det \mathcal{T}(\xi) = T(\xi)_{b\perp} \Lambda_{b\perp}(\xi). \quad (61)$$

Substituting Eqs. (45)–(51) and Eq. (54) into Eq. (61) shows that only terms proportional to $\xi_b^{2n} \xi_c^{8-2n}$ ($n = 0, 1, 2, 3, 4$) appear. This is a unique property of the hexagonal medium. It is the central property which is needed to solve the integration problem (33). Thus, Eq. (54) is a polynomial of degree 3 in a if we put $a = \xi_b^2 / \xi_c^2$. We then can write

$$\Lambda_{b\perp} = P(a)\xi_c^6, \quad (62)$$

where $P(a)$ is a polynomial of degree 3 in a and takes the form

$$P(a) = Aa^3 + Ba^2 + Ca + D \quad (63)$$

and the coefficients A, B, C, D are given by

$$A = C_{11} \left(K_2 C_{44} - R_3^2 \right), \quad (64)$$

$$B = K_1 C_{11} C_{44} + K_2 \left(C_{11} C_{33} - 2C_{13} C_{44} - C_{13}^2 \right) - C_{44} R_3^2 - 2C_{11} R_3 R_2 + 2(C_{13} + C_{44}) R_3 (R_1 + R_3) - C_{44} (R_1 + R_3)^2, \quad (65)$$

$$C = K_1 \left(C_{11} C_{33} - 2C_{13} C_{44} - C_{13}^2 \right) + K_2 C_{33} C_{44} - 2R_3 R_2 C_{44} - R_2^2 C_{11} + 2R_2 (R_1 + R_3) (C_{13} + C_{44}) - C_{33} (R_1 + R_3)^2, \quad (66)$$

$$D = C_{44} \left(K_1 C_{33} - R_2^2 \right). \quad (67)$$

The determinant f can be factorized according to

$$f(\xi) = \xi_c^8 C_{66} A (a + A_1) (a + A_2) (a + A_3) (a + A_4) \quad (68)$$

with $T(a)_{b\perp} = C_{66} (a + A_1) \xi_c^2$, $A_1 = C_{44} / C_{66}$ and

$$P(a) = A (a + A_2) (a + A_3) (a + A_4). \quad (69)$$

The subdeterminant (54) gives with $a = \xi_b^2 / \xi_c^2$ and $\xi_c^2 = 1$

$$\Lambda_{b\perp}(a) = P(a) = Aa^3 + Ba^2 + Ca + D. \quad (70)$$

The numbers A_2, A_3, A_4 are the roots of the cubic equation

$$Aa^3 - Ba^2 + Ca - D = 0 \quad (71)$$

with the coefficients A, B, C, D given in Eqs. (64)–(67). The $A_l, l = 1, 2, 3, 4$ are material quantities and fully determined by the elastic moduli C, D, E . Furthermore, the subdeterminants (55)–(60) give with $a = \xi_b^2 / \xi_c^2$ and $\xi_c^2 = 1$

$$\Lambda_b(a) = (C_{66}a + C_{44}) \left[(K_2a + K_1)(C_{44}a + C_{33}) - (R_3a + R_2)^2 \right], \quad (72)$$

$$\Lambda_{bc}(a) = \sqrt{a} (C_{66}a + C_{44}) [(R_1 + R_3)(R_3a + R_2) - (K_2a + K_1)(C_{13} + C_{44})], \quad (73)$$

$$\Lambda_c(a) = (C_{66}a + C_{44}) \left[(K_2a + K_1)(C_{11}a + C_{44}) - a(R_1 + R_3)^2 \right], \quad (74)$$

$$\Lambda_{b4}(a) = \sqrt{a} (C_{66}a + C_{44}) [(C_{13} + C_{44})(R_3a + R_2) - (C_{44}a + C_{33})(R_1 + R_3)], \quad (75)$$

$$\Lambda_{c4}(a) = -(C_{66}a + C_{44}) [(C_{11}a + C_{44})(R_3a + R_2) - a(C_{13} + C_{44})(R_1 + R_3)], \quad (76)$$

$$\Lambda_4(a) = (C_{66}a + C_{44}) \left[a^2 C_{11} C_{44} + a \left(C_{11} C_{33} - 2C_{13} C_{44} - C_{13}^2 \right) + C_{33} C_{44} \right]. \quad (77)$$

Note that the dependence on a in Eqs. (54)–(60) is obtained by inserting $\xi_b = \sqrt{a}$ and $\xi_c = 1$ in Eqs. (45)–(51).

Furthermore, we use the property

$$\Lambda(\xi\lambda) = \lambda^6 \Lambda(\xi), \quad (78)$$

where λ denotes an arbitrary scalar number. The components of the adjoint Λ are homogeneous functions of degree 6 and the determinant f is homogeneous of degree 8

$$f(\xi\lambda) = \lambda^8 f(\xi). \quad (79)$$

Therefore, it yields

$$\mathcal{T}^{-1}(\xi) = \lambda^2 \frac{\Lambda(\lambda\xi)}{f(\lambda\xi)}. \quad (80)$$

We introduce the complex vector [47]

$$\gamma(\phi) = 2e^{i\phi}\xi(\phi) \quad (81)$$

with $\xi(\phi)$ given by Eq. (35) (i denotes the imaginary unit). Eq. (81) can be written

$$\gamma(s) = \mathbf{h}^*s + \mathbf{h} \quad (82)$$

with the complex variable

$$s = e^{2i\phi} \quad (83)$$

and

$$\mathbf{h} = \mathbf{e}_1 + i\mathbf{e}_2. \quad (84)$$

Using $\lambda = 2e^{i\phi}$, Eq. (80) can be written as

$$\mathcal{T}^{-1}(\xi) = 4s \frac{\Lambda(\gamma(s))}{f(\gamma(s))}. \quad (85)$$

Note that

$$ds = 2is d\phi. \quad (86)$$

The integral (33) can be transformed into an integral over the unit circle as follows

$$\mathcal{G}(r) = \frac{1}{8\pi^2 r} \oint_{|s|=1} \frac{4\Lambda(\gamma(s))}{f(\gamma(s))} \frac{ds}{i}. \quad (87)$$

Using the residue theorem, the integral (87) can be rewritten as

$$\mathcal{G}(r) = \frac{1}{8\pi^2 r} 2\pi i \sum \text{Res} \left(\frac{4\Lambda(\gamma(s))}{if(\gamma(s))} \right). \quad (88)$$

In order to compute Eq.(88), one has to find all roots of $f(\gamma(s))$ which are located within the unit circle. $f(\gamma(s))$ is a polynomial of degree 8 in s . Thus, there exist 8 roots s_j of f . It is assumed that f has no multiple roots s_j and this excludes the degenerate cases¹.

Following Michelitsch and Wunderlin [47], we conclude that there are 4 pairs of roots s_l, \bar{s}_l ($l = 1, 2, 3, 4$) having the property $|s_l \bar{s}_l| = 1$. There are only four roots s_l which are located within the unit circle, four roots \bar{s}_l lie outside the unit circle and the roots can be written in the form [47]

$$s_l = e^{2i\Phi_l} e^{-2\psi_l}, \quad (89)$$

$$\bar{s}_l = e^{2i\Phi_l} e^{+2\psi_l}, \quad (90)$$

where $\psi_l > 0$ ($l = 1, 2, 3, 4$). Here, the degenerate case $|s_l| = |\bar{s}_l|$ is excluded by our assumption of no multiple roots. Only the residues corresponding to the four roots (89) lying within the unit circle contribute to Eq. (88). We obtain

$$\text{Res} \left(\frac{4\Lambda(\gamma(s))}{if(\gamma(s))} \right) \Big|_{s=s_l} = \frac{4\Lambda(\gamma(s_l))}{i \frac{df(\gamma(s))}{ds} \Big|_{s=s_l}}. \quad (91)$$

¹ Analytically such a case is well captured by the present approach by adding a small $\epsilon > 0$ to one or more multiple roots in order to make them different and thereby removing the degeneracy.

Finally, the Green tensor (33) reduces to

$$\mathcal{G}(\mathbf{r}) = \frac{1}{4\pi r} \sum_{l=1}^4 \frac{4\Lambda(\gamma(s_l))}{\left. \frac{df(\gamma(s))}{ds} \right|_{s=s_l}}. \quad (92)$$

The roots s_l of $f(\gamma(s))$ within the unit circle yield

$$s_l = \frac{\sqrt{A_l \rho^2 + z^2} - r}{\sqrt{A_l \rho^2 + z^2} + r}. \quad (93)$$

To obtain Eq. (93), Eq. (68) together with Eqs. (82) and (84) have been used.

Evaluating Eq. (92), the Green tensor takes the form

$$\mathcal{G}(\mathbf{r}) = \frac{1}{4\pi A C_{66}} \sum_{l=1}^4 \frac{\Lambda(\xi^{(l)})}{\sqrt{A_l \rho^2 + z^2} \prod_{j=1, (j \neq l)}^4 (A_j - A_l)}, \quad (94)$$

where $\xi^{(l)}$ ($l = 1, 2, 3, 4$) are the solutions of the equations

$$f(\xi) = 0 \quad (95)$$

or

$$\xi_1^2 + \xi_2^2 + A_l \xi_3^2 = 0 \quad (96)$$

and

$$\xi \mathbf{r} = \xi_1 x + \xi_2 y + \xi_3 z = 0 \quad (97)$$

with $\xi_3^{(l)} = 1$. Eqs. (95) and (97) have the solutions ($l = 1, 2, 3, 4$)

$$\xi_1^{(l)} = \frac{1}{\rho^2} \left[-zx + iy \sqrt{A_l \rho^2 + z^2} \right], \quad (98)$$

$$\xi_2^{(l)} = \frac{1}{\rho^2} \left[-zy - ix \sqrt{A_l \rho^2 + z^2} \right], \quad (99)$$

where

$$\rho = \sqrt{x^2 + y^2}. \quad (100)$$

Note that this formulation is in complete analogy to the result obtained by Kröner [24] for the elastic Green tensor of a hexagonal crystal using Fredholm's method [19].

Using Eq. (94), the Cartesian representation of the *elastic* 4×4 Green tensor for one-dimensional hexagonal quasicrystals of Laue class 10 is given by

$$\mathcal{G}(\mathbf{r}) = \sum_{l=1}^4 \frac{1}{\sqrt{A_l \rho^2 + z^2}} \begin{pmatrix} \mathcal{G}_{11}^{(l)} & \mathcal{G}_{12}^{(l)} & \mathcal{G}_{13}^{(l)} & \mathcal{G}_{14}^{(l)} \\ \mathcal{G}_{12}^{(l)} & \mathcal{G}_{22}^{(l)} & \mathcal{G}_{23}^{(l)} & \mathcal{G}_{24}^{(l)} \\ \mathcal{G}_{13}^{(l)} & \mathcal{G}_{23}^{(l)} & \mathcal{G}_{33}^{(l)} & \mathcal{G}_{34}^{(l)} \\ \mathcal{G}_{14}^{(l)} & \mathcal{G}_{24}^{(l)} & \mathcal{G}_{34}^{(l)} & \mathcal{G}_{44}^{(l)} \end{pmatrix} \quad (101)$$

with the abbreviations

$$g_{11}^{(l)} = \frac{1}{\mathcal{E}_l} \left[-\Gamma_b(-A_l) \frac{x^2 z^2 - y^2 (A_l \rho^2 + z^2)}{\rho^4} + \Lambda_{b\perp}(-A_l) \right], \quad (102)$$

$$g_{22}^{(l)} = \frac{1}{\mathcal{E}_l} \left[-\Gamma_b(-A_l) \frac{y^2 z^2 - x^2 (A_l \rho^2 + z^2)}{\rho^4} + \Lambda_{b\perp}(-A_l) \right], \quad (103)$$

$$g_{12}^{(l)} = \frac{1}{\mathcal{E}_l} \left[-\Gamma_b(-A_l) \frac{xy(A_l \rho^2 + 2z^2)}{\rho^4} \right], \quad (104)$$

$$g_{13}^{(l)} = \frac{1}{\mathcal{E}_l} \left[-\Gamma_{bc}(-A_l) \frac{xz}{\rho^2} \right], \quad (105)$$

$$g_{23}^{(l)} = \frac{1}{\mathcal{E}_l} \left[-\Gamma_{bc}(-A_l) \frac{yz}{\rho^2} \right], \quad (106)$$

$$g_{33}^{(l)} = \frac{1}{\mathcal{E}_l} \Lambda_c(-A_l), \quad (107)$$

$$g_{14}^{(l)} = \frac{1}{\mathcal{E}_l} \left[-\Gamma_{b4}(-A_l) \frac{xz}{\rho^2} \right], \quad (108)$$

$$g_{24}^{(l)} = \frac{1}{\mathcal{E}_l} \left[-\Gamma_{b4}(-A_l) \frac{yz}{\rho^2} \right], \quad (109)$$

$$g_{34}^{(l)} = \frac{1}{\mathcal{E}_l} \Lambda_{c4}(-A_l), \quad (110)$$

$$g_{44}^{(l)} = \frac{1}{\mathcal{E}_l} \Lambda_4(-A_l). \quad (111)$$

Here, we have introduced the following abbreviation

$$\mathcal{E}_l = 4\pi C_{66} A \prod_{j=1, (j \neq l)}^4 (A_j - A_l) \quad (112)$$

and the quantities

$$\Gamma_b(a) = \frac{1}{a} [\Lambda_{b\perp}(a) - \Lambda_b(a)], \quad (113)$$

$$\Gamma_{bc}(a) = \frac{1}{\sqrt{a}} \Lambda_{bc}(a), \quad (114)$$

$$\Gamma_{b4}(a) = \frac{1}{\sqrt{a}} \Lambda_{b4}(a), \quad (115)$$

together with Eq. (70) and Eqs. (72)–(77).

Eq. (101) together with Eqs. (102)–(111) gives the 10 independent components of the Green tensor in closed-form. In particular, Eq. (101) together with Eqs. (102)–(107) gives the 6 phonon components of the Green tensor, Eq. (101) together with Eqs. (108)–(110) gives the 3 phonon-phason coupling components of the Green tensor and Eq. (101) together with Eq. (111) gives the 1 phason component of the Green tensor (see also Eq. (32)). Due to the closed-form expression of the Green tensor (101), it is straightforward to calculate its first and second gradients if they are needed for further applications. This can be done without any numerical tool, revealing one of the main advantages of the present approach. In the piezoelectric framework, the first and second gradients of the corresponding Green tensor are explicitly calculated in the context of the inclusion problem in Michelitsch and Levin [29].

It is interesting to note that the closed-form expression of the 4×4 Green tensor for one-dimensional hexagonal quasicrystals of Laue class 10 given in Eq. (101) with Eqs. (102)–(111) is analogous to the closed-form expression of the 4×4 Green tensor for hexagonal piezoelectric crystals of point group $6mm$ given by Michelitsch [28], due to the analogy in

Table 1. Elastic constants of one-dimensional hexagonal quasicrystals of Laue class 10 given in GPa (see [50]).

Phonon:	$C_{11} = 150$	$C_{12} = 100$	$C_{13} = 90$	$C_{33} = 130$	$C_{44} = 50$
Phason:	$K_1 = 0.18$	$K_2 = 0.30$			
Phonon-phason:	$R_1 = -1.50$	$R_2 = 1.20$	$R_3 = 1.20$		

the constitutive setting between one-dimensional hexagonal quasicrystals of Laue class 10 which possess 10 elastic moduli and hexagonal piezoelectric crystals of point group $6mm$ which possess 10 material moduli.

It should be pointed out that the procedure used in this paper for the derivation of closed-form expressions cannot be applied for example in one-dimensional hexagonal quasicrystals of Laue class 9 which possess 11 elastic moduli and correspond to piezoelectric crystals of point group 6 which possess 11 material moduli, since these are not transversal isotropic materials (see [13,49]). That is also another reason that the distinction between the two Laue classes of one-dimensional hexagonal quasicrystals has to be respected (see [14]).

6. Numerical results for one-dimensional hexagonal quasicrystals of Laue class 10

In this section, the 10 independent components of the 4×4 Green tensor (101) of one-dimensional hexagonal quasicrystals of Laue class 10 are presented numerically in contour plots.

The elastic constants of one-dimensional hexagonal quasicrystals of Laue class 10, which are used for the numerical computation, are tabulated in Table 1 by referring to Li *et al.* [50]. Since there are no values for the elastic constants of one-dimensional hexagonal quasicrystals of Laue class 10 based on experiments or ab-initio calculations, it is crucial to check that the above values fulfil the conditions of positive definiteness of the strain energy density. It is easy to check that the elastic constants given in Table 1 fulfil the conditions of positive definiteness of one-dimensional hexagonal quasicrystals of Laue class 10 given in Eqs. (40)–(42).

The phonon components of the Green tensor, Eq. (101) with Eqs. (102)–(107), are plotted in Fig. 1. The phason and phonon-phason coupling components of the Green tensor, Eq. (101) with Eqs. (108)–(111), are plotted in Fig. 2. Using the elastic constants given in Table 1, it can be seen that the phason component $G_{44}^{\perp\perp}$, Fig. 2(a), gives the strongest contribution in comparison with all the other components of the Green tensor. The anisotropy is visible in the diagonal phonon components $G_{11}^{\parallel\parallel}$, $G_{22}^{\parallel\parallel}$, $G_{33}^{\parallel\parallel}$, Figs. 1(a)–(c) and in the phonon-phason coupling component, $G_{34}^{\parallel\perp}$, Fig. 2(b). One can further observe that the phonon components $G_{13}^{\parallel\parallel}$ and $G_{23}^{\parallel\parallel}$, Figs. 1(e) and 1(f), have the same contour form. This reflects the transversal isotropic symmetry in the basal plane (see Eqs. (105) and (106)). The same holds for the phonon-phason coupling components $G_{14}^{\parallel\perp}$ and $G_{24}^{\parallel\perp}$, Figs. 2(c) and 2(d) (see Eqs. (108) and (109)).

7. Conclusions

In this paper, starting from an integral form expression of the elastic 4×4 Green tensor valid for one-dimensional quasicrystals, a closed-form representation of the 4×4 Green tensor for one-dimensional hexagonal quasicrystals of Laue class 10 is derived using the residuum theorem. Contour plots of the 10 independent components of the obtained elastic 4×4 Green tensor of one-dimensional hexagonal quasicrystals of Laue class 10 have been given to show their main characteristics. It is interesting to obtain that the phason component of the Green tensor has the strongest contribution in comparison with all the other components. The fact that the derived solution is in closed-form can drastically reduce the computational cost in any application making the present result a powerful tool for the implementation into numerical schemes, for instance, solving boundary value problems. In general, the Green tensor derived in the present paper allows to solve a wide range of problems in one-dimensional hexagonal quasicrystals of Laue class 10 such

as Eshelby inclusion problem, Eshelby tensor, dislocation loops and other problems of micromechanics.

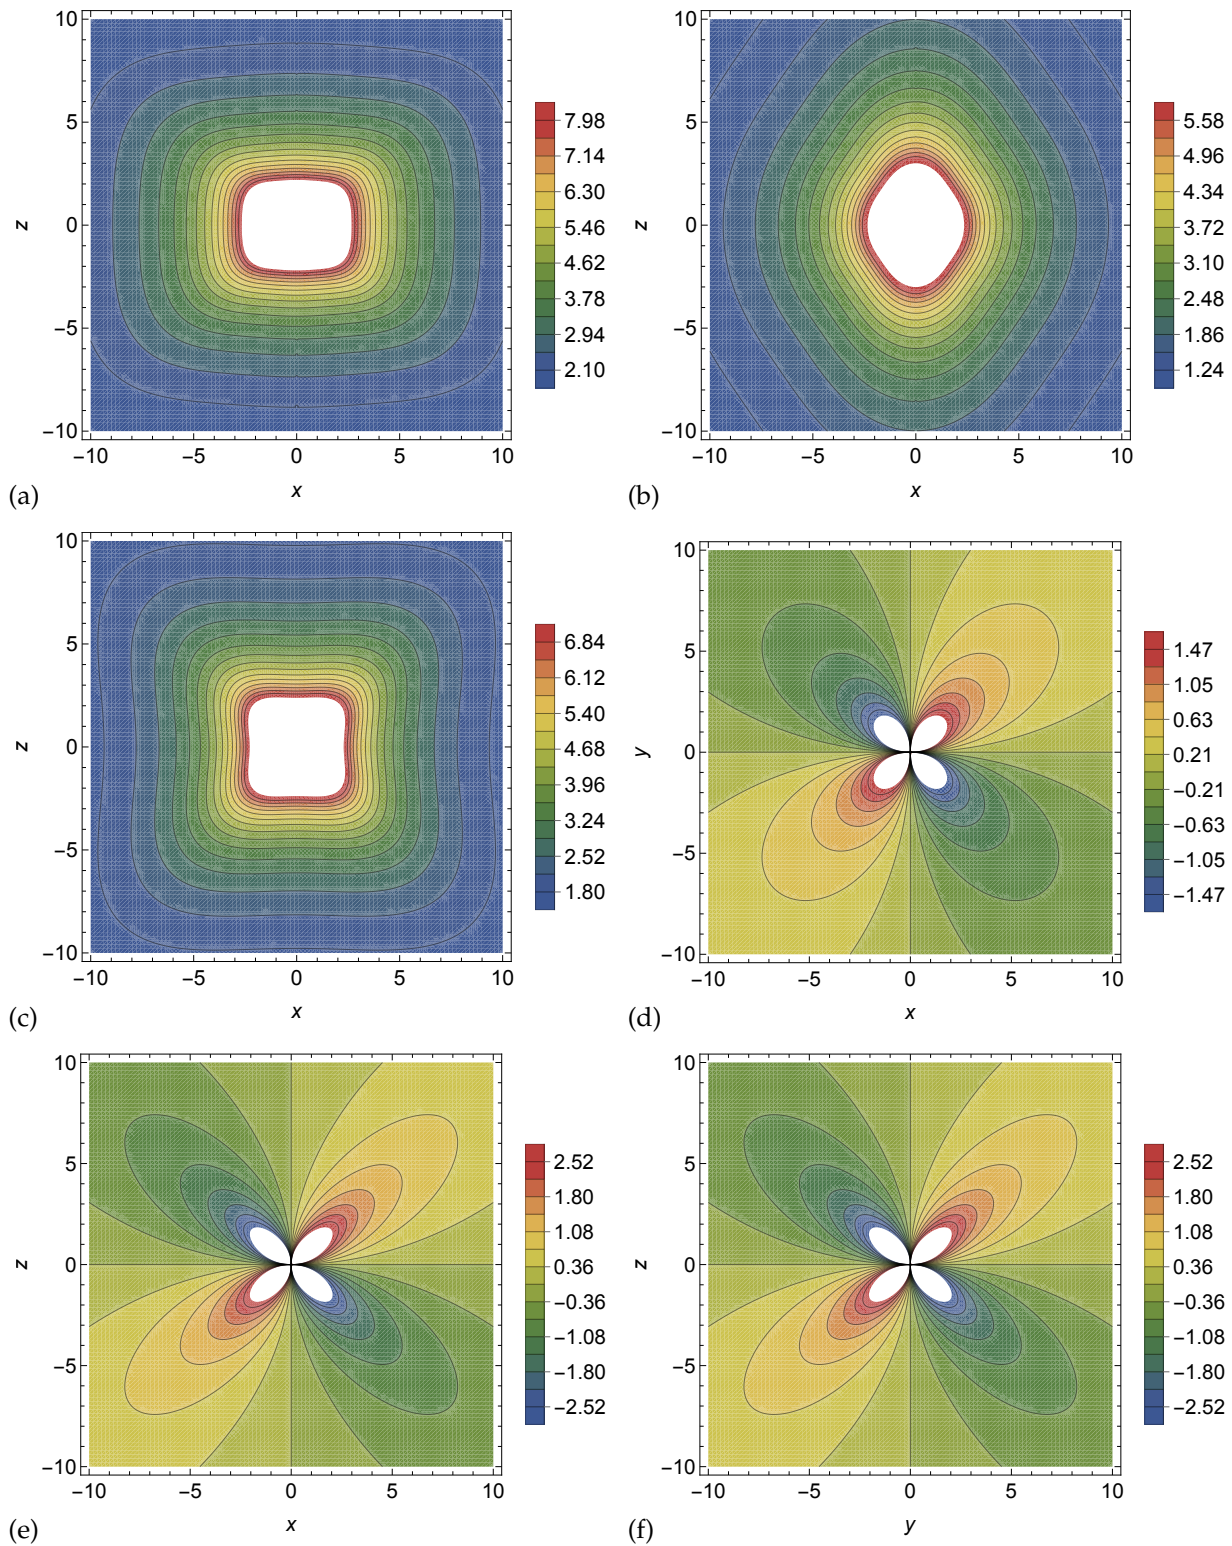


Figure 1. Phonon components of the Green tensor: (a) $G_{11}^{\parallel\parallel} \times 10^4$, (b) $G_{22}^{\parallel\parallel} \times 10^4$, (c) $G_{33}^{\parallel\parallel} \times 10^4$, (d) $G_{12}^{\parallel\parallel} \times 10^4$, (e) $G_{13}^{\parallel\parallel} \times 10^4$, (f) $G_{23}^{\parallel\parallel} \times 10^4$.

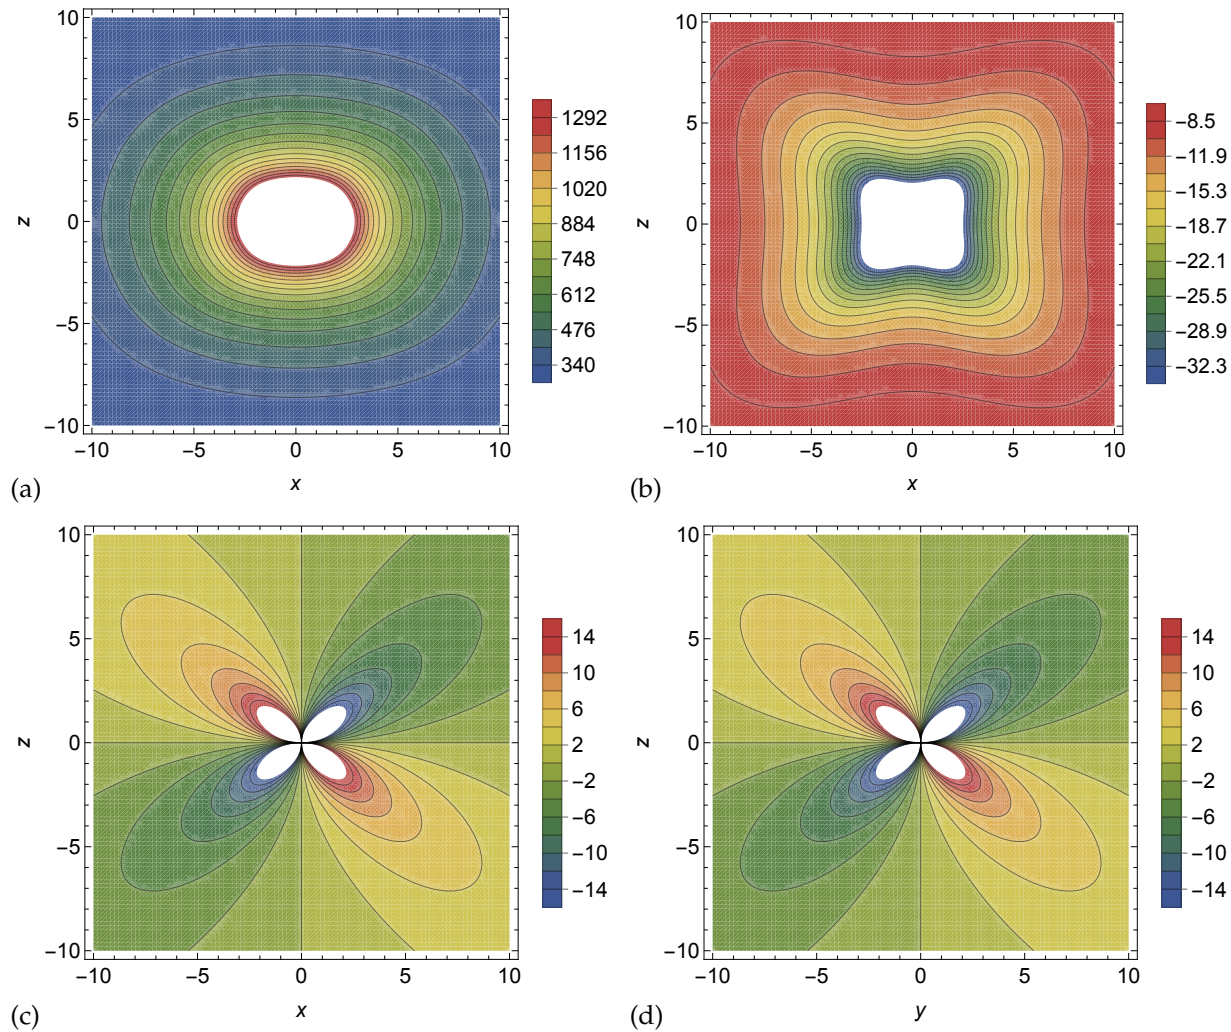


Figure 2. Phason and phonon-phason coupling components of the Green tensor: (a) $G_{44}^{\perp\perp} \times 10^4$, (b) $G_{34}^{\parallel\perp} \times 10^4$, (c) $G_{14}^{\parallel\perp} \times 10^4$, (d) $G_{24}^{\parallel\perp} \times 10^4$.

Author Contributions: Conceptualization, E.A. and M.L.; methodology, T.M. and M.L.; writing—original draft preparation, M.L., T.M. and E.A.; writing—review and editing, M.L. and E.A.; visualization, M.L.; funding acquisition, M.L. and E.A.; All authors have read and agreed to the published version of the manuscript.

Funding: This research was funded by the Deutsche Forschungsgemeinschaft, Grant Numbers LA1974/4-2, AG322/1-2.

Data Availability Statement: Data are contained within the article.

Acknowledgments: Markus Lazar and Eleni Agiasofitou gratefully acknowledge the grants from the Deutsche Forschungsgemeinschaft (Grant numbers LA1974/4-2 and AG322/1-2).

Conflicts of Interest: The authors declare no conflict of interest.

Appendix A. Limit to the three-dimensional Green tensor of hexagonal crystals

In this appendix, we show that in the case of vanishing phonon-phason coupling $D_{ij3l} = 0$, the Green tensor (101) of one-dimensional hexagonal quasicrystals of Laue class 10 yields well-known results. Specifically, the phonon part $\mathcal{G}_{ij} = G_{ij}^{\parallel\parallel}$, $i, j = 1, 2, 3$ provides Kröner's elastic Green tensor of a hexagonal crystal [24], the phason part $\mathcal{G}_{44} = G_{44}^{\perp\perp}$ provides the Green function of a "hexagonal" Poisson equation and the phonon-phason coupling part $\mathcal{G}_{j4} = G_{j4}^{\parallel\perp}$, $j = 1, 2, 3$ vanishes.

We consider the case of vanishing phonon-phason coupling ($D_{ij3l} = 0$ or $R_1 = R_2 = R_3 = 0$). In this case, Eqs. (49) and (50) become

$$t_{b4} = t_{c4} = 0. \quad (\text{A.1})$$

The determinant f (Eq. (61)) simplifies to

$$f(a) = \det \mathcal{T}(a) = \tau(a) T_{b\perp}(a) \left(T_b(a) T_c(a) - T_{bc}^2(a) \right) \quad (\text{A.2})$$

and can be written as

$$f(a) = K_2 C_{11} C_{44} C_{66} (a + a_1)(a + a_2)(a + a_3)(a + a_4), \quad (\text{A.3})$$

where $a_l = A_l$ denote the roots of $f(-a)$ in the decoupled case. In addition,

$$a_1 = \frac{C_{44}}{C_{66}} \quad (\text{A.4})$$

represents the root of $T_{b\perp}(-a)$. Moreover, $a_{2,3}$ are the roots of the quadratic equation

$$T_b(-a) T_c(-a) - T_{bc}^2(-a) = C_{11} C_{44} a^2 + (C_{13}^2 + 2C_{13} C_{44} - C_{11} C_{33}) a + C_{33} C_{44} = 0 \quad (\text{A.5})$$

and they read

$$a_{2,3} = \frac{1}{2C_{11} C_{44}} \left(- (C_{13}^2 + 2C_{13} C_{44} - C_{11} C_{33}) \pm \sqrt{[(C_{13}^2 + 2C_{13} C_{44} - C_{11} C_{33})^2 - 4C_{11} C_{33} C_{44}^2]} \right). \quad (\text{A.6})$$

Moreover, a_4 is given by

$$a_4 = \frac{K_1}{K_2} \quad (\text{A.7})$$

and represents the root of $\tau(-a)$. Using Eqs. (70)–(77) together with Eqs. (113)–(115), we find

$$\Lambda_{b\perp}(a = -a_l) = K_2 C_{11} C_{44} (a_2 - a_l)(a_3 - a_l)(a_4 - a_l) \quad (\text{A.8})$$

$$\Lambda_b(a = -a_l) = K_2 C_{66} (C_{33} - a_l C_{44})(a_1 - a_l)(a_4 - a_l) \quad (\text{A.9})$$

$$\Gamma_b(a = -a_l) = -K_2 (a_4 - a_l) \left[(C_{66} - C_{11})(C_{33} - a_l C_{44}) + (C_{13} + C_{44})^2 \right] \quad (\text{A.10})$$

$$\Gamma_{bc}(a = -a_l) = -K_2 C_{66} (C_{13} + C_{44})(a_1 - a_l)(a_4 - a_l) \quad (\text{A.11})$$

$$\Lambda_c(a = -a_l) = K_2 C_{66} (C_{44} - a_l C_{11})(a_1 - a_l)(a_4 - a_l) \quad (\text{A.12})$$

and

$$\Gamma_{b4}(a = -a_l) = \Lambda_{c4}(a = -a_l) = 0, \quad (\text{A.13})$$

obtaining $\mathcal{G}_{j4} = 0$, $j = 1, 2, 3$ and

$$\Lambda_4(a = -a_l) = C_{11} C_{44} C_{66} (a_1 - a_l)(a_2 - a_l)(a_3 - a_l). \quad (\text{A.14})$$

For $l = 1, 2, 3$:

$$\mathcal{E}_l = K_2 (a_4 - a_l) E_l \quad (\text{A.15})$$

with

$$E_l = 4\pi C_{11} C_{44} C_{66} \prod_{j=1, (j \neq l)}^3 (a_j - a_l). \quad (\text{A.16})$$

The terms (A.16) coincide with Kröner’s (corrected) “ E_l ”. The terms E_l defined in Kröner [24] have been corrected by a prefactor $-C_{11}C_{44}C_{66}$ providing the correct result for the elastic Green tensor (see [25–27]).

For $l = 4$:

$$\mathcal{E}_4 = 4\pi K_2 C_{11} C_{44} C_{66} (a_1 - a_4)(a_2 - a_4)(a_3 - a_4) = 4\pi K_2 \Lambda_4(-a_4). \tag{A.17}$$

We observe from Eqs. (A.8)–(A.12), the following properties

$$\frac{\Lambda_{b\perp}(a = -a_4)}{\mathcal{E}_4} = \frac{\Lambda_b(a = -a_4)}{\mathcal{E}_4} = \frac{\Gamma_b(a = -a_4)}{\mathcal{E}_4} = \frac{\Gamma_{bc}(a = -a_4)}{\mathcal{E}_4} = \frac{\Lambda_c(a = -a_4)}{\mathcal{E}_4} = 0 \tag{A.18}$$

($\mathcal{E}_4 \neq 0$, Eq. (A.17)). Thus, the term $l = 4$ in the sum (101) does not contribute to the elastic phonon components \mathcal{G}_{ij} , $i, j = 1, 2, 3$. Using Eqs. (A.14) and (A.15) together with Eq. (A.16), we obtain for $l = 1, 2, 3$ that

$$\frac{\Lambda_4(a = -a_l)}{\mathcal{E}_l} = 0, \tag{A.19}$$

which means there are no contributions to the sum (101) for $l = 1, 2, 3$ to the phason part \mathcal{G}_{44} . For $l = 4$, we find from Eqs. (A.14) and (A.17) that

$$\frac{\Lambda_4(a = -a_4)}{\mathcal{E}_4} = \frac{1}{4\pi K_2}. \tag{A.20}$$

Note that Eq. (A.20) is independent of the elastic moduli C_{ijkl} , which is a consequence of $D_{ij3l} = 0$. Thus, the phason part \mathcal{G}_{44} of the Green tensor (101) gives

$$\mathcal{G}_{44}(\mathbf{r}) = \frac{\Lambda_4(a = -a_4)}{\mathcal{E}_4} \frac{1}{\sqrt{a_4\rho^2 + z^2}} = \frac{1}{4\pi K_2 \sqrt{a_4\rho^2 + z^2}} \tag{A.21}$$

with a_4 to be given by Eq. (A.7). It can be seen that the phason part \mathcal{G}_{44} of the Green tensor (101), Eq. (A.21), is the fundamental solution of the following “hexagonal” Poisson equation (compare Eqs. (28) and (30))

$$\tau(\nabla)\mathcal{G}_{44}(\mathbf{r}) + \delta^3(\mathbf{r}) = 0 \tag{A.22}$$

with

$$\tau(\nabla) = \left[K_2 \left(\frac{\partial^2}{\partial x^2} + \frac{\partial^2}{\partial y^2} \right) + K_1 \frac{\partial^2}{\partial z^2} \right]. \tag{A.23}$$

Let us consider the cases $l = 1, 2, 3$. From Eqs. (A.8)–(A.12) together with Eq. (A.15), we obtain the following:

- These terms coincide with Kröner’s “ A_l ” in [24]

$$-\frac{\Gamma_b(a = -a_l)}{\mathcal{E}_l} = \mathcal{A}_l = \frac{(C_{66} - C_{11})(C_{33} - a_l C_{44}) + (C_{13} + C_{44})^2}{E_l}. \tag{A.24}$$

- These terms coincide with Kröner’s “ B_l ” in [24]

$$\frac{\Lambda_{b\perp}(a = -a_l)}{\mathcal{E}_l} = \mathcal{B}_l = \frac{C_{11}C_{44}a_l^2 + (C_{13}^2 + 2C_{13}C_{44} - C_{11}C_{33})a_l + C_{33}C_{44}}{E_l}. \tag{A.25}$$

- These terms coincide with Kröner’s “ C_l ” in [24]

$$-\frac{\Gamma_{bc}(a = -a_l)}{\mathcal{E}_l} = \mathcal{C}_l = \frac{(C_{44} - a_l C_{66})(C_{13} + C_{44})}{E_l}. \tag{A.26}$$

- These terms coincide with Kröner's "D_l" from [24]

$$\frac{\Lambda_c(a = -a_l)}{\mathcal{E}_l} = D_l = \frac{(C_{44} - a_l C_{66})(C_{44} - a_l C_{11})}{E_l}. \quad (\text{A.27})$$

Because of the property (A.18), the elastic phonon part of the Green tensor \mathcal{G}_{ij} ($i, j = 1, 2, 3$) by inserting Eqs. (A.24)–(A.27) into Eq. (101) and by using the abbreviations (102)–(107) yields Kröner's Green tensor G_{ij} for hexagonal crystals [24]

$$\mathbf{G}(\mathbf{r}) = \sum_{l=1}^3 \frac{1}{\sqrt{a_l \rho^2 + z^2}} \times \begin{pmatrix} \mathcal{A}_l \frac{x^2 z^2 - y^2 (a_l \rho^2 + 2z^2)}{\rho^4} + \mathcal{B}_l \mathcal{A}_l \frac{xy(a_l \rho^2 + 2z^2)}{\rho^4} & C_l \frac{xz}{\rho^2} \\ \mathcal{A}_l \frac{xy(a_l \rho^2 + 2z^2)}{\rho^4} & \mathcal{A}_l \frac{y^2 z^2 - x^2 (a_l \rho^2 + 2z^2)}{\rho^4} + \mathcal{B}_l C_l \frac{yz}{\rho^2} \\ C_l \frac{xz}{\rho^2} & C_l \frac{yz}{\rho^2} & D_l \end{pmatrix}. \quad (\text{A.28})$$

References

1. Shechtman, D.; Blech, I.; Gratias, D.; Cahn, J.W. Metallic phase with long-range orientational order and no translational symmetry. *Phys. Rev. Lett.* **1984**, *53*, 1951–1953.
2. Dubois, J.M.; Kang, S.S.; Von-stebut, J. Quasicrystalline low-friction coatings. *J. Mater. Sci. Lett.* **1991**, *10*, 537–541.
3. Park, J.Y.; Ogletree, D.F.; Salmeron, M.; Jenks, C.J.; Thiel, P.A. Friction and adhesion properties of clean and oxidized Al-Ni-Co decagonal quasicrystals: a UHV atomic force microscopy/scanning tunneling microscopy study. *Tribol. Lett.* **2004**, *17*, 629–636.
4. Bloom, P.D.; Baikerikar, K.G.; Anderegg, J.W.; Sheares, V.V. Fabrication and wear resistance of Al-Cu-Fe quasicrystal-epoxy composite materials. *Mater. Eng. A* **2003**, *360*, 46–57.
5. Macia E. The role of aperiodic order in science and technology. *Rep. Prog. Phys.* **2006**, *69*, 397–441.
6. Bak, P. Symmetry, stability, and elastic properties of icosahedral incommensurate crystals. *Phys. Rev. B* **1985**, *32*, 5764–5772.
7. Levine, D.; Lubensky, T.C.; Ostlund, S.; Ramaswamy, S.; Steinhardt, P.J.; Toner, J. Elasticity and dislocations in pentagonal and icosahedral quasicrystals. *Phys. Rev. Lett.* **1985**, *54*, 1520–1523.
8. Fan, T.Y. *Mathematical Theory of Elasticity of Quasicrystals and Its Applications*. Beijing: Science Press and Springer Science+Business Media Singapore 2011, 2016.
9. Wang, R.; Yang, W.; Hu, C.; Ding, D.-H. Point and space groups and elastic behaviours of one-dimensional quasicrystals. *J. Phys.: Condens. Matter*, **1997**, *9*, 2411–2422.
10. Li, X.F.; Fan, T.Y. A straight dislocation in one-dimensional hexagonal quasicrystals. *phys. stat. sol. (b)*, **1999**, *212*, 19–26.
11. Li, X.Y. Fundamental solutions of penny-shaped and half-infinite plane cracks embedded in an infinite space of one-dimensional hexagonal quasi-crystal under thermal loading. *Proc. R. Soc. A*, **2014**, *469*, 20130023.
12. Tupholme, G.E. Row of shear cracks moving in one-dimensional hexagonal quasicrystalline materials. *Eng. Fract. Mech.*, **2015**, *134*, 451–458.
13. Lazar, M.; Agiasofitou, E. Eshelbian mechanics of novel materials: Quasicrystals. *J. Micromech. Mol. Phys.* **2016**, *1*, 1640008.
14. Agiasofitou, E.; Lazar, M. On the constitutive modelling of piezoelectric quasicrystals. *Crystals* **2023**, *13*, 1652.
15. Schwartz, L. *Théorie des Distributions*. Paris: Tomes I et II, Hermann, 1950/51.
16. Vladimirov, V.S. *Equations of Mathematical Physics*. New York: Marcel Dekker, Inc., 1971.
17. Ortner, N.; Wagner, P. *Fundamental solutions of linear partial differential operators*. Cham: Springer, 2015.
18. Lord Kelvin. *Mathematical and Physical Papers, Vol. 1*. Cambridge: Cambridge University Press, 1882, p. 97.
19. Fredholm, I. Sur les équations de l'équilibre d'un corps solide élastique. *Acta math.* **1900**, *23*, 1–42.
20. Lifshitz, I.M.; Rosenzweig, L.N. On the construction of the Green's tensor for the basic equation of the theory of elasticity of an anisotropic medium. *Zh. Eksper. Teor. Fiz.* **1947**, *17*, 783–791.
21. Synge, J.L. *The Hypercircle in Mathematical Physics*. Cambridge: Cambridge University Press, 1957.
22. Teodosiu, C. *Elastic Models of Crystal Defects*. Berlin: Springer, 1982.
23. Mura, T. *Micromechanics of Defects in Solids*. Dordrecht: Martinus Nijhoff, 2nd edition, 1987.
24. Kröner, E. Das Fundamentalintegral der anisotropen elastischen Differentialgleichungen. *Z. Phys.* **1953**, *136*, 402–410.
25. Willis, J.R. The elastic interaction energy of dislocation loops in anisotropic media. *Quart. J. Mech. Appl. Math.* **1965**, *18*, 419–433.
26. Chou, T.W.; Pan, Y.C. Elastic energies of disclinations in hexagonal crystals. *J. Appl. Phys.* **1973**, *44*, 63–65.
27. Tupholme, G.E. Dislocation loops in hexagonal crystals. *J. Mech. Phys. Solids*, **1974**, *22*, 309–321.
28. Michelitsch, T. Calculation of the electroelastic Green's function of the hexagonal infinite medium. *Z. Phys. B* **1997**, *104*, 497–503.

29. Michelitsch, T.; Levin, V. Inclusions and inhomogeneities in electroelastic media with hexagonal symmetry. *Eur. Phys. J. B* **2000**, *14*, 527–533.
30. Deeg, W.F.J. The analysis of dislocation, crack, and inclusion problems in piezoelectric solids. Ph.D. Thesis, Stanford Univ., CA., 1980.
31. Chen, T. Green's functions and the non-uniform transformation problem in a piezo electric medium. *Mech. Res. Commun.* **1993**, *20*, 271–278.
32. Dunn, M.L. Electroelastic Green's functions for transversely isotropic piezoelectric media and their application to the solution of inclusion and inhomogeneity problems. *Int. J. Engng. Sci.* **1994**, *32*, 119–131.
33. De, P.; Pelcovits, R.A. Linear elasticity theory of pentagonal quasicrystals. *Phys. Rev. B* **1987**, *35*, 8609–8620.
34. Ding, D.-H.; Wang, R.; Yang, W.; Hu, C. General expressions for the elastic displacement fields induced by dislocations in quasicrystals. *J. Phys.: Condens. Matter* **1995**, *7*, 5423–5436.
35. Bachteler, J.; Trebin, H.-R. Elastic Green's function of icosahedral quasicrystals. *Eur. Phys. J. B* **1998**, *4*, 299–306.
36. Lazar, M.; Agiasofitou, E. Fundamentals in generalized elasticity and dislocation theory of quasicrystals: Green tensor, dislocation key-formulas and dislocation loops. *Phil. Mag.* **2014**, *94*, 4080–4101.
37. Zhang, J.; Zhang, L.; Pan, E.; Gao, Y. Certain problems in constrained cubic quasicrystals: General solutions and infinite-space Green's functions. *Int. J. Solids Struct.*, **2022**, *254*, 111830.
38. Lazar, M.; Agiasofitou, E. Three-dimensional and two-dimensional Green tensors of piezoelectric quasicrystals. *Crystals* **2024**, *14*, 835.
39. Li, X.Y.; Li, P.D. Three-dimensional thermo-elastic general solutions of one-dimensional hexagonal quasi-crystal and fundamental solutions. *Phys. Lett. A* **2012**, *376*, 2004–2009.
40. Sales, M.A.; Gray, L.J. Evaluation of the anisotropic Green's function and its derivatives. *Comput. Struct.* **1998**, *69*, 247–254.
41. Phan, A.-V.; Gray, L.J.; Kaplan, T. On the residue calculus evaluation of the 3-D anisotropic elastic Green's function. *Commun. Numer. Meth. Eng.* **2004**, *20*, 335–341.
42. Phan, A.-V.; Gray, L.J.; Kaplan, T. Residue approach for evaluating the 3D anisotropic elastic Green's function: multiple roots. *Eng. Anal. Bound. Elem.* **2005**, *29*, 570–576.
43. Xie, L.; Zhang, C.; Hwu, C.; Sladek, J.; Sladek, V. A comparison of three evaluation methods for Green's function and its derivatives for 3D generally anisotropic solids. *Eur. J. Comput. Mech.* **2016**, *25*, 109–128.
44. Xie, L.; Zhang, C.; Hwu, C.; Sladek, J.; Sladek, V. On two accurate methods for computing 3D Green's function and its first and second derivatives in piezoelectricity. *Eng. Anal. Bound. Elem.* **2015**, *61*, 183–193.
45. Ding, D.-H.; Wang, W.; Hu, C.; Yang, R. Generalized elasticity theory of quasicrystals. *Phys. Rev. B* **1993**, *48*, 7003–7010.
46. Hu, C.; Wang, R.; Ding, D.H. Symmetry groups, physical property tensors, elasticity and dislocations in quasicrystals. *Rep. Prog. Phys.*, **2000**, *63*, 1–39.
47. Michelitsch, T.; Wunderlin, A. Fundamental solution of the incompatibility problem in three-dimensional infinite anisotropic elasticity theory. *Acta Mech.*, **1996**, *119*, 25–34.
48. Agiasofitou, E.; Lazar, M. Stability and positive definiteness of one-dimensional quasicrystals. Submitted for publication, 2024.
49. Yang, J. *An Introduction to the Theory of Piezoelectricity*. second edition. Cham: Springer, 2018.
50. Li, X.Y.; Li, P.D.; Wu, T.H.; Shi, M.X.; Zhu, Z.W. Three-dimensional fundamental solutions for one-dimensional hexagonal quasicrystal with piezoelectric effect. *Phys. Lett. A* **2014**, *378*, 826–834.

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.