



HAL
open science

Kinetics and mechanism of austenite decomposition in carbonitrided low-alloy steel

Hugo P. van Landeghem, Simon D. Catteau, Julien Teixeira, Jacky Dulcy, Muriel Véron, Abdelkrim Redjaïmia, Sabine Denis, M Courteaux

► **To cite this version:**

Hugo P. van Landeghem, Simon D. Catteau, Julien Teixeira, Jacky Dulcy, Muriel Véron, et al.. Kinetics and mechanism of austenite decomposition in carbonitrided low-alloy steel. Innovative and Sustainable Metallurgy, Labex DAMAS, Oct 2024, Pont à Mousson (France), France. hal-04832682

HAL Id: hal-04832682

<https://hal.science/hal-04832682v1>

Submitted on 12 Dec 2024

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution 4.0 International License

Kinetics and mechanism of austenite decomposition in carbonitrided low-alloy steel

**Hugo P. Van Landeghem^{1,2}, Simon D. Catteau^{2,3}, Julien Teixeira², Jacky Dulcy², Muriel Véron¹,
Abdelkrim Redjaïmia², Sabine Denis², Marc Courteaux³**

¹ Univ. Grenoble Alpes, CNRS, Grenoble INP, SIMAP, F-38000 Grenoble, France

² Institut Jean Lamour, UMR CNRS-Université de Lorraine 7198, F-54000 Nancy, France

³ PSA Peugeot-Citroën, Centre Technique de Belchamp, F-25420 Voujeaucourt, France

Email: hugo.van-landeghem@grenoble-inp.fr

Carbonitriding

*Transmission electron
microscopy (TEM)*

Low-alloy steel

Gear applications typically require high wear and fatigue resistance in order to optimize service times. This combination of properties is obtained by carburizing or carbonitriding of low alloy steel. In particular, the latter has notably been proved more effective than the former [1]. For this reason, carbonitriding is widely deployed in the industry. In spite of that, the metallurgical origin of the observed property improvements with the addition of nitrogen remains poorly understood. While the literature dealing with the effect of carbon content on the microstructural evolution of low-alloy steel is rather comprehensive [2], such is not the case for nitrogen.

In order to better understand the effect of nitrogen on austenite decomposition in low alloy steel, specimens of 23MnCrMo5 were homogeneously enriched in either nitrogen, carbon or both and were isothermally transformed at temperatures ranging from 200 °C to 750 °C after re-austenitization. The transformation progress was monitored *in-situ* by HEXRD and *post-mortem* microstructures were characterized using SEM and TEM. In all cases, nitrogen reduces the incubation time of the transformation of austenite into ferrite and speeds up its completion.

In nitrogen containing samples, large volume fractions of CrN, both inter- and intragranular, were observed at all temperatures with different morphologies and wide size distributions. The size and shape of these nitrides depend on the stage of the thermal schedule at which they form. It has also been shown that other nitrides precipitate during the various stages of the treatment, notably AlN, VN and MnSiN₂. Those other nitrides precipitate heterogeneously on grain boundaries or other preexisting nitrides.

For all interstitial contents, the range of transformation temperatures can be split in two based on the morphology of the ferritic product, the delimiting temperature being assimilated to B_s. Ferrite formed either as equiaxed grains at higher temperature or laths at lower temperature.

Above B_s , nitrogen leads to a pronounced refinement of the ferritic microstructure at identical carbon content. Combined with the absence of incubation for ferrite nucleation, this suggests that CrN precipitated in austenite during nitriding stimulate the nucleation of ferrite. This hypothesis is supported by the Baker-Nutting orientation relationship and the coherent interfaces $(100)_{CrN} // (100)_{\alpha-Fe}$ observed between ferrite and coarse CrNs. The ferrite that is formed is still supersaturated in nitrogen and numerous ($\sim 10^{22} \text{ m}^{-3}$) CrN platelets precipitate intragranularly. This intense precipitation is thought to be mostly responsible for the enhanced hardness of nitrogen-containing materials over nitrogen-free ones in this range of temperature.

Below B_s , the presence of nitrogen changes the arrangement of the ferrite laths which do not show an organization in packets or sheaves. Instead, the laths are strongly entangled in a fashion reminiscent of acicular ferrite, but at a much finer scale. The presence of nitrogen also seems to inhibit the formation of cementite, which is found in nitrogen-free specimens at similar carbon content. Additionally, it also causes very intense nanotwinning of the ferrite laths. Those twins are thought to be transformation twins as the only two twins found in each twin set are those that verify the Kurdjumov-Sachs orientation relationship with the parent austenite.

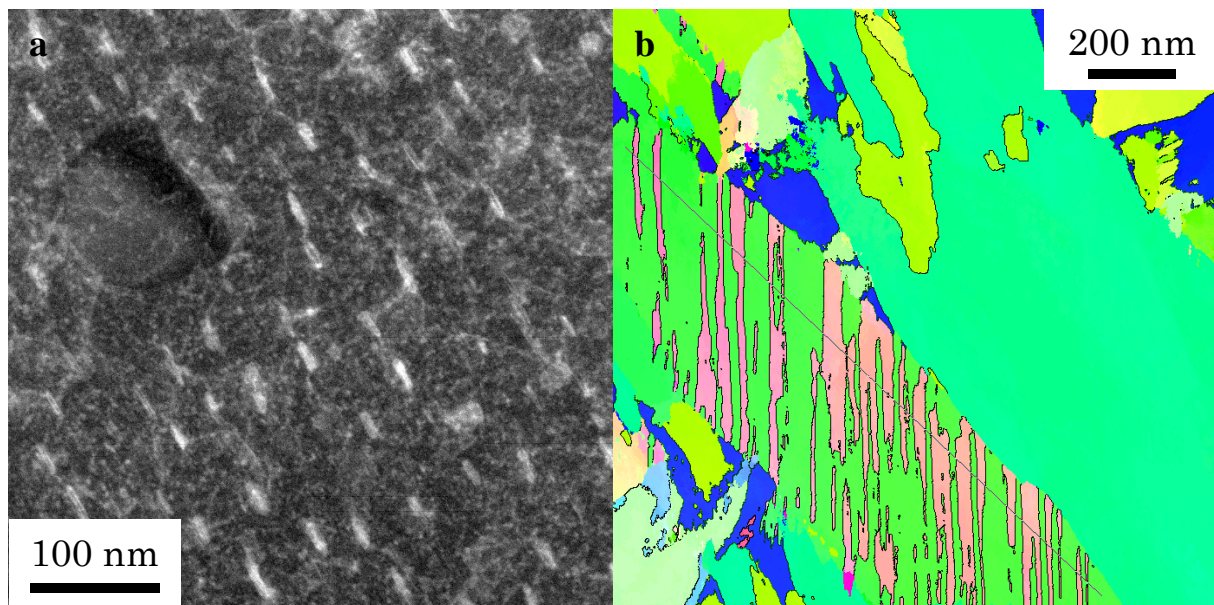


Figure 1 – a) Annular dark field scanning transmission electron micrograph of a 23MnCrMo5 specimen transformed at 650 °C ($> B_s$) for 3 h ($ZA = [001]_{\alpha-Fe}$) showing two CrN morphologies: a coarse spheroid (dark) and fine platelets (bright). b) Ferrite orientation map in a carbonitrided 23MnCrMo5 specimen transformed at 400 °C ($< B_s$) for 2 h showing abundant nanotwins.

References

- [1] A. Goldsteinas, New Vacuum Processes Achieve Mechanical Property Improvement in Gearbox Components, *Gear Technology* (2007) 34–39.
- [2] A. Constant, G. Henry, J.-C. Charbonnier, *Principes de base des traitements thermiques, thermomécaniques et thermochimiques des aciers*, PYC Édition, 1992.